

Cassini Multilayer Insulation Blanket High-Temperature Exposure Tests

Edward I. Lin* and James W. Stultz*

Jet Propulsion Laboratory, California Institute of Technology, Pasadena, California 91109

The Saturn-bound Cassini spacecraft will be subjected to a high-temperature environment at 0.61 AU. Thermal vacuum tests demonstrated that the hybrid Kapton®–Mylar multilayer insulation layup can withstand an outer layer temperature of 250°C without incurring any damage, and the all-Kapton layup can withstand 430°C. The latter will be applied to locales of extremely high temperatures, while the former will be applied to more than 85% of the spacecraft's blanketed surfaces. A solar simulator provided a 2.7-sun exposure to the blanket samples; outer layer temperatures of 200°C and 250°C were observed for second surface aluminized Kapton and black Kapton, respectively, which are in line with predictions. The high-temperature exposure tests established that current blanket designs will survive the Cassini mission thermal environments with margins.

Introduction

THE Cassini spacecraft is currently under development for a mission designed to explore Saturn and its rings, satellites, and magnetosphere. The Venus-Venus-Earth-Jupiter Gravity Assist (VVEJGA) trajectory will subject the spacecraft to a 0.61-AU high-temperature environment at perihelion. Temperatures on some sunlit blanket surfaces at 0.61 AU can reach levels that are beyond the service capability of the conventional Mylar/Dacron® net multilayer insulation (MLI). For example, the radioisotope thermoelectric generator (RTG) shade temperature is predicted to be around 300°C under the combined heating of the RTG (3900 W) and 2.7 suns (i.e., at 0.61 AU) during a trajectory correction maneuver. The main engine blanket temperature can reach 360°C during engine firing in conjunction with the 0.61-AU solar illumination. The majority of the blanket surfaces, however, will experience temperatures with an upper bound of 250°C, since the spacecraft will cruise in the shade of its high-gain antenna, which is sun-pointed most of the time.

These worst-case hot Cassini MLI temperature predictions are significantly higher than those expected for the Jupiter-bound Galileo spacecraft. During the development of Galileo, several tests were conducted to assess the feasibility of protecting the Mylar/Dacron net MLI with crinkled Kapton layers, to determine the upper temperature limit for Mylar/Dacron net, and to compare the performance of embossed Kapton MLI with that of the Mylar/Dacron net type.¹ The Galileo spacecraft ended up using a mixture of both varieties, either separately or as a hybrid, but with the majority being of the Mylar/Dacron net construction.² For Cassini, an MLI layup consisting of 20 layers of embossed Kapton and appropriate outer and inner layers was once considered to be the baseline design, because Kapton can withstand temperatures in excess of 400°C. However, higher cost and inferior thermal performance (i.e., higher effective emittance, as reported in Ref. 6) of the all-embossed Kapton MLI relative to Mylar/Dacron net prompted a redirection of the baseline. In the current design, this all-embossed Kapton layup, designated the high-

temperature layup, will be used only at locations of extremely high temperatures, such as in the vicinity of the RTG and the main engine. A hybrid "standard layup," consisting of 5 layers of embossed Kapton and 15 layers of Mylar/Dacron net with appropriate outer and inner layers, will be used on over 85% of the blanketed surfaces on the spacecraft.

The verification of both layups' capability to meet all thermal requirements has been accomplished by a comprehensive test program that addressed high-temperature survivability, effective emittance, and optical and electrical properties. This article focuses on the high-temperature exposure tests that helped define the hybrid standard layup, and which demonstrated the adequacy of both layups in withstanding their respective thermal environments. Two series of high-temperature exposure tests were conducted. The first employed a small bell-jar vacuum chamber, in which the MLI samples were tested resting between a hot and a cold plate. Subjected to various boundary conditions, the samples were monitored for their temperatures and visually inspected posttest for damages. The second series of tests employed a larger chamber and a solar simulator that provided a 2.7-sun illumination on the test samples. Transient response and steady-state temperature profiles shed light on the behavior of these MLI blankets under solar exposure during spacecraft trajectory correction maneuvers.

This article will describe the MLI layup designs, test setups, and procedures, and present the test results along with pertinent interpretations.

Description and Abbreviation of MLI Layups

For the sake of clarity and convenience of discussion, the MLI constituents and layups discussed in this article will be defined and abbreviated as follows:

Constituents	
SSAK	= second surface aluminized Kapton, 0.013 mm (0.5 mil) thick, ITO (indium tin oxide) coated on the front, Nomex® scrim reinforced on the back, used for outer layer
BK	= black Kapton, carbon-filled, 0.025 mm (1 mil) thick, used for outer layer
BKn	= same as BK except Nomex scrim reinforced on the back, used for outer layer

Presented as Paper 95-0633 at the AIAA 33rd Aerospace Sciences Meeting and Exhibit, Reno, NV, Jan. 9–12, 1995; received Jan. 23, 1995; revision received June 13, 1995; accepted for publication June 13, 1995. Copyright © 1995 by the American Institute of Aeronautics and Astronautics, Inc. All rights reserved.

*Member of Technical Staff, Mechanical Systems Engineering and Research Division, 4800 Oak Grove Drive. Member AIAA.

EK	= embossed Kapton, 0.008 mm (0.33 mil) thick, aluminized on both sides, used for intermediate layer
MN	= Mylar with Dacron net, alternating layers; 0.006-mm- (0.25-mil) thick Mylar aluminized on both sides, used for intermediate layer
AK	= aluminized Kapton, 0.025 mm (1 mil) thick, aluminized on both sides, used for inner layer
Layups	
Standard layup	= blanket assembly consisting of layers SSAK + 5EK + 15MN + AK; to be used on more than 85% of the blanketed surfaces on Cassini
High-temperature layup	= blanket assembly consisting of layers BK + 20EK + AK; to be used at high-temperature locales

Temperature Limits for MLI Constituents/Layups

Temperature limits for various MLI constituents and layups are first reviewed for background information and for focusing attention on areas of vulnerability. Based on manufacturers' information and data from past test programs, "weak links" in several blanket layups are identified. Table 1 summarizes the key data pertinent to Cassini applications. The temperature data are obtained from Refs. 1–5. Several tests conducted in the past for the Galileo Project had converged to an assessment¹ that the maximum allowable temperature for Mylar/Dacron net is 220°C, which is in line with the melting point and zero-strength temperatures for these materials as indicated in Table 1. For the SSAK and BK_n outer layers, both the Kapton substrate and the Nomex scrim reinforcement have high-temperature capability, and the 3P adhesive (a polyester, polyimide and polyamide blend) is the weak link. Hence, in terms of the layups listed in Table 1, the limiting constituent for layups 1 and 2 is the 3P adhesive, and that for layups 3 and 4 is the Mylar/Dacron net. Further, it is clear from Table 1, as well as from numerous past experiences,

Table 1 Temperature limits for MLI blanket constituents and layups

Constituent	Melting point, °C	Zero strength temperature, °C	Field service temperature, °C
Kapton film	None	815	–269 to +400
Mylar film	250	248	–60 to +150
Teflon film	327	310	
Dacron net	256	245	
Nomex scrim	427		
Glass scrim	>400		
Adhesive			
3P			Maximum 200–260
Acrylic			Maximum 120
Silicone			Maximum 150
Allowable temperature range, °C			
Layup	Continuous	Intermittent	
1. SSAK + EK	–184 to +149	–184 to +260	
2. BK _n + EK	–184 to +149	–184 to +260	
3. SSAK + MN	–251 to +121	Maximum 220	
4. BK _n + MN	–251 to +121	Maximum 220	
5. BK + EK	–251 to +288	–251 to +399	

Data sources: DuPont Technical Information Bulletins, Sheldahl Red Book, and past JPL tests.

that cold temperatures of outer space are of no concern for these layups.

Bell-Jar Tests

Test Objectives

The objectives of these tests were to verify that both the standard and high-temperature layups can survive the 0.61-AU thermal environment and to determine the number of embossed Kapton layers necessary to protect the Mylar/Dacron net layers.

Test Article, Setup, and Procedure

The bell-jar vacuum chamber has an approximate height of 0.91 m and diameter of 0.46 m (Fig. 1). It houses a test assembly that consists of a hot plate on the top, a cold plate at the bottom, and an MLI blanket sample sandwiched between the two, as shown in Fig. 2. All three are of approximate

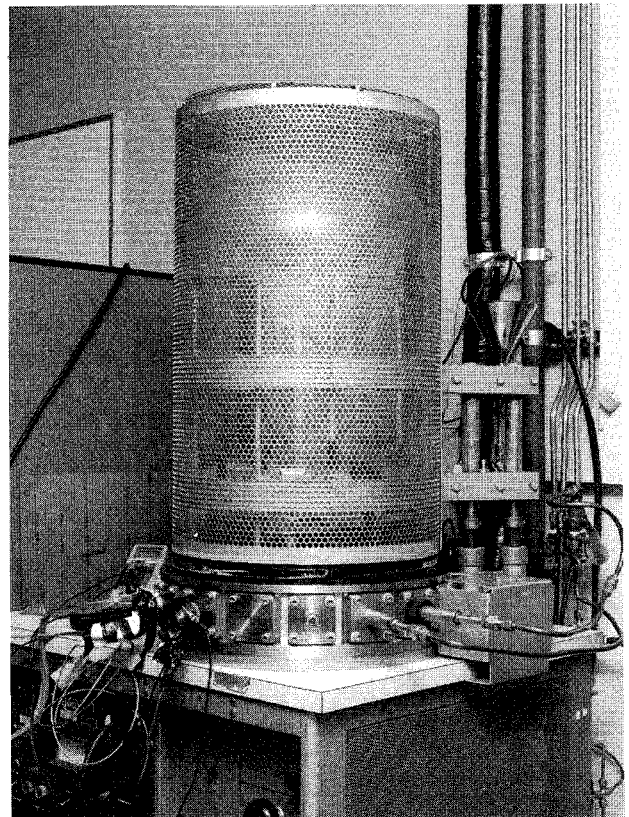


Fig. 1 Bell-jar vacuum chamber.

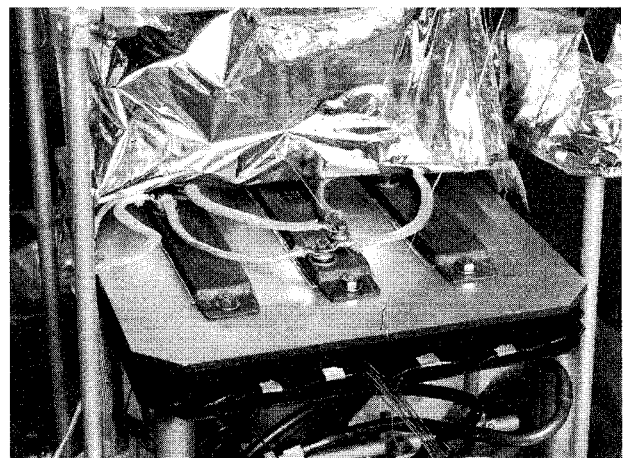


Fig. 2 Hot plate, MLI sample and cold plate.

dimensions 0.3×0.3 m with truncated corners. The aluminum hot plate was 0.64 cm thick, painted black on the bottom side, equipped with three Chromalox® strip heaters, and suspended from a stand. The copper cold plate was roughly 0.16 cm thick, painted black on the top side, fitted with serpentine copper tubing to circulate coolant, and was supported with four short struts from the floor of the chamber. The electric strip heaters were made of chrome steel sheath, each capable of dissipating 400 W and sustaining 650°C.

The space between the hot and cold plates was adjustable, allowing the MLI sample to rest freely on the cold plate. Three MLI blanket samples were tested: 1) the standard layup; 2) a layup consisting of SSAK + 10EK + 15MN + AK, to investigate the effects of the additional five layers of embossed Kapton; and 3) the high-temperature layup. The MLI sample typically appeared as shown in Fig. 3, with thermocouples mounted in the center region of various layers. The blankets were only partially seamed, so as to allow thermocouple at-

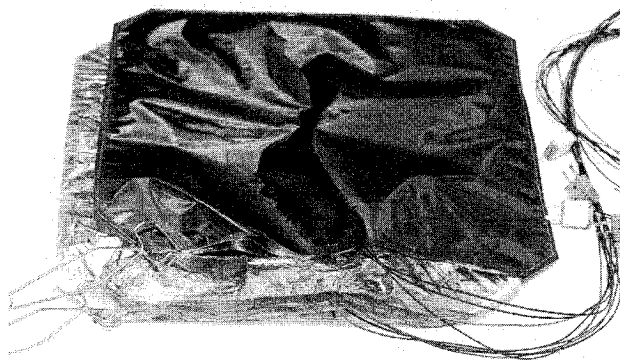


Fig. 3 MLI test sample with thermocouples.

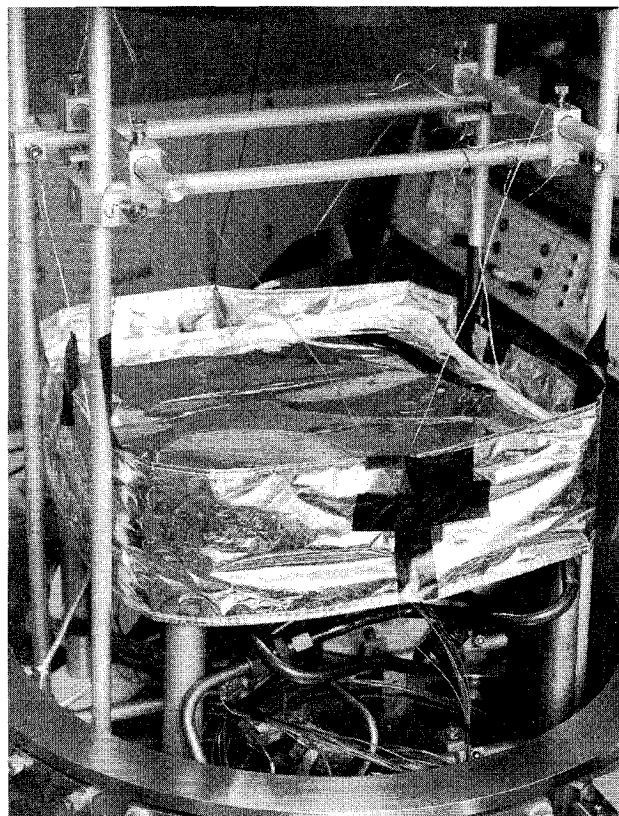


Fig. 4 Test assembly.

tachment/removal and posttest inspection. The thermocouples were of type E (Chromel constantan), gauge 30, and with either Teflon® or fiberglass wrapping, the latter being reserved for higher-temperature locations.

For a typical test run, after the MLI sample is properly installed, the hot plate was covered on top and the test assembly surrounded along the periphery by MLI blankets to prevent heat loss (Fig. 4). Heat was driven from the hot to the cold plate through the MLI sample in a predominantly unidirectional flow. The intent was to heat the hot plate to the point that the top layer of the MLI blanket could be maintained at the target level (250°C for the standard layup, and above 350°C for the high-temperature layup). For most test runs, the cold plate was kept at about 15°C by the circulating tap water. However, film heaters were mounted on the cold plate so that on occasion the plate could be controlled to a higher temperature to simulate a warm hardware surface.

The chamber pressure during a test ranged from 1×10^{-4} to 4×10^{-5} torr. Test conditions were held constant for several hours once steady state was approached. Upon completion of the test the chamber was opened and the MLI sample inspected. Temperature, power, and pressure data were recorded by a data logger.

Results

The standard layup was tested under the conditions with the hot plate at 254°C and the cold plate at 14 and 46°C, respectively. The steady-state temperature profiles across the blanket layers during the 3–4 h of exposure are shown in Fig. 5. The two lower curves that almost coincide with each other were obtained from tests done with the same boundary conditions on two different days, with a chamber break and blanket inspection in between; reproducibility of the test results is good. The upper curve was obtained with a warmer cold plate temperature (46°C) to simulate a warm hardware condition. The top Mylar layer temperature is seen to be below 185°C in all three cases, which is well below the limit of 220°C for Mylar. Considering that the outer layer temperature in flight is predicted to be under 200°C for all but the high-temperature locales on the spacecraft, these results indicate that the standard layup possesses a substantial margin as far as high-temperature survivability is concerned. In addition, inspection of the blanket sample following each of the three tests revealed no visible damage. The white polyester tape along the edges of the blanket turned brown; this is attributed primarily to outgassing from the aged thermocouple wrapping, which will not be present in flight. Also, Mylar shrinkage appeared to be 0.64 cm out of 30.5 cm, or 2%, confirming manufacturer's data and previous test results.

Figure 6 presents the test results that illustrate the effects of adding five layers of embossed Kapton. A comparison of Figs. 5 and 6 indicates that the temperature of the top Mylar layer is reduced by 40°C as a result (i.e., from 180 to 140°C). This is a significant gain in terms of added protection to the Mylar layers and can be exploited where beneficial. However,

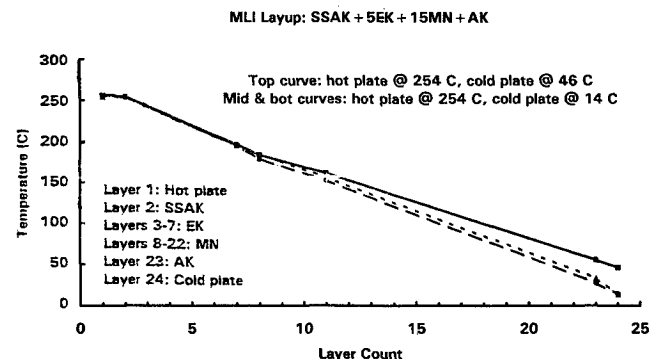


Fig. 5 Steady-state temperature profiles across the standard layup.

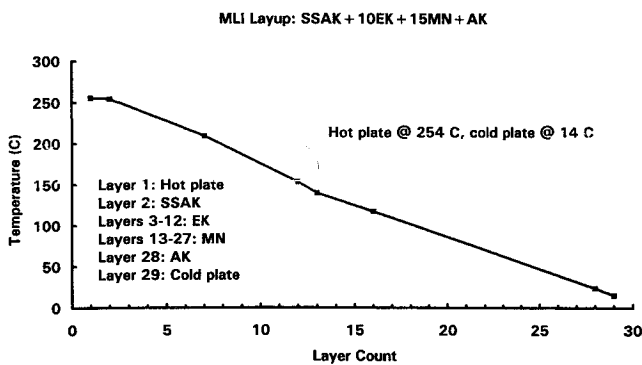


Fig. 6 Effect of adding five additional layers of embossed Kapton.

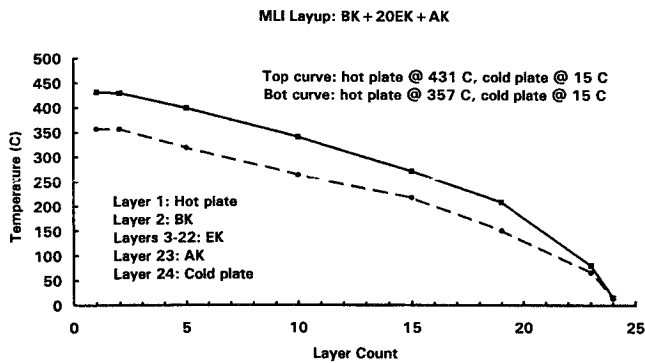


Fig. 7 Steady-state temperature profiles across the high-temperature layup.

for most Cassini applications the standard layup is adequate with the substantial margins already demonstrated.

The high-temperature layup was tested with the cold plate maintained at around 15°C and the hot plate at 357 and 431°C, respectively. The steady-state temperature profiles are presented in Fig. 7. It is obvious that these temperature levels are well within the capability of the Kapton films. Furthermore, posttest inspections revealed no visible damage. After two hours of exposure at these steady temperatures, the black Kapton outer layer still appeared intact, smooth, and shiny. All the embossed Kapton layers with the raised embossed patterns were intact; the annealing, i.e., flattening out, of crinkled Kapton layers observed at high temperatures in past tests did not occur here.

It is worthwhile to note the following by-product information that also resulted from the tests.

1) The strip heater temperatures during the last test ranged between 460–520°C, and five layers in the central region of the cover blanket (i.e., that which covered the top of the hot plate and, hence, in partial contact with the strip heaters) were completely disintegrated into ashes. The cover blanket was made of aluminized and embossed Kapton layers. This illustrated the destructibility of Kapton at temperatures somewhere above 430°C.

2) The skirt blanket around the test assembly was of the Mylar/Dacron net construction. The inside layers were melted through at several places. Although there were no temperature measurements made, this serves to indicate the destructibility of Mylar and the manner of its destruction.

3) Severe outgassing took place, especially during the last test when the temperatures were the highest. Gluey, dark brown deposits occurred in large amounts along the edges of the cold plate and the MLI sample, and on the cold water tubing, the skirt blanket, and other cold spots. In contrast, all the hot surfaces were clean. The sources of outgassing included the adhesives, the brown Kapton tape, the thermocouple wrapping, and others, most of which are not expected to be present in flight. This serves to underscore the

importance of outgassing considerations in blanket materials selection, especially in high-temperature regions.

Solar Simulator Tests

Test Objectives

The objectives of these tests were to determine the response of the standard layup and the high-temperature layup under the 2.7-sun illumination by a solar simulator, and to verify that the blankets can withstand the 2.7-sun exposure for at least 30 min, corroborating the bell-jar tests.

Test Article, Setup, and Procedure

The solar exposure tests were performed on the heels of a series of tests that were designed to determine the effective emittance of the MLI layups (the latter results are reported in Ref. 6). The MLI blankets were tested wrapping around a 0.23-m-cubed aluminum box that was heated from within. The box was made of 0.32-cm-thick aluminum 6061-T6 plates, painted black on the inside, and with film heaters and thermocouples mounted on the inside that can heat and control the box to near uniform temperature at various levels. Two MLI layups were tested: 1) the standard and 2) the high-temperature layups, as described before. The MLI test samples were instrumented with thermocouples at selected locations, and at various layers on the side that was to be illuminated by the solar simulator. Figure 8 shows an MLI sample and the box. The box had Mylar standoffs (3.8 cm high) attached on all surfaces; the standoffs space off the blankets to satisfy a micrometeoroid protection requirement.

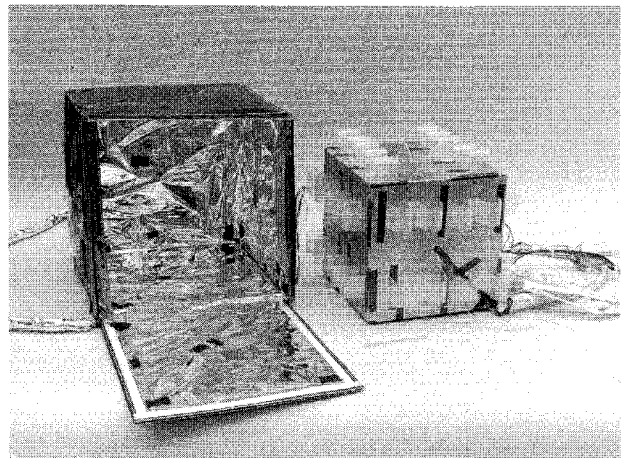


Fig. 8 MLI sample and the aluminum box with Mylar standoffs.

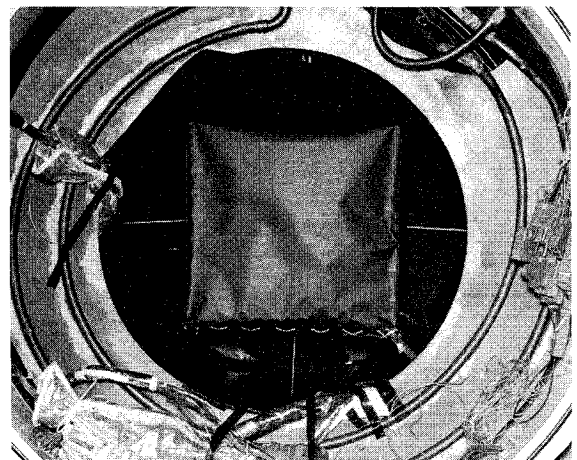


Fig. 9 MLI test article suspended in the vacuum chamber.

The tests were done in a 91-cm-diam, LN₂-cooled vacuum chamber. Figure 9 shows the assembled test article suspended in the chamber with an annular door shroud that allowed the light beams from the solar simulator to come through. The solar simulator was a SpectroLab product, Mark III X25, calibrated to provide 3675 W/m² of irradiance (i.e., 2.7 suns) on the illuminated blanket surface. The chamber was cooled to below -180°C and the pressure maintained at low to high 10⁻⁷ torr during the tests. Typically, when these conditions were reached, the solar simulator was turned on. Power input to the box was adjusted and temperatures at the box as well as all the blanket layers were monitored. After steady state was attained and held for at least one or two hours, the test was terminated. Steady state was operationally defined as a state when all temperatures changed at a rate of less than 0.3°C/h. Upon completion of the test, at chamber break, the test article was removed from the chamber, disassembled, and inspected visually to determine if damages or changes had occurred.

Results

When the solar simulator was turned on, the outer layer temperature changed almost instantaneously, while the innermost layers took up to an hour to respond. This implies that for trajectory correction maneuvers that last no longer than 30 min, no thermal effect from solar exposure on blanketed hardware should be expected. The steady-state temperature profiles across layers of the illuminated blanket typically decrease monotonically toward the hardware. Figure 10 shows the results from three tests that were conducted with the standard layup. The three tests differed principally in the box temperatures, which turned out to affect only the inner layer temperatures. The SSAK outer layer temperature of 200°C is somewhat higher than predicted for a blanket surface viewing the outer space exclusively, because during the test, the blanket viewed the cold annular door shroud as well as the warmer quartz window (estimated to be 40–60°C on the

Table 2 Optical properties before and after solar exposure

Outer layer material	Unexposed sample		Exposed sample	
	α_s	ϵ_h	α_s	ϵ_h
SSAK	0.29	0.66	0.34	0.51
BK	0.92	0.81	0.92	0.80

average). However, for blanket surfaces that also view other parts of the spacecraft, the temperature of 200°C may not be too far removed from reality. The important point, however, is that Fig. 10 indicates that both the Mylar and Kapton layers will be able to survive the 2.7-sun illumination at 0.61 AU, with substantial margins (i.e., in excess of 80°C). Again, post-test inspection revealed no visible damage to any layer.

Steady-state temperature profiles for the high-temperature layup under solar illumination are displayed in Fig. 11. The black Kapton outer layer temperature is 250°C, and the underlying embossed Kapton layers have monotonically decreasing temperatures toward the box. The 250°C is somewhat higher than predicted for a totally space-viewing blanket, but is significantly lower than if the additional heat source of the RTG or main engine is applied.

Absorptivity and Emissivity of Outer Layers

The absorptivity and emissivity of the outer layers (SSAK and BK) were measured before and after the solar exposure. They are presented in Table 2 under the headings "unexposed sample" and "exposed sample," the latter meaning after 8 h of cumulated exposure to 2.7 suns. It is clear that the exposure caused appreciable changes to the SSAK, but almost no change to the BK.

Conclusions

The standard and high-temperature MLI layups being baseline for the Cassini spacecraft have been described. They have been subjected to two series of tests to ascertain their high-temperature survivability. The bell-jar series of tests demonstrated that the standard layup is capable of withstanding an outer layer temperature of 250°C and the high-temperature layup can withstand 430°C. No visible damage occurred to either blanket and all layer temperatures were well within the allowable limits for the constituent materials. The five embossed Kapton layers in the standard layup were shown to provide adequate protection for the 15 underlying Mylar/Dacron net layers; the top Mylar layer temperature was 180°C, substantially below the material limit of 220°C, even with the conservative outer layer temperature.

The solar simulator series of tests demonstrated that both layups can survive the 2.7-sun exposure. Under the simulated 0.61-AU conditions, the SSAK outer layer attained a temperature of 200°C, and the BK outer layer, 250°C. These temperatures, although somewhat conservative due to the warm quartz window the outer layers viewed during the tests, are in line with calculations based on a realistic range of absorptivity and emissivity values for the materials. The two series of tests corroborate to establish that both layups will be able to survive, with substantial margins, the severest high-temperature environments that the Cassini mission will present.

Acknowledgments

The work described in this article was carried out by the Jet Propulsion Laboratory, California Institute of Technology, under a Contract with NASA. The authors wish to thank R. Reeve for the various technical discussions held throughout the test phases. The successful completion of these tests would not have been possible without the efforts of the following contributors: J. Real for fabricating and installing the blan-

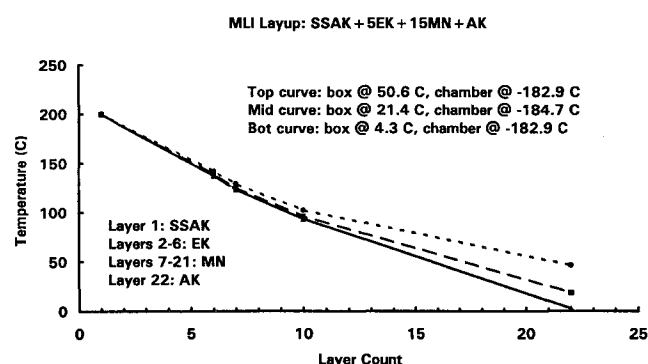


Fig. 10 Steady-state temperature profiles across the standard layup under 2.7-sun illumination.

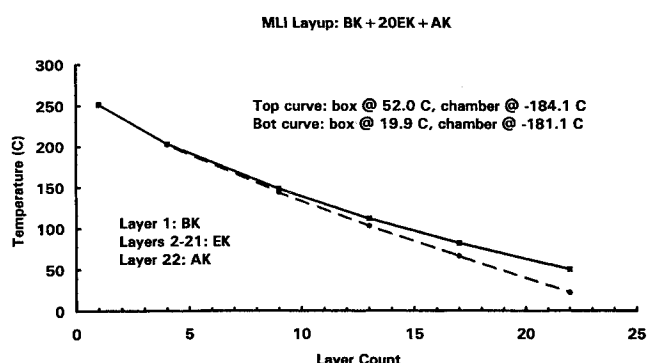


Fig. 11 Steady-state temperature profiles across the high-temperature layup under 2.7-sun illumination.

kets; W. Walker for assisting with the bell-jar tests; R. Okamoto and the Building 18 personnel for fabricating test fixtures; A. Burrows, P. Martin, G. Laugen, and their assistants for operating the vacuum chamber and solar simulator; L. Johnson and H. Winter for fabricating thermocouples; T. Fisher, E. Bailey, and D. Perry for data acquisition; and P. Stevens for measuring optical properties.

References

¹Irwin, T. W., 1982, Cagle, C., 1987, and Mireles, V., 1988, Internal JPL Memoranda, MLI Test Results, California Inst. of Technology, Pasadena, CA.

²Reeve, R. T., "Thermal Redesign of the Galileo Spacecraft for a VEEGA Trajectory," *Journal of Spacecraft and Rockets*, Vol. 28, No. 2, 1991, pp. 130–138.

³DuPont Technical Information Bulletins X-267 (Fibers), M-2C and M-2D (Mylar), and H-2 (Kapton).

⁴*Sheldahl Red Book*, Thermal Control Material and Metalized Films, Sheldahl, Northfield, MN, July 1989.

⁵Whitt, R., and O'Donnell, T., "Thermal Control Film Materials for High Temperature and Deep Space Applications," 33rd National SAMPE Symposium, Anaheim, CA, March 1988.

⁶Lin, E. I., Stultz, J. W., and Reeve, R. T., "Test-Derived Effective Emittance for Cassini MLI Blankets and Heat Loss Characteristics in the Vicinity of Seams," AIAA Paper 95-2015, June 1995.