

Cross-Linked Layered Structure of Magnetically Ordered $[\text{Fe}(\text{TCNE})_2] \cdot z \text{CH}_2\text{Cl}_2$ Determined by Rietveld Refinement of Synchrotron Powder Diffraction Data**

Jae-Hyuk Her, Peter W. Stephens,* Konstantin I. Pokhodnya, Michael Bonner, and Joel S. Miller*

In memory of Robert W. Parry

Since the report of the first organic-based magnet $[\text{Fe}(\text{C}_5\text{Me}_5)_2]^{+}[\text{TCNE}]^{-}$ (TCNE = tetracyanoethylene),^[1] organic-based materials have been synthesized with enhanced and controllable magnetic properties.^[2] $[\text{V}(\text{TCNE})_x] \cdot z \text{CH}_2\text{Cl}_2$ ($x \approx 2$; $z \approx 0.5$) prepared by the reaction of TCNE and $[\text{V}(\text{C}_6\text{H}_6)_2]$ ^[3a] or $[\text{V}(\text{CO})_6]$ ^[3b] is an amorphous organic magnet with a ferrimagnetic ordering temperature (T_c) of approximately 400 K. Solvent-free thin films of $[\text{V}(\text{TCNE})_x]$ have been prepared by chemical vapor deposition and show similar magnetic behavior.^[4] Magnetotransport studies indicate that electrons in valence and conduction bands of $[\text{V}(\text{TCNE})_x]$ are spin polarized, which suggests that it could be suitable for “spintronic” applications.^[5]

With the goal of identifying new organic-based magnets, $[\text{Fe}(\text{TCNE})_2] \cdot z \text{CH}_2\text{Cl}_2$ ($T_c \approx 100$ K)^[6a,b] was prepared through the reaction of TCNE and FeI_2 ^[6c] or $[\text{Fe}(\text{CO})_5]$,^[6b] and $[\text{Mn}(\text{TCNE})_2] \cdot z \text{CH}_2\text{Cl}_2$ ($T_c \approx 75$ K)^[6d] was formed from the reaction of TCNE and MnI_2 .^[6c] Albeit important, the structures of $[\text{M}(\text{TCNE})_2] \cdot z \text{CH}_2\text{Cl}_2$ ($\text{M} = \text{V}, \text{Mn}, \text{Fe}$) have been elusive because of the unavailability of single crystals. Herein, we report the structure of $[\text{Fe}(\text{TCNE})_2] \cdot z \text{CH}_2\text{Cl}_2$ determined from synchrotron powder diffraction data and the implications it provides with respect to the structure of the $[\text{V}(\text{TCNE})_x]$ room temperature magnet.

Although single crystals of the brown compounds $[\text{M}(\text{TCNE})_2] \cdot z \text{CH}_2\text{Cl}_2$ ($\text{M} = \text{Mn}, \text{Fe}$) did not form, X-ray powder diffraction (XRPD) was observed and indicated that they are isomorphous.^[6c] Thus, a high-resolution XRPD

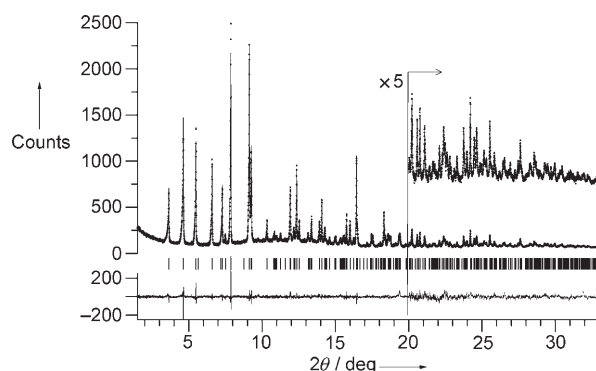


Figure 1. High-resolution synchrotron powder diffraction data (dots) and Rietveld fit of the data for $[\text{Fe}(\text{TCNE})_2] \cdot z \text{CH}_2\text{Cl}_2$ (line). The lower trace is the difference (measured–calculated) plotted against the same vertical scale.

pattern for $\text{M} = \text{Fe}$ was collected at the National Synchrotron Light Source at ambient temperature (Figure 1).^[7]

The XRPD pattern was indexed as a C-centered orthorhombic lattice by using the computer program ITO,^[8a] and the lack of further systematic absences requires the space group to be $Cmmm$, or, unlikely, one of its acentric subgroups. Real-space simulated annealing, assuming that only Fe atoms and TCNE exist in the unit cell, failed to find a solution. The solution was found by using independent atoms (i.e. no molecular shape constraint) in simulated annealing with dynamic occupancy correction in FOX,^[8b] which revealed the unexpected bonding of $[\text{TCNE}]^{-}$ as $[\text{C}_4(\text{CN})_8]^{2-}$ as well as the presence of highly disordered solvent molecules. The structure was refined by using TOPAS-Academic.^[8c] The $[\text{C}_4(\text{CN})_8]^{2-}$ moieties are disordered in sites of mmm symmetry,^[9a] and there is a significant number of disordered solvent molecules in channels running along the c axis, which could not be characterized in detail.

Rietveld refinement of these data revealed a structure consisting of six N atoms octahedrally coordinated to Fe^{II} , with adjacent octahedra canted by 15° (Figure 2). Each Fe^{II} ion bonds to four μ_4 - $[\text{TCNE}]^{-}$ anions in layers that undulate about the ac plane as a result of the canting of the octahedra. The Fe–N bond length is $2.18(2)$ Å, and the Fe–N–C angle is $173(1)^\circ$ for the four μ_4 - $[\text{TCNE}]^{-}$ anions, each bound to four Fe^{II} ions. The average C–C and C–CN bond lengths are $1.35(2)$ and $1.42(2)$ Å, respectively, and the average NC–C–

[*] J.-H. Her, Prof. P. W. Stephens
Department of Physics & Astronomy
Stony Brook University
Stony Brook, NY 11794-3800 (USA)
Fax: (+1) 631-632-8176
E-mail: peter.stephens@sunysb.edu

Dr. K. I. Pokhodnya, M. Bonner, Prof. J. S. Miller
Department of Chemistry
University of Utah
Salt Lake City, UT 84112-0850 (USA)
Fax: (+1) 801-581-8433
E-mail: jsmliller@chem.utah.edu

[**] We appreciate the assistance of E. B. Vickers and the continued partial support by the Department of Energy Division of Material Science (Grant Nos. DE-FG03-93ER45504 and DE-FG02-01ER4593). Use of the National Synchrotron Light Source, Brookhaven National Laboratory, was supported by the US Department of Energy, Office of Basic Energy Sciences, under Contract No. DE-AC02-98CH10886. TCNE = tetracyanoethylene; $T_c \approx 100$ K.

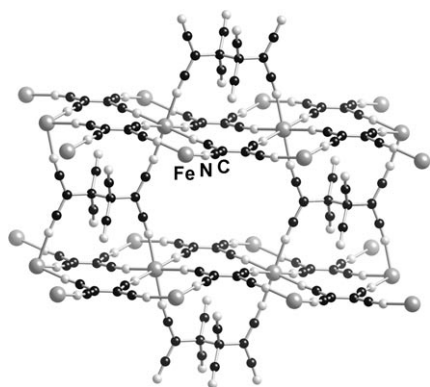


Figure 2. Structure of $[\text{Fe}(\text{TCNE})_2] \cdot z\text{CH}_2\text{Cl}_2$ (that is, $[\text{Fe}(\text{TCNE})\{\text{C}_4(\text{CN})_8\}_{1/2}] \cdot z\text{CH}_2\text{Cl}_2$, $z \approx 0.32$)^[9b] possessing undulating layers of μ_4 - $[\text{TCNE}]^-$ bound to four Fe^{II} ions, which are connected by μ_4 - $[\text{C}_4(\text{CN})_8]^{2-}$. The CH_2Cl_2 solvent molecules are disordered in the channels and not shown for clarity.

CN, C-C≡N, and C-C-CN angles are 121(1), 170(1), and 119(1)°, respectively.

From geometrical considerations, to form an extended layer structure based upon the octahedrally preferred 90° N-Fe-N angles (observed values range from 89.4° to 90.6°), the preferred 180° bonding angle of the sp-hybridized NC group to the Fe center would have to be decreased to 165°. The observed canting of the octahedra leads to undulation of the extended $\{\text{Fe}^{\text{II}}(\text{TCNE})^-\}$ plane, which decreases this deviation of the Fe-N-C angle to the observed compromise value of 173°. Hence, $[\text{M}(\text{TCNE})_2] \cdot z\text{CH}_2\text{Cl}_2$ ($\text{M} = \text{Fe}, \text{Mn}$) is best formulated as $[\text{M}(\text{TCNE})\{\text{C}_4(\text{CN})_8\}_{1/2}] \cdot z\text{CH}_2\text{Cl}_2$.

These $\{\text{Fe}^{\text{II}}(\text{TCNE})^-\}$ layers are interconnected by μ_4 - $[\text{C}_4(\text{CN})_8]^{2-}$ ligands with an Fe-N bond length of 2.16(1) Å, Fe-N-C angle of 174(1)°, and C-C-CN angles of 116(1) and 122(1)°. The backbone CCC-C and CC-CC bond lengths and C-C-C angle are 1.52(1) Å, 1.59(2) Å, and 114(1)°, respectively (Figure 2). The geometry of the μ_4 - $[\text{C}_4(\text{CN})_8]^{2-}$ ligand is comparable to that reported for $[\text{M}\{\text{C}_4(\text{CN})_8\}(\text{NCMe})_2]$ ($\text{M} = \text{Mn}, \text{Fe}$).^[10] The juxtaposition of the Fe^{II} ion and the μ_4 - $[\text{C}_4(\text{CN})_8]^{2-}$ N atoms, which prefer bonding angles of 90 and 180°, respectively, presumably contributes to the canting of the FeN_6 octahedra. This interconnecting motif has linear channels along the *c* axis (Figure 2), where the highly disordered CH_2Cl_2 solvent molecules reside.^[11]

This complex motif possesses two different forms of reduced TCNE and is the second structural characterization of μ_4 - $[\text{TCNE}]^-$,^[12,13] but occurs for the related μ_4 - $[\text{TCNQ}]^-$ ($\text{TCNQ} = 7,7,8,8$ -tetracyano-*p*-quinodimethane) as observed for tetracoordinate $[\text{M}^{\text{I}}(\text{TCNQ})]$ ($\text{M} = \text{Ag}$,^[14a] Cu ^[14b]), and $[\text{Ag}(\text{TCNQF}_4)]$.^[14c] The layer-interconnecting μ_4 - $[\text{C}_4(\text{CN})_8]^{2-}$ motif is rare,^[10,12] but the TCNQ analogue has been reported.^[15]

The presence of two different forms of reduced TCNE in the $[\text{Fe}(\text{TCNE})_2] \cdot z\text{CH}_2\text{Cl}_2$ structure is also evident in its IR spectrum, which has ν_{CN} absorptions at 2221 and 2172 cm^{-1} (Figure 3). Absorptions at 2213 and 2153 cm^{-1} are characteristic for single crystals of materials possessing of μ_4 -

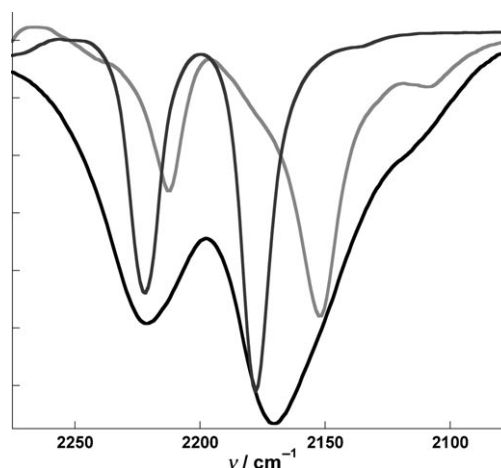


Figure 3. ν_{CN} region of the IR spectra of $[\text{Fe}(\text{TCNE})_2] \cdot z\text{CH}_2\text{Cl}_2$ ($z \approx 0.32$) (black), μ_4 - $[\text{C}_4(\text{CN})_8]^{2-}$ observed for $[\text{Fe}\{\text{C}_4(\text{CN})_8\}(\text{MeCN})_2]$ (light gray),^[10] and μ_4 - $[\text{TCNE}]^-$ present in $[\text{Fe}(\text{TCNE})(\text{NCMe})_2][\text{FeCl}_4]$ (dark gray).^[13]

$[\text{C}_4(\text{CN})_8]^{2-}$, but the shape and positions of these peaks are very sensitive to structural disorder.^[10,12] The absorptions at 2222 and 2178 cm^{-1} are assigned to μ_4 - $[\text{TCNE}]^-$ in accord with that observed for μ_4 - $[\text{TCNE}]^-$ present in $[\text{Fe}(\text{TCNE})(\text{NCMe})_2][\text{FeCl}_4]$,^[13] and the inhomogeneous broadening of both peaks from the low-energy side is attributed to the presence of μ_4 - $[\text{C}_4(\text{CN})_8]^{2-}$.

Within the layers a strong spin coupling is provided by direct exchange between the $S = 2$ Fe^{II} and the $S = 1/2$ μ_4 - $[\text{TCNE}]^-$ ions, and the layers are coupled by superexchange through the diamagnetic μ_4 - $[\text{C}_4(\text{CN})_8]^{2-}$ ligand. The latter coupling is much weaker; hence, the dominant spin exchange contributing to the magnetic ordering as a ferrimagnet at 100 K resides within the layers.

It has been noted that heating paramagnetic $[\text{M}\{\text{C}_4(\text{CN})_8\}(\text{NCMe})_2] \cdot z\text{CH}_2\text{Cl}_2$ ($\text{M} = \text{Mn}, \text{Fe}$) yields materials with magnetic properties comparable to those of the present $[\text{Fe}(\text{TCNE})_2] \cdot z\text{CH}_2\text{Cl}_2$ compound and its Mn analogue.^[10] This is attributed to breaking of the long central C-C bonds of μ_4 - $[\text{C}_4(\text{CN})_8]^{2-}$ to re-form $S = 1/2$ $[\text{TCNE}]^-$, which, owing to its ability to form direct spin exchange, can significantly enhance the spin coupling.

The present structure has implications for the interpretation of the reported saturation magnetization of $[\text{Fe}(\text{TCNE})_2] \cdot z\text{CH}_2\text{Cl}_2$ (i.e. $[\text{Fe}(\text{TCNE})\{\text{C}_4(\text{CN})_8\}_{1/2}] \cdot z\text{CH}_2\text{Cl}_2$).^[6] Albeit still slowly increasing, its $M(H)$ value at 2 K and 9 T is 16400 emu Oe mol^{-1} (Figure 4). This value is substantially higher than that expected for a spin-only $S = 2$ Fe^{II} center antiferromagnetically coupled to two $S = 1/2$ $[\text{TCNE}]^-$ ions ($M_s = 11200 \text{ emu Oe mol}^{-1}$). In contrast, the presence of $[\text{C}_4(\text{CN})_8]^{2-}$ decreases the number of antiferromagnetically coupled $[\text{TCNE}]^-$ species, and the expected M_s is 16800 emu Oe mol^{-1} , in good agreement with the observed data.

The magnitude of the pairwise spin coupling J in units of K can be calculated from the mean field expression for two different spin sites *i* and *j* [Eq. (1)] as $0.177 T_c$ with $z_{\text{TCNE}} =$

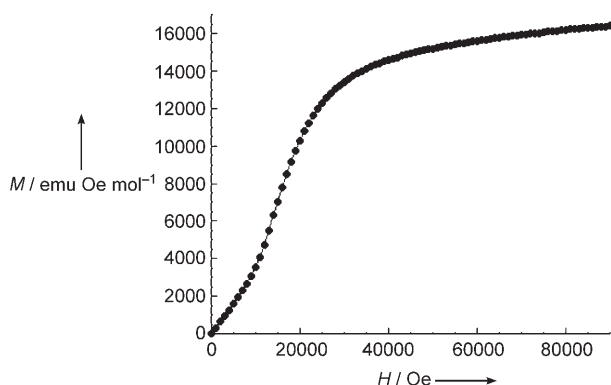


Figure 4. $M(H)$ for $[\text{Fe}(\text{TCNE})\{\text{C}_4(\text{CN})_8\}_{1/2}]\cdot\text{CH}_2\text{Cl}_2$ at 2 K. The line is a guide.

$z_{\text{Fe}} = 4$, $S_{\text{TCNE}} = 1/2$, and $S_{\text{Fe}} = 2$. As $T_c = 100$ K, $J/k_B = 17.7$ K (12.3 cm^{-1}).

$$T_c = \frac{2|J|\sqrt{z_i z_j} \sqrt{S_i(S_i + 1)S_j(S_j + 1)}}{3k_B} \quad (1)$$

The structure of $[\text{Fe}^{\text{II}}(\text{TCNE})_2]\cdot z\text{CH}_2\text{Cl}_2$ implies that the room-temperature $[\text{V}(\text{TCNE})_x]$ -based magnets most probably have V^{II} ions bridged by μ_4 - $[\text{TCNE}]^-$ ligands within a layer and are also connected by μ_4 - $[\text{TCNE}]^-$ ligands between layers and not μ_4 - $[\text{C}_4(\text{CN})_8]^{2-}$ as observed herein for $[\text{Fe}^{\text{II}}(\text{TCNE})_2]\cdot z\text{CH}_2\text{Cl}_2$. The antiferromagnetic coupling of $S = 3/2$ V^{II} to a larger number of μ_4 - $[\text{TCNE}]^-$ spins leads to the observed lower saturation moment with respect to $[\text{Fe}^{\text{II}}(\text{TCNE})_2]\cdot z\text{CH}_2\text{Cl}_2$. Alternatively, $\{\text{V}(\mu_4\text{-}[\text{TCNE}])\}^-$ layers may be interconnected by *trans*- $\{\mu\text{-}[\text{TCNE}]\}^-$ linkages. Both of the bridging moieties have one unpaired spin that can provide a strong interlayer coupling leading to the observed above-room-temperature ordering temperature.

The *trans*- $\{\mu\text{-}[\text{TCNE}]\}^-$ spin-coupling linkage has been established for the $[\text{Mn}^{\text{III}}(\text{porphyrin})]^+[\text{TCNE}]^-$ family of linear chain ferrimagnets, and depending on the dihedral angle between the $\{\text{Mn}_4\}$ and $[\text{TCNE}]^-$ planes can stabilize strong antiferromagnetic coupling [$|J|/k_B > 250$ K (175 cm^{-1}); $H = 2JS_aS_b$].^[16] Thus, although these two descriptions for the structure of $[\text{V}(\text{TCNE})_x]$ cannot be differentiated at present, both provide insight into key aspects of the structure that has been elusive. It should be noted that $[\text{V}(\text{TCNE})_x]$ is amorphous; the proposed local structural order is therefore prone to defects including the presence of $[\text{TCNE}]^{2-}$ (evident from the low-energy ν_{CN} absorption^[3]), which requires a vacant $[\text{TCNE}]^-$ site for charge balance.

Received: October 11, 2006

Published online: January 26, 2007

Keywords: iron · magnetic properties · Rietveld analysis · solid-state structures · X-ray diffraction

- [1] J. S. Miller, J. C. Calabrese, A. J. Epstein, R. W. Bigelow, J. H. Zhang, W. M. Reiff, *J. Chem. Soc. Chem. Commun.* **1986**, 1026; J. S. Miller, J. C. Calabrese, H. Rommelmann, S. Chittipeddi,

A. J. Epstein, J. H. Zhang, W. M. Reiff, *J. Am. Chem. Soc.* **1987**, 109, 769.

- [2] For example, V. I. Ovcharenko, R. Z. Sagdeev, *Russ. Chem. Rev.* **1999**, 68, 345; M. Kinoshita, *Philos. Trans. R. Soc. London Ser. A* **1999**, 357, 2855; J. S. Miller A. J. Epstein, *Chem. Commun.* **1998**, 1319; J. S. Miller A. J. Epstein, *Chem. Eng. News* **1995**, 73(40), 30; S. J. Blundell, F. L. Pratt, *J. Phys. Condens. Matter* **2004**, 16, R771; J. A. Crayston, J. N. Devine, J. C. Walton, *Tetrahedron* **2000**, 56, 7829; J. S. Miller A. J. Epstein, *Angew. Chem.* **1994**, 106, 399; *Angew. Chem. Int. Ed. Engl.* **1994**, 33, 385.
- [3] a) J. M. Manriquez, G. T. Yee, R. S. McLean, A. J. Epstein, J. S. Miller, *Science* **1991**, 252, 1415; J. S. Miller, G. T. Yee, J. M. Manriquez, A. J. Epstein, in the Proceedings of Nobel Symposium #NS-81 *Conjugated Polymers and Related Materials: The Interconnection of Chemical and Electronic Structure*, Oxford University Press, Oxford, **1993**, p. 461; *La Chim. La Ind.* **1992**, 74, 845; b) J. Zhang, J. S. Miller, C. Vazquez, P. Zhou, W. B. Brinckerhoff, A. J. Epstein, *ACS Symp. Ser.* **1996**, 644, 311.
- [4] a) K. I. Pokhodnya, A. J. Epstein, J. S. Miller, *Adv. Mater.* **2000**, 12, 410; b) K. I. Pokhodnya, D. Pejakovic, A. J. Epstein, J. S. Miller, *Phys. Rev. B* **2001**, 63, 174408.
- [5] V. N. Prigodin, N. P. Raju, K. I. Pokhodnya, J. S. Miller, A. J. Epstein, *Adv. Mater.* **2002**, 14, 1230; C. Tengstedt, M. P. de Jong, A. Kanciurawska, E. Carlegrim, M. Fahlman, *Phys. Rev. Lett.* **2006**, 96, 057209.
- [6] a) A. Girtu, C. M. Wynn, J. Zhang, J. S. Miller, A. J. Epstein, *Phys. Rev. B* **2000**, 61, 492; b) K. I. Pokhodnya, N. Petersen, J. S. Miller, *Inorg. Chem.* **2002**, 41, 1996; c) J. Zhang, J. Ensling, V. Ksenofontov, P. Gülich, A. J. Epstein, J. S. Miller, *Angew. Chem.* **1998**, 110, 676; *Angew. Chem. Int. Ed.* **1998**, 37, 657; d) C. M. Wynn, M. A. Girtu, J. Zhang, J. S. Miller, A. J. Epstein, *Phys. Rev. B* **1998**, 58, 8508.
- [7] A Si(111) double-crystal monochromator selected a highly collimated incident beam of 0.70247(5) Å at the X3B1 beamline of the National Synchrotron Light Source, Brookhaven National Laboratory. The diffracted X-rays were analyzed by a Ge(111) single-reflection crystal and detected by using a NaI scintillation counter. The powder sample was sealed in a thin-wall glass capillary and rotated during data collection for better averaging of the powder pattern data.
- [8] a) J. W. Visser, *J. Appl. Crystallogr.* **1969**, 2, 89; b) V. Favre-Nicolin, R. Cerny, *J. Appl. Crystallogr.* **2002**, 35, 734; c) Bruker AXS (2005), *TOPAS V3: General profile and structure analysis software for powder diffraction data*.—User's Manual, Bruker AXS, Karlsruhe, Germany; TOPAS-Academic is available at <http://pws.prserve.net/Alan.Coelho>.
- [9] a) Space group *Cmmm*; $a = 14.317(1)$, $b = 17.402(1)$, $c = 7.3334(5)$ Å, $V = 1827.1(4)$ Å³, $\rho_{\text{calcd}} = 1.32(1) \text{ g cm}^{-3}$, ambient temperature, $R_{\text{wp}} = 4.88$, $\chi^2 = 1.957$. CCDC-623463 contains the supplementary crystallographic data for this paper. These data can be obtained free of charge from The Cambridge Crystallographic Data Centre via www.ccdc.cam.ac.uk/data_request/cif. A refinement without disorder in the $[\text{C}_4(\text{CN})_8]^{2-}$ moieties in space group *C2/m* yields an essentially equivalent fit with $\beta = 90.000 \pm 0.003^\circ$ ($R_{\text{wp}} = 4.87$, $\chi^2 = 1.954$); the data do not distinguish between the two cases. b) $z = 0.32$ was determined from a fit to the elemental analysis.
- [10] J. Zhang, L. M. Liable-Sands, A. L. Rheingold, R. E. Del Sesto, D. C. Gordon, B. M. Burkhart, J. S. Miller, *Chem. Commun.* **1998**, 1385.
- [11] The solvent contribution cannot be determined from the XRPD data; it was modeled by one chlorine and two carbon atoms with their positions, occupancies, and thermal factors refined, and as expected their thermal parameters are very large. Because of their large thermal parameters, they only contribute to the XRPD data at low angles.

- [12] J. S. Miller, *Angew. Chem.* **2006**, *118*, 2570; *Angew. Chem. Int. Ed. Engl.* **2006**, *45*, 2508.
- [13] K. I. Pokhodnya, M. Bonner, J.-H. Her, P. W. Stephens, J. S. Miller, *J. Am. Chem. Soc.* **2006**, *128*, 15592.
- [14] a) L. Shields, *J. Chem. Soc. Faraday Trans. 2* **1985**, *81*, 1; b) R. A. Heintz, H. Zhao, X. Ouyang, G. Grandinetti, J. Cowan, K. R. Dunbar, *Inorg. Chem.* **1999**, *38*, 144; c) S. A. O'Kane, R. Clérac, H. Zhao, X. Ouyang, J. R. Galán-Mascaros, R. A. Heinz, K. R. Dunbar, *J. Solid State Chem.* **2000**, *152*, 159.
- [15] For example, H. Zhao, R. A. Heintz, X. Ouyang, K. R. Dunbar, *Chem. Mater.* **1999**, *11*, 736; V. Dong, H. Endres, H. J. Keller, W. Moroni, D. Nothe, *Acta Crystallogr. Sect. B* **1977**, *33*, 2428; S. K. Hoffmann, P. J. Corvan, P. Singh, C. N. Sethulekshmi, R. M. Metzger, W. E. Hatfield, *J. Am. Chem. Soc.* **1983**, *105*, 4608; H. Endres, H. J. Keller, W. Moroni, D. Nöthe, *Z. Naturforsch. B* **1976**, *31*, 1322; T. P. Radhakrishnan, D. Van Engen, Z. G. Soos, *Mol. Cryst. Liq. Cryst. Sci. Technol. Sect. B* **1987**, *150*, 473; R. H. Harms, H. J. Keller, D. Nöthe, M. Werner, D. Gundel, H. Sixl, Z. G. Soos, R. M. Metzger, *Mol. Cryst. Liq. Cryst.* **1981**, *65*, 179; S. Mikami, K.-i. Sugiura, J. S. Miller, Y. Sakata, *Chem. Lett.* **1999**, 413.
- [16] J. Ribas-Ariño, J. J. Novoa, J. S. Miller, *J. Mater. Chem.* **2006**, *16*, 2600.