

Regioselective Eightfold and Tenfold Additions of a Pyridine-Modified Organocopper Reagent to [60]Fullerene

Yutaka Matsuo, Kazukuni Tahara, Kouhei Morita, Keiko Matsuo, and Eiichi Nakamura*

As the interests of chemists are shifting from single molecules to molecular arrays, the workspace of chemists has expanded from the Ångström scale to the nanometer scale. Because of its size, reactivity, and high degree of symmetry, [60]fullerene is an ideal structural unit for making larger structures. The high symmetry of this molecule, however, has posed serious synthetic problems, that is, chemical reactions may take place multiple times and at various places on this molecule.^[1] The addition of an organocopper reagent to fullerenes that we reported some years ago is an exceptionally selective multiple-addition reaction that exclusively produces pentaadduct **4**.^[2,3] We became intrigued by the possibility of achieving more than five additions, for instance, tenfold additions to synthesize tenfold-substituted [60]fullerenes **1** and **2**. These are interesting molecules not only for their radially expanding multisubstitution, but also for their luminescent hoop-shaped and curved conjugation systems (colored pink, Scheme 1)^[4,5]


and their ability to form metal complexes.^[6] We report herein a one-step synthesis of these compounds by a new class of organocopper reagents. With appropriate choice of the substituent on the organic addend, the reaction also produces eightfold-substituted fullerenes **3** with very high selectivity. The reaction procedure is so simple that we can now consider the use of these compounds for further applications.

A stoichiometric mixture of ArMgX and Cu^I in THF/1,2-Cl₂C₆H₄ reacts with [60]fullerene, and the addition completely stops when the pentaadduct **4** forms as its cyclopentadienide anion. We reasoned that homoconjugation between the top cyclopentadienide moiety and the bottom 50π system causes deactivation of the latter.^[2b] To alleviate such deactivation, we developed some time ago a multistep protection/deprotection synthetic strategy, and achieved the synthesis of decaadducts **1** and **2**.^[4a] The overall yield was too poor (< 10 %) to be useful however. After extensive experimentation,

we found that the desired tenfold addition of the organocopper reaction takes place selectively when an appropriately excessive amount of pyridine is present in the reaction mixture (Table 1). Thus, while the copper reagent prepared from equimolar amounts of 4-*n*BuC₆H₄MgBr and [CuBr(SMe₂)] (30 equiv to fullerene) in an approximately 4:1 mixture of THF and 1,2-Cl₂C₆H₄ exclusively gave the pentaadduct **4a** in 99 % yield (Table 1, entry 1, 4-*n*-butyl-phenyl derivatives are denoted in the compound numbers with “a”), a mixture of the same copper reagent (30 equiv) and 300 equivalents pyridine (ca. 1:2:1 pyridine/THF/1,2-Cl₂C₆H₄) nearly exclusively gave the decaadducts **1a**

and **2a** in 92 % yield as an approximately 1:2 mixture together with trace amounts of the octaadduct **3a**. The reaction could be performed equally easily on a 50-mg or 1-g scale (see the Experimental Section). Since the two regioisomeric decaadducts **1a** and **2a** are structurally very different from each other, they could be separated rather easily by recrystallization and/or chromatography on silica gel.

The regioselectivity arises at the stage of the sixth addition of the ArCu reagent, which can take place either through path a or path b, as shown in Scheme 1. In path a the sixth to the tenth Ar groups are placed around the bottom pentagon to produce **1a**, and in path b these Ar groups are placed

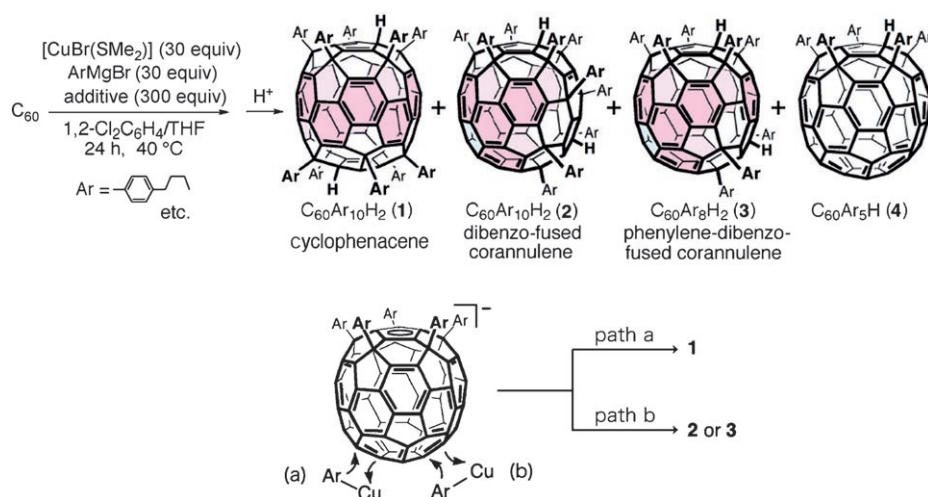

Scheme 1. Formation of octa- and decaadducts through two pathways.

[*] Dr. Y. Matsuo, Dr. K. Matsuo, Prof. E. Nakamura
Nakamura Functional Carbon Cluster Project, ERATO
Japan Science and Technology Agency
Hongo, Bunkyo-ku, Tokyo, 133-0033 (Japan)
Fax: (+ 81) 3-5800-6889
E-mail: nakamura@chem.s.u-tokyo.ac.jp

Dr. K. Tahara, K. Morita
Department of Chemistry
The University of Tokyo
Hongo, Bunkyo-ku, Tokyo, 133-0033 (Japan)

Supporting information for this article is available on the WWW under <http://www.angewandte.org> or from the author.

Table 1: Multiarylation of [60]fullerene in the presence of various additives (30 equiv 4-*n*BuCu₆H₄MgBr and 300 equiv additive).^[a]

Entry	Additive	Yield [%] ^[b]			
		1a	2a	3a	4a
1	none	0	0	0	99
2		32	60	2	5
3 ^[c]		35	6	50	1
4		3	3	2	90
5		12	27	1	60
6		32	3	15	1
7		34	1	48	1
8		3	0	1	95
9	NEt ₃	0	0	3	95
10		26	4	28	18
11		8	0	11	74
12		0	0	0	97
13	PPh ₃	0	0	0	98

[a] The reaction conditions are those in Scheme 1 unless otherwise noted. The reaction was carried out on a 20-mg scale (C₆₀). All adducts comprise isomers owing to the relative positions of the hydrogen atoms of the cyclopentadiene moieties. [b] Yield was determined by HPLC with pyrene as an internal standard. [c] 60% v/v pyridine was used.

around one of the five side pentagons to produce **2a**. The experimental ratio was found to be about 1:2 regardless of which Ar groups were used (Table 2).

The octaadduct **3a** forms when the reaction leading to **2a** prematurely finishes after the addition of the eighth Ar group likely because of steric reasons. The use of a large excess of pyridine (60% v/v pyridine, 27% v/v THF, and 13% v/v 1,2-dichlorobenzene) is a synthetically viable procedure that afforded the decaadduct **1a** (35%) and an octaadduct **3a** (50%; Table 1, entry 3). Thus, we can stop the reaction by further tuning of the basic additive. The reaction with 4-dimethylaminopyridine (Table 1, entry 6), 2,2'-bipyridine (entry 7), tetramethylethylenediamine (entry 10), or pentamethyldiethylenetriamine (entry 11) gave **3a** in preference to **2a**. Experiments on isolated adducts indicated that these additives slow down conversion of **3a** into **2a**. With hindered and less basic pyridines (Table 1, entries 4, 5, and 8) and monodentate triethylamine (entry 9), the reaction simply stopped after the fifth addition, which indicates that coordination of the nitrogen atom of pyridine to a metal atom is crucial for tenfold addition. 1,4-Dioxane, which binds to Mg^{II}, did not show any effects (Table 1, entry 12), and we surmise that the target atom is the copper atom, possibly the copper(III) intermediate, whose reductive elimination leading to C–C bond formation slows down upon coordination of a basic ligand.^[7]

The scope of this multiple-addition reaction is quite broad, as shown in Table 2. In all cases, [60]fullerene was completely consumed, and the pentaadduct **4** accounts for

Table 2: Eightfold and tenfold arylation.^[a]

Entry	Ar	t [h]	Yield [%] ^[b] (compd)		
			1	2	3
1		24	24 (1b)	50 (2b)	0
2		16	24 (1c)	42 (2c)	0
3		40	20 (1d)	45 (2d)	0
4		45	24 (1e)	48 (2e)	0
5		48	17 (1f)	27 (2f)	0
6		48	3 (1g)	0	59 (3g)
7		48	3 (1h)	0	50 (3h)
8		69	21 (1i)	34 (2i)	0
9		30	2 (1j)	7 (2j)	0
10		30	2 (1k)	4 (2k)	0

[a] The reaction conditions are described in Scheme 1 unless otherwise noted. The reaction was carried out on a 50-mg scale (C₆₀). See also the Experimental Section. [b] Yield of isolated product.

most of the rest of the product. Sterically unhindered phenyl groups (Table 2, entries 1–4) gave decaadducts **1** and **2** generally in a ratio of 1:2 in about 70% combined yield. Thus, the ten C–C bond-formation reactions took place in an average of 96.5% yield each time. A *meta*-methyl group on the Ar ring appears to exert some steric effects on the reaction to decrease the yield to 44% combined yield (Table 2, entry 5). Aryl copper reagents bearing an electron-withdrawing group that were previously found to be slow to undergo fivefold addition resisted undergoing either a tenfold- or eightfold-addition reaction (Table 2, entries 9 and 10). The reaction of MeMgBr under the same conditions stopped after the fifth addition and those of other alkyl Grignard reagents was not clean.

We also found that the regioselectivity of the multiple addition, that is, path a versus path b, can be controlled by installation of an *ortho*-methyl group to the incoming phenyl group. Thus, the *ortho*-methylphenylcopper reagent produced the octaadduct **3g** in 59% yield, very little of the D₅ decaadduct **1g**, and none of the C₂ decaadduct **2g** (Table 2, entry 6). The rest of the yield was largely a hexaadduct of unidentified structure. Similarly, an *ortho,para*-disubstituted phenyl copper reagent afforded predominantly the octaadduct **3h** (Table 2, entry 7). The *para*-methyl group may be used for further chemical modifications and chain extension. The regioselectivity between path a and path b was improved

from 1:2 to 1:20. We consider that the steric interaction between the top five Ar groups and the incoming Ar group inhibits path a, while this problem does not exist in path b.

Double-decker ruthenocene was synthesized from **1a**. Treatment of a pale-yellow THF solution of **1a** with KO^tBu (2 equiv) afforded a dark-brown dianion $[K^+(thf)_n]_2[C_{60}Ar_{10}]^{2-}$ (**5**), which reacted with $[RuCp(CH_3CN)_3]PF_6$ to give $[Ru_2(C_{60}Ar_{10})Cp_2]$ (**6**) in 11% yield of the isolated product. The crystal structure shown in Figure 1^[8] illustrates

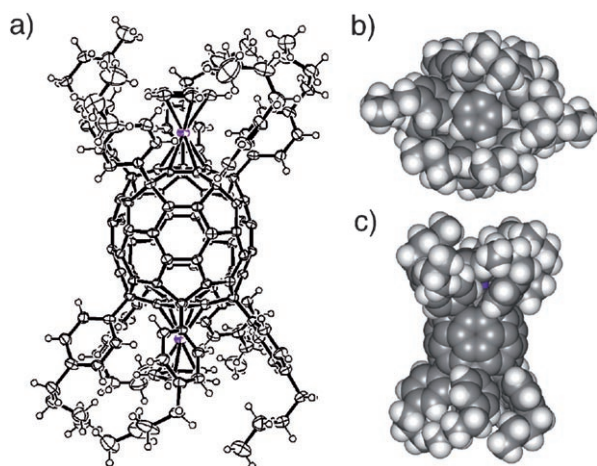


Figure 1. Crystal structure of **6**. a) ORTEP drawing with thermal ellipsoids at the 30% probability level. b) Top view of CPK model. c) Side view of CPK model.

the power of the new tenfold-addition reaction for construction of a well-defined nanostructure (ca. 3 nm along its long axis), which may serve as a useful scaffold for the synthesis of complex, functional molecular arrays. The crystal structure also indicated that the bond alternation pattern characteristic of the 40π [10]cyclophenacene moiety is retained in **6**.^[4]

The deca- and octaadducts **1**, **2**, and **3** are luminescent and emit yellow (**1a**: λ_{max} = 562 and 612 nm, bimodal), blue (**2a**: λ_{max} = 463 and 491 nm), and red (**3a**: λ_{max} = 652 and 715 nm) light (Figure 2). The luminescent quantum yields of **1a**, **2a**, and **3a** are Φ = 0.18, 0.065, and 0.015, respectively. The value of the decaaryl compound **1a** is higher than those of an unsymmetrical decaadduct $C_{60}Me_5Ph_5H_2$ (Φ = 0.10),^[4a] and much higher than those of [60]fullerene (Φ = 0.00032),^[9] monoadducts (Φ = 0.0006–0.0012),^[10] and hexaadducts (Φ = 0.024)^[11] reported in the literature. The origin of the difference of the quantum efficiency as well as the emission wavelength will be an interesting subject of future photo-physical studies.

In summary, we have developed a new pyridine-modified Grignard-based organocopper reagent that undergoes additions to [60]fullerene to the ultimate tenfold-addition stage through two regioisomeric pathways. The reaction may be stopped prematurely at the eightfold-addition stage by increasing the amount of pyridine or by the use of an *ortho*-methylated phenyl Grignard reagent. The one-step multiple functionalization of [60]fullerene can be carried out in a synthetically viable yield, and the products possess intriguing

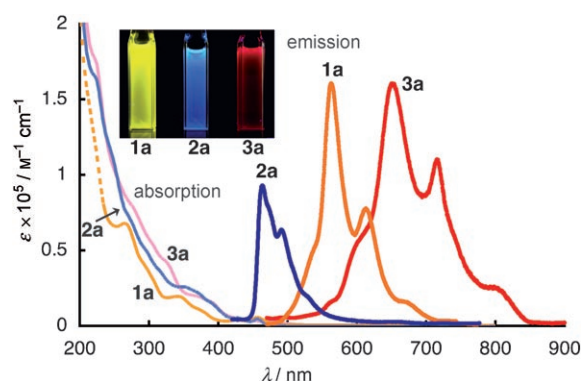


Figure 2. Absorption and emission (excited at λ = 366 nm) spectra of **1a–3a**. Intensities (arbitrary units) of emission spectra for **2a** and **3a** are magnified by factors of 3 and 5, respectively; inset: pictures of photoluminescence for **1a–3a**.

structures and physical properties. The results raise the hope that the reaction will be applicable to multifunctionalization of higher fullerenes and carbon nanotubes. We can envision the use of the reported compounds for host–guest complex formation^[12] and for applications in the field of catalysis and materials research.

Experimental Section

1a and 2a (1-g scale): Pyridine (34 mL) was added to a mixture of an organocopper reagent prepared from 4-*n*BuC₆H₄MgBr (0.95 M, 45 mL, 42 mmol) and $[CuBr(SMe_2)]$ (8.64 g, 42 mmol) in THF (44 mL) by syringe at 30 °C. To this dark-green suspension was added a solution of C₆₀ (1.0 g, 1.4 mmol) in 1,2-Cl₂C₆H₄ (40 mL). The resulting dark-brown suspension was gradually warmed to 40 °C over 30 min. The reaction was monitored by HPLC (RPF fullerene, Develosil; eluent: 1:1 toluene/acetonitrile), which indicated the formation of **1a** (retention time 6.5 min) and **2a** (retention time 9.2 min) after 40 h. The reaction was quenched with aqueous HCl (ca. 1 M, ca. 1 mL), and the solvent was removed under reduced pressure. The mixture was diluted with toluene (ca. 200 mL) and filtered through a pad of silica gel. An orange-colored eluent was evaporated to a solid, and the crude mixture was dissolved in the mixed solvent 1:1 toluene/acetonitrile (ca. 1000 mL). The yellow suspension was filtered and washed three times with the same mixed solvent to obtain **1a** (570 mg, 20%) as a yellow solid. The filtrate was evaporated to an orange solid and dissolved in 1:1 toluene/acetonitrile (ca. 100 mL), then subjected to treatment with preparative HPLC (RPF fullerene, Develosil; eluent: 1:1 toluene/acetonitrile; flow rate: 20 mL min⁻¹). Compound **2a** was separated (retention time 19 min) and recrystallized with CS₂ and ethanol to obtain the desired product (1.1 g, 40%) as an orange solid.

Experimental details for compounds **1b–k**, **2b–f**, **2i–k**, **3a**, **3g**, **3h**, **5**, and **6** and X-ray data are supplied in the Supporting Information.

Received: November 29, 2006

Published online: March 6, 2007

Keywords: copper · cyclophenacenes · fluorescence · fullerenes · ruthenium

[1] a) A. Hirsch, *Synthesis* **1995**, 895–913; b) F. Diederich, C. Thilgen, *Science* **1996**, 271, 317–323; c) M. Prato, *J. Mater. Chem.* **1997**, 7, 1097–1109; d) F. Diederich, R. Kessinger, *Acc.*

- Chem. Res.* **1999**, 32, 537–545; e) R. Taylor, *Lecture Notes on Fullerene Chemistry. A Handbook for Chemists*, Imperial College Press, London, **1999**; f) A. Hirsch, M. Brettreich, *Fullerenes, Chemistry and Reactions*, Wiley-VCH, Weinheim, **2005**.
- [2] a) M. Sawamura, H. Iikura, E. Nakamura, *J. Am. Chem. Soc.* **1996**, 118, 12850–12851; b) H. Iikura, S. Mori, M. Sawamura, E. Nakamura, *J. Org. Chem.* **1997**, 62, 7912–7913; c) M. Sawamura, H. Iikura, T. Ohama, U. E. Hackler, E. Nakamura, *J. Organomet. Chem.* **2000**, 599, 32–36; d) Y.-W. Zhong, Y. Matsuo, E. Nakamura, *Org. Lett.* **2006**, 8, 1463–1466; e) Y. Matsuo, A. Muramatsu, K. Tahara, M. Koide, E. Nakamura, *Org. Synth.* **2006**, 83, 80–87.
- [3] a) S. Zhou, C. Burger, B. Chu, M. Sawamura, M. Nagahama, M. Toganoh, U. E. Hackler, H. Isobe, E. Nakamura, *Science* **2001**, 291, 1944–1947; b) M. Sawamura, K. Kawai, Y. Matsuo, K. Kanie, T. Kato, E. Nakamura, *Nature* **2002**, 419, 702–705; c) E. Nakamura, H. Isobe, *Acc. Chem. Res.* **2003**, 36, 807–815; d) Y. Matsuo, A. Muramatsu, Y. Kamikawa, T. Kato, E. Nakamura, *J. Am. Chem. Soc.* **2006**, 128, 9586–9587.
- [4] a) E. Nakamura, K. Tahara, Y. Matsuo, M. Sawamura, *J. Am. Chem. Soc.* **2003**, 125, 2834–2835; b) Y. Matsuo, K. Tahara, E. Nakamura, *Org. Lett.* **2003**, 5, 3181–3184; c) Y. Matsuo, K. Tahara, M. Sawamura, E. Nakamura, *J. Am. Chem. Soc.* **2004**, 126, 8725–8726; d) Y. Matsuo, E. Nakamura, *J. Am. Chem. Soc.* **2005**, 127, 8457–8466.
- [5] a) R. Hoffmann, *Int. J. Phil. Chem.* **2003**, 9, 7–10; b) M. Randic, *Chem. Rev.* **2003**, 103, 3449–3605; c) L. T. Scott, *Angew. Chem.* **2003**, 115, 4265–4267; *Angew. Chem. Int. Ed.* **2003**, 42, 4133–4135.
- [6] Y. Matsuo, K. Tahara, E. Nakamura, *J. Am. Chem. Soc.* **2006**, 128, 7154–7155.
- [7] E. Nakamura, S. Mori, *Angew. Chem.* **2000**, 112, 3902–3924; *Angew. Chem. Int. Ed.* **2000**, 39, 3750–3771.
- [8] CCDC-629131 contains the supplementary crystallographic data for this paper. The data can be obtained free of charge from the Cambridge Crystallographic Data Centre via www.ccdc.cam.ac.uk/data_request.cif.
- [9] a) M. Lee, O.-K. Song, J.-C. Seo, D. Kim, Y. D. Suh, S. M. Jin, S. K. Kim, *Chem. Phys. Lett.* **1992**, 196, 325–329; b) D. Kim, M. Lee, *J. Am. Chem. Soc.* **1992**, 114, 4429–4430.
- [10] a) R. M. Williams, J. M. Zwier, J. W. Verhoeven, *J. Am. Chem. Soc.* **1995**, 117, 4093–4099; b) S.-K. Lin, L.-L. Shiu, K.-M. Chien, T.-Y. Luh, T.-I. Lin, *J. Phys. Chem.* **1995**, 99, 105–111; c) Y.-P. Sun, G. E. Lawson, J. E. Riggs, B. Ma, N. Wang, D. K. Moton, *J. Phys. Chem. A* **1998**, 102, 5520–5528; d) C. Luo, M. Fujitsuka, A. Watanabe, O. Ito, L. Gan, Y. Huang, C. H. Huang, *J. Chem. Soc. Faraday Trans.* **1998**, 94, 527–532; e) Y. Matsubara, H. Muraoka, H. Tada, Z. Yoshida, *Chem. Lett.* **1996**, 373–374.
- [11] a) G. Schick, M. Levitus, L. Kvetko, B. A. Johnson, I. Lamparth, R. Lunkwitz, B. Ma, S. I. Khan, M. A. Garcia-Garibay, Y. Rubin, *J. Am. Chem. Soc.* **1999**, 121, 3246–3247; b) K. Hutchison, J. Gao, G. Schick, Y. Rubin, F. Wudl, *J. Am. Chem. Soc.* **1999**, 121, 5611–5612.
- [12] Y. Matsuo, A. Muramatsu, R. Hamasaki, N. Mizoshita, T. Kato, E. Nakamura, *J. Am. Chem. Soc.* **2004**, 126, 432–433.