

# Reversible Switching of Lamellar Liquid Crystals into Micellar Solutions using CO<sub>2</sub>\*\*

Jianling Zhang, Buxing Han,\* Wei Li, Yueju Zhao, and Minqiang Hou

Surfactants have the ability to self-assemble into morphologically different structures, such as micelles, vesicles, and liquid crystals. The functions and properties of surfactant systems depend strongly on their microstructures. Therefore, surfactant assemblies have wider applications in different fields of chemical engineering, material science, biology, environmental science, food industry, detergents, and enhanced oil recovery.<sup>[1]</sup> Such applications are due to the desired functionalities that can be achieved by tuning the microstructures. With regular array of surfactant bilayers alternating with water layers, lamellar liquid crystals are anisotropic and highly viscous, which is very different from isotropic and much less viscous micellar solutions.<sup>[2,3]</sup> Switching the phase transition between lamellar liquid crystal (L<sub>a</sub>) and micellar solution (L<sub>1</sub>) is very interesting because these two kinds of surfactant assemblies are used for soaps and detergents,<sup>[4]</sup> drug delivery,<sup>[5]</sup> model membranes,<sup>[6]</sup> and as template for the synthesis of nanosized materials.<sup>[7–9]</sup> Many different methods can be used to induce the phase transition between the lamellar liquid crystal and the micellar solution, including variation of temperature and surfactant concentration, and addition of co-surfactants, inorganic salts or hydrocarbons.<sup>[10,11]</sup> However, additives, such as co-surfactants and salts, can lead to economic and environmental costs. Furthermore, contamination and/or modification of products because of additives should also be taken into consideration. Development of effective, controllable, economical, and environmentally benign methods to switch the phase transition between the lamellar liquid crystal phase and the micellar solution is therefore challenging and of great importance.

Supercritical or compressed CO<sub>2</sub> has received much attention in recent years because of its availability, low cost, nonflammability, and low toxicity. Compressed CO<sub>2</sub> has been widely used in different fields, such as extraction and fractionation,<sup>[12]</sup> chemical reactions and material science,<sup>[13,14]</sup> controlling the stability of reverse micelles,<sup>[15]</sup> induction of nanoemulsions,<sup>[16]</sup> creating microemulsions with CO<sub>2</sub> as continuous phase,<sup>[17–20]</sup> changing membrane fluidity and melting

point of liposome system,<sup>[21]</sup> and tuning the properties of organic solvents.<sup>[22]</sup>


Herein, we present the phase transition between L<sub>a</sub> and L<sub>1</sub> phases using a compressed CO<sub>2</sub> and AOT/water system. The possible mechanism for the CO<sub>2</sub>-induced phase transition is also discussed. The phase diagram and microstructure of AOT/water system has previously been studied in detail.<sup>[23–25]</sup> This phase transition is very interesting from both scientific and practical points of the view. CO<sub>2</sub> can induce the L<sub>a</sub>→L<sub>1</sub> phase transition at ambient temperature, whereas the phase transition occurs at or above 140 °C in the absence of CO<sub>2</sub> for the surfactant concentration used herein (the AOT/water binary phase diagram is shown in Figure S1 in the Supporting Information). The CO<sub>2</sub>-induced L<sub>a</sub>→L<sub>1</sub> phase transition is reversible, and can easily be realized by the application of and release of pressure. As the gas can be easily removed by release of pressure, the post-processing steps are easier. The conventional post-processing steps comprise removal of additives, such as co-surfactants and salts that usually cause contamination or modification of products. Furthermore, this method is environmentally benign.

We studied the phase behavior of AOT/water (1:1 by weight) lamellar liquid crystal in the presence of CO<sub>2</sub> at 290.7 K and at different CO<sub>2</sub> pressures. Figure 1A shows photographs of the liquid crystals at different pressures. All the photographs were taken after stopping the stirrer for 30 minutes. In the low pressure range, the viscosity of the system was very high and gradually decreased with the addition of CO<sub>2</sub> (photographs a–c). Interestingly, as the pressure reached an optimum value, the sample suddenly lost its viscoelasticity and changed into a transparent fluid (photographs d and e). The phase transition from liquid crystal to isotropic fluid was reversible and could be repeated by controlling the pressure (photographs f and g). After releasing CO<sub>2</sub>, the fluid solution shown in photograph d changed into the L<sub>a</sub> phase as shown in photograph f, and the transparent fluid formed again after CO<sub>2</sub> was recharged (photograph g). The viscosity of the AOT/water system at different CO<sub>2</sub> pressures indicates a dramatic decrease in the viscosity over a narrow pressure range. However, the viscosity remained constant upon further application of pressure (Figure 1B). This result is in agreement with the direct phase transition as observed in Figure 1A. The pressure at which the viscosity becomes independent of pressure is termed as the phase transition pressure, *P*<sub>T</sub>.


X-ray scattering is one of the most useful techniques to characterize the lamellar structure.<sup>[26]</sup> Figure 2 shows the X-ray scattering spectra of the AOT/water system (1:1 by weight) at different CO<sub>2</sub> pressures. In the absence of CO<sub>2</sub>, the X-ray scattering spectrum is typical of the lamellar liquid

[\*] Dr. J. Zhang, Prof. B. Han, W. Li, Y. Zhao, Dr. M. Hou  
Beijing National Laboratory for Molecular Sciences  
Institute of Chemistry  
Chinese Academy of Sciences (P.R. China)  
Fax: (+86) 10-62559373  
E-mail: hanbx@iccas.ac.cn

[\*\*] This work is supported by the National Natural Science Foundation of China (20633080), the K.C.Wong Education Foundation, Hong Kong, and the Chinese Academy of Sciences (KJCX2.YW.H16). The X-ray scattering experiments were conducted at Beijing Synchrotron Radiation Facility (BSRF) with the help of Drs. Z. Li and Z. Wu.

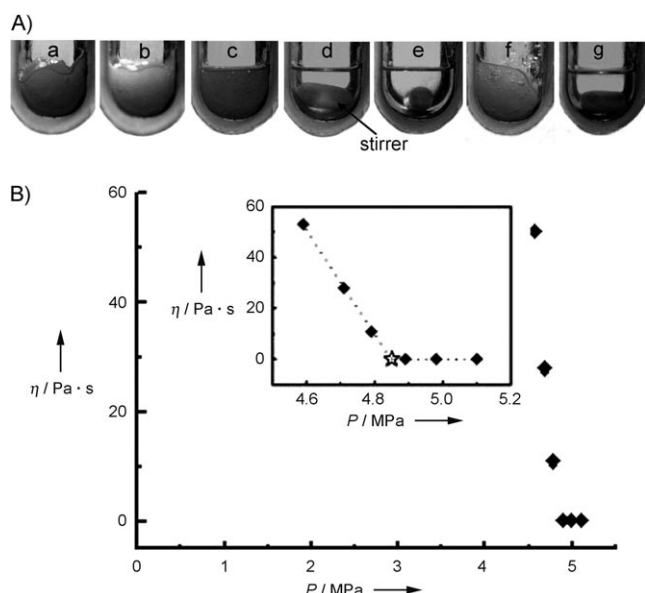

**Figure 1.** A) Photographs of the AOT/water system (1:1 by weight) a) without CO<sub>2</sub>, and at CO<sub>2</sub> pressures of b) 3.09 MPa, c) 4.36 MPa, d) 4.85 MPa, and e) 5.07 MPa at 290.7 K. Photographs f and g correspond to d after releasing of CO<sub>2</sub> and pressurization to 4.85 MPa again, respectively. B) Viscosity of the AOT/water system (1:1 by weight) at different CO<sub>2</sub> pressures and at 290.7 K. The viscosity is too large to be determined in the pressure range of 0–4.5 MPa. The inset shows the magnified viscosity versus pressure curve in the pressure range of 4.5–5.2 MPa, where ☆ is the phase transition pressure  $P_T$ .

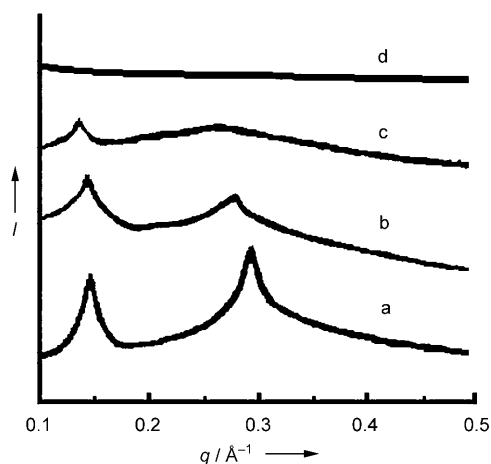


**Figure 2.** X-ray scattering curves of the AOT/water system (1:1 by weight) a) without CO<sub>2</sub> and at different CO<sub>2</sub> pressures of b) 2.70 MPa, c) 3.81 MPa, and d) 4.90 MPa, respectively.

crystal, with the first- and second-order Bragg peaks between 0.1 and 0.5 Å<sup>-1</sup>, and the ratio of the relative positions  $q_2/q_1$  is close to 1:2 (Figure 2a). The lamellar period ( $d = 2\pi/q$ ) is 44 Å, which is consistent with literature values.<sup>[27]</sup> Upon addition of CO<sub>2</sub>, gradual changes were observed in the scattering spectra. At pressures of 2.70 and 3.81 MPa (Figure 2b and c, respectively), the Bragg peaks moved to the lower-angle vector, corresponding to the enlarged spacing values of 46 Å and 50 Å, respectively. This result indicates that CO<sub>2</sub> can swell the lamellar period. In particular, at

3.81 MPa, the first- and the second-order Bragg peaks appear to be suppressed, which suggests the partial short-range disruption of the lamellar structure; however, in the long range, the lamellar structure is preserved. At 4.90 MPa, which is higher than the phase transition pressure, no Bragg peaks were observed, as expected for an isotropic solution. Thus, the results from X-ray scattering measurements give further support to the CO<sub>2</sub>-induced phase transition from anisotropic liquid crystal to isotropic fluid. Furthermore, electrical conductivities of the AOT/water system at different CO<sub>2</sub> pressures were determined, which give further evidence to the  $L_\alpha \rightarrow L_1$  phase transition (Supporting Information, Figure S2).

The effects of CO<sub>2</sub> on the AOT/water lamellae at different AOT concentrations were also studied. For AOT/water lamellar liquid crystals with AOT concentrations of 50, 60, 65, and 70 wt%,  $P_T$  increased with the increasing AOT concentration (Supporting Information, Figure S3). Furthermore, the effect of CO<sub>2</sub> on the AOT/water lamellae at different temperatures was studied, and an increase in  $P_T$  with increasing temperature was observed (Figure S4). This effect is most likely due to the solubility of CO<sub>2</sub> in the system, which according to Henry's law decreases with increasing temperature.

Surfactant assemblies have been widely used as soft templates for the synthesis of different materials.<sup>[28–30]</sup> The morphologies of the products synthesized can also reflect the microstructure of the surfactant assemblies. Therefore, we synthesized gold nanostructures in AOT/water lamellar liquid crystal and AOT/water/CO<sub>2</sub> micelles using the hydrophilic precursor of HAuCl<sub>4</sub>. We found that the surfactant AOT can effectively reduce HAuCl<sub>4</sub>, and no additional reducing reagent was required. Without the addition of CO<sub>2</sub>, large gold plates 10–30 μm in size were formed, which can be clearly observed from the SEM and TEM images (Figure 3a, b). The electron diffraction (ED) pattern shown as an inset in

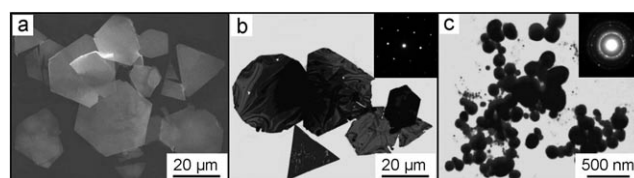


**Figure 3.** a) SEM and b) TEM images of gold plates prepared in AOT/H<sub>2</sub>O lamellar liquid crystal (1:1 by weight) without CO<sub>2</sub>. c) TEM image of gold particles prepared in AOT/H<sub>2</sub>O/CO<sub>2</sub> system at 4.98 MPa. The insets of b and c are the corresponding electron diffraction patterns.

Figure 3b confirms that these plates have fcc single-crystalline gold structures and have  $\langle 111 \rangle$  orientation.<sup>[31,32]</sup> The formation of gold plates is consistent with the structure of the lamellar template. However, at 4.98 MPa, spherical gold particles were obtained (Figure 3c), which aggregated significantly and the size distribution is in the 3–300 nm range. This aggregation is due to the continuous phase of water under the given conditions, and the template effect of lamellae on the reduction of hydrophilic HAuCl<sub>4</sub> is com-

pletely lost. The ED pattern in the inset of the TEM image shows that the obtained gold particles are polycrystalline.

Apart from the gold particles, silica structures were also synthesized from AOT/water lamellar liquid crystals and AOT/water/CO<sub>2</sub> micelles, respectively. The hydrophobic tetraethyl orthosilicate (TEOS) was used as the silica precursor, which can provide further insights into the hydrophobic domain of surfactant assemblies. In the absence of CO<sub>2</sub>, a small amount of hydrochloric acid was added to the AOT/water-lamellar liquid crystal containing TEOS to accelerate the hydrolysis of TEOS. Clearly, silica film was obtained without CO<sub>2</sub>, as can be seen from the SEM and TEM images (Figure 4a, b). The film appears to be wrinkled,

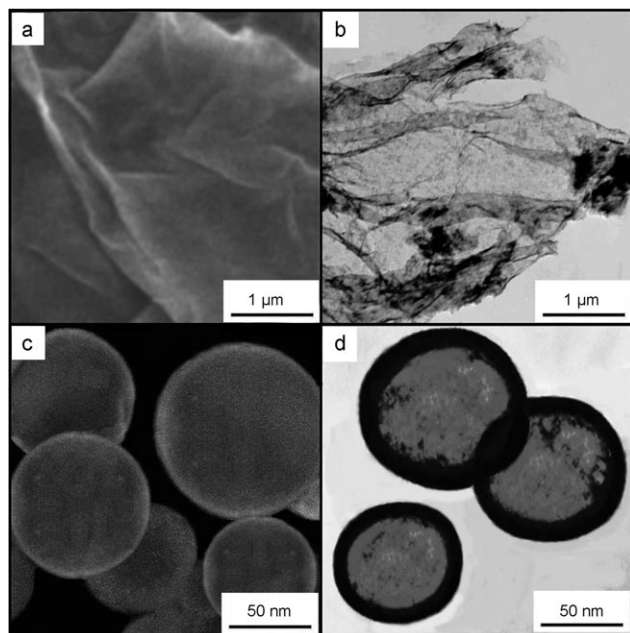


**Figure 4.** SEM and TEM images of silica particles prepared in the AOT/water system (1:1 by weight) without CO<sub>2</sub> (a and b) and at 5.50 MPa (c and d).

mainly because of their large size and small thickness. In the presence of CO<sub>2</sub>, no additional catalyst was added, because CO<sub>2</sub> can dissolve in water and partially ionized to form acid ( $\text{H}_2\text{O} + \text{CO}_2 = \text{H}^+ + \text{HCO}_3^-$ ), which can be used as a catalyst for the hydrolysis reaction of TEOS.<sup>[33]</sup> At 5.50 MPa (higher than  $P_T$ ), hollow silica spheres about 50–100 nm in size were obtained (Figure 4c, d). A mechanism of CO<sub>2</sub>-in-water interface templating can explain the formation of hollow silica, similar to those formed in CO<sub>2</sub>-in-water emulsions.<sup>[34]</sup> Thus, the synthesis of gold and silica structures serve as examples that demonstrate the tuning of morphologies in materials by inducing phase transition with compressed CO<sub>2</sub>. Indirectly, the syntheses support the fact that CO<sub>2</sub> can cause the  $L_\alpha \rightarrow L_1$  phase transition.

The mechanism for this interesting phenomenon of CO<sub>2</sub>-switching  $L_\alpha \rightarrow L_1$  phase transition is of great importance. As mentioned above, CO<sub>2</sub> can be ionized in water to change the acidity of water. To clarify the effect of carbonation of CO<sub>2</sub> with water on the  $L_\alpha \rightarrow L_1$  phase transition, hydrochloric acid

solutions of pH 3–7 were used to replace water in the experiment without CO<sub>2</sub>. The system was typical of the  $L_\alpha$  phase structure, indicating that the ionization of CO<sub>2</sub> in water is not the reason for the  $L_\alpha \rightarrow L_1$  phase transition. It has been reported that compressed CO<sub>2</sub> can be inserted into the surfactant tail region of Triton X-100/cyclohexane reverse micelles, which affects the stability of the reverse micelles.<sup>[15]</sup> As CO<sub>2</sub> is a small nonpolar molecule, it can accumulate in the hydrophobic region of liposome bilayers and change the membrane fluidity.<sup>[21]</sup> To obtain more information on the mechanism, the effect of  $P_T$  on a series of alcohols with different alkyl chain lengths was studied. The amount of alcohol was as low as 0.02 mL/1 g (AOT + water), which does not induce the phase transition. As shown in Figure 5a, the

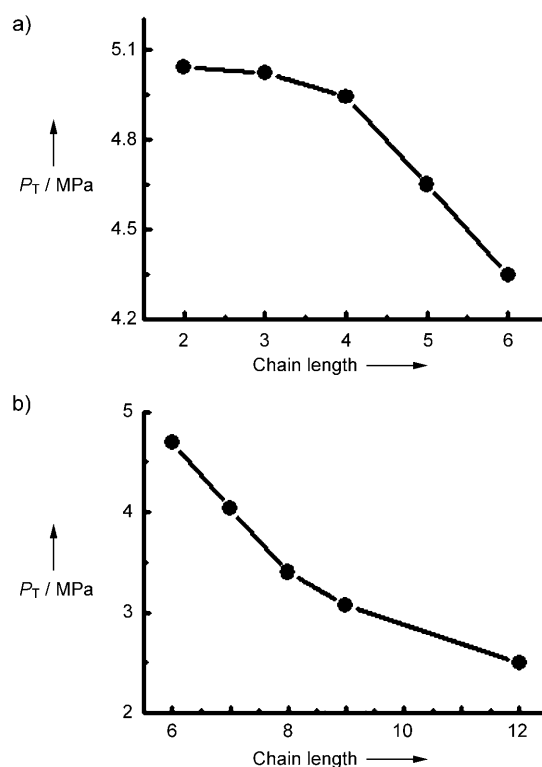


**Figure 5.** Phase-transition pressures ( $P_T$ ) of a) AOT/H<sub>2</sub>O/*n*-alcohol and b) AOT/H<sub>2</sub>O/*n*-alkane at 290.7 K. The weight ratio of AOT to water is 1:1, and the volume of alcohol (or alkane) is 0.02 mL/1 g (AOT + water).

effect of ethanol and 1-propanol, which are water soluble, have a very limited effect on the phase transition pressure. However, *n*-butanol, 1-pentanol and *n*-hexanol, of which the solubility in water is 7.7 wt%, 1.7 wt%, and nearly zero, respectively, reduce the phase transition pressure considerably, and  $P_T$  increases with the increasing alkyl chain length. It can be expected that the alcohols are distributed in between the bilayers and the water layers, the larger alcohols existing preferentially in the bilayer region. Therefore, it can be deduced that an alcohol with longer chain has more significant effect on the bilayers and has a lesser effect on the water layers. Furthermore, the effect of *n*-alkanes on the phase transition pressure was also studied (Figure 5b). The phase

transition pressure decreases markedly with the size of the hydrocarbon chains, which can be expected as the larger alkanes have significant effects on the structure of the bilayers. All of the above studies suggest that the change of the properties of the bilayers is the main reason for the phase transition.

On the basis of the above results, we proposed a possible mechanism for the  $L_\alpha \rightarrow L_1$  phase transition, which is shown in Scheme 1. In the absence of  $\text{CO}_2$ , AOT/water system is in the

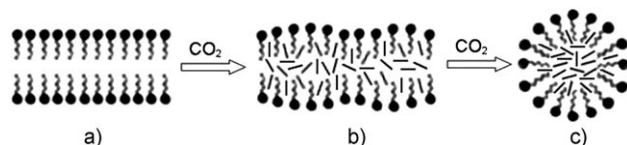

**Scheme 1.** A possible mechanism for the  $L_\alpha \rightarrow L_1$  phase transition induced by compressed  $\text{CO}_2$ . a) Without  $\text{CO}_2$ , and at pressure b) lower and c) higher than  $P_T$ .

$L_\alpha$  phase region, that is, the hydrocarbon tails of the surfactant form the inner part of the bilayer, whereas the ionic heads of the surfactants are strongly hydrated by water and constitute the outer surface of the bilayer (Scheme 1a). Compressed  $\text{CO}_2$  can easily be inserted into the hydrophobic surfactant bilayer of the lamellar  $L_\alpha$  phase, even deep inside the tail region of the surfactant (Scheme 1b). As  $\text{CO}_2$  is very soluble in hydrocarbons, its insertion changes the structure of the bilayers. With increasing pressure of  $\text{CO}_2$ , the ordering structure of  $L_\alpha$  phase is disrupted, and a more thermodynamically stable micellar solution in water as a continuous phase is formed in presence of excess  $\text{CO}_2$  (Scheme 1c). The viscosity of the micellar solution is much lower than the lamellar liquid crystal because the viscosity of water is relatively low, and water acts as the continuous phase. Insight into the detailed mechanism for this phenomenon should be studied further.

In summary, we found that compressed  $\text{CO}_2$  can induce the  $L_\alpha \rightarrow L_1$  phase transition of AOT/water system reversibly at ambient temperature by controlling the pressure. In the absence of  $\text{CO}_2$ , the  $L_\alpha \rightarrow L_1$  phase transition temperature for the studied system is more than  $140^\circ\text{C}$ . The ambient-temperature transition is advantageous because of its simplicity and low-energy consumption. The possible mechanism for this phenomenon is based on insertion of  $\text{CO}_2$  into the hydrophobic region of the lamellae. We intend to study detailed mechanism in future. The  $\text{CO}_2$ -controlled phase transition between surfactant assemblies may have wider applications in material synthesis, polymerization, and chemical reactions.

### Experimental Section

The apparatus for the phase-behavior investigation was similar to that used previously for studying reverse micelle solutions at elevated pressure.<sup>[35]</sup> In a typical experiment, the suitable amount of AOT/water mixture was added into the view cell, and the mixture was stirred. After thermal equilibrium was reached,  $\text{CO}_2$  was charged into the view cell to a suitable pressure, and the phase behavior was observed. The high-pressure falling-ball viscometer and the procedures to determine the viscosity of AOT/water system were similar to those reported previously.<sup>[36]</sup> In a typical experiment, the suitable

amount of AOT/water mixture was charged into the cylindrical viscometer. After the system had reached thermal equilibrium,  $\text{CO}_2$  was compressed into the system until desired pressure was reached. The fall time of the falling ball was determined at equilibrium conditions, which was confirmed by the fact that the viscosity and pressure were independent of equilibration time. The viscosity of  $\text{CO}_2$ /AOT/water mixture was calculated by the equation of  $\eta = K(\rho_0 - \rho)t$ , where  $\rho_0$  and  $\rho$  are the density of the falling ball and the liquid phase, respectively.  $t$  denotes the fall time of the falling ball, and  $K$  is the instrument parameter. The standard oils of different viscosities provided by National Standard Bureau of China were used for calibration. X-ray scattering experiments were carried out at Beijing Synchrotron Radiation Facility (BSRF). The X-ray wavelength used was  $1.54 \text{ \AA}$ . In a typical experiment, the suitable amount of AOT/water mixture was added into the high-pressure cell.  $\text{CO}_2$  was then charged into the system until the suitable pressure was reached. After equilibrium had been reached, X-ray scattering data were recorded.

For the synthesis of gold (or silica), the desired amount of  $\text{HAuCl}_4 \cdot 4\text{H}_2\text{O}$  (or TEOS) was added into the AOT/water mixture (1:1 by weight), and  $\text{CO}_2$  was charged into the autoclave to the desired pressure under stirring. After reaction for 24 h,  $\text{CO}_2$  was released. The products were separated by centrifugation and washed by ethanol for several times. For comparison, gold and silica were also synthesized in the absence of  $\text{CO}_2$ . The SEM images were taken on a scanning electron microscopy (SEM, Hitachi-530). The TEM images and ED pattern were recorded on a JEOL JEM-2010 transmission electron microscopy operating at 200 kV.

Received: July 31, 2008

Published online: November 19, 2008

**Keywords:** carbon dioxide · liquid crystals · micelles · phase transitions · supercritical fluids

- [1] D. F. Evans, H. Wennerstrom, *The Colloid Domain: Where Physics, Chemistry, Biology and Technology Meet*, VCH Publishers, New York, **1994**.
- [2] *Handbook of Liquid Crystals* (Eds.: D. Demus, J. W. Goodby, G. W. Gray, H.-W. Spiess, V. Vill), Wiley-VCH, Weinheim, **1998**.
- [3] J. W. Goodby, *Curr. Opin. Solid State Mater. Sci.* **1999**, *4*, 361.
- [4] N. E. Prieto, W. Lilienthal, P. L. Tortorici, *J. Am. Oil Chem. Soc.* **1996**, *73*, 9.
- [5] N. Laurent, D. Lafont, F. Dumoulin, P. Boullanger, G. Mackenzie, P. H. J. Kouwer, J. W. Goodby, *J. Am. Chem. Soc.* **2003**, *125*, 15499.
- [6] J. M. Brake, M. K. Daschner, Y.-Y. Luk, N. L. Abbott, *Science* **2003**, *302*, 2094.
- [7] G. S. Attard, J. C. Glyde, C. G. Goltner, *Nature* **1995**, *378*, 366.
- [8] G. S. Attard, P. N. Bartlett, N. R. B. Coleman, J. M. Elliott, J. R. Owen, J. H. Wang, *Science* **1997**, *278*, 838.
- [9] S. I. Stupp, P. V. Braun, *Science* **1997**, *277*, 1242.
- [10] M. Gradzielski, *Curr. Opin. Colloid Interface Sci.* **2003**, *8*, 337.
- [11] M. Gradzielski, H. Hoffmann, D. Langevin, *J. Phys. Chem.* **1995**, *99*, 12612.
- [12] L. A. Blanchard, D. Hancu, E. J. Beckman, J. F. Brennecke, *Nature* **1999**, *399*, 28.
- [13] P. G. Jessop, W. Leitner, *Chemical Synthesis Using Supercritical Fluids*, Wiley-VCH, Weinheim, **1999**.
- [14] M. Poliakoff, J. M. Fitzpatrick, T. R. Farren, P. T. Anastas, *Science* **2002**, *297*, 807.
- [15] D. Shen, R. Zhang, B. X. Han, Y. Dong, W. Wu, J. L. Zhang, J. C. Liu, T. Jiang, Z. M. Liu, *Chem. Eur. J.* **2004**, *10*, 5123.
- [16] J. L. Zhang, B. X. Han, C. X. Zhang, W. Li, X. Y. Feng, *Angew. Chem.* **2008**, *120*, 3054; *Angew. Chem. Int. Ed.* **2008**, *47*, 3012.

- [17] T. A. Hoefling, R. M. Enick, E. J. Beckman, *J. Phys. Chem.* **1991**, 95, 7127.
- [18] E. J. Beckman, *Science* **1996**, 271, 613.
- [19] K. P. Johnston, K. L. Harrison, M. J. Clarke, S. M. Howdle, M. P. Heitz, F. V. Bright, C. Carlier and T. W. Randolph, *Science* **1996**, 271, 624.
- [20] J. Eastoe, S. Gold, S. Rogers, P. Wyatt, D. C. Steytler, A. Gurgel, R. K. Heenan, X. Fan, E. J. Beckman, R. M. Enick, *Angew. Chem.* **2006**, 118, 3757; *Angew. Chem. Int. Ed.* **2006**, 45, 3675.
- [21] D. B. Geoffrey, L. K. Barbara, J. S. Herbert, E. N. Sue, *Langmuir* **2005**, 21, 530.
- [22] P. G. Jessop, B. Subramaniam, *Chem. Rev.* **2007**, 107, 2666.
- [23] J. Rogers, P. A. Winsor, *Nature* **1967**, 216, 477.
- [24] K. Fontell, *J. Colloid Interface Sci.* **1973**, 44, 318.
- [25] L. Coppola, R. Muzzalupo, G. A. Ranieri, M. Terenzi, *Langmuir* **1995**, 11, 1116.
- [26] H. F. Gleeson, L. S. Hirst, *ChemPhysChem* **2006**, 7, 321.
- [27] C. Yang, X. Chen, H. Qiu, W. Zhuang, Y. Chai, J. Hao, *J. Phys. Chem. B* **2006**, 110, 21735.
- [28] D. Sun, A. E. Riley, A. J. Cadby, E. K. Richman, S. D. Korlann, S. H. Tolbert, *Nature* **2006**, 441, 1126.
- [29] X. Meng, T. Yokoi, D. Lu, T. Tatsumi, *Angew. Chem.* **2007**, 119, 7942; *Angew. Chem. Int. Ed.* **2007**, 46, 7796.
- [30] Y. Lu, *Angew. Chem.* **2006**, 118, 7826; *Angew. Chem. Int. Ed.* **2006**, 45, 7664.
- [31] X. Sun, S. Dong, E. Wang, *Angew. Chem.* **2004**, 116, 6520; *Angew. Chem. Int. Ed.* **2004**, 43, 6360.
- [32] L. Wang, X. Chen, J. Zhan, Y. Chai, C. Yang, L. Xu, W. Zhuang, B. Jing, *J. Phys. Chem. B* **2005**, 109, 3189.
- [33] C. X. Zhang, J. L. Zhang, X. G. Zhang, X. Y. Feng, J. Chen, B. X. Han, G. Y. Yang, *J. Supercrit. Fluids* **2007**, 42, 142.
- [34] J. W. Wang, Y. D. Xia, W. X. Wang, R. Mokaya, M. Poliakoff, *Chem. Commun.* **2005**, 210.
- [35] X. Y. Feng, J. L. Zhang, J. Chen, B. X. Han, D. Shen, *Chem. Eur. J.* **2006**, 12, 2087.
- [36] Z. M. Liu, W. Z. Wu, B. X. Han, Z. X. Dong, G. Y. Zhao, J. Q. Wang, T. Jiang, G. Y. Yang, *Chem. Eur. J.* **2003**, 9, 3897.