


Selective Knockout of Gold Active Sites**

Anna Maria Nowicka, Ulrich Hasse, Gustav Sievers, Mikołaj Donten, Zbigniew Stojek, Stephen Fletcher, and Fritz Scholz**

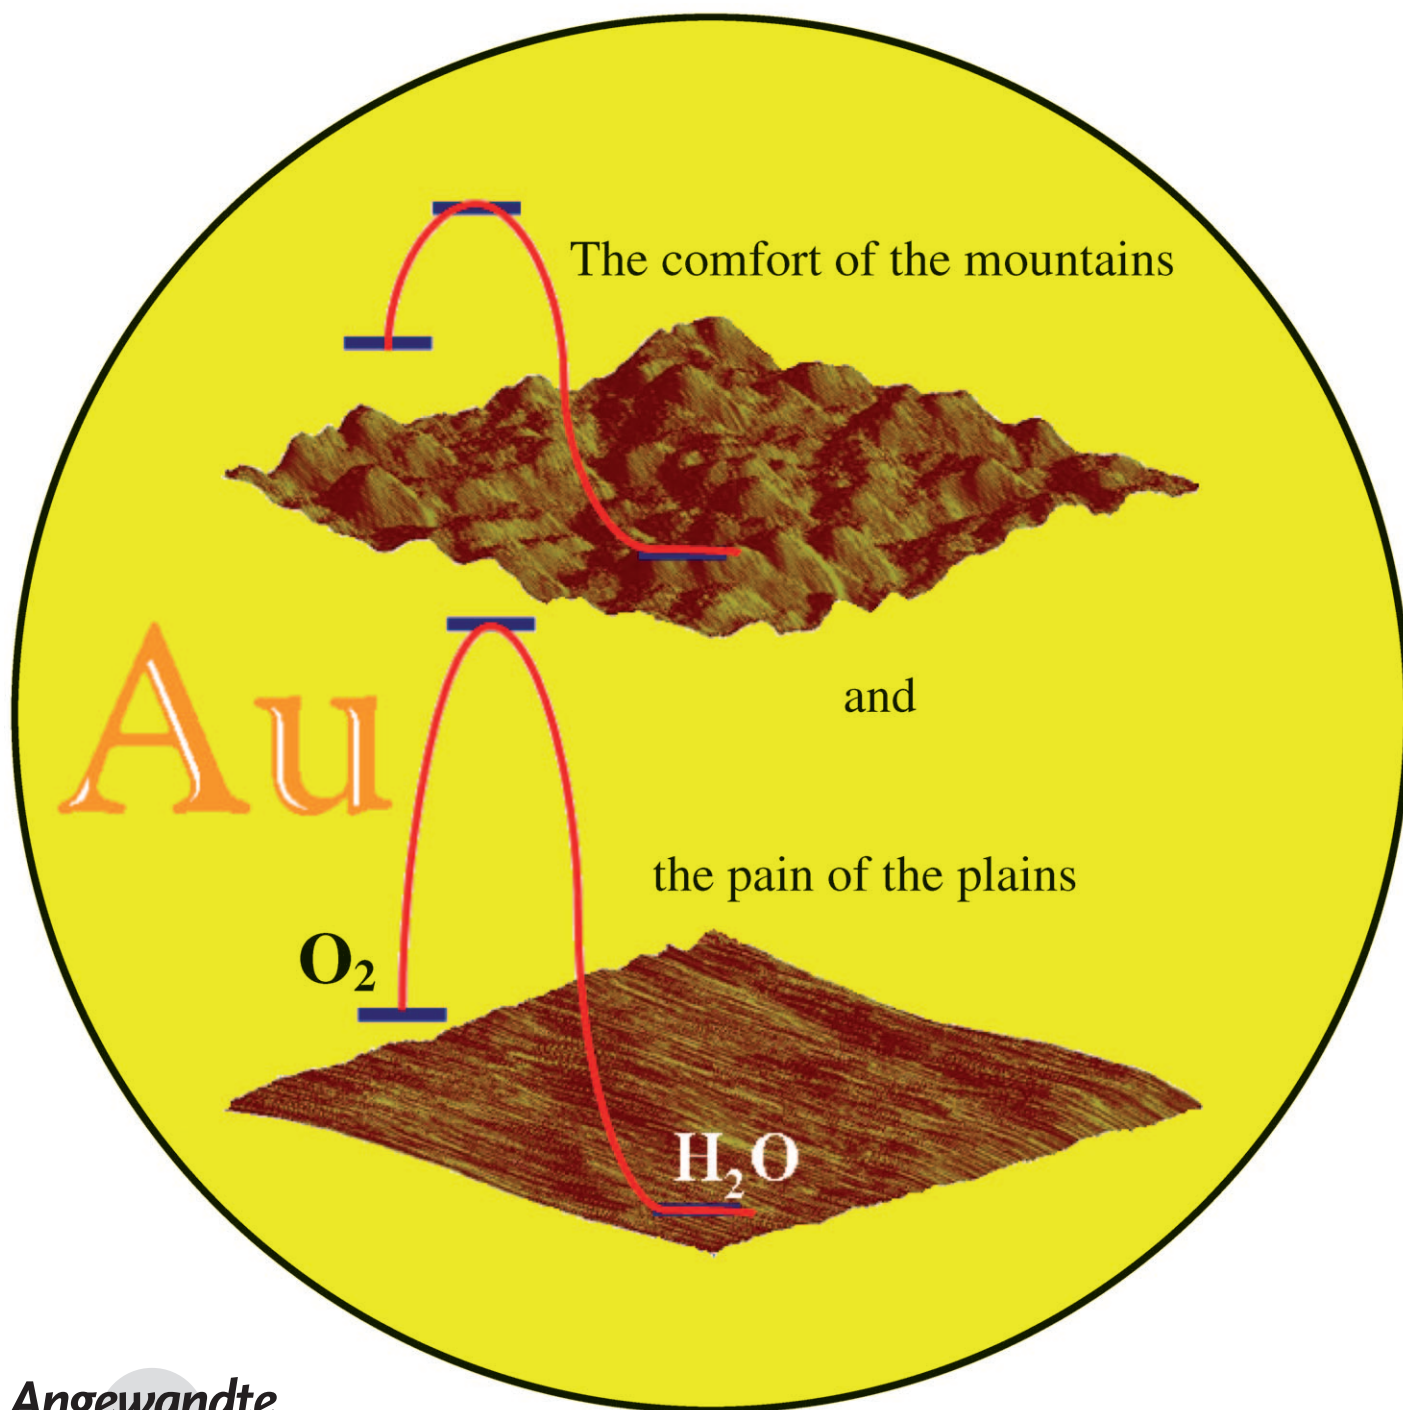

Electrochemists commonly seek two diametrically opposed goals: 1) the activation of electrode surfaces, in order to overcome kinetic barriers and accelerate reactions, and 2) the deactivation of electrode surfaces, in order to prevent unwanted reactions such as corrosion. It has long been known that the activity of electrodes (and of heterogeneous catalysts) is associated with surface defects;^[1–9] Pt black is a familiar example.^[10] In contrast, deactivation is typically achieved by “brute-force” methods such as total passivation.^[11,12]

Recently, we demonstrated that the hydroxyl radicals of Fenton’s reagent could remove self-assembled monolayers (SAMs) from gold electrodes,^[13] and—surprisingly—could also dissolve asperities, thus leading to very smooth surfaces.^[14] Herein we report that gold electrodes prepared by treatment with Fenton’s reagent are also catalytically deactivated, almost certainly because the active sites on gold are selectively knocked out by the attack of the hydroxyl radicals. Unlike crystallographically perfect gold surfaces, which have fully filled d orbitals, the active sites on gold are thought to have partially filled d orbitals. These orbitals resemble platinum surfaces, which normally have half-filled d orbitals, and therefore they are similarly capable of catalyzing reactions that involve free-radical intermediates.

Figure 1 shows current–potential curves of a gold electrode before and after successive treatments with Fenton’s reagent. The solution was saturated with oxygen and the reduction peak of dissolved oxygen is clearly seen. Figure 2 shows the dependences of the peak potential and the peak current as a function of the duration of hydroxyl radical attack. The O₂ reduction potentials shift negatively, while the peak currents remain almost constant. The data are consistent with the selective disappearance of the reactive Au atoms with partially filled d orbitals, leaving behind only the unreactive Au atoms with fully filled d orbitals. Oxygen reduction requires the stabilization of a superoxide-free radical intermediate, which, as dictated by the Pauli exclusion principle, can not be achieved with fully filled d orbitals. It is interesting to compare the effects of polishing with Fenton’s reagent (i.e., OH• attack) with those of electroplating. When a fresh gold layer is electroplated on a mechanically polished gold surface, a partial inhibition of oxygen reduction is observed, which is consistent with the “burying” of some active sites, but not full inhibition. Thus, when the mechan-

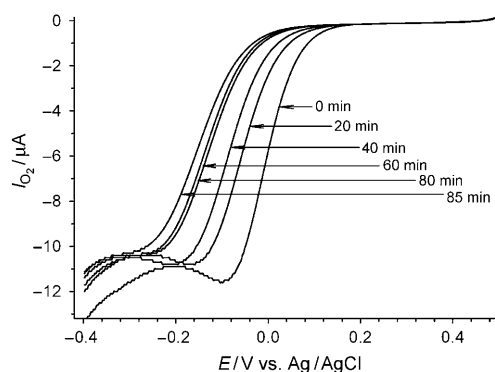


Figure 1. Voltammograms of O₂ reduction obtained in 0.1 M H₂SO₄ after exposure of an Au electrode to Fenton’s reagent. The solution was saturated with oxygen before the experiments were carried out. Conditions: scan rate 50 mV s^{−1}; gold electrode diameter (*d*) 1.6 mm; concentrations of Fe²⁺: 1 mM, EDTA: 1 mM, H₂O₂: 10 mM.

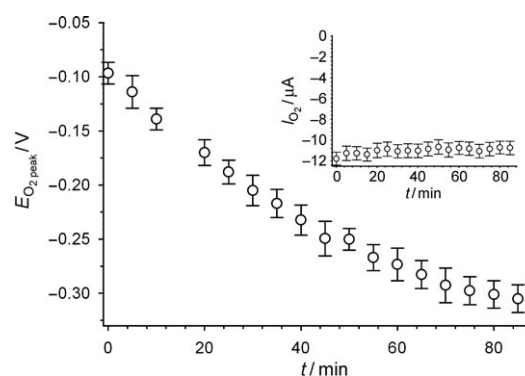


Figure 2. Peak potential of O₂ reduction in oxygen-saturated H₂SO₄ (0.1 M) versus reaction time with hydroxyl radicals. Inset: Peak currents of reduction versus reaction time with hydroxyl radicals. For other conditions see Figure 1.

ically polished Au electrode was gold plated in a solution containing 0.1 M NaClO₄ and 1 mM KAu(CN)₂, the oxygen reduction peak potentials were scattered between −0.19 and −0.22 V (vs. Ag/AgCl), that is, these peak potentials were more negative than in the case of a mechanically polished surface and less negative than for a surface polished with Fenton’s reagent.

The hydrogen evolution reaction also proceeds via a radical intermediate, and, as expected, this reaction was also inhibited on the surface of gold electrodes treated with Fenton’s reagent. In this case, the H⁺ reduction potential was shifted to negative potentials by about 45 mV (results not shown).

The effect of hydroxyl radical attack on gold was probed using two different redox systems with different underlying kinetics, in order to provide critical proof for the catalytic deactivation. The first redox system, quinone–hydroquinone (Q/HQ), proceeds via a free radical intermediate,^[15] but the second redox system, Ru^{III}/Ru^{II}, does not. Figure 3 shows the cyclic voltammograms of Q/HQ obtained with a mechanically polished Au electrode before and after a series of treatments with Fenton’s reagent. The plot of the logarithm of the

[*] Dr. U. Hasse, G. Sievers, Prof. Dr. F. Scholz
Institut für Biochemie, Universität Greifswald
Felix-Hausdorff-Str. 4, 17487 Greifswald (Germany)
Fax: (+49) 3834-864-451
E-mail: fscholz@uni-greifswald.de
Homepage: <http://www.chemie.uni-greifswald.de/~analytik/>
Dr. A. M. Nowicka, Dr. M. Donten, Prof. Dr. Z. Stojek
Dept. of Chemistry, Warsaw University
u. Pasteura 1, 02-093 Warsaw (Poland)
E-mail: anowicka@chem.uw.edu.pl
Prof. Dr. S. Fletcher
Department of Chemistry, University of Loughborough
Loughborough, LE11 3TU (UK)

[**] A.M.N. acknowledges kind support by DAAD, Bonn. G.S. acknowledges support by the Alfried Krupp Wissenschaftskolleg Greifswald.

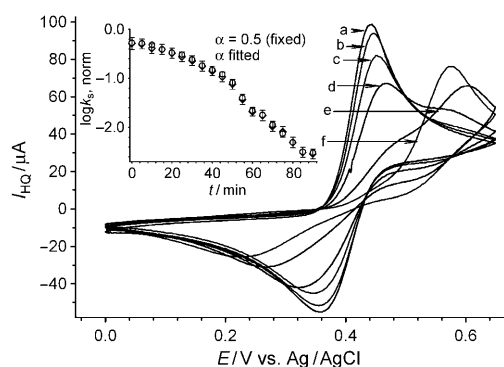


Figure 3. Cyclic voltammograms of HQ recorded in 0.1 M HClO₄ containing 100 mM NaClO₄ after exposure of the Au electrode to OH[•] for a) 0, b) 10, c) 20, d) 40, e) 60, and f) 90 min. Inset: Mean electron transfer rate constant of HQ versus time of reaction with hydroxyl radicals. Conditions: scan rate 10 mVs⁻¹; gold electrode diameter $d = 1.6$ mm; $c_{\text{HQ}} = 5$ mM; concentrations of Fe²⁺: 1 mM, EDTA: 1 mM, H₂O₂: 10 mM.

corresponding normalized heterogeneous electron transfer rate constant versus time of interaction with the hydroxyl radicals is shown in the inset of Figure 3. As expected, the Q/HQ process became slower and slower as the electrode was exposed to hydroxyl radicals and the active sites were selectively knocked out. Chronocoulometry was used to exclude the involvement of any adsorption phenomena. In contrast, the Ru^{III}/Ru^{II} system did not show any changes in peak potential or peak current during attack by hydroxyl radicals; that is, the rate of electron transfer was unaffected within experimental error. Evidently, the active sites that are removed by polishing with Fenton's reagent are precisely those that stabilize free-radical intermediates.

Upon attack by hydroxyl radicals, the open-circuit potentials (OCPs) of the gold electrodes were systematically shifted to more positive potentials: When the electrodes were reduced after each radical attack at 0.5 V versus Ag/AgCl for 30 s (to obtain an oxide-free Au surface), the OCPs shifted from 0.232 V before treatment to 0.247 V after 50 min of treatment with hydroxyl radicals. The effect is small but reproducible, however the complex interplay between oxygen or proton reduction and gold oxidation makes precise interpretation problematic.

The reduction of the rates of catalyzed reactions on gold (and possibly other metals) by selective knockout of active sites is a new concept that may have considerable implications for corrosion protection. The contact of Au with less noble metals is responsible for much unwanted corrosion behavior, in particular in the field of electronics, because Au acts as a galvanic half-cell where O₂ may be reduced (or H⁺ in some cases). An effective means of inhibiting O₂ reduction and H⁺ reduction in these circumstances without blocking the surface of the gold is clearly desirable.

It has long been known that surface defects (i.e., any deviations from the structure of low-index planes) play an important role in electrocatalysis,^[16,17] but the precise mechanism has always been unclear. The present work provides very strong evidence that surface defects are the loci of partially filled d orbitals that can stabilize free-radical inter-

mediates. A simple proof is that these sites can be selectively knocked out by treatment with hydroxyl radicals generated by Fenton's reagent. Furthermore, since partially filled d orbitals are responsible for electrocatalysis in the case of reactions that occur via radical intermediates, their removal is predicted to slow down the rates of O₂, H⁺, and Q reduction reactions, but not the Ru^{III} reduction reaction; this behavior is precisely what is observed. The need for orbital matching prior to electron transfer is emerging as a major theme of electrochemistry, and the theory is discussed in a related paper.^[18]

Experimental Section

Cyclic voltammetry (CV) was performed with an Autolab, model 12 potentiostat (Eco-Chemie, Utrecht) using a three-electrode system. A gold disc electrode (1.6 mm radius; BAS, Kenilworth) was used as the working electrode, a KCl-saturated Ag/AgCl electrode served as the reference electrode, and a platinum wire was used as the auxiliary electrode. The solutions of Fenton's reagent: (NH₄)₂Fe(SO₄)₂·6 (H₂O) (1 mM; Merck), ethylenediaminetetraacetate (EDTA; 1 mM, Merck), acetate buffer (0.01 M, pH 4.7), and H₂O₂ (10 mM) were always freshly prepared. H₂O₂ was added immediately before starting the experiments. The surface of the working electrode was polished with 1.0 and 0.3 μm Al₂O₃ on a wet pad before the measurements. After each polishing, the electrode was rinsed with a direct stream of water (Milli-Q, Millipore, conductivity of ca. 0.056 μS cm⁻¹), and the electrode was dried. Then the electrode was cycled between -0.3 V and 1.5 V (vs. Ag/AgCl) in H₂SO₄ (0.1 M) until a stable voltammogram typical of a clean gold electrode was obtained.^[19] Then the electrode was washed with water and exposed to freshly prepared solutions of Fenton's reagent for 5 minute intervals. The exposure was repeated so that the overall exposure time ranged from 5 to 90 min. The reaction of Fenton's reagent with the gold electrode was terminated by removing the electrode from the solution of Fenton's reagent and washing it with water. The electrocatalytic activity of gold electrodes was probed with O₂ in acidic solution; hydroquinone (5 mM, Fluka, purity ≥ 99 %), and ruthenium(III) hexamine (5 mM solution in 0.1 M NaClO₄; Aldrich, purity ≥ 98 %). The reported electron transfer rate constant was normalized according to the following formula:

$$k_{s,\text{norm}} = k_s \sqrt{\frac{\tau}{D_r}}$$

where k_s is the electron transfer rate constant, $k_{s,\text{norm}}$ is the normalized electron transfer rate constant, D_r is the diffusion coefficient of the reactant, and τ is the characteristic time parameter of the technique. The time parameter for voltammetry takes the form $\tau = \frac{RT}{nF\nu}$, where ν is the scan rate. $k_{s,\text{norm}}$ was determined by fitting the simulated voltammograms to the experimental voltammograms using GEPES software.

Received: January 27, 2010

Published online: March 15, 2010

Keywords: electrochemistry · gold · kinetics · radicals · voltammetry

- [1] G. Ertl, *Angew. Chem.* **2008**, *120*, 3578–3590; *Angew. Chem. Int. Ed.* **2008**, *47*, 3524–3535.
- [2] H.-J. Freund, *Angew. Chem.* **1997**, *109*, 444–468; *Angew. Chem. Int. Ed.* **1997**, *36*, 452–475.
- [3] C. E. Banks, A. Crossley, C. Salter, S. J. Wilkins, R. G. Compton, *Angew. Chem.* **2006**, *118*, 2595–2599.

- [4] L. D. Burke, *Gold Bull.* **2004**, 37, 125–135.
- [5] D. L. Burke, L. M. Hurley, *J. Solid State Electrochem.* **2002**, 6, 101–110.
- [6] L. D. Burke, J. M. Moran, P. F. Nugent, *J. Solid State Electrochem.* **2003**, 7, 529–538.
- [7] A. J. Ahern, L. C. Nagle, D. L. Burke, *J. Solid State Electrochem.* **2002**, 6, 451–462.
- [8] L. D. Burke, A. P. O'Mullane, *J. Solid State Electrochem.* **2000**, 4, 285–297.
- [9] L. D. Burke, M. A. Murphy, *J. Solid State Electrochem.* **2001**, 5, 43–49.
- [10] U. Schröder, J. Nießen, F. Scholz, *Angew. Chem.* **2003**, 115, 2986–2989; *Angew. Chem. Int. Ed.* **2003**, 42, 2880–2883.
- [11] W. A. Badawy, F. M. Al-Kharafi, *Corros. Sci.* **1997**, 39, 681–700.
- [12] L. Q. Zhu, F. Yang, *Corros. Prot.* **2006**, 27, 503–507.
- [13] F. Scholz, G. López de Lara González, L. Machado de Carvalho, M. Hilgemann, Kh. Z. Brainina, H. Kahlert, R. S. Jack, D. T. Minh, *Angew. Chem.* **2007**, 119, 8225–8227; *Angew. Chem. Int. Ed.* **2007**, 46, 8079–8081.
- [14] A. M. Nowicka, U. Hasse, M. Hermes, F. Scholz, *Angew. Chem.* **2010**, 122, 1079–1081; *Angew. Chem. Int. Ed.* **2010**, 49, 1061–1063.
- [15] X. Huang, S. Wang, X. Shan, X. Chang, N. Tao, *J. Electroanal. Chem.*, DOI: 10.1016/j.jelechem.2009.12.027.
- [16] J. O'M. Bockris, A. K. N. Reddy, M. Gamboa-Aldeco, *Modern Electrochemistry, Vol. 2 A, 2nd ed.*, Kluwer, New York, **2000**, p. 1275.
- [17] M. T. M. Koper, *Faraday Discuss.* **2009**, 140, 11–24.
- [18] S. Fletcher, *J. Solid State Electrochem.* **2010**, 14, 705–739.
- [19] H. O. Finklea, S. Avery, M. Lynch, T. Furttsch, *Langmuir* **1987**, 3, 409–413.