


# A Nanotube of Cyclic Porphyrin Dimers Connected by Nonclassical Hydrogen Bonds and Its Inclusion of C<sub>60</sub> in a Linear Arrangement\*\*

Hirofumi Nobukuni, Yuichi Shimazaki, Fumito Tani,\* and Yoshinori Naruta


Recently, there has been great interest in the design and synthesis of nanotubular assemblies composed of porphyrin derivatives.<sup>[1]</sup> They are expected to offer tailored one-dimensional spaces and to be employed in technological applications, such as molecular-scale electronics, optical devices, sensors, light-energy conversion, and catalysis.<sup>[2,3]</sup> Moreover, supramolecular architectures consisting of porphyrin derivatives and fullerenes are currently attracting much attention as functional materials,<sup>[4,5]</sup> and a synthetic supramolecular peapod in which fullerenes are aligned within an organic nanotube has been of interest as an analogue to fullerenes included in carbon nanotubes.<sup>[1a,6,7]</sup> However, it has still been difficult to create the rationally predictable structure of a porphyrin nanotube, and there have been only a few examples of porphyrin nanotubes crystallographically analyzed at the atomic level.<sup>[1b-f]</sup> One method to construct organic nanotubes is to introduce self-assembling substituents into rigid cyclic molecules to stack them in one direction (Scheme 1).<sup>[8]</sup> We

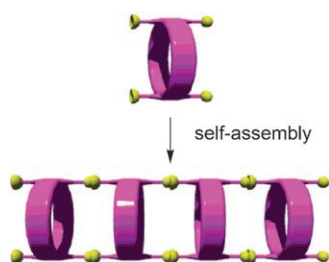

**Scheme 1.** Schematic representation of the strategy for the formation of a tubular assembly with cyclic molecules.

have tried to build a new nanotube by applying this method to a rigid cyclic porphyrin dimer bearing self-assembling substituents. The resulting porphyrin nanotube was characterized by X-ray crystallography, and it can include C<sub>60</sub> in its inner channel to produce a one-dimensional array.

A cyclic porphyrin dimer<sup>[9]</sup> linked by butadiyne moieties was chosen as the rigid ring, and the 4-pyridyl group was adopted as the self-assembling substituent vertical to the ring plane (Scheme 2). The designed dimer (Ni<sub>2</sub>-CPD<sub>Py</sub>) was

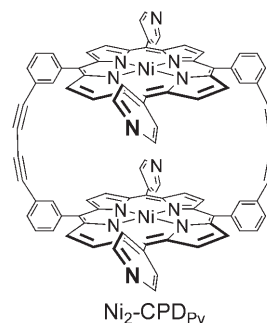

**Scheme 2.**

predicted to construct a tubular assembly through complexation of the pyridyl groups with hydrogen-bonding donors or metal ions.<sup>[10-13]</sup> Ni<sub>2</sub>-CPD<sub>Py</sub> was synthesized from the corresponding nickel porphyrin monomer with two terminal C–C triple bonds by Glaser coupling catalyzed by copper(I) under air in 30% yield.<sup>[14]</sup>


Red single crystals of Ni<sub>2</sub>-CPD<sub>Py</sub> suitable for X-ray crystallography were obtained after slow evaporation of a CHCl<sub>3</sub>/toluene solution. The Ni<sub>2</sub>-CPD<sub>Py</sub> molecule has a rectangular shape and a C<sub>2</sub> axis, which is parallel to the crystallographic *b* axis and bisects the axis through the two Ni ions (Figure 1a and Figure S1 in the Supporting Information).<sup>[15]</sup> The distances between the two Ni ions and the two midpoints of the butadiyne moieties are 11.635(1) Å and 13.585 Å, respectively. The porphyrin rings are ruffled, with alternating displacements of the *meso* carbon atoms above and below the plane formed by the four nitrogen atoms. The *meso* carbon atoms with pyridyl substituents are displaced outward by 0.503 and 0.553 Å, and the other *meso* carbon atoms are displaced inward by 0.473 and 0.603 Å. In comparison with the structure of the analogous porphyrin dimer,<sup>[9c]</sup> the most important differences are that the two porphyrin rings are rotated around the center-to-center axis by 26.4° with respect to each other and that the two butadiyne moieties are not coplanar; they display a torsion angle of 34.4° (Figure 1b,c and Figure S1 in the Supporting Information). Four solvent toluene molecules are incorporated into the structure per Ni<sub>2</sub>-CPD<sub>Py</sub> molecule, two inside the cavity and two outside.

Interestingly, a nanosized tubular assembly is observed in the crystal packing of Ni<sub>2</sub>-CPD<sub>Py</sub> without an additional hydrogen-bonding donor or metal ion. The tubular structure

[\*] H. Nobukuni, Dr. Y. Shimazaki, Prof. Dr. F. Tani, Prof. Dr. Y. Naruta  
Institute for Materials Chemistry and Engineering  
Kyushu University  
Higashi-ku, Fukuoka 812-8581 (Japan)  
Fax: (+81) 92-642-2715  
E-mail: tanif@ms.ifoc.kyushu-u.ac.jp


[\*\*] This work was supported by Grants-in-Aid (Nos. 17350029 and 17036050 to F. T., and the Global COE Program, “Science for Future Molecular Systems”) from the Ministry of Education, Culture, Sports, Science and Technology of Japan.

Supporting information for this article is available on the WWW under <http://www.angewandte.org> or from the author.

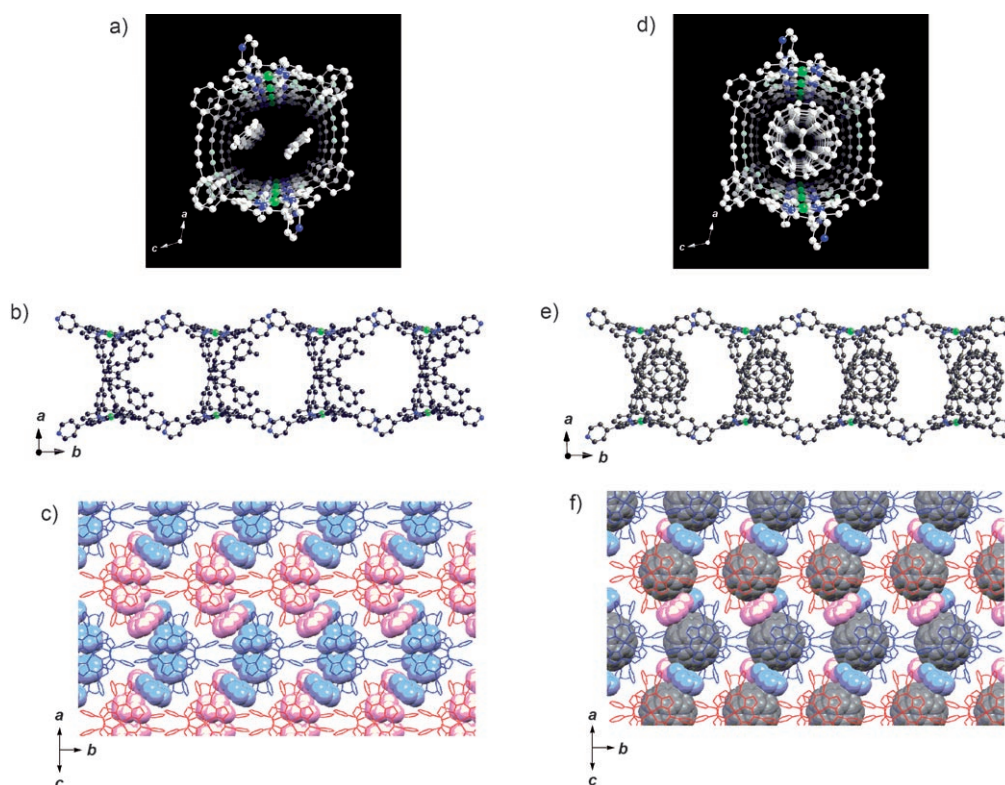

**Figure 1.** Crystal structures of tubular assemblies of a–c)  $\text{Ni}_2\text{-CPDpy}$  and d–f)  $\text{C}_{60}\text{-Ni}_2\text{-CPDpy}$ . Hydrogen atoms are omitted for clarity. a, d) front view; b, e) side view; c, f) top view. In (a, b, c, d), Ni green, N blue.

along the crystallographic  $b$  direction is formed by self-assembly through two kinds of cooperative noncovalent interactions between the cyclic molecules (Figure 2). One is a pair of complementary  $\text{C-H}\cdots\text{N}$  hydrogen-bonding interactions between the pyrrole  $\beta\text{-CH}$  and the nitrogen atoms of the pyridyl groups with  $\text{C}\cdots\text{N}$  distances of 3.328(5) and 4.020(6) Å, whereby the latter indicates a fairly weak bond. Such a nonclassical  $\text{C-H}\cdots\text{N}$  hydrogen bond has rarely been observed for pyridyl groups in supramolecular structures,<sup>[16,17]</sup> in contrast to numerous examples of self-assembly through the coordination of pyridyl ligands to metal ions.<sup>[12,13]</sup> The other noncovalent interaction is a weak  $\pi\text{-}\pi$  interaction between the pyridyl groups. For this interaction, the shortest

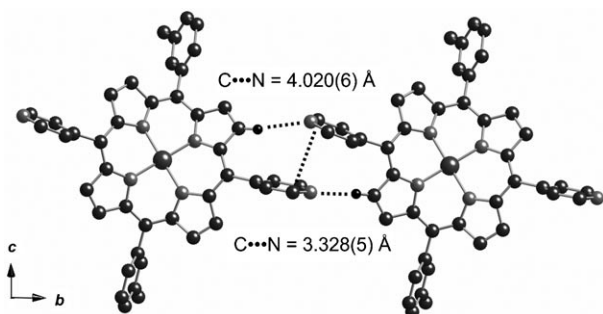

**Figure 2.** Details of the noncovalent interactions linking the cyclic porphyrin dimers in the crystal of  $\text{Ni}_2\text{-CPDpy}$ . Hydrogen atoms are omitted except in the  $\text{C-H}\cdots\text{N}$  moieties. N, Ni gray; C, H black.


carbon–carbon distance is 3.478(7) Å and the dihedral angle of 13.04°. As a whole, the adjacent dimers along the  $b$  axis are linked by four hydrogen bonds and two  $\pi\text{-}\pi$  interactions. These noncovalent interactions construct a one-dimensional porphyrin array with a center-to-center distance of 14.537(1) Å, and the porphyrin planes and the butadiyne moieties form a rectangular channel along the  $b$  axis. The two toluene molecules outside the cavity also constitute part of the side wall of the tube.  $\text{Ni}_2\text{-CPDpy}$  has an axial chirality stemming from the rotation of the two porphyrin molecules around the center-to-center axis. Each tube along the  $b$  axis is also chiral, because it comprises molecules of only one enantiomer. The tubes are aligned along the  $c$  direction with alternating enantiomers to make the crystal racemic.

Since  $\text{Ni}_2\text{-CPDpy}$  has a suitable size for  $\text{C}_{60}$  inclusion, we investigated its potential as a host for  $\text{C}_{60}$ . The Job plot (415 nm) based on the UV/Vis absorption spectrum upon mixing of  $\text{Ni}_2\text{-CPDpy}$  and  $\text{C}_{60}$  in  $\text{CHCl}_3$ /toluene at room temperature displayed a typical signature pattern for the formation of a 1:1 host–guest complex.<sup>[14]</sup> From the titration of  $\text{Ni}_2\text{-CPDpy}$  with  $\text{C}_{60}$ , the association constant ( $K_{\text{assoc}}$ ) was evaluated to be  $2.0 \times 10^5 \text{ M}^{-1}$ .<sup>[14]</sup> This value is nearly the same as that of the cyclic nickel porphyrin dimer linked by  $-\text{O}(\text{CH}_2)_6\text{O}-$  spacers rather than by butadiyne.<sup>[18]</sup> Electrospray ionization mass spectrometry (ESI-MS) of a 1:1 mixture of  $\text{Ni}_2\text{-CPDpy}$  and  $\text{C}_{60}$  in  $\text{CH}_2\text{Cl}_2/\text{MeOH}/\text{CH}_3\text{COOH}$  (50/50/0.2) revealed two peak clusters at  $m/z$  2160.2 [ $[\text{Ni}_2\text{-CPDpy} + \text{C}_{60}]^+$ ] and 1080.3 [ $[\text{Ni}_2\text{-CPDpy} + \text{C}_{60}]^{2+}$ ].<sup>[14]</sup> The  $^{13}\text{C}$  NMR spectrum of a 1:1 mixture of  $\text{Ni}_2\text{-CPDpy}$  and  $^{13}\text{C}$ -enriched

$C_{60}$  in  $[D_8]$ toluene/ $CDCl_3$  (1:1) showed a singlet signal arising from included  $C_{60}$  at  $\delta = 141.7$  ppm, which is upfield from that of free  $C_{60}$  (143.4 ppm).<sup>[14]</sup>

One molar equivalent of  $C_{60}$  in toluene was added during the crystallization of  $Ni_2$ -CPD<sub>py</sub> in  $CHCl_3$  to obtain reddish-black single crystals. X-ray crystallography revealed the 1:1 inclusion complex of  $C_{60}$  with  $Ni_2$ -CPD<sub>py</sub> ( $C_{60} \subset Ni_2$ -CPD<sub>py</sub>, see Figure S1 in the Supporting Information).<sup>[15]</sup> Both  $C_{60} \subset Ni_2$ -CPD<sub>py</sub> and  $Ni_2$ -CPD<sub>py</sub> crystallize in the same space group ( $C2/c$ ) and have very similar lattice parameters. Therefore, the structure of  $Ni_2$ -CPD<sub>py</sub> with included  $C_{60}$  is similar; it displays  $C_2$  symmetry and a slight increase of the ruffling distortion of the porphyrin rings.<sup>[19]</sup> In the crystal structure, two toluene molecules per  $C_{60} \subset Ni_2$ -CPD<sub>py</sub> molecule occupy almost the same positions outside the cavity as in the crystal of  $Ni_2$ -CPD<sub>py</sub>. A tubular assembly formed by the same C–H...N hydrogen bonds and  $\pi$ – $\pi$  interactions is observed in the crystal packing of  $C_{60} \subset Ni_2$ -CPD<sub>py</sub> as in  $Ni_2$ -CPD<sub>py</sub> (Figure 1 d–f).<sup>[20]</sup> On the basis of the structural parameters of the C–H...N and pyridyl...pyridyl motifs, the weaker hydrogen bond and the  $\pi$ – $\pi$  interaction appear to be enhanced in  $C_{60} \subset Ni_2$ -CPD<sub>py</sub>. The  $C_{60}$  molecules are linearly arranged in the inner channel to give a supramolecular peapod.<sup>[1a,6,7]</sup> The distance between the centers of the  $C_{60}$  molecules along the channel is 14.498(2) Å. There is a small difference in arrangement of the tubes between  $Ni_2$ -CPD<sub>py</sub> and  $C_{60} \subset Ni_2$ -CPD<sub>py</sub>. The molecular framework of  $Ni_2$ -CPD<sub>py</sub> changes from rectangular to square upon inclusion, as evidenced by the increased distance (12.596(2) Å) between the two Ni ions and the decreased distance (12.735 Å) between the midpoints of the butadiyne moieties. These results indicate that the inclusion takes place in an “induced fit” fashion. In most examples of inclusion complexes of  $C_{60}$  with porphyrins, the  $C_{60}$  molecule is situated above the center of porphyrin unit, and a 6:6 ring-juncture C–C bond of the fullerene is closest to the porphyrin, rather than a 6:5 junction.<sup>[4,18]</sup> However, in the present case (Figure 3), the  $C_{60}$  molecules are not located above the centers of the porphyrin units, because the cavity is slightly smaller than in the reported face-to-face porphyrin dimer with the  $-O(CH_2)_6O-$  linkages.<sup>[18]</sup> The closest interaction in  $C_{60} \subset Ni_2$ -CPD<sub>py</sub> is a  $\pi$ – $\pi$  stacking interaction between a six-membered ring of  $C_{60}$  and the six-membered ring composed of a pyridyl-substituted *meso* carbon atom, two  $\alpha$  carbon atoms, two pyrrole nitrogen atoms, and the Ni ion. This interaction has a center-to-center distance of 3.459 Å and a dihedral angle of 11.46°. The nearest atoms of the  $Ni_2$ -CPD<sub>py</sub> molecule to  $C_{60}$  are two pairs of *ortho* hydrogen atoms of the pyridyl and phenyl groups, the C–H bonds of which are oriented towards  $C_{60}$  six-membered rings with separations between the carbon atoms and the ring centers of 3.525 and 3.796 Å, respectively, to realize multiple C–H... $\pi$  interactions. It is likely that  $C_{60}$  is fixed by these noncovalent interactions with the  $Ni_2$ -CPD<sub>py</sub> molecule.

In conclusion, we have demonstrated the synthesis of a new porphyrin nanotube from the cyclic porphyrin dimer  $Ni_2$ -CPD<sub>py</sub> with self-assembling pyridyl substituents. The tube is constructed by the stacking of the cyclic molecules through unique C–H...N hydrogen bonds and  $\pi$ – $\pi$  interactions of the

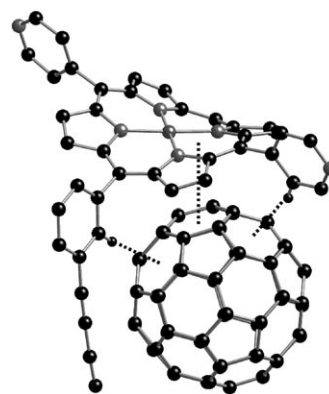

**Figure 3.** Details of the noncovalent interactions between  $Ni_2$ -CPD<sub>py</sub> and  $C_{60}$ . Hydrogen atoms are omitted except in the C–H... $\pi$  motifs. N, Ni gray; C, H black.

pyridyl groups in the crystal. Furthermore, the formation of the 1:1 inclusion complex of  $C_{60}$  with  $Ni_2$ -CPD<sub>py</sub> ( $C_{60} \subset Ni_2$ -CPD<sub>py</sub>) was confirmed both in solution and in the crystal.  $C_{60}$  molecules are linearly arranged in the inner channel of the tubular assembly in the crystal. To the best of our knowledge, this is the first example of an X-ray crystal structure determination for a supramolecular peapod.<sup>[1a,4–7]</sup> Some previous porphyrin nanotubes needed specific guest molecules for their formation and disassembled in the absence of the guests.<sup>[1a–d]</sup> In contrast, there are only small changes in the tubular structures between  $Ni_2$ -CPD<sub>py</sub> and  $C_{60} \subset Ni_2$ -CPD<sub>py</sub>, thus indicating the large tolerance of this porphyrin nanotube toward guest inclusion. Investigation of the inclusion properties of the present tubular assembly are in progress.

Received: September 4, 2007

Published online: October 23, 2007

**Keywords:** fullerenes · hydrogen bonds · nanotubes · porphyrinoids · self-assembly

- [1] a) T. Yamaguchi, N. Ishii, K. Tashiro, T. Aida, *J. Am. Chem. Soc.* **2003**, *125*, 13934–13935; b) R. Harada, Y. Matsuda, H. Okawa, T. Kojima, *Angew. Chem.* **2004**, *116*, 1861–1864; *Angew. Chem. Int. Ed.* **2004**, *43*, 1825–1828; c) T. Kojima, R. Harada, T. Nakanishi, K. Kaneko, S. Fukuzumi, *Chem. Mater.* **2007**, *19*, 51–58; d) R. Harada, T. Kojima, *Chem. Commun.* **2005**, 716–718; e) B. F. Abrahams, B. F. Hoskins, D. M. Michail, R. Robson, *Nature* **1994**, *369*, 727–729; f) T. Kamada, N. Aratani, T. Ikeda, N. Shibata, Y. Higuchi, A. Wakamiya, S. Yamaguchi, K. S. Kim, Z. S. Yoon, D. Kim, A. Osuka, *J. Am. Chem. Soc.* **2006**, *128*, 7670–7678; g) Z. Wang, C. J. Medforth, J. A. Shelnutt, *J. Am. Chem. Soc.* **2004**, *126*, 15954–15955; h) Z. Wang, C. J. Medforth, J. A. Shelnutt, *J. Am. Chem. Soc.* **2004**, *126*, 16720–16721; i) V. Gulbinas, R. Karpicz, R. Augulis, R. Rotomskis, *Chem. Phys.* **2007**, *332*, 255–261; j) R. Rotomskis, R. Augulis, V. Snitka, R. Valiokas, B. Liedberg, *J. Phys. Chem. B* **2004**, *108*, 2833–2838; k) S. C. M. Gandini, E. L. Gelamo, R. Itri, M. Tabak, *Biophys. J.* **2003**, *85*, 1259–1268; l) S. Sadasivan, K. Köhler, G. B. Sukhorukov, *Adv. Funct. Mater.* **2006**, *16*, 2083–2088; m) Y. Kubo, Y. Kitada, R. Wakabayashi, T. Kishida, M. Ayabe, K. Kaneko, M. Takeuchi, S. Shinkai, *Angew. Chem.* **2006**, *118*, 1578–1583; *Angew. Chem. Int. Ed.* **2006**, *45*, 1548–1553; n) T. Ishida, Y.

- Morisaki, Y. Chujo, *Tetrahedron Lett.* **2006**, *47*, 5265–5268; o) A. Tsuda, H. Hu, R. Tanaka, T. Aida, *Angew. Chem.* **2005**, *117*, 4962–4966; *Angew. Chem. Int. Ed.* **2005**, *44*, 4884–4888; p) J. S. Hu, Y. G. Guo, H. P. Liang, L. J. Wan, L. Jiang, *J. Am. Chem. Soc.* **2005**, *127*, 17090–17095; q) S. Tamaru, M. Takeuchi, M. Sano, S. Shinkai, *Angew. Chem.* **2002**, *114*, 881–884; *Angew. Chem. Int. Ed.* **2002**, *41*, 853–856; r) H. Matsui, R. MacCuspie, *Nano Lett.* **2001**, *1*, 671–675.
- [2] a) F. J. M. Hoeben, P. Jonkheijm, E. W. Meijer, A. P. H. J. Schenning, *Chem. Rev.* **2005**, *105*, 1491–1546; b) R. E. Martin, F. Diederich, *Angew. Chem.* **1999**, *111*, 1440–1469; *Angew. Chem. Int. Ed.* **1999**, *38*, 1350–1377; c) P. F. H. Schwab, M. D. Levin, J. Michl, *Chem. Rev.* **1999**, *99*, 1863–1933; d) J. M. Tour, *Chem. Rev.* **1996**, *96*, 537–553; e) J. M. Lehn, *Angew. Chem.* **1990**, *102*, 1347–1362; *Angew. Chem. Int. Ed. Engl.* **1990**, *29*, 1304–1319.
- [3] C. Joachim, J. K. Gimzewski, A. Aviram, *Nature* **2000**, *408*, 541–548.
- [4] P. D. W. Boyd, C. A. Reed, *Acc. Chem. Res.* **2005**, *38*, 235–242.
- [5] K. Tashiro, T. Aida, *Chem. Soc. Rev.* **2007**, *36*, 189–197.
- [6] G. D. Pantoş, J. L. Wietor, J. K. M. Sanders, *Angew. Chem.* **2007**, *119*, 2288–2290; *Angew. Chem. Int. Ed.* **2007**, *46*, 2238–2240.
- [7] a) B. W. Smith, M. Monthieux, D. E. Luzzi, *Nature* **1998**, *396*, 323–324; b) O. Vostrowsky, A. Hirsch, *Angew. Chem.* **2004**, *116*, 2380–2383; *Angew. Chem. Int. Ed.* **2004**, *43*, 2326–2329.
- [8] D. Pasini, M. Ricci, *Curr. Org. Synth.* **2007**, *4*, 59–80.
- [9] a) H. L. Anderson, J. K. M. Sanders, *Angew. Chem.* **1990**, *102*, 1478–1480; *Angew. Chem. Int. Ed. Engl.* **1990**, *29*, 1400–1403; b) H. L. Anderson, J. K. M. Sanders, *J. Chem. Soc. Perkin Trans. I* **1995**, 2223–2229; c) H.-J. Kim, J. E. Redman, M. Nakash, N. Feeder, S. J. Teat, J. K. M. Sanders, *Inorg. Chem.* **1999**, *38*, 5178–5183.
- [10] G. A. Jeffrey, *An Introduction to Hydrogen Bonding*, Oxford University Press, New York, **1997**.
- [11] a) J. Nakazawa, M. Mizuki, Y. Shimazaki, F. Tani, Y. Naruta, *Org. Lett.* **2006**, *8*, 4275–4278; b) S. Muniappan, S. Lipstman, I. Goldberg, *Acta Crystallogr. Sect. C* **2007**, *63*, o395–o399; c) S. Lipstman, S. Muniappan, S. George, I. Goldberg, *CrystEngComm* **2006**, *8*, 601–607; d) I. Goldberg, *Chem. Commun.* **2005**, 1243–1254; e) M. Vinodu, I. Goldberg, *CrystEngComm* **2005**, *7*, 133–138; f) S. Tanaka, M. Shirakawa, K. Kaneko, M. Takeuchi, S. Shinkai, *Langmuir* **2005**, *21*, 2163–2172.
- [12] *Supramolecular Engineering of Synthetic Metallic Materials* (Eds.: J. Veciana, C. Rovira, D. B. Amabilino), Kluwer Academic Pub., Dordrecht, **1999**.
- [13] E. Iengo, E. Zangrando, E. Alessio, *Acc. Chem. Res.* **2006**, *39*, 841–851, and references therein.
- [14] For experimental details, see the Supporting Information.
- [15] The X-ray experiments for Ni<sub>2</sub>-CPD<sub>Py</sub> and C<sub>60</sub>CNi<sub>2</sub>-CPD<sub>Py</sub> were carried out on a Rigaku RAXIS imaging plate area detector with graphite-monochromated MoK $\alpha$  radiation ( $\lambda = 0.71073$  Å). The crystals were mounted on a glass fiber. The data were collected for Ni<sub>2</sub>-CPD<sub>Py</sub> ( $2\theta \leq 54.86^\circ$ ) and C<sub>60</sub>CNi<sub>2</sub>-CPD<sub>Py</sub> ( $2\theta \leq 54.92^\circ$ ) at  $-140^\circ\text{C}$ . To determine the cell constant and orientation matrix, three oscillation photographs were taken with an oscillation angle of  $3.0^\circ$  and exposure time of 60 s per degree for each frame. Intensity data were collected by taking 180 oscillation photographs with an oscillation angle of  $5.0^\circ$  and exposure time of 90 s per degree for each frame. Refraction data were corrected for both Lorentz and polarization effects. Ni<sub>2</sub>-CPD<sub>Py</sub>: C<sub>120</sub>H<sub>80</sub>N<sub>12</sub>Ni<sub>2</sub>, red crystal, crystal dimensions  $0.21 \times 0.18 \times 0.12$  mm<sup>3</sup>, monoclinic, space group *C2/c*,  $a = 35.645(4)$ ,  $b = 14.537(1)$ ,  $c = 24.693(2)$  Å,  $\beta = 118.835(5)^\circ$ ,  $V = 11208(2)$  Å<sup>3</sup>,  $Z = 4$ ,  $\rho_{\text{calcd}} = 1.071$  g cm<sup>-3</sup>, 92256 reflections collected, 12752 reflections used and 793 parameters.  $R_1 = 0.0706$  ( $I > 2.0\sigma(I)$ ),  $R_w = 0.2075$  (all data). C<sub>60</sub>CNi<sub>2</sub>-CPD<sub>Py</sub>: C<sub>166</sub>H<sub>64</sub>N<sub>12</sub>Ni<sub>2</sub>, reddish black crystal, crystal dimensions  $0.31 \times 0.15 \times 0.10$  mm<sup>3</sup>, monoclinic, space group *C2/c*,  $a = 36.842(4)$ ,  $b = 14.498(2)$ ,  $c = 24.607(4)$  Å,  $\beta = 115.396(5)^\circ$ ,  $V = 11837(3)$  Å<sup>3</sup>,  $Z = 4$ ,  $\rho_{\text{calcd}} = 1.311$  g cm<sup>-3</sup>, 97678 reflections collected, 13545 reflections used and 839 parameters.  $R_1 = 0.0767$  ( $I > 2.0\sigma(I)$ ),  $R_w = 0.2024$  (all data). CCDC-658588 and -658587 contain the supplementary crystallographic data for this paper. These data can be obtained free of charge from The Cambridge Crystallographic Data Centre via [www.ccdc.cam.ac.uk/data\\_request/cif](http://www.ccdc.cam.ac.uk/data_request/cif).
- [16] a) R. Taylor, O. Kennard, *J. Am. Chem. Soc.* **1982**, *104*, 5063–5070; b) G. R. Desiraju, T. Steiner, *The Weak Hydrogen Bond in Structural Chemistry and Biology*, Oxford University Press, Oxford, **1999**; c) M. Mascal, *Chem. Commun.* **1998**, 303–304; d) T. Steiner, *Angew. Chem.* **2002**, *114*, 50–80; *Angew. Chem. Int. Ed.* **2002**, *41*, 48–76.
- [17] a) E. Weber, S. Franken, H. Puff, J. Ahrendt, *J. Chem. Soc. Chem. Commun.* **1986**, 467–469; b) S. Boryczka, A. M. M. Schreurs, J. Kroon, T. Steiner, *Acta Crystallogr. Sect. C* **2000**, *56*, 263–264; c) M. Mazik, D. Bläser, R. Boese, *Tetrahedron* **2001**, *57*, 5791–5797; d) K. I. Nättinen, K. Rissanen, *Cryst. Growth Des.* **2003**, *3*, 339–353; e) R. J. Bowen, M. A. Fernandes, P. W. Gitari, M. Layh, *Acta Crystallogr. Sect. C* **2004**, *60*, o258–o260; f) E. Q. Gao, *Acta Crystallogr. Sect. C* **2005**, *61*, o110–o111.
- [18] J. Y. Zheng, K. Tashiro, Y. Hirabayashi, K. Kinbara, K. Saigo, T. Aida, S. Sakamoto, K. Yamaguchi, *Angew. Chem.* **2001**, *113*, 1909–1913; *Angew. Chem. Int. Ed.* **2001**, *40*, 1857–1861.
- [19] In the crystal of C<sub>60</sub>CNi<sub>2</sub>-CPD<sub>Py</sub>, the displacements of the *meso* carbon atoms from the four-nitrogen plane are 0.558,  $-0.418$ ,  $0.599$ ,  $-0.658$  Å, positive values meaning outward. The rotation angle of the two porphyrins around the center-to-center axis is  $24.3^\circ$ , and the torsion angle of the two butadiyne moieties is  $31.1^\circ$ .
- [20] In the crystal of C<sub>60</sub>CNi<sub>2</sub>-CPD<sub>Py</sub>, the C $\cdots$ N distances between the pyrrole  $\beta$  carbon atoms and the nitrogen atoms of the pyridyl groups are  $3.406(4)$  and  $3.773(5)$  Å, the shortest carbon–carbon separation between the adjacent pyridyl groups is  $3.414(7)$  Å, and the dihedral angle is  $7.04^\circ$ .