


# Thermoresponsive Chemical Connectors Based on Hybrid Nanowire Forests\*\*

Hyunhyub Ko, Zhenxing Zhang, Yu-Lun Chueh, Eduardo Saiz, and Ali Javey\*

Micro- and nanostructured surfaces found in biological systems have inspired the fabrication of functional materials with unique optical, chemical, and mechanical properties.<sup>[1]</sup> Inspired by the nanofibrillar structures of gecko adhesives,<sup>[2]</sup> we recently reported self-selective, chemical connectors (i.e., fasteners) based on interpenetrating nanowire (NW) forests, which primarily use the highly tunable van der Waals (vdW) interactions to enable efficient binding of components at both macro- and microscales.<sup>[3]</sup> Of particular interest to certain practical applications are programmable fasteners that can change their adhesion properties on command, for example, in response to external stimuli. In this regard, herein, we report programmable NW fasteners that reversibly change their wet adhesion strength in response to a thermal change of the environment. The thermoresponsive NW fasteners are based on core/multishell hybrid NW forests with an outer shell of poly(*N*-isopropylacrylamide) (PNIPAM). PNIPAM is a thermoresponsive hydrogel with a lower critical solution temperature (LCST) of approximately 32 °C in water.<sup>[4]</sup> Specifically, at room temperature, PNIPAM absorbs water, resulting in the swelling of the polymer and hydrophilic surface properties. However, PNIPAM shrinks at temperatures higher than the LCST and transforms to a hydrophobic state. We utilized this well known property of PNIPAM in conjunction with high aspect ratio nanofibrillar structures to enable programmable fasteners with tunable properties.

The fabrication procedure for the thermoresponsive NW fasteners is outlined in Figure 1a. First, Ge/parylene core/shell NW forests were prepared by growing Ge NW forests

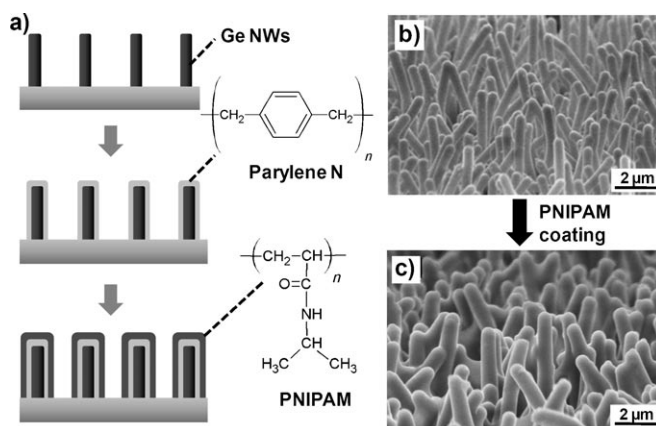

**Figure 1.** a) Fabrication procedure for a thermoresponsive NW forest, used as one mate of the proposed unisex fasteners. b,c) Scanning electron microscopy (SEM) images of Ge/parylene NW forests before and after the deposition of the PNIPAM outer shell.


(length ca. 10 μm, diameter 20–30 nm) on Si/SiO<sub>2</sub> substrates and then depositing a parylene N shell (ca. 200 nm) as we previously reported elsewhere.<sup>[3]</sup> Next, a thin layer of PNIPAM shell was deposited on the NW arrays by photopolymerization of a solution mixture of NIPAM monomers, 2,2'-diethoxyacetophenone photoinitiator, and *N,N*-methylenebisacrylamide cross-linker (see the Experimental Section for process details). In this structure, the Ge core with high Young's modulus serves as the backbone template. The parylene shell provides surface compliance and structural robustness, without which the inorganic NWs readily break and detach from the substrate. Furthermore, the hydrophobic parylene shell, which enhances the stiffness of the NWs, minimizes the aggregation of the NW arrays during the PNIPAM deposition processing. Finally, the PNIPAM outer shell serves as the thermoresponsive layer for modulation of the adhesion properties.

The hybrid NW forests modified with thermoresponsive PNIPAM outer shell exhibited thermally tunable surface wetting properties. Specifically, a transition of the water contact angle (CA) from 70 to 138° is observed as the temperature is raised to greater than 32 °C (Figure 2). In contrast, a planar PNIPAM film shows a change in water CA from 60 to 76° as the temperature is raised above LCST (Figure 2), which is consistent with previously reported

[\*] Dr. H. Ko, Z. Zhang, Dr. Y.-L. Chueh, Prof. A. Javey  
Department of Electrical Engineering and Computer Sciences and  
Berkeley Sensor and Actuator Center  
University of California at Berkeley, Berkeley, CA 94720 (USA)  
E-mail: ajavey@eecs.berkeley.edu  
and  
Materials Sciences Division, Lawrence Berkeley National Laboratory  
Berkeley, CA 94720 (USA)  
Fax: (+1) 510-643-7846  
Z. Zhang  
Key Laboratory for Magnetism and Magnetic Materials of the  
Ministry of Education, Lanzhou University (China)  
Dr. E. Saiz  
Materials Sciences Division, Lawrence Berkeley National Laboratory  
(USA)

[\*\*] This work was supported by DARPA/DSO, NSF Center of Integrated Nanomechanical Systems, and Berkeley Sensor and Actuator Center. Z.Z. acknowledges a fellowship from the China Scholarship Council. The nanowire synthesis part of this project was supported by a Laboratory Directed Research and Development grant from Lawrence Berkeley National Laboratory.

Supporting information for this article is available on the WWW under <http://dx.doi.org/10.1002/anie.200904724>.

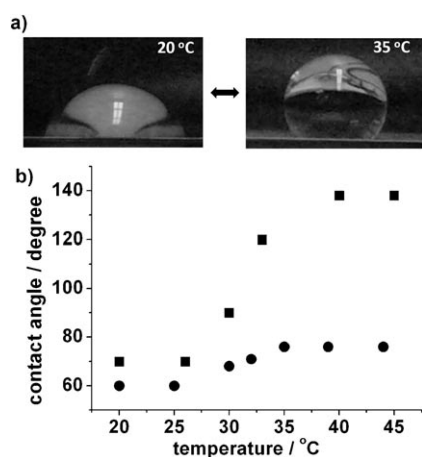


**Figure 2.** Thermoresponsive wetting properties of NW forests. a) Water droplet on the surface of Ge/parylene/PNIPAM core/multi-shell NW forests at 20 (left) and 35 °C (right). b) Contact angle as a function of temperature for Ge/parylene/PNIPAM NW forests (■) and planar PNIPAM films (●).

studies.<sup>[4,5]</sup> The significant enhancement of the surface wetting modulation for the NW forests compared with the planar surfaces results from the geometric amplification effects of the wetting properties. The hydrophobicity of a rough surface has been known to increase with the increase of water/air interface area.<sup>[6]</sup> In our study, the micro- and nanoscale roughness of NW forests can trap air below the water drop and thus intensify the water contact angle relative to that of the planar film. This change of the contact angle of hybrid NW forests confirms the phase transition (i.e., hydrophilic/hydrophobic, swelling/shrinking) of PNIPAM at the LCST (ca. 32 °C), which in turn affects the shear adhesion of NW fasteners as described below.

Shear adhesion strengths were measured in water (Figure 3a schematic) as a function of temperature to investigate the thermoresponsive wet adhesion properties of the NW fasteners. The fasteners showed minimal shear adhesion strength of around  $0.2 \text{ N cm}^{-2}$  at temperatures of 20–30 °C (Figure 3a). However, a drastic enhancement of the shear adhesion strength by 170 times ( $34 \text{ N cm}^{-2}$ ) was observed when the water temperature was increased to 32 °C. The sharp transition of shear adhesion strength at 32 °C arises from the phase transition of PNIPAM at the LCST, directly affecting the interactions between PNIPAM surfaces. Our previous studies of Ge/parylene NW fasteners in both wet and dry environments have shed light on the dominant role of vdW interactions in the adhesion properties.<sup>[7]</sup> Since the vdW interactions between two identical surfaces with dielectric constant of  $\epsilon_1$  in a liquid medium with dielectric constant of  $\epsilon_2$  is known to depend on  $F = [(\epsilon_1 - \epsilon_2)/(\epsilon_1 + \epsilon_2)]^2$ ,<sup>[8]</sup> the adhesion can be readily tuned by changing the dielectric constant of the surfaces (in this case, PNIPAM outer shell).

Previous studies have shown that the dielectric constant of PNIPAM decreases from around 63 to around 17 when the temperature is increased from 15 °C to 40 °C.<sup>[9]</sup> A similar temperature dependency of the dielectric constant is expected for the PNIPAM outer shell of our NW fasteners, which

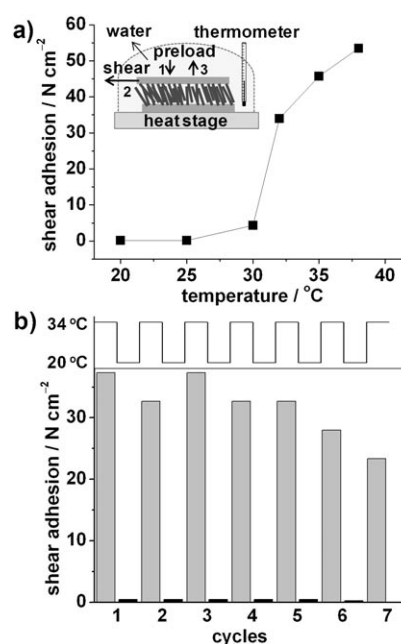

**Figure 3.** Thermoresponsive shear adhesion strength of hybrid NW fasteners. a) Shear wet adhesion strengths of the thermoresponsive NW fasteners involving the engagement of two NW forest substrates. The forests consist of Ge/parylene/PNIPAM core/multishell NWs. The inset shows the adhesion tests by sequential procedures of: 1) applying a normal preload stress (ca.  $70 \text{ N cm}^{-2}$ ) to engage the fasteners, 2) applying a shear force, and 3) removing the preload stress. b) Reversible modulation of shear adhesion strength of the thermoresponsive NW fasteners at two different water temperatures (20 and 34 °C). The gray and black bars correspond to the adhesion strength at 34 and 20 °C, respectively. The samples were allowed to equilibrate for 20 min at each temperature prior to performing the adhesion tests.


results in large modulation of vdW interactions [ $F(40^\circ\text{C})/F(15^\circ\text{C}) \approx 30$ ]. In fact, this thermoresponsive modulation of binding interactions has been previously utilized to induce flocculation of PNIPAM microgel particles dispersed in water,<sup>[10]</sup> and to control the adsorption and release of proteins on PNIPAM surfaces.<sup>[5]</sup> In addition to the modulation of  $\epsilon_1$ , hydrophobic effects arising from the thermally tunable surface wetting properties may contribute to the observed thermoresponsive adhesion behavior.<sup>[4]</sup> Specifically, the drastic transition to a superhydrophobic state at temperatures higher than the LCST (Figure 2) enhances the NW binding interactions in water. Finally, the induced swelling/deswelling behavior of PNIPAM may affect the filling factor and thus the interpenetration efficiency and the contact area of the NW arrays. However, the change in the filling factor is negligible with the overall NW diameter change of only 6–10% (corresponding to 25–40% change in the thickness of the PNIPAM outer shell) between the wet and dry states as estimated from the environmental SEM analyses (Figure S1 in the Supporting Information). Most likely, the observed thermoresponsive adhesion trend arises from a complex combination of the forces described above.

Notably, the thermoresponsive NW fasteners show selective adhesion behavior with low binding strengths to non-self-

similar surfaces. As can be seen in Figure S2 (in the Supporting Information), PNIPAM coated NW forests show minimal adhesion ( $< 1.6 \text{ N cm}^{-2}$ ) on flat glass surfaces for the temperature range  $20\text{--}40^\circ\text{C}$ . Furthermore, the adhesion strength between PNIPAM coated NW forests and planar PNIPAM films is only approximately  $4 \text{ N cm}^{-2}$  at high temperatures (Figure S2), which is 11 times lower than when NW forests are engaged with self-similar surfaces (i.e., in a fastener configuration). This selective binding is due to the drastic amplification of the contact area for NW/NW interfaces relative to the NW/planar surfaces for the relatively stiff NWs explored in this study.<sup>[3,7]</sup> Selective binding is an important characteristic of a fastener technology, as distinct from global adhesives, such as synthetic gecko materials, which are specifically designed to bind nonselectively to most surfaces.

Reversible adhesion with the capability of strong binding and easy detachment, controllable by temperature, is an important property of NW fasteners for practical applications. To demonstrate the reversible switching of adhesion strength of NW fasteners, we repeatedly measured the shear adhesion of NW fasteners by alternately transferring them between high ( $34^\circ\text{C}$ , above LCST) and low ( $20^\circ\text{C}$ , below LCST) temperature water baths. For each test, we immersed the NW forests in water for 20 min to provide enough time for swelling or shrinking of PNIPAM outer shells before engaging the NW fasteners for adhesion tests. The thermoresponsive wet adhesion behavior of the NW fasteners is reversible. Figure 3b shows the reversible switching of the shear adhesion strength of a fastener with strong adhesion ( $23\text{--}37 \text{ N cm}^{-2}$ ) at  $34^\circ\text{C}$  (gray bars in Figure 3b) and minimal adhesion ( $< 0.5 \text{ N cm}^{-2}$ ) at  $20^\circ\text{C}$  (red bars in Figure 3b) for seven cycles of operation. The thermoresponsive fasteners show excellent reversible modulation of adhesion strengths over multiple cycles, exhibiting only minimal degradation, as depicted in Figure 3b. The slight degradation of the shear adhesion of NW fasteners is due to surface damage of the NW fasteners during the adhesion test.

Since the adhesion strength of NW fasteners depends on the level of phase transition of PNIPAM shell above LCST, it is important to test the time required for NW fasteners to exhibit their maximum adhesion strength. To further elucidate the phase transition properties of PNIPAM shell and operational mechanics of NW fasteners, we examined the response time of NW fasteners by measuring the shear adhesion strength of NW fasteners at specified time intervals after immersing the samples in high temperature (above LCST) water bath. We observed a drastic linear enhancement in the shear adhesion within the first 5 min after transferring the fastener samples from a low ( $20^\circ\text{C}$ ) to high ( $35^\circ\text{C}$ ) temperature water bath (Figure 4). Beyond the first 5 min, the adhesion remained fairly constant at  $40\text{--}45 \text{ N cm}^{-2}$ . This result indicates that NW fasteners are fully operational within 5 min, beyond which the adhesion strength is close to the maximum value. Notably, the response times of the NW fasteners are significantly faster than the typical deswelling rate of millimeter-scale, bulk PNIPAM films (few minutes vs. several hours).<sup>[11,12]</sup> The faster response time is attributed to the use of nanofibrillar structures with large surface areas and

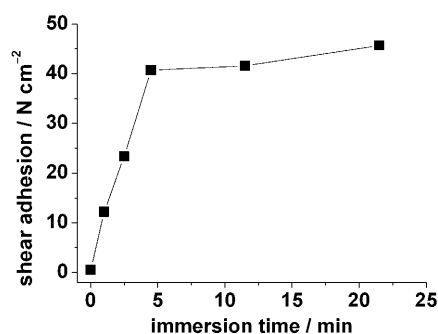

**Figure 4.** Shear adhesion strength as a function of the immersion time in water when the thermoresponsive NW fasteners were transferred from a low ( $20^\circ\text{C}$ ) to high ( $35^\circ\text{C}$ ) temperature water bath.

relatively thin PNIPAM films (ca. 100 nm thick shells) in this study, requiring minimal water diffusion lengths.

In summary, a unique platform for programmable fasteners based on core/multishell NW forests that reversibly change their wet adhesion strength by around 170 times in response to a water temperature change of less than  $5^\circ\text{C}$  is reported. The unique properties of the thermoresponsive PNIPAM outer shell in conjunction with the 3D geometric configuration of the high aspect NWs enables highly unique binding properties that arise primarily from tunable vdW interactions along with hydrophobic surface effects. In the future, programmable fasteners that respond to other external stimuli, such as chemical changes of the ambient environment or light, may be enabled by using a similar system to that proposed herein, but with a different responsive functional material for the outer shell.<sup>[13]</sup> This concept could potentially provide a wide range of applications ranging from tissue engineering<sup>[14]</sup> to macroscale self-assembly of materials.<sup>[15]</sup>

## Experimental Section

**PNIPAM coating:** A thin layer of PNIPAM was deposited on hybrid Ge/parylene core/shell NW forests by photopolymerization of a solution mixture containing *N*-isopropylacrylamide (NIPAM) monomers, 2,2'-diethoxyacetophenone (DEAP) photoinitiator, and *N,N*-methylenebisacrylamide (bis-AMD) crosslinker. The solution mixture was prepared by mixing 1.6 mmol of NIPAM, 30  $\mu\text{mol}$  of bis-AMD, and 6  $\mu\text{mol}$  DEAP in 2 mL deionized water. The solution mixture was degassed with nitrogen gas for 10 min to remove dissolved oxygen in the solution. The resulting solution was spread on the NW arrays and squeezed by gently pressing a glass slide cover on top. Finally, the polymerization was performed by using a UV lamp (365 nm, 15 W) for 60 min. These processing conditions resulted in a PNIPAM outer shell thickness of approximately 100 nm and the NW forests maintaining the nanofibrillar structures with some degree of aggregation, as evident from SEM analysis (Figure 1b and c).

Macroscopic wet adhesion tests at different temperatures: The wet adhesion tests were performed by immersing the NW fasteners inside a PDMS liquid cell filled with water. Then, a normal preload stress was applied to engage the NW fasteners (ca.  $0.5 \times 0.6 \text{ cm}^2$ ), then a shear force was applied, and finally the preload stress was removed to measure the pure shear adhesion strength. The shear stress at failure corresponds to the maximum shear adhesion strength. These adhesion tests were performed at different temperatures by checking

the water temperature with using a thermometer immersed in the water bath on top of a hot plate (inset in Figure 3a).

Received: August 25, 2009

Revised: October 21, 2009

Published online: December 8, 2009

**Keywords:** adhesion · gels · nanostructures · nanowires · noncovalent interactions

- [1] C. Sanchez, H. Arribart, M. M. G. Guille, *Nat. Mater.* **2005**, *4*, 277.
- [2] a) K. Autumn, Y. A. Liang, S. T. Hsieh, W. Zesch, W.-P. Chan, W. T. Kenny, R. Fearing, R. J. Full, *Nature* **2000**, *405*, 681; b) A. K. Geim, S. V. Dubonos, I. V. Grigorieva, K. S. Novoselov, A. A. Zhukov, S. Yu. Shapoval, *Nat. Mater.* **2003**, *2*, 461; c) L. Ge, S. Sethi, L. Ci, P. M. Ajayan, A. Dhinojwala, *Proc. Natl. Acad. Sci. USA* **2007**, *104*, 10792; d) G. Huber, H. Mantz, R. Spolenak, K. Mecke, K. Jacobs, S. N. Gorb, E. Arzt, *Proc. Natl. Acad. Sci. USA* **2005**, *102*, 16293; e) L. Qu, L. Dai, M. Stone, Z. Xia, Z. L. Wang, *Science* **2008**, *322*, 238; f) M. Murphy, B. Aksak, M. Sitti, *J. Adhes. Sci. Technol.* **2007**, *21*, 1281.
- [3] a) H. Ko, J. Lee, B. E. Schubert, Y.-L. Chueh, P. W. Leu, R. S. Fearing, A. Javey, *Nano Lett.* **2009**, *9*, 2054; b) R. Kapadia, H. Ko, Y.-L. Chueh, J. C. Ho, T. Takahashi, Z. Zhang, A. Javey, *Appl. Phys. Lett.* **2009**, *94*, 263110.
- [4] a) H. G. Schild, *Prog. Polym. Sci.* **1992**, *17*, 163; b) L. Liang, X. Feng, J. Liu, P. C. Rieke, G. E. Fryxell, *Macromolecules* **1998**, *31*, 7845.
- [5] D. L. Huber, R. P. Manginell, M. A. Samara, B. Kim, B. C. Bunker, *Science* **2003**, *301*, 352.
- [6] M. Miwa, A. Nakajima, A. Fujishima, K. Hashimoto, T. Watanabe, *Langmuir* **2000**, *16*, 5754.
- [7] H. Ko, Z. Zhang, Y.-L. Chueh, J. C. Ho, J. Lee, R. S. Fearing, A. Javey, *Adv. Funct. Mater.* **2009**, *19*, 3098.
- [8] *Intermolecular and Surface Forces*; J. Israelachvili, Academic, New York, **1992**.
- [9] K. Iwai, K. Hanasaki, M. Yamamoto, *J. Lumin.* **2000**, *87*, 1289.
- [10] J. Wu, B. Zhou, Z. Hu, *Phys. Rev. Lett.* **2003**, *90*, 048304.
- [11] R. Yoshida, K. Uchida, Y. Kaneko, K. Sakai, A. Kikuchi, Y. Sakurai, T. Okano, *Nature* **1995**, *374*, 240.
- [12] M. Shibayama, K. Nagai, *Macromolecules* **1999**, *32*, 7461.
- [13] R. Yerushalmi, A. Scherz, M. E. van der Boom, H. B. Kraatz, *J. Mater. Chem.* **2005**, *15*, 4480.
- [14] S. Ohya, Y. Nakayama, T. Matsuda, *Biomacromolecules* **2001**, *2*, 856.
- [15] G. Whitesides, M. Boncheva, *Proc. Natl. Acad. Sci. USA* **2002**, *99*, 4769.