

Majority-Rules-Type Helical Poly(quinoxaline-2,3-diyl)s as Highly Efficient Chirality-Amplification Systems for Asymmetric Catalysis**

Yuan-Zhen Ke, Yuuya Nagata, Tetsuya Yamada, and Michinori Sugimoto*

Abstract: A highly efficient majority-rules effect of poly(quinoxaline-2,3-diyl)s (PQXs) bearing 2-butoxymethyl chiral side chains at the 6- and 7-positions was established and attributed to large ΔG_h values (0.22–0.41 kJ mol⁻¹), which are defined as the energy difference between *P*- and *M*-helical conformations per chiral unit. A PQX copolymer prepared from a monomer derived from (*R*)-2-octanol (23 % *ee*) and a monomer bearing a PPh₂ group adopted a single-handed helical structure (>99 %) and could be used as a highly enantioselective chiral ligand in palladium-catalyzed asymmetric reactions (products formed with up to 94 % *ee*), in which the enantioselectivity could be switched by solvent-dependent inversion of the helical PQX backbone.

Helical majority-rules-type polymers,^[1,2] which are derived from chiral monomers with low *ee* values and adopt nonlinearly enhanced single-handed helical conformations, are among the most promising platforms for the development of new asymmetric-amplification systems.^[3] The concept of the enantioselective synthesis of chiral compounds through asymmetric amplification^[4] has attracted considerable interest, as it may afford useful model systems for the elucidation of the origin of natural homochirality^[5] as well as practical methods for the generation of optically active molecules.^[6] Although a number of helical polymers^[7] with efficient asymmetric amplification in terms of helix-sense induction have been developed, the highly enantioselective production of chiral compounds on the basis of asymmetric amplification by majority-rules-type helical polymers has not been reported. According to the theory developed by Green and co-workers for polymers containing helix-sense-reversal conformations (Green theory, case 3),^[8] the maximum value of the screw-sense excess (*se*) of a helical polymer, whose degree of polymerization (DP) is sufficiently large, is limited by ΔG_h

(the energy difference between *P*- and *M*-helical conformations) and ΔG_r (the energy difference of the helix-sense-reversal conformation relative to the helical conformation). For most helical polymers, the ΔG_h and/or ΔG_r values are too small to induce a purely single handed screw sense. A cis-transoidal poly(aryl acetylene) bearing (*R*)-(1-phenylethyl)-carbamate side chains ($\Delta G_h = 0.0048$ kJ mol⁻¹, $\Delta G_r = 15.5$ kJ mol⁻¹), for example, exhibits even at very high degrees of polymerization merely 49.5 % *se* at room temperature.^[9] For the enantioselective generation of chiral compounds from a majority-rules-type helical polymer, the use of a polymer backbone exhibiting large ΔG_h and ΔG_r values is therefore of critical importance.

Recently, we reported sergeants-and-soldiers-type^[10] poly(quinoxaline-2,3-diyl)s (PQXs) containing (*R*)-2-butoxymethyl and propoxymethyl groups in a random manner.^[11] A ΔG_h value of 0.59 kJ mol⁻¹ was estimated for the chiral unit of this polymer system, thus indicating that 22 chiral units are required for a screw-sense induction of 99.0 % *se*. We have also reported that single-handed helically chiral PQXs with pendent diarylphosphanyl groups^[12] can serve as effective chiral ligands for various asymmetric reactions.^[13] However, the controlled screw-sense induction of majority-rules-type PQXs, prepared from monomers with low *ee* values, still remains to be fully explored.

We herein demonstrate efficient asymmetric screw-sense amplification in majority-rules-type PQXs prepared from starting materials with low *ee* values. In contrast to reported majority-rules-type polymers, which bear only one chiral group, the chiral units of the PQXs discussed herein contain two chiral side chains. Accordingly, two different types of majority-rules-type PQXs are discussed separately: 1) PQXs consisting of two enantiomeric monomer units in various ratios, and 2) PQXs that also contain *meso* units. Quantification of the ΔG_h and ΔG_r values by circular dichroism (CD) measurements suggested that they should be sufficient to induce a purely single-handed helical structure. Finally, we carried out asymmetric reactions in the presence of majority-rules-type PQXs with PPh₂ pendant groups as chiral ligands to prove the concept of asymmetric amplification based on majority-rules-type helical polymers.


We obtained chiral monomers with varying *ee* values by preparing the enantiomeric diisocyanobenzenes (*R,R*)-**1** and (*S,S*)-**1** separately and then mixing them in various ratios (Scheme 1). To investigate the influence of the DP on the screw-sense induction, we first polymerized a 55:45 mixture of (*R,R*)-**1** and (*S,S*)-**1** (10 % *ee*), which resulted in the formation of oligo- and polymeric PQXs (DP: 40–1000; Figure 1). These polymers exhibited a nonlinear relationship between their DPs and their Kuhn dissymmetry factors (g_{abs}), that is, they

[*] Dr. Y.-Z. Ke,^[†] Dr. Y. Nagata,^[†] Dr. T. Yamada, Prof. Dr. M. Sugimoto
Department of Synthetic Chemistry and Biological Chemistry
Graduate School of Engineering, Kyoto University
Katsura, Nishikyo-ku, Kyoto 615-8510 (Japan)
E-mail: sugimoto@sbchem.kyoto-u.ac.jp
Prof. Dr. M. Sugimoto
JST, CREST
Katsura, Nishikyo-ku, Kyoto 615-8510 (Japan)

[†] These authors contributed equally.

[**] Financial support for this research was provided by the Japan Science and Technology Corporation (CREST, "Development of High-Performance Nanostructures for Process Integration" and "Establishment of Molecular Technology towards the Creation of New Function").

Supporting information for this article is available on the WWW under <http://dx.doi.org/10.1002/anie.201502209>.

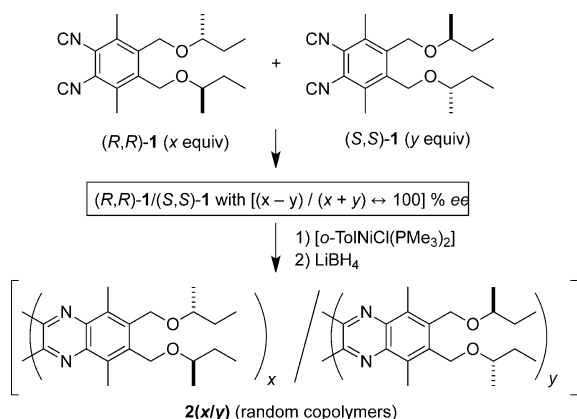

Scheme 1. Synthesis of random copolymers **2(x/y)** from chiral monomers **(R,R)-1** and **(S,S)-1** with varying *ee* values.

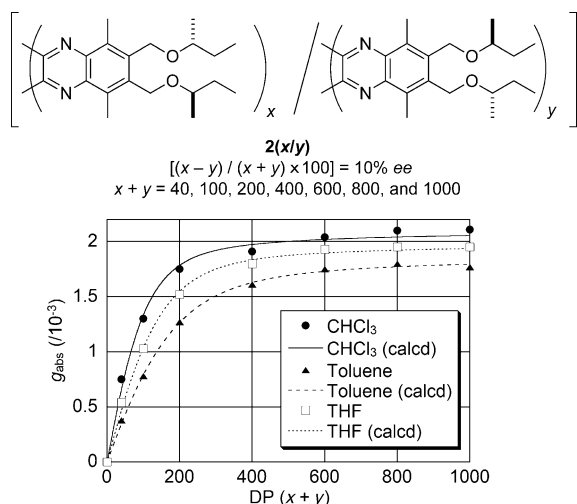


Figure 1. Correlation between the DP and g_{abs} values ($\Delta\epsilon/\epsilon$ at 362.5 nm) of **2(x/y)** prepared from monomers with 10% *ee* in CHCl_3 , toluene, or THF.

did not obey the Green theory for polymers without helix-reversal conformations (Green theory, case 1).^[8] Although we previously reported that the helix-sense-reversal conformation in the polymer chain of PQXs is negligible for low molecular weights (DP < 200; see also the Supporting Information),^[11b] these results nevertheless suggested that it is necessary to take the helix reversal into account for a quantitative understanding of high-molecular-weight PQXs containing chiral units with low *ee* values. Therefore, the observed g_{abs} values were fitted by using the general theory proposed by Green and co-workers for polymers containing helix-reversal conformations (Green theory, case 3).^[8] Accordingly, nonlinear least-square fittings of g_{abs} versus DP were carried out, and the square sums of the deviations were minimized by variation of the three parameters ΔG_{h} , g_{max} , and ΔG_{r} .

For DP > 200, the g_{abs} values were found to converge (final values for the three different solvents are given in Table 1). The observed ΔG_{h} values (0.22–0.41 kJ mol⁻¹) were almost identical to those of previously reported PQXs (0.24–

Table 1: Calculated ΔG_{h} , ΔG_{r} , and g_{max} values for **2(x/y)** (DP: 40–1000).

Solvent	ΔG_{h} [kJ mol ⁻¹]	ΔG_{r} [kJ mol ⁻¹]	g_{max} [$\times 10^{-3}$]
CHCl_3	−0.41	13.4	+2.37
toluene	−0.22	14.9	+2.14
THF	−0.30	14.4	+2.24

0.59 kJ mol⁻¹)^[11] and significantly larger than those of other helical polymers, such as polyacetylenes, polyisocyanates, and polysilanes (0.005–0.06 kJ mol⁻¹).^[2e] The ΔG_{r} values (13.4–14.9 kJ mol⁻¹) for **2(x/y)** were found to be comparable with those of previously reported helical polymers (7–17 kJ mol⁻¹).^[2e] The large ΔG_{h} values of PQXs played a central role in the highly efficient control of the screw sense of their helical main chains. Nevertheless, the values in Table 1 and Figure 1 also suggest that the use of monomers with 10% *ee* is insufficient for the induction of absolute screw senses, even for polymers with a DP of 1000.

Subsequently, polymers **2(x/y)** with a DP of 1000 were prepared from chiral monomers with varying *ee* values (Figure 2a). These polymers also showed a nonlinear relationship between their g_{abs} value and the *ee* value of the monomer. Regression curves were calculated in accordance with the Green general theory (case 3),^[8] in which the reversal conformation is considered with the determined values of ΔG_{h} , ΔG_{r} , and g_{max} . Good agreement was observed between the experimentally obtained g_{abs} values and the calculated



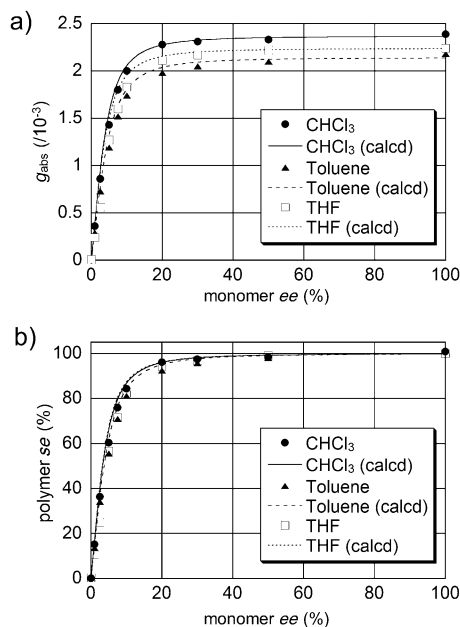


Figure 2. Correlation between the monomer *ee* value and the a) g_{abs} ($\Delta\epsilon/\epsilon$ at 362.5 nm) or b) *se* value of **2(x/y)** (DP: 1000) in CHCl_3 , THF, or toluene.



curves, thus suggesting that the obtained values should be representative for these PQX polymers. On the basis of the calculated values, a correlation between the *se* value of the polymer backbone and the *ee* value of the monomer was established (Figure 2b). The majority-rules effect was clearly observable, and in the examined solvents, monomers with 30% *ee* were able to induce >97% *se* in the polymer backbone.

Subsequently, we attempted to apply this substantial majority-rules effect in asymmetric catalysis. For that purpose, polymer **3**, bearing pendent PPh₂ groups, was synthesized from the corresponding chiral monomer **1** with 30% *ee*. According to its CD spectrum, polymer ligand **3** exhibited an almost absolute *P*-helical conformation (see the Supporting Information). When **3** was used as a ligand in the palladium-catalyzed asymmetric hydrosilylation of β -methylstyrene with trichlorosilane, the corresponding product was obtained with 94% *ee*, thus reflecting the almost exclusive single-handedness of the helical main chain as induced by the chiral monomers with 30% *ee*. (Scheme 2).^[14]

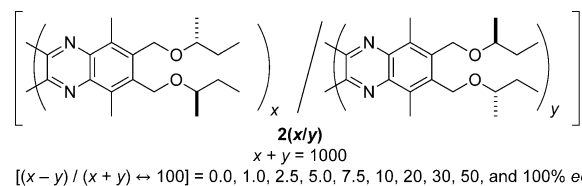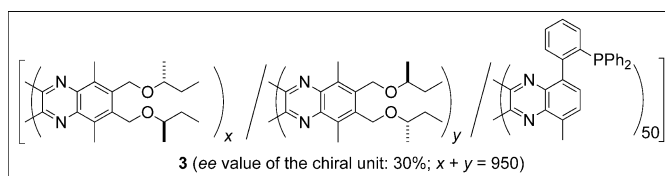

Scheme 2. Asymmetric hydrosilylation of β -methylstyrene in the presence of polymer ligand **3** prepared from a chiral monomer (30% *ee*) and a monomer bearing a PPh₂ group.

To prevent the formation of *meso*-**1** during the preparation of **3**, we synthesized optically pure (*R,R*)-**1** and (*S,S*)-**1** separately and then mixed them. To increase the practicality of this system, we prepared monomers with 30% *ee* from (*R*)-2-butanol. Monomers consisted of (*R,R*)-**1**, (*S,S*)-**1**, and *meso*-**1** in a 43.3:13.3:43.4 ratio (see the Supporting Information). According to the Green theory,^[8] the *se* value of a helical polymer is determined from the difference between the numbers of repeating units derived from *d* and *l* monomers in the polymer chain. Although enantiomeric enrichment of *d,l* monomers ((*R,R*)-**1** and (*S,S*)-**1**; 53% *ee*) occurs, the difference between the numbers of repeating units derived from *d* and *l* monomers in a polymer prepared from (*R,R*)-**1**, (*S,S*)-**1**, and *meso*-**1** is equal to that of a polymer prepared from (*R,R*)-**1** and (*S,S*)-**1** (30% *ee*) as long as their DPs are identical, owing to the inclusion of *meso* isomers. Therefore, the screw-sense induction in polymers obtained from a ternary monomer mixture including the *meso* isomer is expected to be identical to that in polymers obtained from a corresponding binary monomer mixture consisting of (*R,R*)-**1** and (*S,S*)-**1** (30% *ee*). Indeed, polymer **4**, obtained from such a ternary monomer mixture, exhibited an absolute *P*-helical single-handed screw sense (Scheme 3). Polymer **4** can be regarded both as a majority-rules-type polymer, as well as a sergeants-

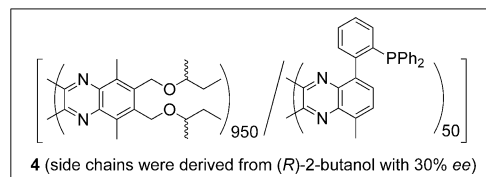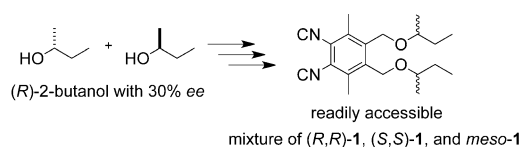


Scheme 3. Asymmetric hydrosilylation of β -methylstyrene in the presence of polymer ligand **3** derived from (*R*)-2-butanol with 30% *ee*.

and-soldiers-type polymer, whereby the *meso*-**1** units act as the soldiers. In the asymmetric hydrosilylation, **4** generated the corresponding product with high enantioselectivity (96% *ee*), which indicates that the *meso* units behaved as normal soldier units in the sergeants-and-soldiers-type screw-sense induction and did not affect the enantioselectivity of the catalysis.

Subsequently, we demonstrated the synthesis of single-handed polymer ligands by using an optically active secondary alcohol with a low *ee* value. This alcohol was obtained by ruthenium-catalyzed asymmetric hydrogenation in the presence of an inexpensive chiral ligand based on L-proline.^[15] Thus, 2-octanol was obtained with 23% *ee* from the hydrogenation of 2-octanone (Scheme 4). This optically active alcohol enabled the synthesis of the corresponding optically active monomer in a ratio of 38.8:15.8:45.4 with respect to *d*, *l*, and *meso* isomers (see the Supporting Information). Polymerization of this mixture of stereoisomers with the corresponding phosphorous-containing monomer provided copolymer **5**. CD measurements revealed a purely right handed helical structure for this polymer ligand, (*P*)-**5**, which afforded the *S* product with 94% *ee* when used in the palladium-catalyzed asymmetric hydrosilylation.

Most importantly, the helical sense of the PQXs bearing optically active 2-butoxymethyl side chains was found to be chirality-switchable.^[13a–d] The corresponding exclusively left handed helical polymer ligand (*M*)-**5** was obtained when a solution of (*P*)-**5** in 1,1,2-TCE/toluene (3:1 v/v) was heated at 60 °C for 24 h. The left-handed-helical polymer (*M*)-**5** was then used as a ligand in the asymmetric hydrosilylation, and under similar conditions, the *R* product was obtained with high enantioselectivity (95% *ee*). This result demonstrates that the treatment of (*P*)-**5** in 1,1,2-TCE/toluene induced an almost absolute *M*-helical conformation in **5**.

To prove the general viability of this asymmetric-amplification system, we also carried out an asymmetric Suzuki–Miyaura coupling reaction^[16] in the presence of (*P*)-**5**. The reaction afforded the axially chiral *S* product with high enantioselectivity (93% *ee*). When (*M*)-**5** with inverted helical chirality was used, the corresponding *R* product was obtained with high enantioselectivity (92% *ee*; Scheme 4).

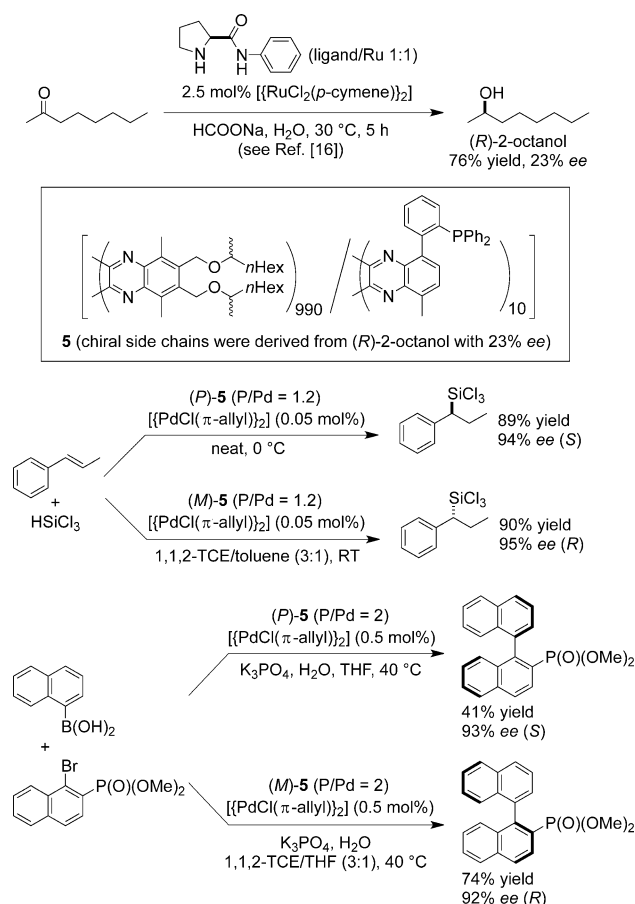

Scheme 4. Asymmetric hydrosilylation of β-methylstyrene and asymmetric Suzuki–Miyaura cross-coupling in the presence of polymeric ligand **5** prepared from (R)-2-octanol with 23% ee. 1,1,2-TCE = 1,1,2-trichloroethane.

These results again demonstrate that the low enantiomeric purity of 2-octanol was amplified by the formation of a single-handed screw sense and multiplied through the generation of enantiomerically pure products in the asymmetric reactions. Furthermore, the highly enantioselective generation of both enantiomers from a single chiral source with low ee values was possible by taking advantage of the solvent-dependent helix inversion of PQXs.

In summary, we have described screw-sense induction in the helical main chain of majority-rules-type poly(quinoxaline-2,3-diyl)s derived from starting materials with low ee values. A copolymer bearing pendent PPh₂ groups and chiral side chains derived from (R)-2-octanol with a low ee value adopted a purely single handed helical structure, thus affording high enantioselectivities in asymmetric palladium-catalyzed hydrosilylation and Suzuki–Miyaura cross-coupling reactions. From these reactions, both enantiomeric products were obtained with high enantioselectivity through solvent-dependent inversion of the helical sense in the same polymer catalyst. To the best of our knowledge, the highly enantioselective generation of both enantiomers of a catalyst from a single chiral source with a low ee value has not been reported previously. It was made possible by the asymmetric amplification of majority-rules-type helical polymers. This

outstanding molecular function of PQXs relies on their extremely large intrinsic ΔG_h values. We are currently carrying out further investigations into catalytic applications of these single-handed-helical PQXs as a new class of chiral supporting ligands characterized by highly efficient asymmetric amplification and multiplication.

Keywords: asymmetric amplification · asymmetric synthesis · helical structures · ligand design · polymer catalysts

How to cite: *Angew. Chem. Int. Ed.* **2015**, *54*, 9333–9337
Angew. Chem. **2015**, *127*, 9465–9469

- [1] M. M. Green, B. A. Garetz, B. Munoz, H. P. Chang, S. Hoke, R. G. Cooks, *J. Am. Chem. Soc.* **1995**, *117*, 4181–4182.
- [2] a) R. P. Cheng, S. H. Gellman, W. F. DeGrado, *Chem. Rev.* **2001**, *101*, 3219–3232; b) J. J. L. M. Cornelissen, A. E. Rowan, R. J. M. Nolte, N. A. J. M. Sommerdijk, *Chem. Rev.* **2001**, *101*, 4039–4070; c) D. J. Hill, M. J. Mio, R. B. Prince, T. S. Hughes, J. S. Moore, *Chem. Rev.* **2001**, *101*, 3893–4011; d) T. Nakano, Y. Okamoto, *Chem. Rev.* **2001**, *101*, 4013–4038; e) E. Yashima, K. Maeda, H. Iida, Y. Furusho, K. Nagai, *Chem. Rev.* **2009**, *109*, 6102–6211.
- [3] M. M. Green, J. W. Park, T. Sato, A. Teramoto, S. Lifson, R. L. B. Selinger, J. V. Selinger, *Angew. Chem. Int. Ed.* **1999**, *38*, 3138–3154; *Angew. Chem.* **1999**, *111*, 3328–3345.
- [4] a) C. Girard, H. B. Kagan, *Angew. Chem. Int. Ed.* **1998**, *37*, 2922–2959; *Angew. Chem.* **1998**, *110*, 3088–3127; b) R. Noyori, M. Kitamura, *Angew. Chem. Int. Ed. Engl.* **1991**, *30*, 49–69; *Angew. Chem.* **1991**, *103*, 34–55; c) B. L. Feringa, R. A. van Delden, *Angew. Chem. Int. Ed.* **1999**, *38*, 3418–3438; *Angew. Chem.* **1999**, *111*, 3624–3645.
- [5] a) J. L. Bada, *Nature* **1995**, *374*, 594–595; b) J. S. Siegel, *Chirality* **1998**, *10*, 24–27; c) J. Bailey, *Origins Life Evol. Biospheres* **2001**, *31*, 167–183; d) K. Soai, T. Kawasaki, A. Matsumoto, *Chem. Rec.* **2014**, *14*, 70–83.
- [6] a) A. O. King, E. G. Corley, R. K. Anderson, R. D. Larsen, T. R. Verhoeven, P. J. Reider, Y. B. Xiang, M. Belley, Y. Leblanc, M. Labelle, P. Prasit, R. J. Zamboni, *J. Org. Chem.* **1993**, *58*, 3731–3735; b) M. Z. Zhao, A. O. King, R. D. Larsen, T. R. Verhoeven, P. J. Reider, *Tetrahedron Lett.* **1997**, *38*, 2641–2644; c) H. B. Kagan, *Adv. Synth. Catal.* **2001**, *343*, 227–233.
- [7] a) E. Yashima, K. Maeda, *Macromolecules* **2008**, *41*, 3–12; b) E. Yashima, K. Maeda, T. Nishimura, *Chem. Eur. J.* **2004**, *10*, 42–51.
- [8] S. Lifson, C. Andreola, N. C. Peterson, M. M. Green, *J. Am. Chem. Soc.* **1989**, *111*, 8850–8858.
- [9] K. Morino, K. Maeda, Y. Okamoto, E. Yashima, T. Sato, *Chem. Eur. J.* **2002**, *8*, 5112–5120.
- [10] M. M. Green, M. P. Reidy, R. J. Johnson, G. Darling, D. J. O'Leary, G. Willson, *J. Am. Chem. Soc.* **1989**, *111*, 6452–6454.
- [11] a) T. Yamada, Y. Nagata, M. Sugimoto, *Chem. Commun.* **2010**, *46*, 4914–4916; b) Y. Nagata, T. Yamada, T. Adachi, Y. Akai, T. Yamamoto, M. Sugimoto, *J. Am. Chem. Soc.* **2013**, *135*, 10104–10113.
- [12] T. Yamamoto, M. Sugimoto, *Angew. Chem. Int. Ed.* **2009**, *48*, 539–542; *Angew. Chem.* **2009**, *121*, 547–550.
- [13] a) T. Yamamoto, T. Yamada, Y. Nagata, M. Sugimoto, *J. Am. Chem. Soc.* **2010**, *132*, 7899–7901; b) T. Yamamoto, Y. Akai, Y. Nagata, M. Sugimoto, *Angew. Chem. Int. Ed.* **2011**, *50*, 8844–8847; *Angew. Chem.* **2011**, *123*, 9006–9009; c) Y. Akai, T. Yamamoto, Y. Nagata, T. Ohmura, M. Sugimoto, *J. Am. Chem. Soc.* **2012**, *134*, 11092–11095; d) M. Sugimoto, T. Yamamoto, Y. Nagata, T. Yamada, Y. Akai, *Pure Appl. Chem.* **2012**, *84*, 1759–1769; e) T. Yamamoto, Y. Akai, M. Sugimoto, *Angew. Chem. Int.*

- Ed.* **2014**, 53, 12785–12788; *Angew. Chem.* **2014**, 126, 12999–13002.
- [14] a) T. Hayashi, S. Hirate, K. Kitayama, H. Tsuji, A. Torii, Y. Uozumi, *J. Org. Chem.* **2001**, 66, 1441–1449; b) T. Hayashi, *Acc. Chem. Res.* **2000**, 33, 354–362; c) Y. Uozumi, T. Hayashi, *J. Am. Chem. Soc.* **1991**, 113, 9887–9888.
- [15] M. Boukachabia, S. Zeror, J. Collin, J. C. Fiaud, L. A. Zouiouche, *Tetrahedron Lett.* **2011**, 52, 1485–1489.
- [16] a) A. N. Cammidge, K. V. L. Crepy, *Chem. Commun.* **2000**, 1723–1724; b) J. J. Yin, S. L. Buchwald, *J. Am. Chem. Soc.* **2000**, 122, 12051–12052; c) Y. Uozumi, Y. Matsuura, T. Arakawa, Y. M. A. Yamada, *Angew. Chem. Int. Ed.* **2009**, 48, 2708–2710; *Angew. Chem.* **2009**, 121, 2746–2748; d) X. Q. Shen, G. O. Jones, D. A. Watson, B. Bhayana, S. L. Buchwald, *J. Am. Chem. Soc.* **2010**, 132, 11278–11287.

Received: March 9, 2015

Revised: April 25, 2015

Published online: June 11, 2015