


temperatures above 100 °C and the high molecular weight of the obtained polyethylene were comparable to the best values achieved with the previously optimized systems, such as Pd/phosphine-sulfonate catalysts **2-Pd**. Moreover, Pd/IzQO catalysts do not require high concentrations of polar monomers for effective incorporation; their incorporation affinity toward polar monomers over ethylene was 5–10 times higher than that of Pd/phosphine-sulfonate catalysts **2-Pd**, and polyethylene with comparable molecular weight is produced. In light of the above-mentioned issues regarding nickel-based catalysts, we envisioned that IzQO ligands might be well suitable for complexing nickel ions.

The synthetic procedure for Ni/IzQO complexes is summarized in Scheme 1. An initial attempt using [(tmeda)-NiMe₂] (tmeda = *N,N,N,N*-tetramethylethylenediamine) and imidazolium salt **L^a** in the presence of pyridine or 2,6-lutidine

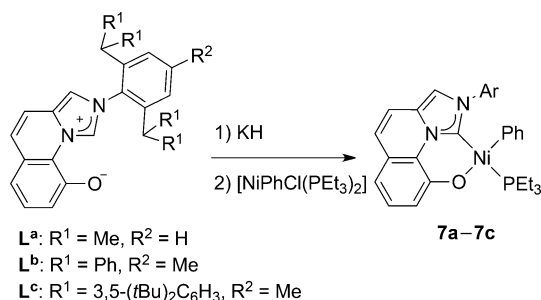

Scheme 1. Synthesis of Ni/IzQO complexes **7a–c**.

afforded a mixture of the desired pyridine- or 2,6-lutidine-coordinated complexes [(C⁺O)NiMeL] and an oxygen-bridged nickel methyl dimer [(C⁺O)NiMe]₂. Therefore, a stronger neutral ligand PEt₃ was used, as reported by Grubbs et al. for the synthesis of related complexes **6-Ni**.^[19] Treatment of [NiPhCl(PEt₃)₂] with deprotonated carbene salts afforded nickel complexes [(C⁺O)NiPh(PEt₃)] (**7a–c**) selectively. The solid-state structure of complex **7a** was confirmed by X-ray crystallography (Figure 2).^[25] Similarly to previously reported nickel complexes **3**, **5**, and **6-Ni**, because of the strong *trans* effect of the NHC moiety, the carbene was located in the *trans* position through weak coordination with PEt₃. The Ni–C1 and Ni–O1 bond lengths (1.902(4) Å and 1.908(2) Å, respectively) are slightly longer than those reported by Waymouth and coworkers for complex **5** (1.848(3) Å and 1.891(2) Å, respectively).^[18a] The 2,6-diisopropylphenyl ring on the nitrogen atom is nearly perpendicular to the NHC plane, with a dihedral angle of 67.8°. The mean dihedral angle between the NHC plane and the metal coordination square,^[23] which corresponds to the averaged torsion angle of the NHC plane from the coordination square, was found to be 32.5° in complex **7a**, which is slightly larger than that in complex **5** (21.9°) and that in the Pd/IzQO complex bearing ligand **L^a** (23.6°).

With nickel complexes **7a–c** in hand, we first investigated their catalytic activity for ethylene polymerization for 0.5 h (Table 1). At 100 °C, which was the optimal temperature for the Pd/IzQO system,^[23] nickel complex **7a** can initiate

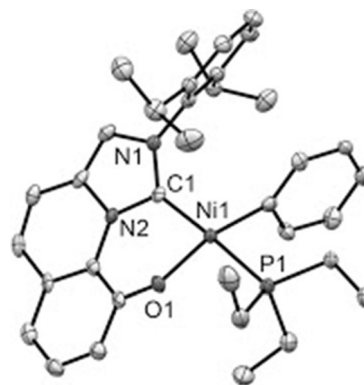


Figure 2. X-ray structure of **7a**. Selected bond lengths [Å]: Ni1–C1 = 1.902(4), Ni1–O1 = 1.908(2), Ni1–P1 = 2.2202(12).

Table 1: Ethylene polymerization by Ni/IzQO complexes **7a–c**.^[a]

Entry	Cat.	<i>T</i> [°C]	Activity [kg mol ^{−1} h ^{−1}]	<i>M</i> _n ^[b] [kg mol ^{−1}]	<i>M</i> _w / <i>M</i> _n ^[b]	Branch ^[c]
1	7a	100	240	2.6	2.3	0
2	7b	100	320	6.9	2.3	0
3	7c	100	720	16	2.3	0
4	7c	80	630	16	2.7	0
5	7c	50	340	39	2.1	0
6	7c	30	0	–	–	–
7 ^[d]	7c	50	1190	54	2.1	0
8 ^[d]	7c	30	1000	84	2.0	0

[a] A mixture of catalyst (2.5 μmol) and ethylene (4.0 MPa) in toluene (7.5 mL) was stirred for 0.50 h at the indicated temperature. [b] Number-average molecular weight measured by size-exclusion chromatography using polystyrene as an internal standard and corrected by universal calibration. [c] Methyl branches per 1000 C determined by quantitative ¹³C NMR analysis. [d] A solution of [Ni(cod)₂] (5.0 μmol; 2.0 equivalents to the Ni/IzQO catalyst) in toluene (1.0 mL) was added.

ethylene polymerization without any cocatalyst (entry 1), affording a linear polyethylene with *M*_n = 2.6 kg mol^{−1}. The linear structure of the polyethylene was confirmed by ¹H NMR and quantitative ¹³C NMR analyses; it is noteworthy that no signals attributed to methyl or other alkyl branches were observed in the quantitative ¹³C NMR spectrum. When using complexes **7b** or **7c**, which bear bulkier substituents on the nitrogen atom (Table 1, entries 2 and 3), the molecular weight (*M*_n) of the obtained polyethylene increased to 6.9 kg mol^{−1} and 16.0 kg mol^{−1}, respectively. The steric hindrance at the strong σ-donor motif is known to be important for increasing the molecular weight of the polyolefin with the Pd/phosphine-sulfonate catalysts **2-Pd**^[4d] and the related NHC-based complex **5**.^[18a] When the reaction time was prolonged to 1.0 h, it was found that complex **7a** had lost its activity for ethylene polymerization within 0.5 h at 100 °C. On the other hand, complexes **7b** and **7c** could continue to produce polyethylene after 0.5 h at that temperature, although their catalytic activities were gradually reduced.^[26] Then, we investigated the effect of the reaction temperature on the polymerization by using **7c**, which gives the highest molecular weight (Table 1, entries 4–6). When the reaction temperature was lowered to 50 °C,^[27] the molecular weight of

the polyethylene increased, presumably owing to a decreased rate of chain transfer (Table 1, entries 3–5). At 30 °C, however, **7c** cannot initiate the polymerization (Table 1, entry 6). In the presence of $[\text{Ni}(\text{cod})_2]$, a well-known phosphine scavenger, **7c** was found to catalyze ethylene polymerization at 50 °C and even at 30 °C (Table 1, entries 7 and 8). Activation by $[\text{Ni}(\text{cod})_2]$ thus led to an increase in both the catalytic activity (up to $1.19 \times 10^3 \text{ kg mol}^{-1} \text{ h}^{-1}$; entry 7, 50 °C) and the M_n of the polyethylene (up to 84 kg mol^{-1} ; entry 8, 30 °C).

Encouraged by these findings, we investigated the copolymerization of ethylene with polar monomers (Table 2). In the absence of $[\text{Ni}(\text{cod})_2]$, **7a** catalyzed the co-oligomerization of ethylene with allyl acetate at 100 °C, affording a co-oligomer

Table 2: Copolymerization of ethylene with polar monomers by Ni/IzQO complexes.^[a]


Entry	Cat.	Comonomer (mmol) ^[b]	Activity [$\text{kg mol}^{-1} \text{ h}^{-1}$]	$M_n^{[c]}$ [kg mol^{-1}]	$M_w/M_n^{[c]}$	i.r. ^[d] (mol %)
1 ^[e]	7a	AAc (5.0)	0.50	0.63	2.3	0.49
2	7a	AAc (20)	0.16	1.5	2.8	0.83
3	7b	AAc (20)	0.13	4.5	2.5	0.72
4	7c	AAc (20)	0.44	8.5	2.5	0.20
5	7a	DAE (16)	0.87	2.8	2.6	1.9
6	7c	DAE (16)	0.97	14	3.9	0.98
7	7a	AEE (18)	0.88	1.2	2.1	0.68
8	7c	AEE (18)	2.1	10	2.1	0.39
9 ^[f]	7a	MA (1.0)	0	—	—	—
10 ^[f]	7a	AN (1.5)	0	—	—	—

[a] A mixture of **7a**, **7b**, or **7c** (10 μmol), $[\text{Ni}(\text{cod})_2]$ (20 μmol), a polar monomer (ca. 2.0 mL), and ethylene (3.0 MPa) in toluene (8.0 mL) was stirred for 15 h at 60 °C. [b] AAc = allyl acetate, DAE = diallyl ether, AEE = allyl ethyl ether, MA = methyl acrylate, AN = acrylonitrile. [c] Number-average molecular weight measured by size-exclusion chromatography using polystyrene as an internal standard and corrected by universal calibration. [d] Incorporation ratio (i.r.) of polar monomers determined by ^1H NMR analysis. [e] Copolymerization was performed with allyl acetate (0.5 mL) in toluene (9.5 mL) at 100 °C in the absence of $[\text{Ni}(\text{cod})_2]$. [f] Copolymerization was performed with a polar monomer (0.1 mL) in toluene (10 mL) at 100 °C in the absence of $[\text{Ni}(\text{cod})_2]$.

with M_n 0.63 kg mol^{-1} and 0.49 mol % incorporation of allyl acetate (Table 2, entry 1). It is worth noting that ethylene/allyl acetate copolymerization under similar conditions by the corresponding Pd/IzQO complex afforded the copolymer (M_n of 7.4×10^3 and 1.4 mol % incorporation ratio) with a polymerization activity of $4.5 \text{ kg mol}^{-1} \text{ h}^{-1}$.^[23] Since lowering the reaction temperature led to ethylene homopolymers with higher molecular weight, the copolymerization was carried out at 60 °C using $[\text{Ni}(\text{cod})_2]$ as cocatalyst (Table 2, entry 2). As expected, the molecular weight of the copolymer increased to 1.5 kg mol^{-1} , with 0.83 mol % of incorporated allyl acetate. Similar to the trend observed in ethylene homopolymerization, complexes **7b** and **7c**, which bear bulky substituents on the nitrogen atom, effectively increased the molecular weight of ethylene/allyl acetate copolymers to 4.5 kg mol^{-1} and 8.5 kg mol^{-1} , respectively; however, the degree of allyl acetate incorporation was significantly lowered to 0.72 mol % and 0.20 mol %, respectively (Table 2,

entries 2–4). Nevertheless, higher molecular weight and allyl acetate incorporation could be achieved by using the Ni/IzQO system compared to the values obtained with the Ni/phosphine–sulfonate catalyst **2-Ni**, which generates co-oligomers with M_n up to 1000 and allyl acetate incorporation up to 0.24 %.^[11]

Based on these results, we attempted the copolymerization with allyl ethers.^[28] Complex **7a** activated by $[\text{Ni}(\text{cod})_2]$ catalyzed the copolymerization of ethylene with diallyl ether (DAE) and allyl ethyl ether, affording the corresponding copolymers with M_n 2.8 kg mol^{-1} and 1.2 kg mol^{-1} and incorporation values of 1.9 mol % and 0.68 mol %, respectively (Table 2, entries 5 and 7). The higher DAE incorporation can be attributed to the doubled concentration of terminal double bonds in diallyl ether. Also, in this case, complex **7c**, which bears a bulkier substituent on the nitrogen atom, generates a copolymer with higher molecular weight, albeit with lower allyl ether incorporation (Table 2, entries 6 and 8). NMR analysis revealed that linear structure **I**, 3,4-disubstituted tetrahydrofuran structure **II**, and 3,5-disubstituted tetrahydropyran structure **III** were included in the ethylene/DAE copolymer, whereas 3,6-disubstituted oxepane structure **IV** was not observed.^[26] The ratio of structures **I/II/III** was approximately 1:1:2 for entries 5 and 6. Based on the observed copolymers structures, the insertion mechanism of DAE is explored in Scheme 2. There are two possible insertion modes of DAE: 1) 2,1-insertion to form β -alkoxy intermediate **A**, and 2) 1,2-insertion to form γ -alkoxy intermediate **B**. In both cases, ethylene incorporation without cyclization can form structure **I**, which has one terminal

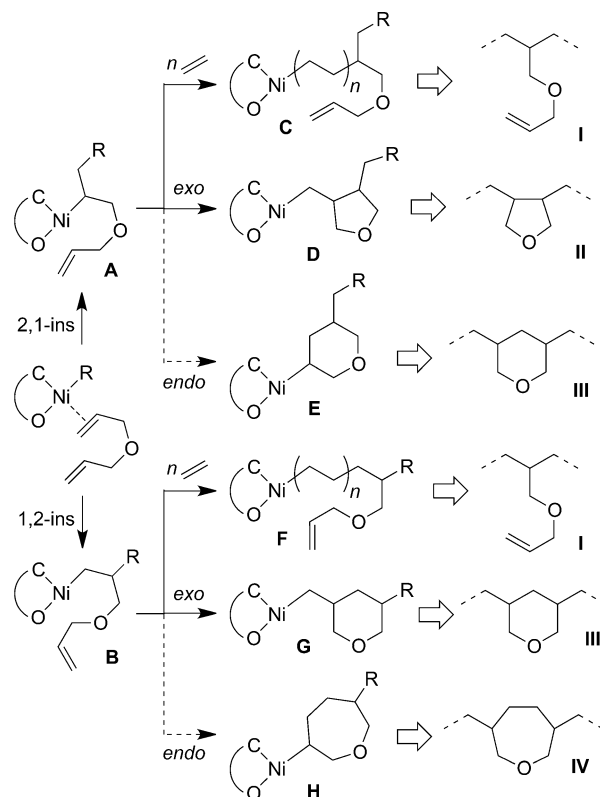

Scheme 2. Mechanism for the incorporation of diallyl ether.

double bond. From intermediate **A**, *exo*-cyclization forms 5-membered ring structure **D** and *endo*-cyclization forms 6-membered ring structure **E**, leading to structures **II** and **III**, respectively. The former pathway is much more probable because, according to the literature, [2-(allyloxy)ethyl] nickel species predominantly undergo *exo*-cyclization.^[29] The formation of **III** results from the 1,2-insertion of DAE to form intermediate **B** and subsequent *exo*-cyclization to generate intermediate **G**. *Endo*-cyclization to form 7-membered ring structure **H** was excluded by the absence of structure **IV** in the copolymer.

Other comonomers, such as methyl acrylate (Table 2, MA; entry 9) and acrylonitrile (entry 10), suppressed the polymerization reaction. In a recent study on bisphosphine monoxide palladium complexes, we found that the copolymerization of ethylene and MA is significantly retarded after 1,2-insertion of MA.^[5b] Considering that in the Pd/IzQO system, 1,2-selective MA insertion was suggested,^[23] we propose that 1,2-insertion of MA to form a five-membered chelation ring might have occurred, thereby suppressing coordination to the nickel center.

In summary, a series of phenyl(triethylphosphine)nickel complexes bearing imidazo[1,5-*a*]quinolin-9-olate-1-ylidene (IzQO) ligands (**7a–c**) were synthesized and characterized. The Ni/IzQO complexes can initiate ethylene polymerization at 50–100 °C without any cocatalyst. Activation by [Ni(cod)₂] increased the catalytic activity up to $1.2 \times 10^3 \text{ kg mol}^{-1} \text{ h}^{-1}$, and lowered the reaction temperature, thereby increasing the M_n of polyethylene up to 84 kg mol^{-1} . In addition, the Ni/IzQO system can catalyze the copolymerization of ethylene with allyl acetate and allyl ethers. To the best of our knowledge, this is the first reported nickel catalyst that can form copolymers of ethylene and allyl acetate with M_n greater than 4.5 kg mol^{-1} , and is the first reported nickel-catalyzed ethylene/allyl ether copolymerization. Further expansion of the substrate scope for the Ni/IzQO system, including propylene polymerization, is currently underway in our laboratory.

Acknowledgements

This work was supported by CREST, JST. A part of this work was conducted in Research Hub for Advanced Nano Characterization, The University of Tokyo, supported by MEXT, Japan. W.-J. T. is grateful for the financial support from Shanghai Institute of Organic Chemistry, Zhejiang Medicine, and Pharmaron for a joint postdoctoral fellowship. R.N. acknowledges the Japan Society for the Promotion of Science (JSPS) for a Research Fellowship for Young Scientists.

Keywords: ethylene · IzQO · nickel · polar monomers · polymerization

How to cite: *Angew. Chem. Int. Ed.* **2016**, *55*, 2835–2839
Angew. Chem. **2016**, *128*, 2885–2889

- [1] a) L. K. Johnson, C. M. Killian, M. Brookhart, *J. Am. Chem. Soc.* **1995**, *117*, 6414–6415; b) L. K. Johnson, S. Mecking, M.

Brookhart, *J. Am. Chem. Soc.* **1996**, *118*, 267–268; c) S. Mecking, L. K. Johnson, L. Wang, M. Brookhart, *J. Am. Chem. Soc.* **1998**, *120*, 888–899.

- [2] a) T. C. Chung, *Functionalization of Polyolefins*, Academic Press, London, **2002**; b) S. D. Ittel, L. K. Johnson, M. Brookhart, *Chem. Rev.* **2000**, *100*, 1169–1204; c) J.-Y. Dong, Y. L. Hu, *Coord. Chem. Rev.* **2006**, *250*, 47–65; d) A. Berkefeld, S. Mecking, *Angew. Chem. Int. Ed.* **2008**, *47*, 2538–2542; *Angew. Chem.* **2008**, *120*, 2572–2576; e) A. Nakamura, S. Ito, K. Nozaki, *Chem. Rev.* **2009**, *109*, 5215–5244; f) S. Ito, K. Nozaki, *Chem. Rec.* **2010**, *10*, 315–325; g) B. P. Carrow, K. Nozaki, *Macromolecules* **2014**, *47*, 2541–2555.
- [3] a) E. Drent, R. van Dijk, R. van Ginkel, B. van Oort, R. I. Pugh, *Chem. Commun.* **2002**, 744–745; A review: b) A. Nakamura, T. M. J. Anselment, J. Claverie, B. Goodall, R. F. Jordan, S. Mecking, B. Rieger, A. Sen, P. W. N. M. van Leeuwen, K. Nozaki, *Acc. Chem. Res.* **2013**, *46*, 1438–1449.
- [4] Recent examples not included in Ref. [3b]: a) H. Leicht, I. Göttker-Schnetmann, S. Mecking, *Angew. Chem. Int. Ed.* **2013**, *52*, 3963–3966; *Angew. Chem.* **2013**, *125*, 4055–4058; b) D. Lanzinger, M. M. Giuman, T. M. J. Anselment, B. Rieger, *ACS Macro Lett.* **2014**, *3*, 931–934; c) Z. Jian, P. Wucher, S. Mecking, *Organometallics* **2014**, *33*, 2879–2888; d) Y. Ota, S. Ito, J. Kuroda, Y. Okumura, K. Nozaki, *J. Am. Chem. Soc.* **2014**, *136*, 11898–11901; e) Z. Jian, M. C. Baier, S. Mecking, *J. Am. Chem. Soc.* **2015**, *137*, 2836–2839; f) M. Chen, B. Yang, C. Chen, *Angew. Chem. Int. Ed.* **2015**, *54*, 15520–15524; *Angew. Chem.* **2015**, *127*, 15740–15744.
- [5] a) B. P. Carrow, K. Nozaki, *J. Am. Chem. Soc.* **2012**, *134*, 8802–8805; b) Y. Mitsushige, B. P. Carrow, S. Ito, K. Nozaki, *Chem. Sci.* **2016**, *7*, 737–744.
- [6] H. Mu, L. Pan, D. Song, Y. Li, *Chem. Rev.* **2015**, *115*, 12091–12137.
- [7] Homopolymerization of ethylene: a) D. H. Camacho, E. V. Salo, J. W. Ziller, Z. Guan, *Angew. Chem. Int. Ed.* **2004**, *43*, 1821–1825; *Angew. Chem.* **2004**, *116*, 1857–1861; b) D. Meinhard, M. Wegner, G. Kipiani, A. Hearley, P. Reuter, S. Fischer, O. Marti, B. Rieger, *J. Am. Chem. Soc.* **2007**, *129*, 9182–9191; c) F.-S. Liu, H.-B. Hu, Y. Xu, L.-H. Guo, S.-B. Zai, K.-M. Song, H.-Y. Gao, L. Zhang, F.-M. Zhu, Q. Wu, *Macromolecules* **2009**, *42*, 7789–7796; d) J. L. Rhinehart, L. A. Brown, B. K. Long, *J. Am. Chem. Soc.* **2013**, *135*, 16316–16319.
- [8] Copolymerization of olefins bearing a polar functional group: a) S. G. Correia, M. M. Marques, J. R. Ascenso, A. F. G. Ribeiro, P. T. Gomes, A. R. Dias, M. Blais, M. D. Rausch, J. C. W. Chien, *J. Polym. Sci. Part A* **1999**, *37*, 2471–2480; b) C. L. P. Carone, G. L. Crossetti, N. R. S. Basso, Á. G. O. Moraes, J. H. Z. dos Santos, R. Bisatto, G. B. Galland, *J. Polym. Sci. Part A* **2007**, *45*, 5199–5208.
- [9] Copolymerization of polar vinyl monomers: a) L. Johnson, A. Bennett, K. Dobbs, E. Hauptman, A. Ionkin, S. Ittel, E. McCord, S. McLain, C. Radzewich, Z. Yin, L. Wang, Y. Wang, M. Brookhart, *Polym. Mater. Sci. Eng.* **2002**, *86*, 319; b) S. J. McLain, K. J. Sweetman, L. K. Johnson, E. McCord, *Polym. Mater. Sci. Eng.* **2002**, *86*, 320.
- [10] Homopolymerization of ethylene: a) X. Zhou, S. Bontemps, R. F. Jordan, *Organometallics* **2008**, *27*, 4821–4824; b) D. Guironnet, T. Rünzi, I. Göttker-Schnetmann, S. Mecking, *Chem. Commun.* **2008**, 4965–4967; c) S. Noda, T. Kochi, K. Nozaki, *Organometallics* **2009**, *28*, 656–658; d) P. Perrotin, J. S. J. McCahill, G. Wu, S. L. Scott, *Chem. Commun.* **2011**, 47, 6948–6950.
- [11] Co-oligomerization of allyl monomers: S. Ito, Y. Ota, K. Nozaki, *Dalton Trans.* **2012**, *41*, 13807–13809.
- [12] Homopolymerization of ethylene: a) C. Wang, S. Friedrich, T. R. Younkin, R. T. Li, R. H. Grubbs, D. A. Bansleben, M. W. Day, *Organometallics* **1998**, *17*, 3149–3151; b) M. A. Zuideveld, P.

- Wehrmann, C. Röhr, S. Mecking, *Angew. Chem. Int. Ed.* **2004**, *43*, 869–873; *Angew. Chem.* **2004**, *116*, 887–891; c) T. Wiedemann, G. Voit, A. Tchernook, P. Roesle, I. Göttker-Schnetmann, S. Mecking, *J. Am. Chem. Soc.* **2014**, *136*, 2078–2085; d) Z. Chen, M. Mesgar, P. S. White, O. Daugulis, M. Brookhart, *ACS Catal.* **2015**, *5*, 631–636.
- [13] Copolymerization of olefins bearing a polar functional group: a) T. R. Younkin, E. F. Connor, J. I. Henderson, S. K. Friedrich, R. H. Grubbs, D. A. Bansleben, *Science* **2000**, *287*, 460–462; b) E. F. Connor, T. R. Younkin, J. I. Henderson, S. Hwang, R. H. Grubbs, W. P. Roberts, J. J. Litzau, *J. Polym. Sci. Part A* **2002**, *40*, 2842–2854; c) M. R. Radlauer, A. K. Buckley, L. M. Henling, T. Agapie, *J. Am. Chem. Soc.* **2013**, *135*, 3784–3787; Mechanistic studies of copolymerization: d) A. W. Waltman, T. R. Younkin, R. H. Grubbs, *Organometallics* **2004**, *23*, 5121–5123; e) A. Berkefeld, M. Drexler, H. M. Möller, S. Mecking, *J. Am. Chem. Soc.* **2009**, *131*, 12613–12622.
- [14] Review of SHOP-type catalysts: P. Kuhn, D. Sémeril, D. Matt, M. J. Chetcuti, P. Lutz, *Dalton Trans.* **2007**, 515–528.
- [15] Oligo- or polymerization of ethylene: a) P. W. Glockner, W. Keim, R. F. Mason, U.S. patent 3647914, **1972**; b) R. S. Bauer, H. Chung, P. W. Glockner, W. Keim, H. van Zwet, U.S. patent 3635937, **1972**; c) W. Keim, F. H. Kowaldt, R. Goddard, C. Krüger, *Angew. Chem. Int. Ed. Engl.* **1978**, *17*, 466–467; *Angew. Chem.* **1978**, *90*, 493.
- [16] Copolymerization of olefins bearing a polar functional group: a) U. Klabunde, S. D. Ittel, *J. Mol. Catal.* **1987**, *41*, 123–134; b) V. C. Gibson, A. Tomov, *Chem. Commun.* **2001**, 1964–1965.
- [17] In industrial studies, nickel complexes bearing elaborated SHOP-type ligands have been patented as highly active catalysts for the copolymerization of ethylene and (meth)acrylates: F. Shimizu, S. Shin, A. Tanna, S. Goromaru, Y. Matsubara, WO 2010/050256, **2010**.
- [18] a) B. E. Ketz, X. G. Ottenwaelder, R. M. Waymouth, *Chem. Commun.* **2005**, 5693–5695; b) S. Benson, B. Payne, R. M. Waymouth, *J. Polym. Sci. Part A* **2007**, *45*, 3637–3647.
- [19] a) A. W. Waltman, T. Ritter, R. H. Grubbs, *Organometallics* **2006**, *25*, 4238–4239; b) A. W. Waltman, PhD Thesis, California Institute of Technology (USA), **2006**.
- [20] (Co)polymerizations by nickel/ α -iminocarboxamidate and related complexes: a) B. M. Boardman, G. C. Bazan, *Acc. Chem. Res.* **2009**, *42*, 1597–1606; b) S. J. Diamanti, P. Ghosh, F. Shimizu, G. C. Bazan, *Macromolecules* **2003**, *36*, 9731–9735.
- [21] a) F. A. Hicks, M. Brookhart, *Organometallics* **2001**, *20*, 3217–3219; b) W. Liu, J. M. Malinoski, M. Brookhart, *Organometallics* **2002**, *21*, 2836–2838; c) M. Brasse, J. Cámpora, P. Palma, E. Álvarez, V. Cruz, J. Ramos, M. L. Reyes, *Organometallics* **2008**, *27*, 4711–4723.
- [22] Nickel catalysts are generally active at lower temperatures of less than 60 °C. Continuous efforts have been devoted to raise the thermal stability of nickel catalysts by ligand modification. For successful examples, see Refs. [7,9a], and [10b–d].
- [23] R. Nakano, K. Nozaki, *J. Am. Chem. Soc.* **2015**, *137*, 10934–10937.
- [24] A. W. Waltman, R. H. Grubbs, *Organometallics* **2004**, *23*, 3105–3107.
- [25] CCDC 1429402 (**7a**) contains the supplementary crystallographic data for this paper. These data can be obtained free of charge from The Cambridge Crystallographic Data Centre.
- [26] See the Supporting Information for details.
- [27] Catalyst **7c** was stable during ethylene polymerization at 50 °C. See the Supporting Information for details.
- [28] While the manuscript was under review, the copolymerization of ethylene with allyl ethers was reported: Z. Jian, S. Mecking, *Angew. Chem. Int. Ed.* **2015**, *54*, 15845–15849; *Angew. Chem.* **2015**, *127*, 16071–16075.
- [29] a) V. B. Phapale, E. Buñuel, M. García-Iglesias, D. J. Cárdenas, *Angew. Chem. Int. Ed.* **2007**, *46*, 8790–8795; *Angew. Chem.* **2007**, *119*, 8946–8951; b) C.-S. Yan, Y. Peng, X.-B. Xu, Y.-W. Wang, *Chem. Eur. J.* **2012**, *18*, 6039–6048.

Received: October 29, 2015

Published online: January 25, 2016