

Electrostatic interactions and complement activation on the surface of phospholipid vesicle containing acidic lipids: Effect of the structure of acidic groups

Keitaro Sou, Eishun Tsuchida *

Research Institute for Science and Engineering, Waseda University, Tokyo 169-8555, Japan

Received 5 September 2007; received in revised form 22 November 2007; accepted 7 January 2008

Available online 16 January 2008

Abstract

Anionic vesicles containing acidic phospholipids are known complement activators. To clarify which negative physicochemical electrostatic charges on vesicles and structural specificities of acidic lipids are critical to complement activation, the electrostatic properties and activity to complement of two anionic vesicles modified with a carboxylic acid derivative or a conventional acidic phospholipid were compared. Electrophoretic mobility measurements indicated that the negative zeta potential and the electrostatic interactivity of these two anionic vesicles were equal at pH 7.4. However, the infusion of vesicles containing acidic phospholipid induced significant complement activation, while vesicles containing the carboxylic acid derivative failed to activate complement. These results indicate that the negative charge on the surface of vesicles is not critical for the activation complement, suggesting that complement activation is specific to the structure of acidic groups. This finding is likely to be important to the design of anionic biointerfaces and may support the promising medical applications of this anionic vesicle modified with a carboxylic acid derivative.

© 2008 Elsevier B.V. All rights reserved.

Keywords: Liposome; Acidic lipid; Anionic surface; Electrostatic interaction; Complement activation

1. Introduction

Anionic vesicles (liposomes), commonly formulated by mixing acidic phospholipids such as phosphoglycerol, phosphoserine, phosphoinositol, phosphatidic acid, cardiolipin, and poly (ethylene glycol) (PEG) conjugated phosphoethanolamine in lipid components are known to mediate complement activation [1–5]. Complement activation, which is followed by systemic immune activation and anaphylaxis shock, is regarded as a critical problem in the clinical setting of various biomaterials. The C1q subcomponent of C1 has a highly cationic region in residues 14–26 of the C1qA polypeptide chain, and this specific region of the collagenous stalk of C1q has been identified as being involved in interactions with negatively charged activators [5–8]. It is

believed that the antibody-independent binding of C1q to the negatively charged surface of vesicles initiates the activation of the complement cascade via the classical complement pathway [2]. To prevent complement activation, the acidic phospholipids can be removed or their negative charge can be protected by chemical modification [2,4]. It has also been reported that surface modification with a dense PEG layer is effective for preventing complement activation by covering the surface charge [9].

Our group has developed phospholipid vesicles called hemoglobin-vesicles that encapsulate human hemoglobin and that can be used as a substitute for red blood cells and as an alternative to conventional transfusion [10–14]. To achieve this challenging application of vesicles, we had to develop anionic vesicles capable of encapsulating hemoglobin using a minimum amount of lipids, retaining the negative charge on the membrane which reduces the lamellarity of vesicles and is required for improving encapsulation capacity [11–13]. Several acidic lipids have been tested and a carboxylic acid derivative, L-glutamic

* Corresponding author. Tel.: +81 3 5286 3120; fax: +81 3 3205 4740.

E-mail addresses: ksou@waseda.jp (K. Sou), eishun@waseda.jp (E. Tsuchida).

acid, *N*-(3-carboxy-1-oxopropyl)-, 1,5-dihexadecyl ester (SA), has been used as an anionic component. Vesicles containing SA have been demonstrated to efficiently encapsulated hemoglobin, and given their stability, can be infused in considerably large doses as a red blood cell substitute [15,16]. In addition, administration of this formulation is not associated with considerable rejection by the blood immune system and complement in animals [17,18]. Recent collaboration involving our group found that vesicles containing SA are selectively captured by bone marrow macrophages at small injection doses in rabbits [19]. This targeting of bone marrow has not yet been reported for conventional anionic vesicles. These findings suggest that the surface characteristics of the anionic vesicles have a marked effect on their associated biological events and that this is highly dependent upon the nature of the acidic groups.

Based on the hypothesis that the negative electrostatic charge of acidic phospholipids on the surface of vesicles is one of the factors responsible for inducing complement activation, the electrostatics of vesicles containing SA may differ from those of vesicles containing acidic phospholipids. Conversely, when the electrostatic interactivity of these acidic lipids is equal, biological events such as complement activation are likely to be mediated by the molecular specificity of acidic lipids. To elucidate what aspects are critical to the biocompatibility and performance of anionic vesicles, a comparative analysis of the electrostatic interfacial properties of vesicles containing either SA or acidic phospholipids is essential. In this study, we elucidated the electrostatic interfacial properties of vesicles containing SA or an acidic phospholipid by electrophoretic mobility measurement and observed complement activation after the infusion of these vesicles in animals. The results clearly demonstrated that the negatively charged group on the surface of anionic vesicles is not critical to the activation of complement.

2. Materials and methods

2.1. Materials

1,2-Dipalmitoyl-*sn*-glycero-3-phosphocholine (PC), cholesterol (CH), and 1,2-dipalmitoyl-*sn*-glycero-3-phosphoglycerol (PG), and *L*-glutamic acid, *N*-(3-carboxy-1-oxopropyl)-, 1,5-dihexadecyl ester (SA), were purchased from Nippon Fine Chemical Co. Ltd. (Osaka, Japan). 1,2-Distearoyl-*sn*-glycero-3-phosphoethanolamine-*N*-[monomethoxy poly(ethylene glycol) (5000)] (PEG-DSPE) was purchased from NOF Co. (Tokyo, Japan). Pentylsine and poly-*L*-lysine (Mw. 15–30 kDa) were purchased from SIGMA (St. Louis, MO).

2.2. Preparation of vesicles

Vesicle samples were produced using PC and CH (1:1, molar ratio, PC-vesicles), and varying amounts of SA (SA-vesicles) or PG (PG-vesicles). The mixed lipids were added to 10 mM phosphate buffer (NaCl; 20 mM, pH 7.4) and the dispersion was introduced into an extruder (Lipex Biomembrane, Canada) and extruded through the membrane filters (final pore size: 0.2 μ m, Isopore®, Millipore, Tokyo, Japan) under pressure using nitrogen gas. For animal experiments, vesicles were composed of PC, CH, and SA or PG (1:1:0.2, molar ratio), with 0.3 mol% of PEG-DSPE incorporated to prevent the aggregation of vesicles [20]. Samples for animal experiments were prepared under sterile conditions.

2.3. Characterization of vesicles

The diameters of the resulting vesicles were determined with a COULTER submicron particle analyzer (N4SD, Coulter, Hialeah, FL), and the average

diameter \pm standard deviation (SD) was calculated. The phospholipid concentration was determined using a cholineoxidase method (Phospholipid C Test Wako; Wako Pure Chem., Tokyo). Endotoxin contamination in the samples prepared for the animal experiment was determined to be less than 0.1 EU/mL by the Limulus assay test [21].

2.4. Determination of zeta potential

A 10 μ L aliquot of vesicles (lipid concentration: 2 g/dL) was diluted in 2 mL of 10 mM phosphate buffer (pH 3–9, 37 °C) containing 20 mM NaCl and incubated for 1 h at 37 °C. The pH was determined using a pH meter with a pH electrode (F-52, HORIBA, Kyoto, Japan) at 37 °C and the electrophoretic mobility of vesicles (lipid concentration: 0.01 g/dL) were determined by Laser Doppler Velocimetry (Zeta-Sizer Nano ZS, Malvern Instruments, Malvern, Worcestershire, UK). Measurement conditions and parameters were as follows: 37 °C, dielectric constant 74.4 (for dilute water solution), viscosity 0.6864 cP (for dilute water solution), and the applied voltage was 20 V/cm. The zeta potential was determined by measuring the electrophoretic mobility (U_E), and the zeta potential (ζ) and applied to the Henry equation:

$$U_E = \frac{2e\zeta f(\kappa R)}{3\eta} \quad (1)$$

where ε is the dielectric constant, η is the viscosity of the solvent, $f(\kappa R)$ is the Henry function, κ is the Debye–Hückel parameter and the R is the radius of the particle. The Smoluchowski equation was used with $f(\kappa R) = 1.5$ employed in the zeta potential calculations. Measurements were performed four times for each sample and statistical analysis was conducted using the average \pm SD of the four measurements.

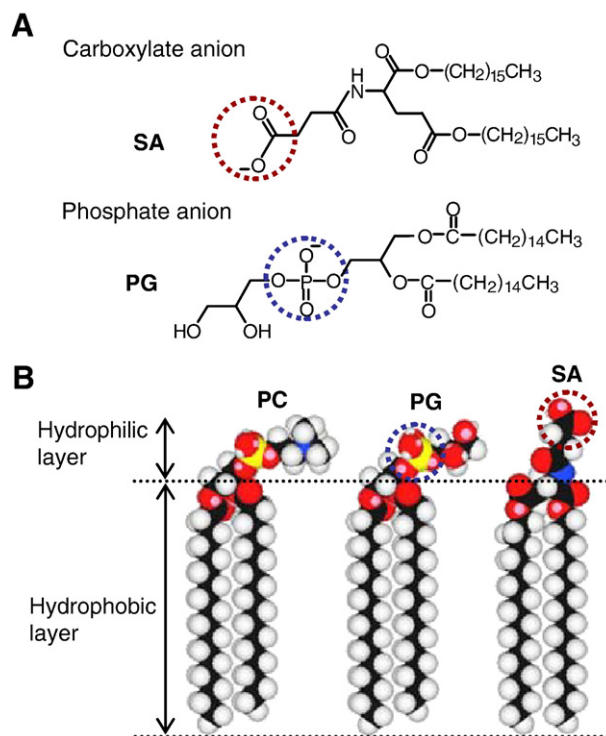


Fig. 1. Structure of acidic lipids for surface modification of vesicles. (A) Chemical structure of *L*-glutamic acid, *N*-(3-carboxy-1-oxopropyl)-, 1,5-dihexadecyl ester (SA) and 1,2-dipalmitoyl-*sn*-glycero-3-phosphoglycerol (PG). The focus of this study is the different acidic groups shown in the dotted circle. (B) The CPK model of SA and PG with 1,2-dipalmitoyl-*sn*-glycero-3-phosphocholine (PC) to estimate the distance of acidic groups from the membrane surface of PC. CPK models show the structure with minimized energy in molecular mechanistic calculation.

2.5. Electrostatic interactivity

The electrostatic interactivity of the anionic vesicles was evaluated using the change in the zeta potential in presence of Ca^{2+} , pentalysine, and poly-L-lysine (Mw. 15–30 kDa) as an index. A 10 μL aliquot of vesicles (lipid concentration: 2 g/dL) was diluted in 2 mL of 10 mM 2-[4-(2-Hydroxyethyl)-1-piperazinyl] ethanesulfonic acid (HEPES) buffer (pH 7.4, 37 °C) containing 0–3 mM CaCl_2 and 17–20 mM NaCl (total 20 mM), or containing varying amounts of pentalysine or poly-L-lysine (Mw. 15–30 kDa) with 20 mM NaCl. The dispersions were incubated for 1 h at 37 °C before mobility measurement of the vesicles was performed by electrophoresis as described in Section 2.4.

2.6. Animal experiments

Animal experiments were conducted under the guidelines recommended by the National Institutes of Health, Animal Use and Care and the protocol was approved by the Steering Committee for Animal Experimentation at Waseda University. Male Wistar rats (250 ± 20 g) were anesthetized with ether. The vesicular dispersion (5 g/dL) was introduced into rats through the tail veins at 1 mL/min ($n=5$ for each sample). Each rat received 5.6 mL/kg of body weight of vesicle dispersion (lipids: 280 mg/kg of body weight). At 1 or 24 h after injection, the blood was collected and centrifuged to separate the serum (1×10^3 g, 10 min). The collected serum was further ultracentrifuged to remove the vesicles (3×10^5 g, 30 min). The 50% hemolytic unit of complement serum (CH50) was determined in accordance with general procedures for clinical laboratory tests by a commercial company (BML, Japan).

2.7. Statistical methods

The data from the animal experiments are reported as means \pm standard error of the mean. Statistical analysis was performed using Microsoft Excel for Windows and CH50 values were compared using Student's unpaired *t* test.

3. Results and discussion

3.1. Samples

Two characteristic acidic lipids used in this study are shown in Fig. 1. SA and PG each have carboxylic acid and phosphoric acid as ionized groups, respectively. Both lipids have a strongly hydrophobic dialkyl structure to fix the ionized groups on vesicle surface. The molecular length indicated by the CPK model showed that the carboxylate anion of SA and the phosphate anion of PG would be located at the surface of PC-vesicles (Fig. 1B). Various amounts of SA and PG were incorporated into the PC/CH membrane (1:1, molar ratio) of the anionic vesicles. The size of vesicles was controlled by extrusion methods (final pore size: 0.2 μm), with final mean diameters of approximately 200 nm (Table 1). The vesicles prepared without acidic lipids

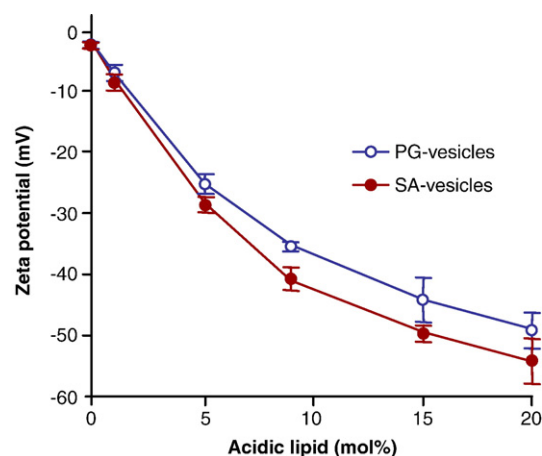


Fig. 2. Zeta potential of vesicles modified with SA (SA-vesicles) and PG (PG-vesicles) as a function of acidic lipid content. Zeta potentials were measured in 10 mM phosphate buffer (pH 7.4, NaCl; 20 mM) at 37 °C.

or with 1 mol% of acidic lipids tended to be slightly larger (ca 30 nm) than vesicles containing more acidic lipids. This effect of acidic lipids on the size of vesicles could be due to the improved dispersion stability of vesicles and electrostatic repulsion of the anionic surfaces. The vesicles without acidic lipids were observed to precipitate in a day, indicating poor dispersion stability. Vesicles without acidic lipids containing small amount of PEG-DSPE to prevent aggregation had diameters of 202 ± 49 nm. Therefore, the slightly large diameter of vesicles without acidic lipids or with 1 mol% of acidic lipids may be the cause for their increased aggregability. The low aggregability of vesicles having large zeta potential is due to their electrostatic repulsive interaction causing anionic vesicles to exist as stable dispersions.

3.2. Zeta potential of vesicles

The zeta potential is the electrostatic potential at the hydrodynamic slip plane, and is characterized as having an electrical double-layer consisting of the Stern layer and the diffuse layer. Fig. 2 shows the zeta potential of prepared vesicles as a function of acidic lipid content at pH 7.4. Vesicles containing PC/CH (1:1, molar ratio) have an almost neutral surface (zeta potential: -2.22 ± 0.62 mV), indicating that the surface is inactive for electrostatic events. The magnitude of the negative charge on the surface increased with the incorporation of SA or PG, indicating that the ionized groups of SA and PG act to characterize the vesicle surface depending on their content. The zeta potentials of SA-vesicles and PG-vesicles reached -54.2 ± 3.68 mV and -49.0 ± 2.89 mV for acidic lipids of 20 mol%, respectively, with the negative zeta potential of SA-vesicles being relatively higher compared to that of PG-vesicles at any concentration. In theory, the electrostatic potential is dependent upon distance from the membrane surface as well as surface charge density [22]. The slightly extended negative charge of SA from the surface shown in Fig. 1B, would reduce the distance between the charge to slip plane, resulting in the higher negative zeta potential of SA-vesicles.

Table 1
Diameter of prepared vesicles containing various amounts of acidic lipid

Acidic lipid (mol%)	Mean diameter \pm SD (nm)	
	SA-vesicles	PG-vesicles
0 (PC-vesicles)	232 \pm 60	232 \pm 60
1	224 \pm 58	230 \pm 60
5	193 \pm 50	196 \pm 58
9	205 \pm 40	204 \pm 49
15	194 \pm 45	199 \pm 55
20	198 \pm 52	194 \pm 64

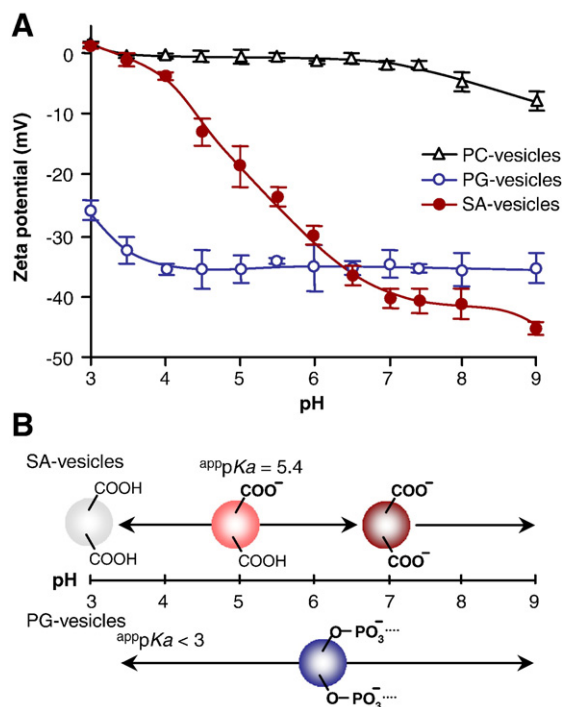


Fig. 3. Ionization state of acidic groups as a function of pH. (A) Zeta potential of vesicles (PC/CH, 1:1, molar ratio) (PC-vesicles), and vesicles containing 9 mol% of SA (SA-vesicles) or PG (PG-vesicles) at various pH. Zeta potentials were measured in 10 mM phosphate buffer (NaCl; 20 mM) at various pH (37 °C). (B) Schematic representation of the ionization state of acidic groups with pH. The apparent pK_as of SA-vesicles and PG-vesicles were calculated to be 5.4 and <3.

This result demonstrated that the capacity of SA as an anionic component of vesicles is equal to acidic phospholipids at pH 7.4.

3.3. Ionization properties of acidic lipids

Stability of the ionization state conferred by acidity is an important characteristic of acidic compounds. We examined the ionization properties of acidic lipids as a function of pH using SA-vesicles and PG-vesicles containing acidic lipids of 9 mol% with zeta potentials of -40.7 ± 2.09 mV and -35.4 ± 0.61 mV (at pH 7.4), respectively. As shown in Fig. 3A, the zeta potential of SA-vesicles varied markedly depending on the environmental pH (pH 3–7). The change in the zeta potential of SA-vesicles is thought to reflect the ionization state of SA, as control vesicles without SA, namely PC-vesicles, maintained almost neutral surfaces irrespective of pH. The relationship between pH and the pK_a of the acid is expressed using the well-known Henderson–Hasselbalch equation as follows:

$$\text{pH} = \text{pK}_a + \log \frac{[-\text{COO}^-]}{[-\text{COOH}]} \quad (2)$$

When we analyzed the data shown in Fig. 3A using Eq. (2) and the assumption that the zeta potential was linearly correlated with the ionization acid, the pK_a of the carboxyl group of SA was estimated as 5.4 (Fig. 3B). Above pH 7, the zeta potential of SA-vesicles was almost constant, indicating that the carboxyl

group of SA would mostly be ionized above pH 7. The zeta potentials of PG-vesicles were almost constant in the range pH 4–9, indicating that the ionized form of the phosphoric acid moiety is stable in this range. The change in the zeta potential observed at a pH lower than pH 4, and its pK_a would be lower than pH 3 [23,24]. Thus, we confirmed that the surface of SA-vesicles and PG-vesicles exhibited the characteristics of a weak acid with SA and a strong acid with PG, respectively, indicating that the individual characteristics of acidic groups are expressed on the surface of vesicles. We also observed that the magnitude of the negative electrostatic charges in SA-vesicles was equal to that observed in PG-vesicles at approximately neutral pH.

3.4. Electrostatic interactivity

Ca²⁺ is found in biological fluids (normally 2–3 mM in plasma) and is known to mediate biological processes by binding to the anionic domains such as those involved in the specific binding of proteins to membranes [25,26]. Acidic phospholipids, such as PG and PS, are also known to bind Ca²⁺ [27–29]. As shown in Fig. 4, the negative charge on anionic vesicles was suppressed by increasing the concentration of Ca²⁺. When the concentration of Ca²⁺ was increased to 3 mM, the zeta potentials of SA-vesicles and PG-vesicles were -16.4 ± 1.9 mV and -13.8 ± 1.4 mV, respectively. Recently, Hautala et al. reported that vesicles containing phosphatidic acid possess a specifically strong affinity for Ca²⁺, and that the zeta potential of these vesicles changed from being strongly negative to positive after binding Ca²⁺ [29]. These authors also showed that other acidic phospholipids, including PG, do not exhibit a strong affinity towards becoming cationic. Consequently, one aim of this experiment was to determine whether the binding of Ca²⁺ is a specificity factor between SA-vesicles and PG-vesicles, and also whether the surface of SA-vesicles remained negative in the presence of Ca²⁺. Our experiment showed that the surface of the SA-vesicles remained

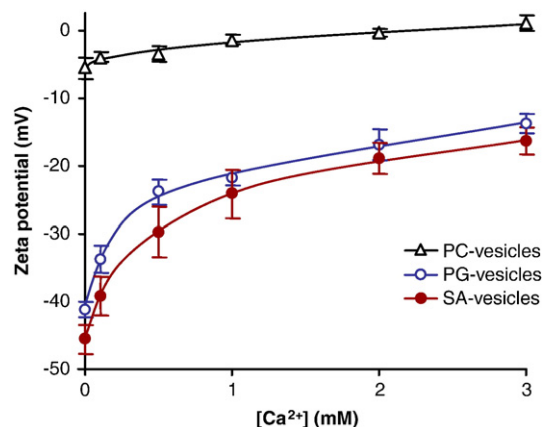


Fig. 4. Change in zeta potential of vesicles as a function of Ca²⁺ concentration. Vesicles were dispersed at 100 µg/mL in 10 mM HEPES buffer (pH 7.4, at 37 °C) containing NaCl and CaCl₂ (total: 20 mM). PC-vesicles: PC/CH (1:1, molar ratio), SA-vesicles: PC/CH/SA (1:1:0.2, molar ratio), and PG-vesicles: PC/CH/PG (1:1:0.2, molar ratio).

negative in the presence of Ca^{2+} . In addition, comparisons of SA-vesicles and PG-vesicles also showed that the specificity of binding Ca^{2+} was not observed.

Additional model-based studies of electrostatic interactivity, pentalysine and poly-L-lysine (Mw. 15–30 kDa with a repeating primary lysine amine) were also conducted. Oligomers or polymers of lysine are often used to model basic peptides or macromolecules and their electrostatic interactions on membranes [30,31]. As shown in Fig. 5, the zeta potential is a linear function of the concentration of pentalysine. The lines, which represent the least-squares best fit, have slopes of 9.3 and 7.4 mV per decade for the pentalysine concentrations in SA-vesicles and PG-vesicles. The slope for PC-vesicles was as little as 0.26 mV per decade of pentalysine concentration (data not shown), indicating that the negative charge of acidic lipids mediate the interaction with basic pentalysine. A change in the zeta potential is due to binding of basic peptide [31] and a similar decay slope of the zeta potential would indicate that the binding constant of a basic peptide to SA-vesicles and PG-vesicles was similar. As shown in Fig. 6, the change in the zeta potential of these vesicles due to the interaction with poly-L-lysine increased drastically, changing from a negative to a positive in presence of 1.5–2 $\mu\text{g}/\text{mL}$ poly-L-lysine. Conversely, the change in the surface potential of PC-vesicles was negligible, indicating that the acidic lipids mediate the interaction with basic macromolecules. This experiment also demonstrates that the interactivity of SA-vesicles and PG-vesicles to basic macromolecules is equal at pH 7.4, and that within an electrostatic context, SA-vesicles and PG-vesicles interact similarly with basic compounds at physiological pH. It has been shown that electrostatic interactions are involved in the binding of C1q to the surface of anionic vesicles containing acidic phospholipid [6]. In the event that the negative

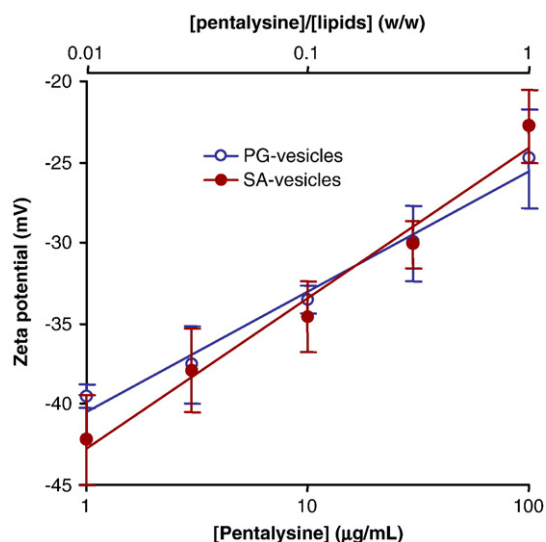


Fig. 5. Change in zeta potential of vesicles as a function of the concentration of basic oligomer (pentalysine). Vesicles were dispersed at 100 $\mu\text{g}/\text{mL}$ in 10 mM HEPES buffer (pH 7.4, at 37 °C, NaCl, 20 mM) containing various amount of pentalysine. The lines have slopes of 9.3 and 7.4 mV per decade for the pentaly sine concentrations in SA-vesicles and PG-vesicles. SA-vesicles: PC/CH/SA (1:1:0.2, molar ratio) and PG-vesicles: PC/CH/PG (1:1:0.2, molar ratio).

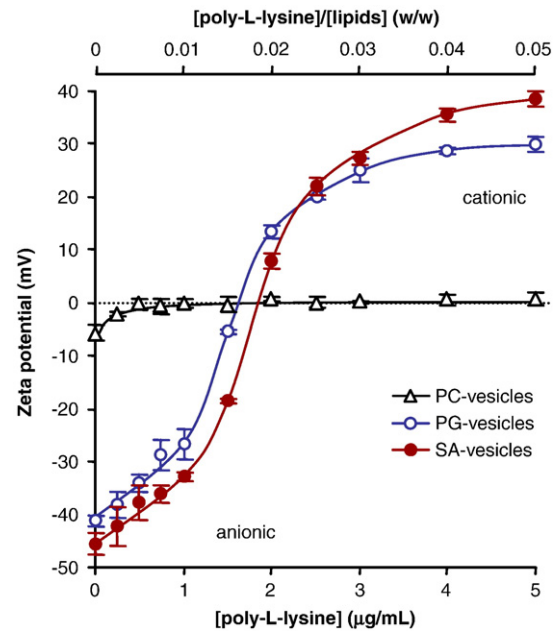


Fig. 6. Change in zeta potential of vesicles as a function of the concentration of basic macromolecule (poly-L-lysine, Mw. 15–30 kDa). Vesicles were dispersed at 100 $\mu\text{g}/\text{mL}$ in 10 mM HEPES buffer (pH 7.4, at 37 °C, NaCl, 20 mM) containing various amount of poly-L-lysine. PC-vesicles: PC/CH (1:1, molar ratio), SA-vesicles: PC/CH/SA (1:1:0.2, molar ratio), and PG-vesicles: PC/CH/PG (1:1:0.2, molar ratio).

charge on the surface of vesicles is critical for complement activation, both the SA-vesicles and PG-vesicles should be capable of activating the complement system to similar degree. We therefore conducted animal experiments to clarify the issue of complement activation by the anionic electrostatic charge of vesicles.

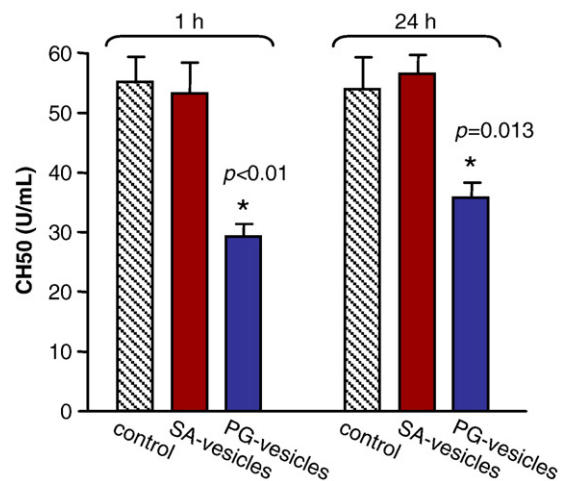


Fig. 7. Comparison of the 50% hemolytic unit of complement (CH50) in rat serum at 1 or 24 h after infusion of saline (control), SA-vesicles, or PG-vesicles. CH50 value for PG-vesicles was significantly lower than that of the control ($p < 0.01$ at 1 h, $p = 0.013$ at 24 h), indicating the complement consumption in serum after activation. Equal CH50 value for SA-vesicles with the control indicates that SA-vesicles failed to activate complement.

3.5. Complement activation

Serum was collected at 1 and 24 h after the infusion of SA-vesicles or PG-vesicles in experimental rats to determine CH50 levels. The control group received saline as a vehicle. The values of CH50 in control rats, and SA-vesicles- and PG-vesicles-administered rats, were 55.1 ± 4.1 U/mL, 53.2 ± 4.8 U/mL, and 29.3 ± 1.6 U/mL at 1 h after infusion of sample, respectively. At 24 h, the values of CH50 in control rats, and SA-vesicles- and PG-vesicles-administered rats, were 54.0 ± 4.7 U/mL, 56.5 ± 3.3 U/mL, and 35.8 ± 2.3 U/mL, respectively (Fig. 7). The lower CH50 levels observed in the PG-vesicles-administered group in comparison with the control group indicate that complement consumption occurred after activation. These findings imply that significant complement activation is induced in rats receiving PG-vesicles compared to the control group ($p < 0.01$ at 1 h, $p = 0.013$ at 24 h). Complement consumption was not observed in rats administered SA-vesicles.

Since the negative charge and electrostatic interactivity of SA-vesicles were the same as in PG-vesicles (Figs. 2–6), the data obtained from the animal experiments indicates that the negative charge on the anionic vesicle is not a critical factor underlying the activation of complement. The first step in the activation of the classical complement pathway involves the binding of an activator to C1q, resulting in the activation of serine proteases C1r and C1s. It has been suggested that the negative charge of an activator such as PG-vesicles is involved in some way with the binding of the activator to C1q [1–8]. Assuming that the electrostatic interaction is non-specific, SA-vesicles should interact with C1q electrostatically. Since the action of complement proteases, which follows the binding of the activator to the C1q, is known to be highly specific [32,33], it seems likely that complement activation on anionic surface is limited to an activation step rather than a binding step. Such specific activation of complement by the anionic vesicles in the present study may be involved in the physiological regulation of complement activation on anionic biomembranes.

4. Conclusions

The carboxylic acid of SA and phosphoric acid of PG have equal capacity as anionic components of vesicles at neutral pH. The results presented in this investigation demonstrated that the negative electrostatic charge of anionic vesicles is not a critical factor in the activation of complement. Rather, the induction of complement activation by anionic vesicles is dependent on the structure of acidic lipids. This finding may facilitate development and various biological applications of anionic vesicles.

Acknowledgements

This work was partly supported by Health Sciences Research Grants (Research on Regulatory Science); the Ministry of Health, Labour and Welfare, Japan, and the Ministry of Education, Science, Sports and Culture, Grant-in-Aid for Scientific Research (B), 17300162. The authors gratefully acknowledge

Dr. K. Kobayashi and Dr. H. Horinouchi (Keio University) for their support in the animal experiments, Dr. M. Suematsu (Keio University) for an important suggestion on bioactivity of anionic vesicles, and Dr. S. Takeoka and Dr. H. Sakai (Waseda University) for advice and discussions related to this research.

References

- [1] H.C. Loughrey, M.B. Bally, L.M. Reinish, P.R. Cullis, The binding of phosphatidylglycerol liposomes to rat platelets is mediated by complement, *Thromb. Haemost.* 64 (1990) 172–176.
- [2] A. Chonn, P.R. Cullis, D.V. Devine, The role of surface charge in the activation of the classical and alternative pathways of complement by liposomes, *J. Immunol.* 146 (1991) 4234–4241.
- [3] J. Szebeni, The interaction of liposomes with the complement system, *Crit. Rev. Ther. Drug Carr. Syst.* 15 (1998) 57–88.
- [4] S.M. Moghimi, I. Hamad, T.L. Andresen, K. Jorgensen, J. Szebeni, Methylation of the phosphate oxygen moiety of phospholipid-methoxy (polyethylene glycol) conjugate prevents PEGylated liposome-mediated complement activation and anaphylatoxin production, *FASEB J.* 20 (2006) 2591–2593.
- [5] A.J. Bradley, D.E. Brooks, R. Norris-Jones, D.V. Devine, C1q binding to liposomes is surface charge dependent and is inhibited by peptides consisting of residues 14–26 of the human C1qA chain in a sequence independent manner, *Biochim. Biophys. Acta* 1418 (1999) 19–30.
- [6] A.J. Bradley, E. Maurer-Spurej, D.E. Brooks, D.V. Devine, Unusual electrostatic effects on binding of C1q to anionic liposomes: role of anionic phospholipid domains and their line tension, *Biochemistry* 38 (1999) 8112.
- [7] H. Jiang, B. Cooper, F.A. Robey, H. Gewurz, DNA binds and activates complement via residues 14–26 of the human C1q A chain, *J. Biol. Chem.* 267 (1992) 25597–25601.
- [8] H. Jiang, D. Burdick, C.G. Glabe, C.W. Cotman, A.J. Tenner, beta-Amyloid activates complement by binding to a specific region of the collagen-like domain of the C1q A chain, *J. Immunol.* 152 (1994) 5050–5059.
- [9] A.J. Bradley, D.V. Devine, S.M. Ansell, J. Janzen, D.E. Brooks, Inhibition of liposome-induced complement activation by incorporated poly(ethylene glycol)-lipids, *Arch. Biochem. Biophys.* 357 (1998) 185–194.
- [10] E. Tsuchida (Ed.), *Substitute: Present and Future Perspective*, Elsevier Science, Amsterdam, 1998.
- [11] S. Takeoka, T. Ohgushi, K. Terase, T. Ohmori, E. Tsuchida, Layer-controlled hemoglobin vesicles by interaction of hemoglobin with a phospholipid assembly, *Langmuir* 12 (1996) 1755–1759.
- [12] H. Sakai, K. Hamada, S. Takeoka, H. Nishide, E. Tsuchida, Physical properties of hemoglobin vesicles as red cell substitutes, *Biotechnol. Prog.* 12 (1996) 119–125.
- [13] K. Sou, Y. Naito, T. Endo, S. Takeoka, E. Tsuchida, Effective encapsulation of proteins into size-controlled phospholipid vesicles using freeze-thawing and extrusion, *Biotechnol. Prog.* 19 (2003) 1547–1552.
- [14] H. Sakai, H. Horinouchi, M. Yamamoto, E. Ikeda, S. Takeoka, M. Takaori, E. Tsuchida, K. Kobayashi, Acute 40 percent exchange-transfusion with hemoglobin-vesicles (HbV) suspended in recombinant human serum albumin solution: degradation of HbV and erythropoiesis in a rat spleen for 2 weeks, *Transfusion* 46 (2006) 339–347.
- [15] H. Sakai, Y. Masada, H. Horinouchi, E. Ikeda, K. Sou, S. Takeoka, M. Suematsu, M. Takaori, K. Kobayashi, E. Tsuchida, Physiological capacity of the reticuloendothelial system for the degradation of hemoglobin vesicles (artificial oxygen carriers) after massive intravenous doses by daily repeated infusions for 14 days, *J. Pharmacol. Exp. Ther.* 311 (2004) 874–884.
- [16] K. Sou, R. Klipper, B. Goins, E. Tsuchida, W.T. Phillips, Circulation kinetics and organ distribution of Hb-vesicles developed as a red blood cell substitute, *J. Pharmacol. Exp. Ther.* 312 (2005) 702–709.
- [17] H. Abe, M. Fujihara, H. Azuma, H. Ikeda, K. Ikebuchi, S. Takeoka, E. Tsuchida, H. Harashima, Interaction of hemoglobin vesicles, a cellular-type artificial oxygen carrier, with human plasma: effects on coagulation, kallikrein-kinin, and complement systems, *Artif. Cells Blood Substit. Biotechnol.* 34 (2006) 1–10.

- [18] H. Abe, H. Azuma, M. Yamaguchi, M. Fujihara, H. Ikeda, H. Sakai, S. Takeoka, E. Tsuchida, Effects of hemoglobin vesicles, a liposomal artificial oxygen carrier, on hematological responses, complement and anaphylactic reactions in rats, *Artif. Cells Blood Substit. Biotechnol.* 35 (2007) 157–172.
- [19] K. Sou, B. Goins, S. Takeoka, E. Tsuchida, W.T. Phillips, Selective uptake of surface-modified phospholipid vesicles by bone marrow macrophages in vivo, *Biomaterials* 28 (2007) 2655–2666.
- [20] K. Sou, T. Endo, S. Takeoka, E. Tsuchida, Poly(ethylene glycol)-modification of the phospholipid vesicles by using the spontaneous incorporation of poly(ethylene glycol)-lipid into the vesicles, *Bioconjug. Chem.* 11 (2000) 372–379.
- [21] H. Sakai, S. Hisamoto, I. Fukutomi, K. Sou, S. Takeoka, E. Tsuchida, Detection of lipopolysaccharide in hemoglobin-vesicles by Limulus amoebocyte lysate test with kinetic-turbidimetric gel clotting analysis and pretreatment of surfactant, *J. Pharm. Sci.* 93 (2004) 310–321.
- [22] S. McLaughlin, The electrostatic properties of membranes, *Annu. Rev. Biophys. Biophys. Chem.* 18 (1989) 113–136.
- [23] A. Watts, K. Harlos, W. Maschke, D. Marsh, Control of the structure and fluidity of phosphatidylglycerol bilayers by pH titration, *Biochim. Biophys. Acta* 510 (1978) 63–74.
- [24] J.F. Tocanne, J. Teissié, Ionization of phospholipids and phospholipid-supported interfacial lateral diffusion of protons in membrane model systems, *Biochim. Biophys. Acta* 1031 (1990) 111–142.
- [25] J. Rizo, T.C. Sudhof, C2-domains, structure and function of a universal Ca^{2+} -binding domain, *J. Biol. Chem.* 273 (1998) 15879–15882.
- [26] J.E. Murphy, D. Tacon, P.R. Tedbury, J.M. Hadden, S. Knowling, T. Sawamura, M. Peckham, S.E. Phillips, J.H. Walker, S. Ponnambalam, LOX-1 scavenger receptor mediates calcium-dependent recognition of phosphatidylserine and apoptotic cells, *Biochem. J.* 393 (2006) 107–115.
- [27] A. Lau, A. McLaughlin, S. McLaughlin, The adsorption of divalent cations to phosphatidylglycerol bilayer membranes, *Biochim. Biophys. Acta* 645 (1981) 279–292.
- [28] C.G. Sinn, M. Antonietti, R. Dimova, Binding of calcium to phosphatidylcholine-phosphatidylserine membranes, *Colloids and Surfaces A: Physicochem. Eng. Aspects* 282–283 (2006) 410–419.
- [29] J.T. Hautala, M.L. Riekkola, S.K. Wiedmer, Anionic phospholipid coatings in capillary electrochromatography. Binding of Ca^{2+} to phospholipid phosphate group, *J. Chromatogr. A* 1150 (2007) 339–347.
- [30] D. Volodkin, V. Ball, P. Schaaf, J.C. Voegel, H. Mohwald, Complexation of phosphocholine liposomes with polylysine. Stabilization by surface coverage versus aggregation, *Biochim. Biophys. Acta* 1768 (2007) 280–290.
- [31] D. Murray, A. Arbuzova, G. Hangyás-Mihályiné, A. Gambhir, N. Ben-Tal, B. Honig, S. MaLaughlin, Electrostatic properties of membranes containing acidic lipids and adsorbed basic peptides: theory and experiment, *Biophys. J.* 77 (1999) 3176–3188.
- [32] G.J. Arlaud, C. Gaboriaud, N.M. Thielens, M. Budayova-Spano, V. Rossi, J.C. Fontecilla-Camps, Structural biology of the C1 complex of complement unveils the mechanisms of its activation and proteolytic activity, *Mol. Immunol.* 39 (2002) 383–394.
- [33] G. O'Brien, N.S. Quinsey, J.C. Whistock, R.N. Pike, Importance of the prime subsites of the C1s protease of the classical complement pathway for recognition of substrates, *Biochemistry* 42 (2003) 14939–14945.