

Mild and efficient oxidation of alcohols with sodium periodate catalyzed by polystyrene-bound Mn(III)porphyrin

Majid Moghadam,^{a,*} Shahram Tangestaninejad,^b Valiollah Mirkhani,^b
Iraj Mohammadpoor-Baltork^b and Hadi Kargar^b

^aDepartment of Chemistry, Yasouj University, Yasouj 75914-353, Iran

^bDepartment of Chemistry, Isfahan University, Isfahan 81746-73441, Iran

Received 5 October 2004; revised 2 February 2005; accepted 9 February 2005


Abstract—Mild and efficient oxidation of primary and secondary alcohols with sodium periodate catalyzed by Mn(TPyP), [manganese(III)tetra(4-pyridyl)porphyrin], supported on chloromethylated polystyrene, [Mn(TPyP)-CMP], at room temperature were reported. This catalyst can be reused consecutively four times in the oxidation of 4-chlorobenzyl alcohol in 97% yield without significant loss of its activity.

© 2005 Elsevier Ltd. All rights reserved.

1. Introduction

The development of an efficient model of systems mimicking the activity of cytochrome P-450 has been one of the areas of most intense research activity.¹ Many metalloporphyrin complexes, mainly iron and manganese, proved to be able to catalyze oxidation reactions with single oxygen atom donors such as PhIO, ClO[−], H₂O₂ or IO₄[−].^{2–7} High yields and rates have been obtained with these biomimetic systems making them useful for complete conversion of various substrates and potentially useful preparative oxidations in organic chemistry. However, difficulty of recovery and instability are two major drawbacks of these expensive catalysts. These limitations have prevented practical application of metalloporphyrin catalysts in synthesis. One way to prepare commercial metalloporphyrin catalysts is to anchor them onto solid supports. The possibility of recovery and recycling these expensive catalysts has positive effects from the economical and environmental points of view. Further benefit is the ease of product isolation and purification.

Recently, we have reported the use of supported manganese(III)porphyrin/periodate systems in epoxidation of

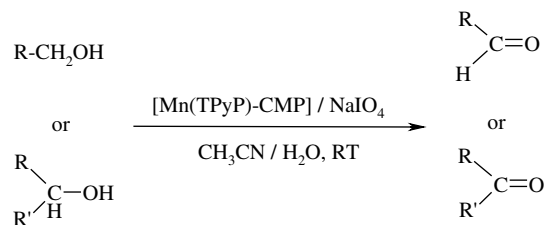

Scheme 1.

alkenes, hydroxylation of alkanes, oxidative decarboxylation of carboxylic acids and oxidation of amines to azo compounds.^{8–16} High catalytic activity of Mn(TPyP)-CMP in the alkene epoxidation and alkane hydroxylation¹⁶ prompted us to explore the potential of this catalyst in the oxidation of alcohols with sodium periodate in 1:1 CH₃CN/H₂O mixture at room temperature (Scheme 1).

2. Results and discussion

2.1. Oxidation of alcohols with sodium periodate catalyzed by MnTPyP-CMP

We first investigated the ability of this supported manganese(III)porphyrin as catalyst in the oxidation of 4-chlorobenzyl alcohol in the presence of sodium periodate. Among the 1:1 mixture of methanol, ethanol,

Keywords: Alcohol; Oxidation; Supported; Metalloporphyrin.

*Corresponding author. Tel.: +98 913 310 8960; fax: +98 741 2223048; e-mail: moghadamm@mai.yu.ac.ir

Table 1. Effect of solvent on the oxidation of 4-chlorobenzyl alcohol with Mn(III)porphyrin/NaIO₄ system

Entry	Solvent	Time (min)	Yield (%) ^a
1	CH ₃ CN/H ₂ O	45	100
2	CH ₃ COCH ₃ /H ₂ O	45	77
3	CH ₃ OH/H ₂ O	45	21
4	CH ₃ CH ₂ OH/H ₂ O	45	17
5	CHCl ₃ /H ₂ O	45	6
6	CCl ₄ /H ₂ O	45	4

^a GC yields.**Table 2.** The effect of different axial ligands on the oxidation of 4-chlorobenzyl alcohol with Mn(III)porphyrin/NaIO₄ system

Entry	Axial base	Time (min)	Yield (%) ^a
1	Imidazole	45	100
2	1-Methylimidazole	45	90
3	4- <i>t</i> -Butyl pyridine	45	34
4	Pyridine	45	15
5	No axial base	45	7

^a GC yields.

acetone and acetonitrile with water (single-phase systems), chloroform and carbontetrachloride (two phase systems with Bu₄NBr as phase transfer catalyst), the 1:1 acetonitrile/water mixture was chosen as the solvent in which higher carbonyl yield was observed (Table 1). The manganese porphyrin is not an efficient catalyst

for oxidation of alcohols without adding imidazole as axial ligand because imidazole coordinates to Mn and activates the catalyst. The effect of different axial ligands upon the oxidation rate of 4-chlorobenzyl alcohol was also investigated. The results showed that the imidazole is the best (Table 2). The optimum condition used for the oxidation of 4-chlorobenzyl alcohol with this heterogenized system, was catalyst, oxidant, imidazole and substrate in a molar ratio of 1:100:10:50. During the course of oxidation, the reaction solution remained colorless and there was no evidence for leaching of the catalyst from polymeric support into solution. This fact was also investigated by examining the UV–vis spectrum of the filtered reaction mixture.

This heterogeneous catalyst can be applied to a wide variety of primary and secondary alcohols. As shown in Table 3, benzyl alcohol and substituted benzyl alcohols are converted to their corresponding aldehydes efficiently. In the case of benzyl alcohol, after 45 min, only benzaldehyde was obtained in 90% yield. In longer reaction times (1 h), the obtained products are 63% benzaldehyde and 35% benzoic acid. The results show that the substituents have no significant effect on the oxidation of benzylic alcohols. In the case of linear alcohols such as *n*-octanol, the resulted products are 17% octanal and 51% octanoic acid. A good selectivity observed in the case of cinnamyl alcohol and only alcoholic group is oxidized and no epoxide yield was obtained.

Table 3. Oxidation of alcohols with NaIO₄ catalyzed by MnTPyP-CMP at room temperature













































Entry	Alcohol	Product (%)	Yield (%) ^a	Time (min)
1			90	45
2			100	70
3			100	70
4			100	45
5			100	45
6			96	60
7			92	60
8			100	30
9			94	90

Table 3 (continued)

Entry	Alcohol	Product (%)	Yield (%) ^a	Time (min)
10			100	45
11			80	90
12			91	90
13			75	70
14			70 ^b	60
15			17	150
			51	
16			10	150
			50	
17			70	110
18			67	120
19			68	120
20			71	120
21			81	90

^a GLC yield based on starting alcohol.^b Isolated yield.

Polystyrene-bound tetra (4-pyridyl)porphyrinato manganese(III) was also used for oxidation of secondary alcohols and their corresponding ketones were obtained in good yields.

2.2. Catalyst reuse and stability

The stability of the supported catalyst was monitored using multiple sequential oxidation of 4-chlorobenzyl alcohol with sodium periodate. For each of the repeated reactions, the catalyst was recovered, washed exhaus-

tively with water, methanol, acetonitrile and diethyl ether, respectively, and dried before being used with fresh 4-chlorobenzyl alcohol and sodium periodate. The catalyst was consecutively reused four times without a detectable catalyst leaching or a significant loss of its activity (Table 4).

This polystyrene-bound Mn-porphyrin can be used as a robust, reusable and active heterogeneous catalyst in the oxidation of primary and secondary alcohols with sodium periodate.

Table 4. The results of [Mn(TPyP)-CMP] catalyst recovery and the manganese leached in the oxidation of 4-chlorobenzyl alcohol with sodium periodate

Run	Conversion (%) ^a	Mn leached (%)
1	100	0
2	100	0
3	98	0
4	97	0

^a GLC yield based on starting alcohol.

Blank experiments in the absence catalyst or in the absence of NaIO₄ showed that only negligible amounts of oxidation products were detected.

3. Experimental

All materials were commercial reagent grade. Alcohols were obtained from Merck or Fluka. All of these tetra(4-pyridyl)porphyrin was metalated and supported according to the literature procedure.^{16,17}

Reactions were quantified by GLC (Shimadzu 16 A) using a 3 m Silicon DC-200 packed column with a FID detector using decane as internal standard.

3.1. Typical procedure for oxidation of alcohols with NaIO₄ catalyzed by MnTPyP-CMP

All of the reactions were carried out at room temperature under air in a 25 mL flask equipped with a magnetic stirrer bar. A solution of NaIO₄ (2 mmol) in H₂O (10 mL) was added to a mixture of alcohol (1 mmol), MnTPyP-CMP (20 μmol) and imidazole (0.2 mmol) in CH₃CN (10 mL). The progress of reaction was monitored by GLC. The reaction mixture was diluted with CH₂Cl₂ (20 mL) and filtered. The resin was thoroughly washed with CH₂Cl₂ and combined washings and filtrates were purified on silica-gel plates or silica-gel column. IR and ¹H NMR spectral data confirmed the identities of the products.

3.2. Catalyst reuse and stability

The stability of MnTPyP-CMP was studied in repeated oxidation reactions. The oxidation of 4-chlorobenzyl alcohol was chosen as a model substrate for studying of catalyst reuse and stability. The reaction was carried out as described above. At the end of reaction, the catalyst was removed by filtration, washed with water and acetonitrile and reused. After the use of catalyst for four consecutive times, the aldehyde yield was 97%. No manganese was detectable in the filtrates by atomic absorption spectrometry.

4. Conclusions

In this paper we have demonstrated the utility of Mn(TPyP)-CMP catalyst in the oxidation of primary

and secondary alcohols to carbonyl compounds with NaIO₄. This catalytic system has some advantageous over the previous reported systems^{18–21} such as: (i) mild reaction conditions (room temperature); (ii) simple preparation of the catalyst from commercially available materials (porphyrin and polystyrene resin) and it seems binding of porphyrin pyridyl groups to polystyrene resin is a good method to model the microenvironment of active centre of cytochrome P-450; (iii) nontoxicity of the catalyst; (iv) the use of supported metalloporphyrins provides an easy way to recover and recycle the catalyst from the reaction media and (v) the catalytic activity of this catalyst in the oxidation of secondary alcohols has been found to be higher compared with corresponding non-supported manganese(III)porphyrin.²²

Acknowledgements

The partial support of this work by Yasouj and Isfahan Universities Council Research is acknowledged.

References and notes

- (a) Coon, M. J.; White, R. E. In *Dioxygen Binding and Activation by Metal Centers*; Spiro, T. G., Ed.; Wiley: New York, 1980; p 73; (b) White, R. E.; Coon, M. J. *Annu. Rev. Biochem.* **1980**, *49*, 315.
- Groves, J. T.; Nemo, T. E. *J. Am. Chem. Soc.* **1983**, *105*, 5786.
- Bortolini, O.; Meunier, B. *J. Chem. Soc., Perkin Trans. 2* **1984**, 1967.
- Meunier, B.; Cuilmel, E.; De Carvallho, M. E.; Poiblane, R. *J. Am. Chem. Soc.* **1984**, *106*, 6668.
- (a) Mohajer, D.; Tangestaninejad, S. *J. Chem. Soc., Chem. Commun.* **1993**, 240; (b) Mohajer, D.; Tangestaninejad, S. *Tetrahedron Lett.* **1994**, *35*, 945.
- Wohler, D.; Gitzel, J. *Makromol. Chem., Rapid Commun.* **1988**, *9*, 229.
- (a) Leonard, D. R.; Lindsay Smith, J. R. *J. Chem. Soc., Perkin Trans. 2* **1990**, 1917; (b) Leonard, D. R.; Lindsay Smith, J. R. *J. Chem. Soc., Perkin Trans. 2* **1991**, 25.
- Tangestaninejad, S.; Mirkhani, V. *J. Chem. Res. (S)* **1998**, 788.
- Tangestaninejad, S.; Habibi, M. H.; Mirkhani, V.; Moghadam, M. *Molecules* **2002**, *7*, 264.
- Tangestaninejad, S.; Moghadam, M. *J. Chem. Res. (S)* **1998**, 242.
- Tangestaninejad, S.; Moghadam, M. *Synth. Commun.* **1998**, *28*, 427.
- Mirkhani, V.; Tangestaninejad, S.; Moghadam, M. *J. Chem. Res. (S)* **1999**, 722.
- Tangestaninejad, S.; Habibi, M. H.; Mirkhani, V.; Moghadam, M. *J. Chem. Res. (S)* **2001**, 444.
- Mirkhani, V.; Tangestaninejad, S.; Moghadam, M.; Karimian, Z. *Bioorg. Med. Chem. Lett.* **2003**, *13*, 3433.
- Mirkhani, V.; Tangestaninejad, S.; Moghadam, M.; Karimian, Z. *J. Chem. Res. (S)* **2003**, 792.
- Moghadam, M.; Tangestaninejad, S.; Habibi, M. H.; Mirkhani, V. *J. Mol. Catal. A: Chem.* **2004**, *217*, 9.
- Harriman, A.; Porter, G. *J. Chem. Soc., Faraday II* **1979**, *75*, 1532.
- Linares, M. L.; Sanchez, N.; Alajarin, R.; Vaquero, J. J.; Alvarez-Builla, J. *Synthesis* **2001**, *3*, 382.

19. Hashimoto, K.; Kitaichi, Y.; Tanaka, H.; Ikeno, T.; Yamada, T. *Chem. Lett.* **2001**, 922.
20. Ishii, Y.; Yamawaki, K.; Ura, T.; Yamada, H.; Yoshida, T.; Ogawa, M. *J. Org. Chem.* **1988**, 53, 3587.
21. Firouzabadi, H.; Mohammadpoor-Baltork, I. *Bull. Chem. Soc. Jpn.* **1992**, 65, 1131.
22. Baciocchi, E.; Belvedere, S. *Tetrahedron Lett.* **1998**, 39, 4711.