



# Tenascin-X increases the stiffness of collagen gels without affecting fibrillogenesis

Yoran Margaron<sup>a</sup>, Luciana Bostan<sup>b,c</sup>, Jean-Yves Exposito<sup>a</sup>, Maryline Malbouyres<sup>a</sup>, Ana-Maria Trunfio-Sfarghiu<sup>b</sup>, Yves Berthier<sup>b</sup>, Claire Lethias<sup>a,\*</sup>

<sup>a</sup> Institut de Biologie et Chimie des Protéines, IFR 128 Biosciences Lyon-Gerland, CNRS UMR 5086, Université de Lyon, 7 passage du Vercors, F-69367 Lyon Cedex 07, France

<sup>b</sup> Université de Lyon, CNRS INSA-Lyon, LaMCoS UMR5259, F-69621 Villeurbanne Cedex, France

<sup>c</sup> The "Gh. Asachi" Technical University of Iasi, Faculty of Chemical Engineering and Environmental Protection, Bd Mangeron, 71A, 700050, Iasi, Romania

## ARTICLE INFO

### Article history:

Received 10 November 2009

Received in revised form 23 December 2009

Accepted 27 December 2009

Available online 4 January 2010

### Keywords:

Extracellular matrix  
Ehlers-Danlos Syndrome  
Tenascin-X  
Collagen  
Elastic modulus

## ABSTRACT

Tenascin-X is an extracellular matrix protein whose absence leads to an Ehlers-Danlos Syndrome in humans, mainly characterised by connective tissue defects including the disorganisation of fibrillar networks, a reduced collagen deposition, and modifications in the mechanical properties of dense tissues. Here we tested the effect of tenascin-X on *in vitro* collagen fibril formation. We observed that the main parameters of fibrillogenesis were unchanged, and that the diameter of fibrils was not significantly different when they were formed in the presence of tenascin-X. Interestingly, mechanical analysis of collagen gels showed an increased compressive resistance of the gels containing tenascin-X, indicating that this protein might be directly involved in determining the mechanical properties of collagen-rich tissues *in vivo*.

© 2009 Elsevier B.V. All rights reserved.

## 1. Introduction

Tenascin-X (TNX) is a huge extracellular matrix glycoprotein that has a multidomain structure consisting of an N-terminal region involved in oligomerisation, a series of epidermal growth factor (EGF)-like repeats, a variable number of fibronectin-type III (FNIII) modules and a C-terminal domain homologous to fibrinogen (Fbg) [1]. Several observations suggest that TNX is involved in the deposition and/or stabilisation of collagen fibrils, and in influencing the mechanical properties of connective tissues. Indeed, TNX deficiency leads to the appearance of an Ehlers-Danlos Syndrome in humans [2]. Major clinical symptoms consist of skin hyperextensibility and joint laxity, while ultrastructural analyses reveal abnormalities in collagen fibril networks and elastic fibre morphology. Mice deficient in TNX partly reproduced this phenotype [3], and fibroblasts isolated from these mice failed to deposit collagen in cell culture [4]. Moreover, we have previously demonstrated that TNX is localised at the surface of collagen fibrils within tissues [5]. This association might be explained by the interaction of TNX with several molecular components of these fibrils i.e., decorin, fibrillar and FACIT collagens [6–8]. More recently, it was shown that TNX has elastic properties, due to the extension/refolding of its constitutive FNIII modules [9]. Taken together, these data suggest that TNX might affect collagen fibrillogenesis and/or act as a bridge between collagen fibrils and consequently modulate the mechanical properties of

connective tissues. In order to test these hypotheses, we analysed the consequences of TNX-collagen interaction *in vitro*, by studying the influence of TNX on collagen fibrillogenesis, and by measuring the mechanical properties of collagen gels polymerised in the presence of TNX.

## 2. Materials and methods

### 2.1. Production and purification of recombinant TNX

Recombinant full length bovine TNX was produced in mammalian HEK293 cells as previously described [7,10]. TNX was further purified from the culture medium by two chromatographic steps: firstly on heparin-Sepharose (GE Healthcare), and secondly on Q-Sepharose (GE Healthcare) [7]. TNX fractions were dialysed against phosphate-buffered saline (PBS) and stored at  $-80^{\circ}\text{C}$ . Protein concentration was determined using the QuantiPro BCA assay kit (Sigma) according to the manufacturer's instructions.

### 2.2. Preparation of acid-soluble collagen

Acid-soluble collagen was extracted from tail tendons of young rats using standard procedures. All steps were performed at  $4^{\circ}\text{C}$ . Tendons were dissected in 0.2 M NaCl, then dilacerated and transferred to 0.5 M acetic acid/0.2 M NaCl for 48 h. The extract was centrifuged at 20,000 g for 20 min, and the resulting supernatant was dialysed against 0.5 M acetic acid/0.9 M NaCl. After centrifugation (20,000 g, 20 min), the pellet was treated with 70% ethanol, dried in a

\* Corresponding author. Tel.: +33 472 72 26 53; fax: +33 472 72 26 04.

E-mail address: [c.lethias@ibcp.fr](mailto:c.lethias@ibcp.fr) (C. Lethias).

sterile atmosphere, and dissolved in 0.001 M HCl. Collagen concentration was determined by both QuantiPro BCA assay kit and amino-acid analysis.

### 2.3. Collagen fibrillogenesis assays

Collagen solutions (3 to 5.6 mg/mL) were neutralised on ice using 0.5 M NaOH and diluted to a final concentration of 1 mg/mL by the addition of PBS containing recombinant TNX or control protein. Fibrillogenesis was initiated by warming the solutions to 37 °C in a thermostated cuvette, and gelation was detected by monitoring turbidity at 400 nm in a DU 640 spectrophotometer (Beckman). Assays were performed in triplicate and a minimum of three independent experiments were carried out. Pepsin-extracted bovine collagen was purchased from BD Biosciences (Le Pont de Claix, France).

### 2.4. Scanning electron microscopy

Collagen gels, prepared as described for the fibrillogenesis assay, were briefly rinsed in 0.15 M sodium cacodylate (Sigma) pH 7.4 then fixed for 1 h in 2% glutaraldehyde (Electron Microscopy Sciences) diluted in the same buffer. After further rinsing, gels were treated for 45 min with 1% osmium tetroxide diluted in 0.1 M sodium cacodylate. Samples were then dehydrated by a series of graded ethanol solutions, impregnated in hexamethyldisilazane (Sigma), and air-dried. After coating with gold-palladium by sputtering, the gels were observed with a Hitachi S800 microscope (operating at 15 kV) at the “Centre Technologique des Microstructures” (Université de Lyon). Collagen fibril diameters were measured using NIH Image J software.


### 2.5. Mechanical tests

Neutralised collagen solutions were prepared as described in the fibrillogenesis section, and 10.5 mL aliquots were transferred to 60 mm diameter cell culture Petri dishes (Falcon). Gelation was carried out for 30 min at 37 °C, then collagen gels were stored at 4 °C in the presence of PBS until mechanical testing. Collagen gel samples had a cylindrical form, with diameter ~50 mm and height ~3 mm, and their mechanical resistance was measured by compression testing in an unconfined configuration.

Step-wise compression tests were performed with an Advanced Rheometric Expansion System (ARES) equipped with a maximum cell load of 20 N and controlled gap (hi) (TA Instruments). The load assembly consists of two stainless steel 50 mm diameter parallel plates above and below the sample. In order to control the boundary conditions, the stainless steel platens were sonicated twice for 10 min at 25 °C in ethanol before use. For each test, a cycle of 4 strains was performed at an imposed speed deformation of 0.02 mm/s, the compression level representing 5% of the sample thickness. Every compression strain ramp was followed by a period of stress relaxation of 600 s. This period of stress relaxation was necessary to reach the balance of stress equilibrium characteristic to cartilage biphasic materials [11].

The normal force and the gap thickness were directly measured by the rheometer sensors. To reproduce the same initial load condition, the test began after having submitted each sample to a compressive force of 0.02 N followed by a 600 s relaxation period. Stress-relaxation curves were generated for each sample, including compressive and relaxation stresses, calculated as normal force divided by gel area, and were drawn as a function of time. Stress-strain curves were generated for each sample by taking only into consideration the compression peak stress, where the compressive strain was calculated as  $(h_0 - h_i)/h_0$  (where  $h_0$  is the initial gap). The linear regression slope of the stress-strain curve was used to estimate the apparent elastic modulus of each gel.

For each type of gel (collagen only, collagen and BSA, collagen and TNX), four samples were tested, and each test was repeated three times to verify the reproducibility of measurements.

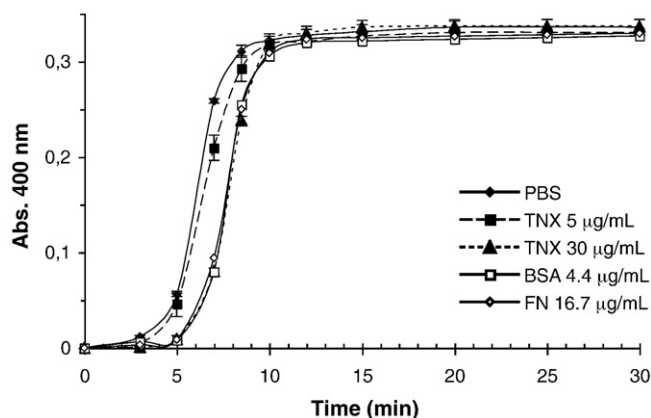

**Fig. 1.** Effect of TNX on collagen fibrillogenesis. Fibril formation was measured by monitoring collagen solution turbidity at 400 nm. The different curves represent control experiment with collagen alone (◆), collagen plus TNX at 5 µg/mL (■) or 30 µg/mL (▲), collagen plus BSA at 4.4 µg/mL (□), or collagen plus fibronectin at 16.7 µg/mL (◇). Each point is the mean of triplicate values and error bars are SEM. The data shown are representative of three independent experiments.

## 3. Results and discussion

### 3.1. Influence of TNX on collagen fibrillogenesis

The effect of TNX on collagen fibril formation was tested *in vitro* by monitoring turbidity during the gelation process. As shown in Fig. 1, TNX did not seem to affect collagen fibrillogenesis except at high concentrations where a slight delay in the initiation step was apparent. However, the same effect was obtained by the addition of a control protein (BSA), which does not specifically interact with fibrillar collagens. A careful examination of the fibrillogenesis parameters led to the same conclusion (Table 1). Neither the lag phase, nor the fibrillogenesis rate or the absorbance plateau were significantly modified by the presence of TNX. These results are somehow contradictory with previous results [12] showing a diminished lag phase and an increased absorbance plateau of collagen solutions when fibrillogenesis assays were done in the presence of TNX.


The first point of divergence that might explain the discrepancy between our results and those of Minamitani et al. [12] concern the source of the collagen. Their collagen solution was from a commercial source, and gave rise to slow fibrillogenesis in control conditions (2 h for their lag phase instead of 5 min in our experiments and elsewhere [13,14]). One explanation could be that the commercial collagen was pepsinised and consequently devoid of telopeptides, which have been shown to be important for fibrillogenesis [15]. To test this hypothesis, we performed fibrillogenesis assays with bovine pepsinised collagen and indeed observed a slower fibrillogenesis. However, even in these conditions, the presence of TNX did not modify the fibrillogenesis parameters compared to the control protein BSA (data not shown).

The differences observed might also result from the concentration and presence of FNIII repeats present in the recombinant TNX used during the fibrillogenesis assays. These discrepancies seem not to be due

**Table 1**


Collagen fibrillogenesis parameters corresponding to Fig. 1 experiments. Lag time, rate of fibrillogenesis, and absorbance plateau were calculated according to the method published by Sullivan et al. [12].

	Lag time (min)	Rate of fibrillogenesis ( $1 \times 10^{-2}/\text{min}$ )	Absorbance plateau (400 nm)
Control	$5.1 \pm 0.2$	$6.5 \pm 0.1$	$0.34 \pm 0.08$
TNX (5 µg/mL)	$5.5 \pm 0.1$	$5.8 \pm 0.4$	$0.34 \pm 0.04$
TNX (30 µg/mL)	$6.6 \pm 0.4$	$6.3 \pm 0.3$	$0.35 \pm 0.01$
BSA (4.4 µg/mL)	$6.6 \pm 0.4$	$6.3 \pm 0.4$	$0.34 \pm 0.07$
Fibronectin (16.7 µg/mL)	$6.6 \pm 0.4$	$6.2 \pm 0.2$	$0.33 \pm 0.01$

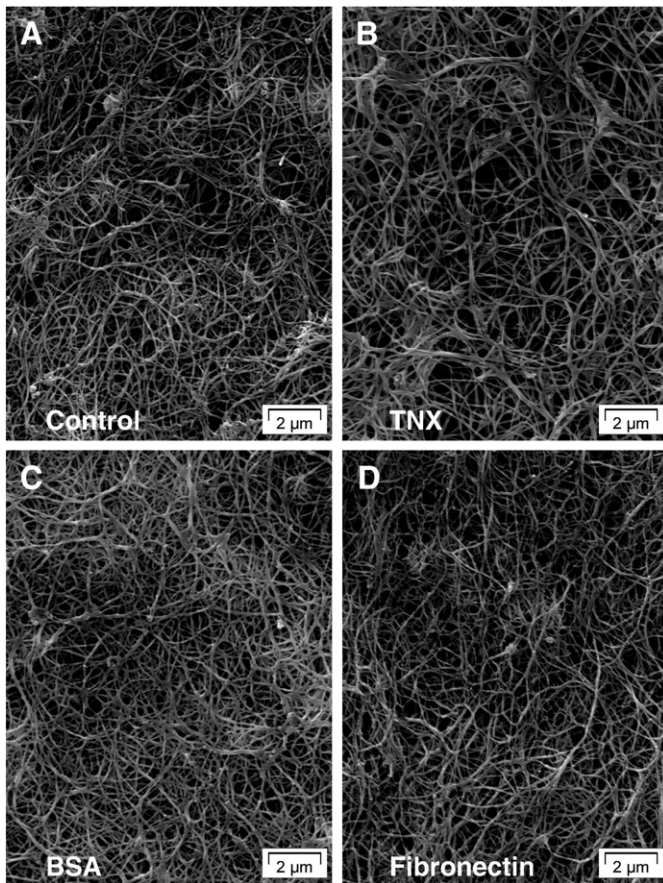


**Fig. 2.** Morphology of collagen gels examined by Scanning Electron Microscopy. Gels formed with collagen alone (A), or in the presence of TNX (B), BSA (C) or fibronectin (D) at equimolar concentration (66.6 nM).

to the lower TNX-concentrations (0.2 to 0.5  $\mu\text{g}/\text{mL}$ ) used in Ref. [12], since we did not observe any differences in the fibrillogenesis parameters in this range of concentration (data not shown). Moreover, these authors used a small isoform lacking the central FNIII modules, whereas we produced the full-length protein comprising 30 FNIII domains. Interestingly, another group has shown that the 29th FNIII module of TNX accelerates collagen fibrillogenesis [8], but this modulatory effect seems to be masked in larger constructs. Taken together, these data indicate that the modulatory effects of TNX on collagen fibrillogenesis seems to be dependent on its constitutive domains.

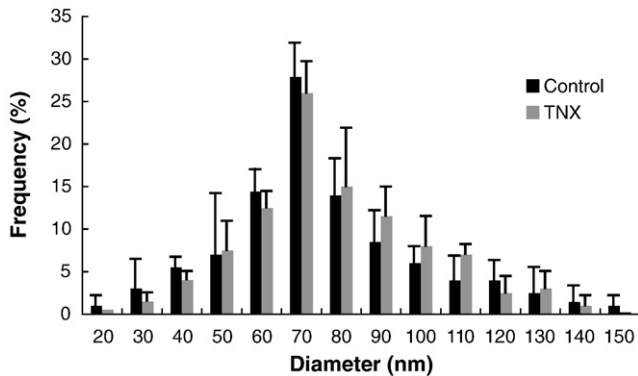

**Fig. 3.** Fibril diameter distribution within collagen gels. Measurements were performed on scanning electron micrographs obtained from control (black bars) or TNX-containing (grey bars) gels. A minimum of two-hundred fibrils were measured for each condition. Error bars are Standard Deviation, and a statistical analysis of the fibril diameters distribution was performed by non-parametric Mann–Whitney *U* tests. Each sample was compared to the PBS condition.

With the aim of determining if TNX had an influence on the morphology of the collagen fibrils, we examined the gels by scanning electron microscopy after the gelation process was completed. The resulting micrographs are shown in Fig. 2, and no striking difference was highlighted by comparison of gels formed in the presence of TNX or control proteins (BSA, fibronectin). Consistent with this observation, measurement of collagen fibril diameter distribution did not show an effect of TNX on this parameter (Fig. 3).

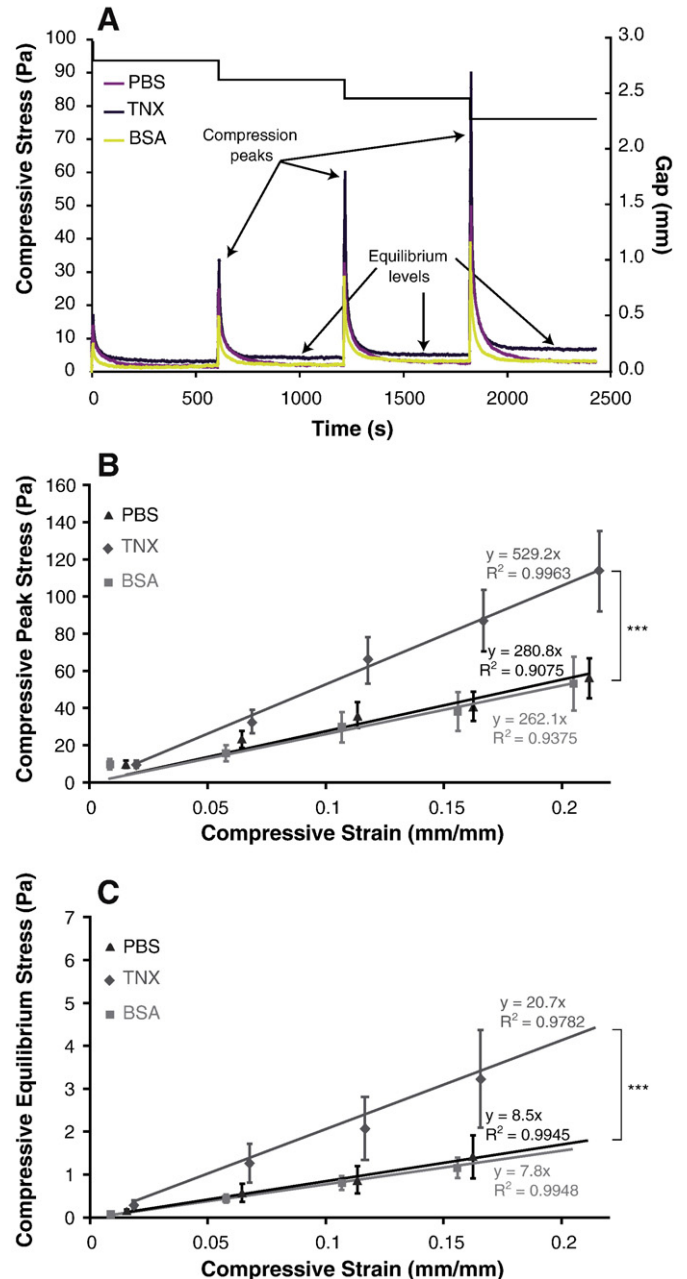

**Fig. 4.** Stress–relaxation response of collagen gels. (A) Stress versus compression time curves. The purple, blue, and yellow curves correspond to collagen gels prepared in the presence of PBS, TNX (66.6 nM) and BSA (66.6 nM) respectively. The black curve represents the gap between the two platens. For each condition, four different samples were tested by three cycles of three successive compressions. For each type of gel, the average stress–strain response is plotted by taking into account the mean of the peak compression values (B) or of the equilibrium level values (C). The linear regression lines shown allowed the calculation of the apparent compressive elastic modulus for each gel tested. Error bars represent min/max values and an ANOVA test was performed as statistical analysis. Each sample was compared to PBS. \*\*\* $p < 0.001$ .




### 3.2. Effect of TNX on the mechanical properties of collagen gels

Considering the interaction of TNX with fibrillar collagens [7,8] and the elastic properties of TNX [9], we decided to examine the physical behaviour of the collagen gels formed in the presence of TNX by rheometry, and to compare them to control gels consisting of collagen alone, or collagen and BSA.

The average stress–relaxation response under unconfined compression for the three types of gel is shown in Fig. 4A. The highest stress values were obtained for collagen/TNX gels while there was no obvious difference between collagen/BSA and collagen gels.

The average stress–strain response is plotted in Fig. 4B and C, in terms of the peak compression values (PCV; Fig. 4B) or the equilibrium level values (ELV; Fig. 4C). The linear regression based on these data showed that the compressive elastic modulus of the collagen/TNX gel was  $529.2 \pm 94$  Pa for PCV and  $20.7 \pm 7.4$  Pa for ELV. These values are approximately twice as high as the apparent compressive elastic modulus of the collagen/BSA gel (PCV =  $262.1 \pm 73$  Pa and ELV =  $7.8 \pm 1.6$  Pa) or the collagen gel (PCV =  $280.8 \pm 51$  Pa and ELV =  $8.5 \pm 2.9$  Pa). These values are smaller in comparison to the data obtained by Kreger and Voytik-Harbin on collagen gels [16]. This difference can be explained in two ways. The first concerns the boundary condition. In this study, the gel sample was free to slide on the stainless steel platen, which can decrease the apparent compressive elastic modulus compared to that obtained when the gel sample is fixed on the stainless steel platen. Secondly, the collagen concentration that we used is two-fold lower than in the previously published study (1 mg/mL instead of 2 mg/mL). In agreement with the latter explanation, it has been shown that both linear modulus and failure stress values increase linearly with collagen gel concentrations in the range 0.3 to 3 mg/mL [17].

The effect of TNX on the mechanical properties of collagen gels was further examined in a dose–response experiment shown in Fig. 5. The results clearly demonstrate an increase in elastic modulus correlated with an augmentation of TNX concentration. Finally, since previous experiments were performed with rat collagen combined with bovine TNX, we confirmed these results by the use of bovine collagen gels (data not shown). Firstly, values of elastic modulus in control conditions were similar to those obtained with rat collagen, and secondly, the increase in elastic modulus in the presence of TNX was of the same order of magnitude.

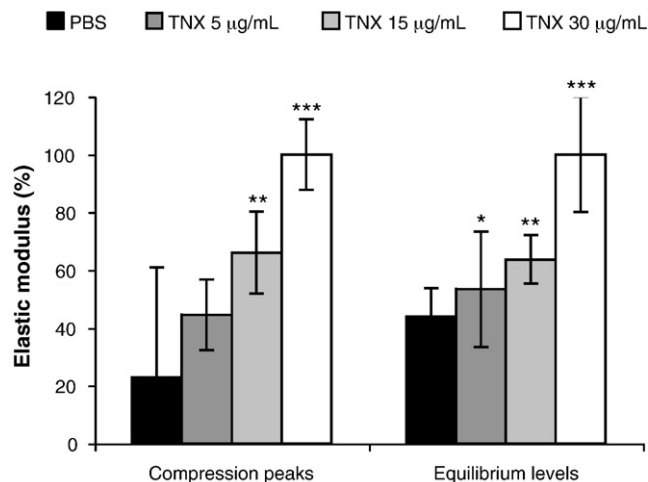

**Fig. 5.** Dose–response effect of TNX on the stress–relaxation behaviour of collagen gels. Results are given as a percentage of the elastic modulus measured in the presence of 30 µg/mL TNX (878.18 Pa for compression peak and 15.27 Pa for equilibrium level). Error bars represent Standard Deviation and statistical analyses were performed by ANOVA. Each TNX sample was compared to the PBS condition. \* $p < 0.05$ , \*\* $p < 0.01$ , \*\*\* $p < 0.001$ .

Thus, by these rheological studies, we can conclude that the presence of TNX within the collagen gels significantly increased their mechanical compressive behaviour, in a dose–dependent manner.

### 3.3. Conclusion

As demonstrated by Mao et al. [3], TNX deficiency in mice strongly influences the mechanical properties of skin. Indeed, these authors observed an increased deformability and reduced tensile strength of this tissue in the absence of TNX. The reduced fibrillar collagen content of the tissues and the failure of fibroblasts to deposit collagen in cell cultures led to the conclusion that TNX is critical for the cell-mediated fibrillogenesis process. Our results demonstrate that TNX increases collagen gel stiffness, probably by reinforcing the association between collagen fibrils. The dose–response effect that we observed might be of significant importance *in vivo* since in humans, different phenotypes (classical Ehlers–Danlos Syndrome *versus* joint hypermobility only) are observed in patients homozygous or heterozygous for TNX mutations, indicating a gene–dosage effect [18]. These data suggest that TNX should be involved directly in determining the mechanical properties of tissue components and might in part explain how TNX contributes to the mechanical resistance *in vivo*.

### Acknowledgements

This work was supported by a grant from the Ligue Nationale contre le Cancer (Comité Départemental de l'Ardèche), and Y. Margaron received a PhD fellowship from the Ligue Nationale contre le Cancer. The authors are grateful to Dr M.C. Ronzière (IBCP, Lyon) for providing acid-soluble collagen extracted from bovine skin and to D.J.S. Hulmes for revising english.

### References

- [1] F.S. Jones, P.L. Jones, The tenascin family of ECM glycoproteins: structure, function, and regulation during embryonic development and tissue remodeling, *Dev. Dyn.* 218 (2000) 235–259.
- [2] G.H. Burch, Y. Gong, W.H. Liu, R.W. Dettman, C.J. Curry, L. Smith, W.L. Miller, J. Bristow, Tenascin-X deficiency is associated with Ehlers–Danlos syndrome, *Nature Genet.* 17 (1997) 104–108.
- [3] J.R. Mao, G. Taylor, W.B. Dean, D.R. Wagner, V. Afzal, J.C. Lotz, E.M. Rubin, J. Bristow, Tenascin-X deficiency mimics Ehlers–Danlos syndrome in mice through alteration of collagen deposition, *Nature Genet.* 30 (2002) 421–425.
- [4] J. Schalkwijk, M.C. Zweers, P.M. Steulen, W.B. Dean, G. Taylor, Y.M. van Vlijmen, B. van Haren, W.L. Miller, J. Bristow, A recessive form of the Ehlers–Danlos syndrome caused by tenascin-X deficiency, *N. Engl. J. Med.* 345 (2001) 1167–1175.
- [5] C. Lethias, Y. Descollonges, M.M. Boutillon, R. Garrone, Flexilin: a new extracellular matrix glycoprotein localized on collagen fibrils, *Matrix Biol.* 15 (1996) 11–19.
- [6] F. Eleftheriou, J.-Y. Exposito, R. Garrone, C. Lethias, Binding of tenascin-X to decorin, *FEBS Lett.* 495 (2001) 44–47.
- [7] C. Lethias, A. Carisey, J. Comte, C. Cluzel, J.-Y. Exposito, A model of tenascin-X integration within the collagenous network, *FEBS Lett.* 580 (2006) 6281–6285.
- [8] D.E. Egging, F. van den Bergmolen, G. Taylor, J. Bristow, J. Schalkwijk, Interactions of human tenascin-X domains with dermal extracellular matrix molecules, *Arch. Dermatol. Res.* 73 (2007) 1–11.
- [9] A. Jollymore, C. Lethias, Q. Peng, Y. Cao, H. Li, Nanomechanical properties of tenascin-X revealed by single-molecule force spectroscopy, *J. Mol. Biol.* 385 (2009) 1277–1286.
- [10] C. Lethias, F. Eleftheriou, G. Parsiegla, J.-Y. Exposito, R. Garrone, Identification and characterization of a conformational heparin-binding site involving two fibronectin type III modules of bovine tenascin-X, *J. Biol. Chem.* 276 (2001) 16432–16438.
- [11] G.A. Ateshian, W.H. Warden, J.J. Kim, R.P. Grelsamer, V.V. Mow, Finite deformation biphasic material properties of bovine articular cartilage, *J. Biomech.* 30 (1997) 157–164.
- [12] T. Minamitani, T. Ikuta, Y. Saito, G. Takebe, M. Sato, H. Sawa, T. Nishimura, F. Nakamura, K. Takahashi, H. Ariga, K.-I. Matsumoto, Modulation of collagen fibrillogenesis by tenascin-X and type VI collagen, *Exp. Cell Res.* 298 (2004) 305–315.
- [13] M.M. Sullivan, T.H. Barker, S.E. Funk, A. Karchin, N.S. Seo, M. Hook, J. Sanders, B. Starcher, T.N. Wight, P. Puolakkainen, E.H. Sage, Matricellular hevin regulates decorin production and collagen assembly, *J. Biol. Chem.* 281 (2006) 27621–27632.
- [14] C. Giudici, N. Raynal, H. Wiedemann, W.A. Cabral, J.C. Marini, R. Timpl, H.P. Bachinger, R.W. Farndale, T. Sasaki, R. Tenni, Mapping of SPARC/BM40/

- osteonection-binding sites on fibrillar collagens, *J. Biol. Chem.* 283 (2008) 19551–19560.
- [15] N. Kuznetsova, S. Leikin, Does the triple helical domain of type I collagen encode several molecular recognition and fiber assembly while telopeptides serve as catalytic domains? *J. Biol. Chem.* 274 (1999) 36083–36088.
- [16] S.T. Kreger, S.L. Voytik-Harbin, Hyaluronan concentration within a 3D collagen matrix modulates matrix viscoelasticity, but not fibroblast response, *Matrix Biol.* 28 (2009) 336–346.
- [17] B.A. Roeder, K. Kokini, J.E. Sturgis, J.P. Robinson, S.L. Voytik-Harbin, Tensile mechanical properties of three-dimensional type I collagen extracellular matrices with varied microstructures, *J. Biomech. Eng.* 124 (2002) 214–222.
- [18] M.C. Zweers, J. Bristow, P.M. Steijlen, W.B. Dean, B.C. Hamel, M. Otero, M. Kucharekova, J.B. Boezeman, J. Schalkwijk, Haploinsufficiency of *TNXB* is associated with hypermobility type of Ehlers-Danlos syndrome, *Am. J. Hum. Genet.* 73 (2003) 214–217.