

## Catalytic Activity of V-Sn Oxides for Oxidation Reactions

Takehiko ONO,\* Yoshiro NAKAGAWA, and Yutaka KUBOKAWA

Department of Applied Chemistry, University of Osaka Prefecture, Sakai, Osaka 591

(Received March 28, 1980)

The rate of oxidation of  $C_3H_6$ ,  $C_2H_4$ ,  $C_3H_8$ , and CO has been investigated over V-Sn oxides of various compositions. The rate shows two maxima at V-Sn(V/Sn=2/1) and (1/8) oxides. Comparison between the rate of reduction of the oxides with  $C_3H_6$  and that of the corresponding catalytic oxidation suggests that the oxygen species responsible for oxidation differs for V-Sn(2/1) and V-Sn(1/8) oxides. The amount of oxygen desorbed in the temperature range 400–530 °C varies with the composition of the V-Sn oxides, showing a maximum at V-Sn(2/1) oxide. With V-Sn(1/8) oxide, little or no oxygen desorption is observed. On the basis of these results together with those of structural studies, it is concluded that the rate maximum with V-Sn(2/1) oxide arises from formation of an amorphous material from which lattice oxygen is easily released, while the rate maximum with V-Sn(1/8) oxide is associated with the presence of  $V^{4+}$  ions dissolved in  $SnO_2$ .

It has been shown by many workers that catalytic oxidation over  $V_2O_5$  proceeds *via* lattice oxygen,<sup>1)</sup> its activity being promoted by addition of the second component such as  $MoO_3$ ,  $SnO_2$ , etc. As regards the  $V_2O_5$ - $SnO_2$  system, several explanations have been proposed for the effect of promoters.<sup>2–5)</sup> Sachtler *et al.*<sup>2)</sup> reported that the promoter action of  $SnO_2$  in V-Sn oxides is due to the lowering of  $\Delta G$  for oxygen release from the oxide which arises from the dissolution of V ions in the  $SnO_2$  lattice.

In the present work, the rate of  $C_3H_6$ ,  $C_2H_4$ ,  $C_3H_8$ , and CO oxidation has been measured over V-Sn oxides of various compositions. Oxygen desorption experiments as well as measurements of the rate of reduction of the oxides with  $C_3H_6$  have been carried out. On the basis of these results together with those of structural studies such as X-ray diffraction, IR, and ESR, the nature of the promoter effect has been discussed.

## Experimental

**Materials.** V-Sn oxide catalysts were prepared as follows. The precipitate obtained from solutions of tin(II) chloride and ammonia was added to a solution containing the required quantity of ammonium metavanadate. The resulting precipitate was washed, dried, and heated in the air at 450 °C. The atomic ratio V/Sn of the catalysts and their surface area determined by the BET method are as follows. (V/Sn=1/0), 2.1; (4/1), 12.3; (2/1), 14.7; (1/2), 26.1; (1/8), 43.2; and (0/1), 6.8 m<sup>2</sup>/g.

**Apparatus and Procedure.** Catalytic oxidation and reduction of the oxides were carried out in a closed circulation system (290 cm<sup>3</sup>). In order to obtain the initial rates, the conversions were kept below  $\approx 5\%$ . The reaction products such as acrylaldehyde,  $CO_2$ , and CO were analyzed by gas chromatography. Carbonaceous deposits formed during the course of reduction were converted into  $CO_2$  by oxidation with oxygen at 450 °C. The amount was then determined.

X-Ray diffraction patterns of the catalysts were obtained on a Rigaku Denki D-3F X-ray diffractometer using Cu  $K\alpha$  radiation with a Ni filter. IR spectra were recorded on a Hitachi G2 spectrometer, the samples being prepared by the KBr pellet technique, and ESR spectra on a JES-ME-1X spectrometer. Oxygen desorption from V-Sn oxides was investigated by means of a Töpler pump. It was confirmed by gas chromatography that desorbed gas consists entirely of oxygen.

## Results

**Catalytic Oxidation of  $C_3H_6$  over V-Sn Oxides and Their Reduction with  $C_3H_6$ .** The rate of  $C_3H_6$  oxidation on various V-Sn oxides at 320 °C (Fig. 1) shows two maxima at V-Sn(2/1) and (1/8) oxides. Similar maxima are observed in low oxygen pressure experiments. Selectivity toward acrylaldehyde formation was determined for all the V-Sn oxides at similar conversion values, which were obtained by adjusting the catalyst weight as well as the reaction time (Fig. 2). The

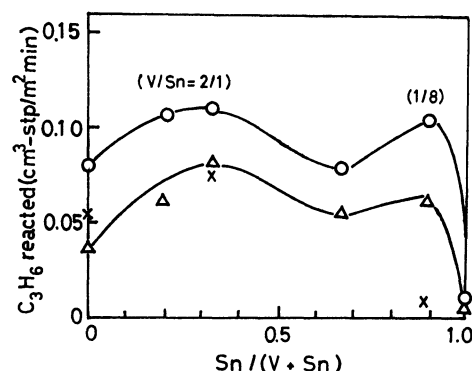


Fig. 1. Rates of  $C_3H_6$  oxidation at 320 °C.  $P_{C_3H_6}$  = 35 Torr (1 Torr = 133.3 Nm<sup>-2</sup>);  $P_{O_2}$ : —△—, 8; —○—, 40 Torr; X, rates of reduction of the oxides with  $C_3H_6$ .

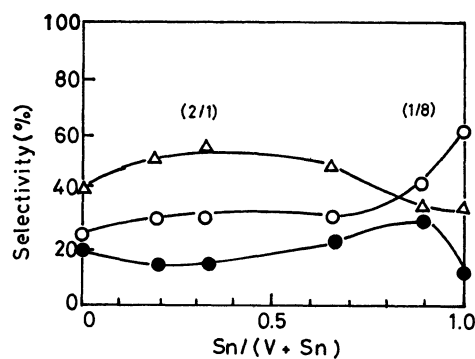


Fig. 2. Selectivities of  $C_3H_6$  oxidation. Experimental conditions are the same as in Fig. 1. —●—, Acrylaldehyde; —○—,  $CO_2$ ; —△—, CO.

selectivity toward acrylaldehyde formation is  $\approx 20\%$  for  $V_2O_5$ ,  $\approx 15\%$  for V-Sn(2/1) oxide and  $\approx 30\%$  for V-Sn(1/8) oxide. As regards CO and  $CO_2$  formation, with  $V_2O_5$ , V-Sn(4/1) and (2/1) oxides the ratio of the amount of CO to that of  $CO_2$  in the products is *ca.* 2, being essentially the same, while with  $SnO_2$  and V-Sn(1/8) oxide,  $CO_2$  formation is larger than CO formation. This indicates that the same mechanism is involved in CO and  $CO_2$  formation for the former group of oxides.

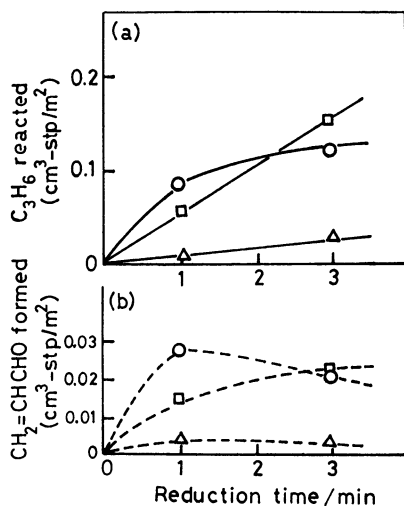


Fig. 3. Reduction of V-Sn oxides with  $C_3H_6$  at  $320^\circ C$ .  $P_{C_3H_6}=35$  Torr;  $\bigcirc$ —, V-Sn(2/1) oxide;  $\square$ —,  $V_2O_5$ ;  $\triangle$ —, V-Sn(1/8) oxide.

Figure 3a shows the rate of reduction of various oxides with  $C_3H_6$ . The initial rates of reduction obtained from the plots are  $0.06$ – $0.05$  for  $V_2O_5$ ,  $0.08$  for V-Sn(2/1) oxide and  $0.01$   $cm^3/m^2$  min for V-Sn(1/8) oxide. The initial rate values are also given in Fig. 1. Carbonaceous deposits were formed during the course of reduction. The amount formed for one minute was found to *ca.*  $0.03$  for  $V_2O_5$ ,  $0.05$  for V-Sn(2/1) oxide and  $0.04$   $cm^3/m^2$  for V-Sn(1/8) oxide. No significant difference among the three catalysts suggests that the extent of inhibition by carbonaceous deposits is essentially the same for all the catalysts.

Comparison of catalytic oxidation at two different oxygen pressures (Fig. 1) yields the reaction order  $0.3$ – $0.5$  in oxygen for all the V-Sn oxides investigated. The difference between the rate of reduction of the oxides with  $C_3H_6$  and that of the corresponding catalytic oxidation is considerably larger for V-Sn(1/8) oxide than for  $V_2O_5$  and V-Sn(2/1) oxides. It seems that the oxygen species responsible for oxidation differs for both groups of oxides.

In the initial stage of the reaction acrylaldehyde formation is larger over V-Sn(2/1) oxide than over  $V_2O_5$  (Fig. 3b). In fact, the initial selectivity toward acrylaldehyde formation obtained with V-Sn(2/1) oxide is  $30\%$ , being higher than the selectivity with  $V_2O_5$  ( $\approx 20\%$ ). As regards the selectivity in the later stage, the situation is reversed.  $V_2O_5$  is more selective than V-Sn(2/1) oxide, indicating that further oxidation of acrylaldehyde to CO and  $CO_2$  occurs more efficiently over V-Sn(2/1) oxide.

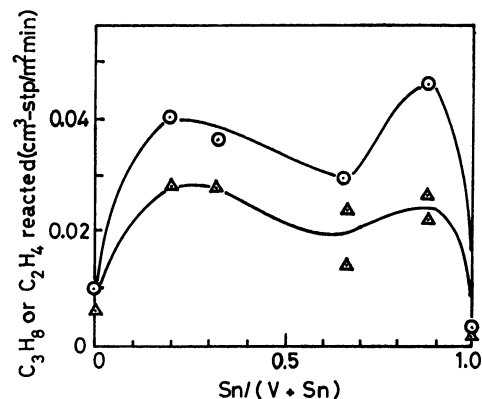


Fig. 4. Rates of oxidation of  $C_2H_4$  and  $C_3H_8$  at  $320^\circ C$ .  $P_{C_2H_4}, P_{C_3H_8}=40$  Torr;  $P_{O_2}=40$  Torr;  $\bigcirc$ —,  $C_2H_4$ ;  $\triangle$ —,  $C_3H_8$ .

*Catalytic Oxidation of  $C_2H_4$ ,  $C_3H_8$ , and CO.* The rates of oxidation of  $C_2H_4$  and  $C_3H_8$  are shown in Fig. 4. With the V-Sn(2/1) and (1/8) oxides, two maximum rates of oxidation similar to those with  $C_3H_8$  oxidation are observed. No partial oxidation products were formed. Rate enhancement by the addition of  $SnO_2$  is more significant for  $C_2H_4$  and  $C_3H_8$  oxidation than for the  $C_3H_8$  oxidation.

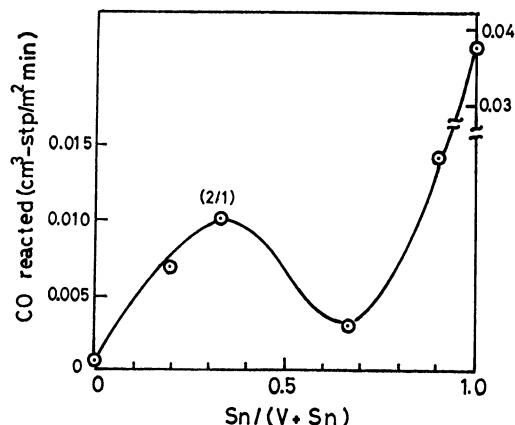


Fig. 5. Rates of CO oxidation at  $320^\circ C$ .  $P_{CO}=40$  Torr,  $P_{O_2}=40$  Torr.

The rate of CO oxidation over  $SnO_2$ , shown in Fig. 5, is about 140 times higher than that over  $V_2O_5$ . If the V-Sn oxide is a mixture of  $V_2O_5$  and  $SnO_2$ , its catalytic activity would increase monotonously with increasing  $SnO_2$  content, in disagreement with the result shown. The rate of CO oxidation passes through a maximum at V-Sn(2/1) oxide. Another maximum seems to be masked by a high rate of oxidation of CO over  $SnO_2$ . Thus, the existence of two different types of maximum rate of oxidation has been established.

*Oxygen Desorption from V-Sn Oxides.* Oxygen easily desorbs from V-Sn oxides at  $350$ – $500^\circ C$ .<sup>2)</sup> It was found that the dissociation pressure of oxygen over V-Sn oxides depends upon the amount of sample, decreasing with increase in the amount of oxygen removed from the oxides.<sup>2)</sup> Accordingly, dissociation pressure measurements appear to be inadequate for comparison of the ability to release oxygen from various oxides.

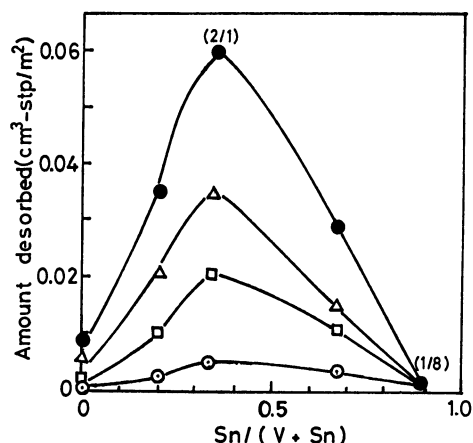



Fig. 6. Oxygen desorption from V-Sn oxides.

—○—, 450 °C; —□—, 500 °C; —△—, 530 °C;  
—●—, amount desorbed up to 530 °C; desorption  
time, 1 h at each temperature.

After the catalyst had been treated with oxygen at 400 °C followed by evacuation at 150 °C for 10 h, the temperature of the catalyst was raised stepwise up to 530 °C, the amount of oxygen desorbed being determined. During the course of experiments the pressure over the catalyst was kept below  $10^{-2}$  Torr. As seen in Fig. 6, the amount of oxygen desorbed changes with the composition of V-Sn oxide, showing a maximum at V-Sn(2/1) oxide, in a similar manner to that observed with the rate of oxidation. With V-Sn(1/8) oxide, little or no oxygen desorption is observed. The oxygen desorption begins around 400 °C, being predominant in the temperature range 450–530 °C. This suggests that the oxygen desorbed originates from lattice oxygen and not from adsorbed oxygen. The interaction of vanadium oxide with tin oxide would lead to formation of some active part, from which oxygen release takes place easily.


**Structure of V-Sn Oxides.** *X-Ray Diffraction:* X-Ray diffraction studies of the V-Sn oxides showed only diffraction lines due to  $V_2O_5$  and  $SnO_2$ . No lines indicating formation of a new compound between  $V_2O_5$  and  $SnO_2$  appeared, in agreement with the results of previous workers.<sup>2,6</sup> It appears that the active part described above exhibits no definite diffraction lines. As a result of the interaction of vanadium oxide and tin oxide an amorphous material might be formed. In fact, with V-Sn(4/1), (2/1), and (1/2) oxides, the intensities of the lines due to  $V_2O_5$  were found to be much smaller than what are expected from the composition of V-Sn oxides. V-Sn(4/1) oxide showed lines due to  $V_2O_5$  alone. With V-Sn(1/8) oxide only lines which are attributed to  $SnO_2$  appeared, the observed lattice constants being somewhat smaller than those of the crystalline  $SnO_2$ . The sizes of  $V_2O_5$  and  $SnO_2$  crystals in various V-Sn oxides, determined from the broadening of the diffraction lines,<sup>7</sup> were  $>200$  nm and 10–20 nm, respectively.

**IR:** IR spectra of V-Sn(2/1) oxide (Fig. 7a) show bands at  $1020\text{ cm}^{-1}$  (V=O stretching vibration) and  $818\text{ cm}^{-1}$  (V–O–V stretching vibration). Similar spectra were obtained with V-Sn(4/1) and (1/2) oxides.

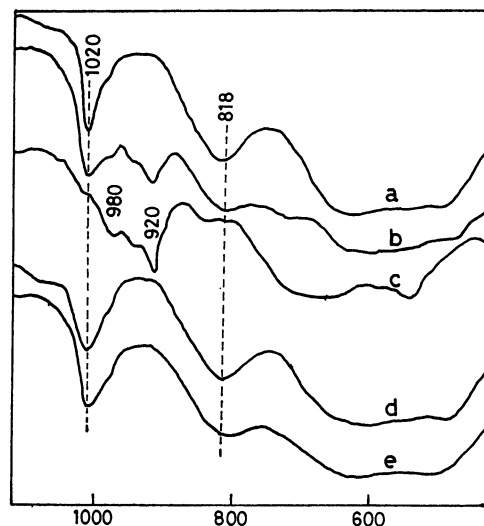Fig. 7. IR spectra of V-Sn (2/1) oxide before and after the reduction by  $C_3H_6$  and CO.

Before reduction (a), after reduction with  $C_3H_6$  at 320–350 °C; 1.1 atom% (b) or 6.3% (c) of lattice oxygen was removed: After reduction with CO at 450–500 °C; 2.0% (d) or 3.8% (e). 1 wt% of V-Sn oxide in KBr ( $\approx 50$  mg).

V-Sn(1/8) oxide exhibited no IR absorption due to  $V_2O_5$ . IR spectra of  $SnO_2$  showed a broad band at  $\approx 620\text{ cm}^{-1}$ . In order to examine the amorphous part in the V-Sn oxides, the intensity of the band at  $1020\text{ cm}^{-1}$  observed with the V-Sn oxides has been determined as a function of the concentration of vanadium ions in the KBr pellets. Similar experiments have been carried out for  $V_2O_5$  with the result that Lambert-Beer's law is applicable (Fig. 8). The intensity of the band at  $1020\text{ cm}^{-1}$  with the V-Sn oxides is about 30% of the intensity observed with  $V_2O_5$ , suggesting that a considerable fraction of vanadium oxide in V-Sn oxides exhibits no IR absorption. Figure 7a shows that

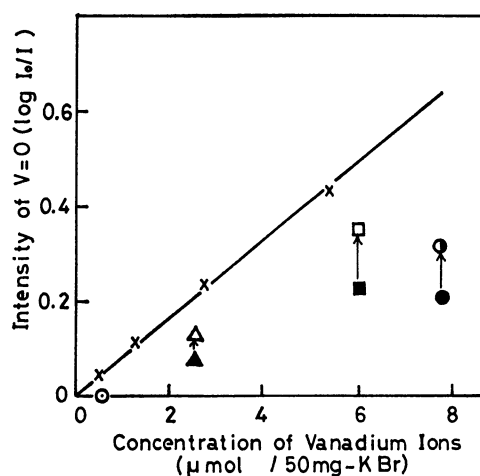Fig. 8. Estimation of  $V_2O_5$  concentration in V-Sn oxides.

×,  $V_2O_5$ ; ○, V-Sn (1/8) oxide; ▲, (1/2); ■, (2/1); ●, (4/1); △, □, ○, After calcination at 600 °C; 2 wt% of V-Sn oxide in KBr.

no alternative new bands appear. So far no explanation can be offered. The new bands might be masked by the bands due to  $V_2O_5$  or  $SnO_2$ . It appears that the part which exists in the amorphous state corresponds to the part which exhibits no IR absorption.

It seems necessary to consider the effect of crystal size of the sample upon the intensity of the IR band. Since only V=O groups in the surface layer are responsible for IR absorption, the intensity of the band at  $1020\text{ cm}^{-1}$  would increase with increase in the surface area of  $V_2O_5$  crystals, *i.e.*, with decrease in particle size. From the extent of broadening of diffraction lines, it was concluded that the size of  $V_2O_5$  crystals in V-Sn oxides is somewhat smaller than that in  $V_2O_5$  specimen. The fraction of the amorphous state to the total amount of  $V_2O_5$  in the V-Sn oxides seems to be larger than that shown in Fig. 8.

When the V-Sn oxides are calcined at  $600^\circ\text{C}$ , the intensity of the band at  $1020\text{ cm}^{-1}$  increase from  $\approx 30\%$  to  $\approx 60\%$  of those expected from the composition of the V-Sn oxides. This suggests that the amorphous part in the V-Sn oxides is decomposed to form  $V_2O_5$  and  $SnO_2$ .

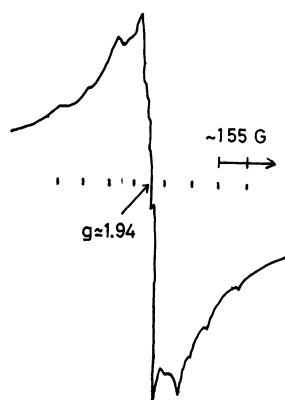


Fig. 9. ESR spectrum of V-Sn (1/8) oxide at 77 K after reduction with  $C_3H_8$ .

**ESR:** ESR measurements have been carried out with V-Sn(2/1) and (1/8) oxides, which exhibited the maximum oxidation activities. With V-Sn(2/1) oxide, only a broad signal appeared at  $g=1.96$ . After reduction with  $C_3H_8$  there was no hyperfine structure at 77 K. On the other hand, after reduction with  $C_3H_8$  V-Sn(1/8) oxide showed a signal having a hyperfine structure (Fig. 9) with  $g=1.94$  and  $A \approx 155\text{ G}$  at 77 K, in agreement with the results of Kasai,<sup>8)</sup> who reported a signal with  $g_z=1.942$  and  $A_z=155\text{ G}$  for  $V^{4+}$  ions dissolved in the  $SnO_2$  crystalline. On the basis of these results together with a slight contraction of  $SnO_2$  lattice in V-Sn(1/8) oxide described above, it is concluded that with V-Sn(1/8) oxide some fraction of vanadium ions are dissolved in the  $SnO_2$  lattice as  $V^{4+}$  ions.

### Discussion

Two maxima are observed at V-Sn(2/1) and (1/8) oxides for the rate of oxidation of various reactants

such as  $C_3H_8$ ,  $C_2H_4$ ,  $C_3H_6$ , and CO, although in the case of CO one maximum is masked by a high activity of pure  $SnO_2$ . Considering the marked difference between the rate of reduction of the oxides with  $C_3H_8$  and that of the corresponding catalytic oxidation observed with V-Sn(1/8) oxide, it is concluded that the oxygen species responsible for oxidation differs for V-Sn(2/1) and (1/8) oxides.

The rate of catalytic oxidation as well as of oxygen desorption shows a maximum at the same composition of V-Sn oxide (V/Sn=2/1). From the results together with those of structural studies such as X-ray diffraction and IR absorption, it is concluded that the maximum rate of oxidation observed with V-Sn(2/1) oxide can be attributed to formation of amorphous material from which lattice oxygen is easily released. The fraction of vanadium ions in the amorphous state is roughly constant with V-Sn(4/1), (2/1), and (1/2) oxides, being somewhat in contradiction with the maximum activity observed with V-Sn oxide (Fig. 8). When tin oxide is added to vanadium oxide, both enhancement of the activity due to formation of the amorphous part and decrease in the number of vanadium ions present in unit mass occurs simultaneously. Such a decrease in the number of vanadium ions would cause decrease in the activity of V-Sn oxides resulting from the presence of vanadium ions. Thus, the maximum activity with V-Sn(2/1) oxide is explicable.

The following results suggest that the reactivity of the amorphous material differs from that of the crystalline  $V_2O_5$  and  $SnO_2$ . With the reduction of V-Sn(2/1) oxide by CO (Fig. 7), the intensity of the band due to V=O scarcely changes (Figs. 7d, e), while it decreases markedly in the case of the reduction by  $C_3H_8$  (b, c). New bands appear in the region  $920\text{--}980\text{ cm}^{-1}$ . Similar spectra have been reported by Vadelievre *et al.*<sup>9)</sup> and Inomata *et al.*<sup>10)</sup> There is no marked difference between the amount of oxygen removed by the reduction in both cases. This suggests that the reduction by  $C_3H_8$  proceeds on  $V_2O_5$  crystals as well as on the part which exhibits no IR absorption, *i.e.*, the amorphous part, while the reduction by CO is limited to such an amorphous part alone, thus confirming the above conclusion.

Another maximum, *i.e.*, the maximum rate observed with V-Sn(1/8) oxide is not associated with the oxygen release. From the results of ESR and X-ray diffraction studies, it appears that the maximum rate observed with V-Sn(1/8) is associated with the presence of  $V^{4+}$  ions in  $SnO_2$  lattice. According to the work of Kon *et al.*,<sup>11)</sup> Yoshida *et al.*,<sup>12)</sup> and Takita *et al.*,<sup>13)</sup> the presence of  $V^{4+}$  ions appear to facilitate the formation of adsorbed oxygen species which play a significant role in the oxidation reaction. A similar situation would be expected for V-Sn oxides. A marked enhancement in the rate of oxidation of  $C_3H_8$  by the presence of gaseous oxygen observed with V-Sn(1/8) oxide might support this conclusion. However, the reactivity of adsorbed oxygen appears to be similar to that of lattice oxygen, since there is little or no difference between the product distributions for the  $C_3H_8$  oxidation over V-Sn(2/1) and (1/8) oxides. It seems very difficult to distinguish adsorbed oxygen from surface lattice oxygen,

*i.e.*, adsorbed oxygen can be regarded as a special type of surface lattice oxygen.

Considering the fact that two maximum activities are observed with the V-Sn oxides, it seems unlikely that the lowering of  $\Delta G$  for oxygen release from the oxide is closely associated with dissolution of V ions in the  $\text{SnO}_2$  lattice as suggested by Sachler *et al.*<sup>2)</sup> The maximum activity observed with V-Sn oxides containing a small amount of V ions as described above has not been found by Sachler *et al.*<sup>2)</sup> and other workers.<sup>3,4)</sup> They used silica or pumice supported V-Sn oxides, in contrast to the present work which deals with unsupported V-Sn oxides. Lack of the maximum rate of oxidation of CO over V-Sn oxides reported by Tarama *et al.*<sup>5)</sup> appears to be attributed to the preparation of their catalyst by fusion of mixture of  $\text{V}_2\text{O}_5$  and  $\text{SnO}_2$ , where formation of the amorphous material is unexpected.

The authors wish to thank Mr. Shinji Doi for carrying out part of the experiments.

#### References

- 1) E. G. J. Mars and D. W. Van Krevelen, *Chem. Eng. Sci.*, (s. p. Suppl.), **3**, 4 (1954); S. Yoshida, *Shokubai*, **10**, 90 (1968); K. Hirota, Y. Kera, and S. Teratani, *J. Phys. Chem.*, **72**, 3133 (1968); Y. Kubokawa and T. Ono, *Bull. Chem. Soc. Jpn.*, **51**, 3435 (1978).
- 2) W. M. H. Sachtler, G. H. Dorgero, J. Fahrenfort, and R. J. H. Voorhoeve, *Proc. 4th Int. Cong. Catal.*, Moscow, 1968, Vol. 1, p. 454.
- 3) M. Ai, *J. Catal.*, **40**, 318 (1975).
- 4) K. Kaneko, T. Koyama, Y. Nagashima, and S. Wada, *Nippon Kagaku Kaishi*, **1974**, 1105.
- 5) K. Tarama, S. Teranishi, N. Tamura, and S. Yoshida, *Shokubai*, **4**, 346 (1961).
- 6) L. N. Kurina and N. V. Kudrina, *Kinet. Catal.*, **16**, 1416 (1975).
- 7) "X-Sen Kessho-Gaku," ed by I. Nitta, Maruzen, Tokyo (1961).
- 8) P. H. Kasai, *Phys. Lett.*, **7**, 5 (1963).
- 9) M. Valdelievère, H. Baussart, R. Delobel, and J. M. Leroy, *Bull. Soc. Chim. Fr.*, **1975**, 2467.
- 10) M. Inomata, A. Miyamoto, and Y. Murakami, *J. Catal.*, **62**, 140 (1980).
- 11) Ya. M. Kon, A. M. Gritskov, V. A. Shvets, and V. B. Kazansky, *Kinet. Catal.*, **17**, 834 (1976).
- 12) S. Yoshida, T. Matsuzaki, T. Kashiwazaki, K. Mori, and K. Tarama, *Bull. Chem. Soc. Jpn.*, **47**, 1564 (1974).
- 13) Y. Takita, K. Iwanaga, N. Yamazone, and T. Seiyama, *Oxidation Communications*, **1**, No. 2 (1979); K. Nitta, Y. Takita, N. Yamazoe, and T. Seiyama, *Catal. Sympo. Catal. Soc. Jpn.*, Prepr. No. 3H12, 1976.