

## Infrared Study of Hydrogenation of Benzoic Acid to Benzaldehyde on $\text{ZrO}_2$ Catalysts

Junko KONDO, Nan DING, Ken-ichi MARUYA, Kazunari DOMEN,\* Toshiharu YOKOYAMA,<sup>†</sup>  
Naoko FUJITA,<sup>†</sup> and Takao MAKI<sup>†</sup>

Research Laboratory of Resources Utilization, Tokyo Institute of Technology,  
4259 Nagatsuta, Midori-ku, Yokohama 227

<sup>†</sup>Research Center, Mitsubishi Kasei Corporation, 1000 Kamoshida, Midori-ku, Yokohama 227

(Received May 10, 1993)

The selective hydrogenation of benzoic acid to benzaldehyde on  $\text{ZrO}_2$  and  $\text{Cr}_2\text{O}_3\text{--ZrO}_2$  at 523 K was studied by IR spectroscopy. An enhancement of the hydrogenation rate of benzoic acid by  $\text{Cr}_2\text{O}_3$  doping to  $\text{ZrO}_2$  was observed. The main role of  $\text{Cr}_2\text{O}_3$  was considered to be the step of activating hydrogen. An intermediate species was observed based on the IR bands during a transformation from the adsorbed benzaldehyde to the benzoate at lower temperatures. This is discussed in conjunction with the reaction mechanism of the hydrogenation. The intermediate species was regarded as being the chemisorbed benzaldehyde by an analysis of the observed IR bands.

Recently, a direct formation of aldehydes from carboxylic acids and  $\text{H}_2$  has been industrially realized.<sup>1–3)</sup> In this process various carboxylic acids are selectively hydrogenated into the corresponding aldehydes over a modified  $\text{ZrO}_2$  catalyst under relatively mild conditions. For example, benzaldehyde is produced from benzoic acid and  $\text{H}_2$  on the catalyst at between 623 and 673 K with a 98% conversion and a 96% selectivity. One of the characteristic points regarding this process is that a further reduction of the aldehydes to the corresponding alcohols or the decarboxylation reaction are negligible under the reaction conditions. When pure  $\text{ZrO}_2$  was used under the same reaction condition, benzaldehyde was produced with a 51% conversion and a 97% selectivity. Cr doping ( $\text{Cr}/\text{Zr}=5/100$  atomic ratio) enhanced the surface area as well as conversion to 98%.<sup>4)</sup> The adsorption and reaction of pivalic acid (2,2-dimethylpropionic acid) and 2,2-dimethylpropanal on a  $\text{Cr}_2\text{O}_3\text{--ZrO}_2$  were previously investigated by means of Fourier-transform infrared (FT-IR) spectroscopy over a wide temperature range.<sup>5)</sup> Chemisorbed 2,2-dimethylpropanal was detected during an aldehyde adsorption study at low temperature, which was expected to exist as an intermediate during the hydrogenation reaction. In the present paper, the hydrogenation of a typical aromatic carboxylic acid, benzoic acid, was studied in order to make a comparison with previous studies. The role of  $\text{Cr}_2\text{O}_3$  in the catalyst is also discussed.

### Experimental

An IR cell made of quartz was connected to a closed gas-circulation system.  $\text{ZrO}_2$  was obtained by calcination of zirconyl hydroxide ( $\text{ZrO}(\text{OH})_2$ ) at 873 K for 3 h.  $\text{Cr}_2\text{O}_3\text{--ZrO}_2$  ( $\text{Cr}/\text{Zr}=5/100$ , atomic ratio) was prepared by the impregnation of zirconium oxide dihydroxide with chromium(III) nitrate nonahydrate ( $\text{Cr}(\text{NO}_3)_3 \cdot 9\text{H}_2\text{O}$ ) and calcination in air at 823 K for 3 h. The BET surface areas of  $\text{ZrO}_2$  and  $\text{Cr}_2\text{O}_3\text{--ZrO}_2$  were 49 and 122  $\text{m}^2 \text{g}^{-1}$ , respectively. About 30 mg of the sample was pressed into a self-supporting disc of 20 mm in diameter. The spectra were recorded on a JASCO

7300 Fourier-transform infrared (FT-IR) spectrometer with a MCT detector at 4  $\text{cm}^{-1}$  resolution. The IR spectra of the adsorbed species were obtained by subtracting the spectra of  $\text{ZrO}_2$  from those of  $\text{ZrO}_2$  and the adsorbed species taken at the same temperatures. The bands between 2400 and 2200  $\text{cm}^{-1}$  in the IR spectra are due to gaseous  $\text{CO}_2$  in the optical path. A pretreatment of both  $\text{Cr}_2\text{O}_3\text{--ZrO}_2$  and  $\text{ZrO}_2$  samples was performed in an IR cell by heating in about 100 Torr of oxygen at 773 K for 8 h, followed by evacuation at the same temperature for 30 min. Each sample is designated as Cr- $\text{ZrO}_2$  and  $\text{ZrO}_2$ , respectively. Both  $\text{H}_2$  (Toyo Oxygen Company, 99.9999%) and  $\text{O}_2$  (Toyo Oxygen Company, 99.7%) were refined by passing through a liquid- $\text{N}_2$  trap. Benzoic acid (Wako Pure Chemical Industries, Ltd. 99+%) and benzaldehyde (Wako Pure Chemical Industries, Ltd. 99%) were introduced to the sample at vapor pressures without further purification.

### Results and Discussion

**1. Adsorption of Benzoic Acid.** The IR spectra of adsorbed benzoic acid on Cr- $\text{ZrO}_2$  are shown in Fig. 1. Benzoic acid was introduced at room temperature followed by evacuation at the same temperature. While the sample was heated gradually under evacuation, the spectra remained unchanged up to 673 K. All of the bands commenced to decrease at 723 K, and completely disappeared at 823 K. In order to assign the observed bands, the IR spectra of silver benzoate,<sup>10)</sup> sodium benzoate,<sup>11)</sup> and liquid benzoic acid<sup>12)</sup> were referred to. In the spectrum of liquid benzoic acid a strong band was observed at around 1690  $\text{cm}^{-1}$ , and assigned to the C=O stretching mode of the  $-\text{COOH}$  group. On the other hand, in spectra of benzoate salts two strong bands were observed at 1550—1520 and 1410—1390  $\text{cm}^{-1}$ , which were assigned to the OCO asymmetric stretching and the OCO symmetric stretching modes. These two bands are characteristic for ionic bidentate carboxylate, which is usually represented by the separation of ca. 150  $\text{cm}^{-1}$  between the two modes<sup>13,14)</sup> (Table 1). Since the spectra of the adsorbed species

Table 1. Assignment of the Benzoate Ion, Benzaldehyde, and Observed Bands<sup>a)</sup>

| Assignment <sup>15-17)</sup> | Benzoate ion <sup>17-21)</sup> | Observed species |                      |                      |                                |
|------------------------------|--------------------------------|------------------|----------------------|----------------------|--------------------------------|
|                              |                                | Benzoate         | Chemisorbed aldehyde | Physisorbed aldehyde | Benzaldehyde <sup>21-26)</sup> |
| *C-H str. in-phase           | 3091—3088                      |                  |                      |                      | 3084—3088                      |
| *C-H str.                    | 3067—3073                      |                  |                      |                      |                                |
| *C-H str.                    | 3053—3063                      | 3061             | 3065                 | 3065                 | 3063—3065                      |
| *C-H str.                    | 3036                           | 3032             |                      |                      | 3035—3040                      |
| *C-H str.                    | 3027                           |                  |                      |                      | 3026—3028                      |
| C-H str. (—CHO)              |                                |                  |                      | 2817 s               |                                |
| C=O str. (—CHO)              |                                |                  | 2850 br              | 2736 s               | 2817—2833 s                    |
| *C—C str.                    | 1600—1605 vs                   | 1600 sh          | 1681, 1649 vs        | 1701 vs              | 1703—1728 vs                   |
| *C—C str.                    | 1595—1598 vs, sh               | 1596 s           | 1602 s               | 1598 vs              | 1596—1614 vs                   |
| OCO a-str. (—OCO)            | 1522—1569 vs                   | 1528 vs          | 1582 s               | 1582 s               | 1583—1603 s                    |
| *C—C str.                    | 1488—1499 m-w                  | 1497 w           | 1495 w               | 1494 m               | 1491—1496 vw                   |
| *C—C str.                    | 1440—1452 m-vw, sh             | 1453 vs          | 1455 m               | 1455 s               | 1450—1460 s                    |
| OCO s-str.                   | 1391—1421 vs                   | 1435 vs          |                      |                      |                                |
| C-H bend. (—CHO)             |                                |                  |                      |                      | 1387—1394 m                    |
| *C—C str., kekule            | 1305—1318                      | 1309 w           | 1318 w               | 1311 m               | 1308—1314 s                    |
| *C-H in-plane bend, in-phase | 1272—1282 m-vw                 |                  | 1290 vw              | 1290 vw              | 1276—1292 m                    |
| *C—C str.                    | 1141—1150 vw                   | 1145 w           | 1219 s               | 1204 vs              | 1202—1206 vs                   |
| *C-H in-plane bend.          | 1178—1187 m-w                  | 1181 w           | 1174 w               | 1168 w               | 1164—1170 m                    |
| *C-H in-plane bend.          | 1148—1159 vw                   |                  |                      |                      | 1158—1160                      |
| *C-H in-plane bend.          | 1065—1072 m-w                  | 1070 w           | 1068 w               | 1068 w               | 1069—1074 sh                   |
| *C-H in-plane bend.          | 1020—1029 m-w, sh              | 1027 w           | 1026 w               | 1026 m               | 1021—1026 m                    |

a) \* represents an aromatic carbon. s, strong; m, medium; w, weak; v, very; sh, shoulder and br, broad.


formed by benzoic acid adsorption on Cr-ZrO<sub>2</sub> in Fig. 1 showed two intense bands at 1523 and 1424 cm<sup>-1</sup>, the observed species on Cr-ZrO<sub>2</sub> could be reasonably assigned to the bidentate carboxylate species,



Details concerning the assignment are listed in Table 1 along a summary of the observed bands of metal-coordinated benzoic acid ions including adsorbed benzoate on Al<sub>2</sub>O<sub>3</sub> formed from benzoic acid<sup>20)</sup> and benzaldehyde<sup>21)</sup> adsorption. The bands at 1592 and 1451 cm<sup>-1</sup> are attributed to the aromatic group. These two bands became less pronounced as the temperature increased (Fig. 1), probably because of a band broadening of two intense bands of the —OCO group. The adsorption of benzoic acid on ZrO<sub>2</sub> resulted in the same spectral change, depending on the temperatures, as those on Cr-ZrO<sub>2</sub>, with the exception of the reverse peaks due to the Cr=O<sup>5-8)</sup> species in the case of Cr-ZrO<sub>2</sub>. It is therefore considered that the stability of adsorbed benzoic acid was not affected by the existence of Cr.

**2. Hydrogenation of Benzoate.** Benzoic acid was introduced to Cr-ZrO<sub>2</sub> at 623 K where the benzoate was stable under evacuation. Then, H<sub>2</sub> (400 Torr, 1 Torr=133.322 Pa) was admitted at the same temperature. This temperature was chosen in order to study

the adsorbed species under similar conditions to that of the industrial production of benzaldehyde from benzoic acid and H<sub>2</sub>. Figure 2 shows the adsorbed benzoate (a) and the time course of the IR spectra taken during hydrogenation ((b)—(d)). All of the bands, except for those of the OH stretching (3600—3800 cm<sup>-1</sup>) mode, decreased constantly as the reaction proceeded, and almost disappeared after 30 min. The increase in the IR absorption in the OH stretching region after H<sub>2</sub> admission is not due to the production of H<sub>2</sub>O, according to



Since the OH species increased immediately after the introduction of H<sub>2</sub>, as shown in (b). Therefore, the increase in the OH species is due to hydrogen adsorption on the benzoate adsorbed-Cr-ZrO<sub>2</sub> surface. The IR spectra taken during hydrogenation of benzoate over ZrO<sub>2</sub> are shown in Fig. 3. It is noticed that the reaction proceeded more slowly over ZrO<sub>2</sub> than over Cr-ZrO<sub>2</sub> (Fig. 2) under the same reaction conditions, although the stability of benzoate under evacuation was not affected by Cr. It is therefore suggested that one of the roles of Cr is to facilitate the activation of H<sub>2</sub>.

Both on Cr-ZrO<sub>2</sub> and on ZrO<sub>2</sub> the adsorbed benzoate species reacted with H<sub>2</sub>; no intermediate species or product aldehyde were observed at 623 K, as shown in Figs. 2 and 3.

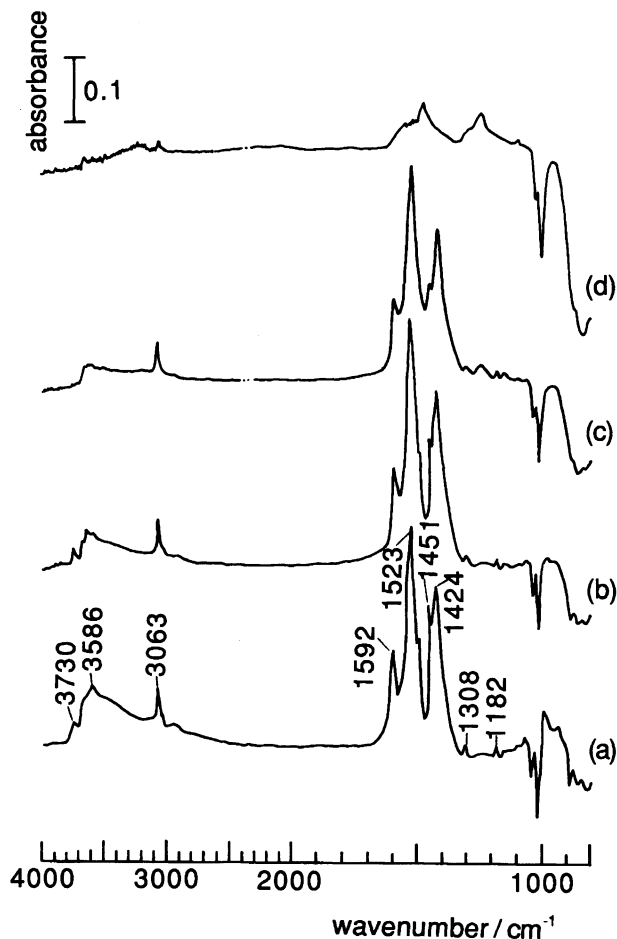


Fig. 1. FT-IR spectra of adsorbed benzoic acid on  $\text{Cr-ZrO}_2$  at various temperatures: (a) 473 K, (b) 573 K, (c) 673 K, and (d) 773 K.

**3. Adsorption of Benzaldehyde.** The reverse reaction from an aldehyde and  $\text{H}_2\text{O}$  to the corresponding carboxylic acid and  $\text{H}_2$  was also observed over  $\text{Cr-ZrO}_2$ .<sup>28)</sup> Therefore, the adsorption of benzaldehyde and the transformation on the catalyst were studied by IR spectroscopy. Benzaldehyde was adsorbed on  $\text{Cr-ZrO}_2$  and  $\text{ZrO}_2$  at about 200 K, followed by evacuation. The sample was then gradually ( $2 \text{ K s}^{-1}$ ) heated under evacuation. IR spectra of the adsorbed benzaldehyde on  $\text{Cr-ZrO}_2$  are presented in Fig. 4. Heating from 273 K (a) to 373 K (b) caused the disappearance of the bands between 2950 and 2650  $\text{cm}^{-1}$  in the CH stretching region and at 1701, 1311, and 1204  $\text{cm}^{-1}$ . These bands were assigned to physically adsorbed benzaldehyde, with reference to the IR and Raman spectra of liquid benzaldehyde<sup>21–26)</sup> (see Table 1). The physically adsorbed benzaldehyde desorbed at 373 K.

Above 373 K, several bands at 1681, 1649, and 1219  $\text{cm}^{-1}$  and a weak band in the CH stretching region (ca. 2850  $\text{cm}^{-1}$ ) decreased. The decrease of these bands in intensity was accompanied by an increase of the bands at 1522 and 1421  $\text{cm}^{-1}$ , attributed to the benzoate species; they became dominant at 573 K (d). Since

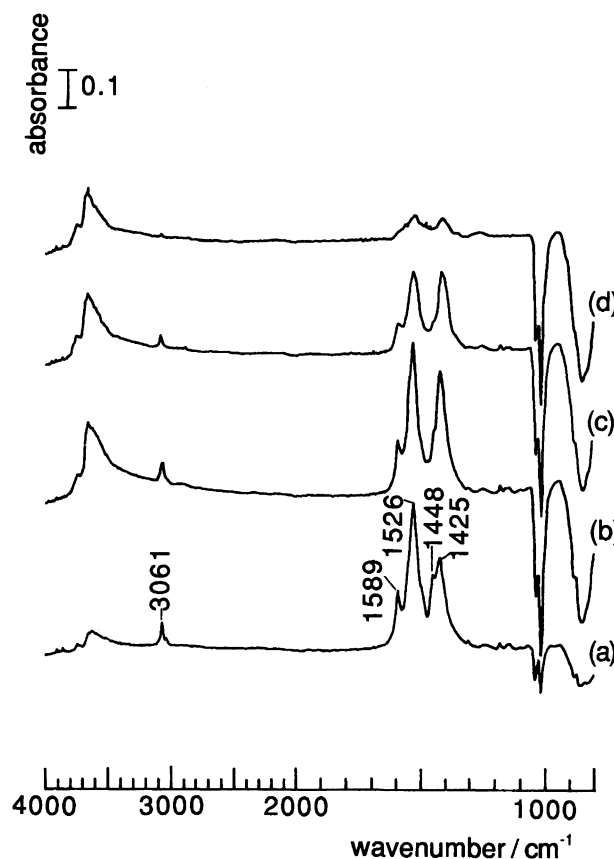


Fig. 2. FT-IR spectra taken during the hydrogenation of benzoate on  $\text{Cr-ZrO}_2$  at 623 K: (a) adsorbed benzoate, (b) immediately, (c) 10 min, and (d) 30 min after introduction of  $\text{H}_2$  (400 Torr).

these spectra were taken under evacuation, it is concluded that these bands shown in Fig. 4 (b) were attributed to the precursor species for benzoate formation. Although this intermediate species and the physically adsorbed species coexisted at 273 K, the physically adsorbed species was simply desorbed and did not take part in the production of benzoate.

The structure of the intermediate was then considered based on the observed IR bands. The bands assigned to the intermediate were observed at 3065, 2850, 1681, 1649, 1602, 1582, 1455, 1318, and 1219  $\text{cm}^{-1}$ . Among the observed bands, those at 3065, 1602, 1582, 1495, 1455, and 1318  $\text{cm}^{-1}$  are attributed to the absorption bands of the phenyl group (Table 1). Other bands at 2850, 1681, 1649, and 1219  $\text{cm}^{-1}$  are attributed to the aldehyde group. The band at 2850  $\text{cm}^{-1}$  is attributed to the CH stretching mode derived from the CHO group. The bands assigned to aromatic group appear to be sharp, probably due to the absence of a direct interaction with the surface. In Fig. 4, a simultaneous production of the OH species between 3550 and 3600  $\text{cm}^{-1}$  and a decrease in the intermediate were observed. This feature was not observed in case of  $\text{ZrO}_2$  in Fig. 5 (discussed below) because of the perturbation


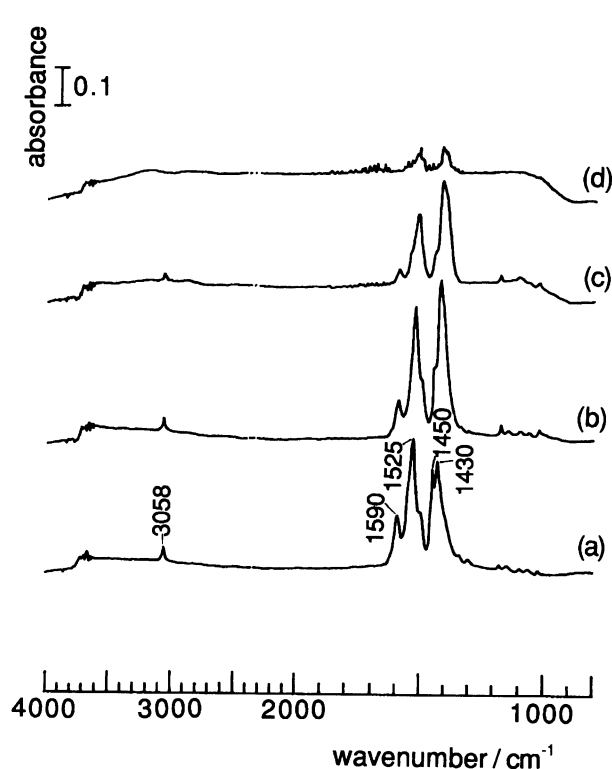


Fig. 3. FT-IR spectra taken during the hydrogenation of benzoate on  $\text{ZrO}_2$  at 623 K: (a) adsorbed benzoate, (b) immediately, (c) 30 min, and (d) 120 min after introduction of  $\text{H}_2$  (400 Torr).

of the originally existing OH species after a pretreatment. Combining the OH formation and the decrease in the intermediate, it is concluded that the C-H bond of the formyl group in the intermediate species dissociated at the same temperature to the produce benzoate and hydroxyl species. Regarding the structure of the intermediate, the bisoxide species, as described below, is unlikely:



This is because the bisoxide species should show a strong band due to a CH deformation at between 1200 and  $1000 \text{ cm}^{-1}$ . Moreover, the IR absorption band of single-bonded C-O should appear at between 1200 and  $950 \text{ cm}^{-1}$ .<sup>29)</sup> Among the absorption bands attributed to the intermediate species, two bands at 1682 and  $1649 \text{ cm}^{-1}$  are regarded as being the C=O stretching mode based on their peak position. While in the case of free aldehydes, the C=O bands appear at  $1700 \text{ cm}^{-1}$ , the observed bands appeared in a lower frequency region, suggesting that the C=O bond is weakened via an interaction with the catalyst surface. The slight shift of the C=O stretching band of the intermediate by less than  $100 \text{ cm}^{-1}$  from physically adsorbed species eliminates the possibility of any resonant structures, such as those proposed in metalloacyls, as described in Eq. 4 or 5.<sup>30)</sup>




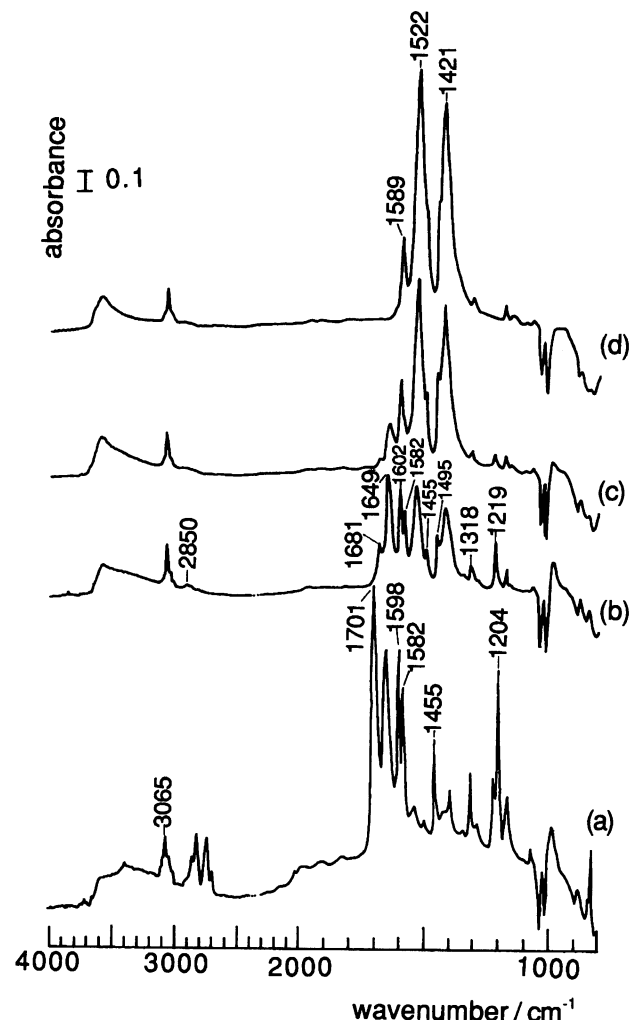


Fig. 4. FT-IR spectra of benzaldehyde adsorbed on  $\text{Cr-ZrO}_2$  at various temperatures: (a) 273 K, (b) 373 K, (c) 473 K and (d) 573 K.



In both cases, the C=O stretching bands are shifted by  $150\text{--}300 \text{ cm}^{-1}$  from the free acyl C=O stretching bands. From the observed bands, we therefore, propose the structure of the intermediate as follows:

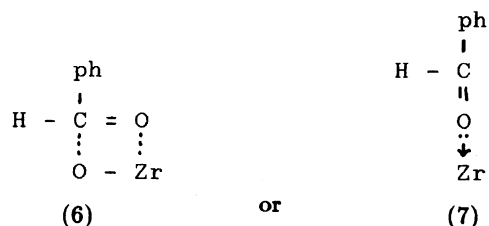

Taking into account that the intermediate transformed into OH and benzoate with an increase in temperature,

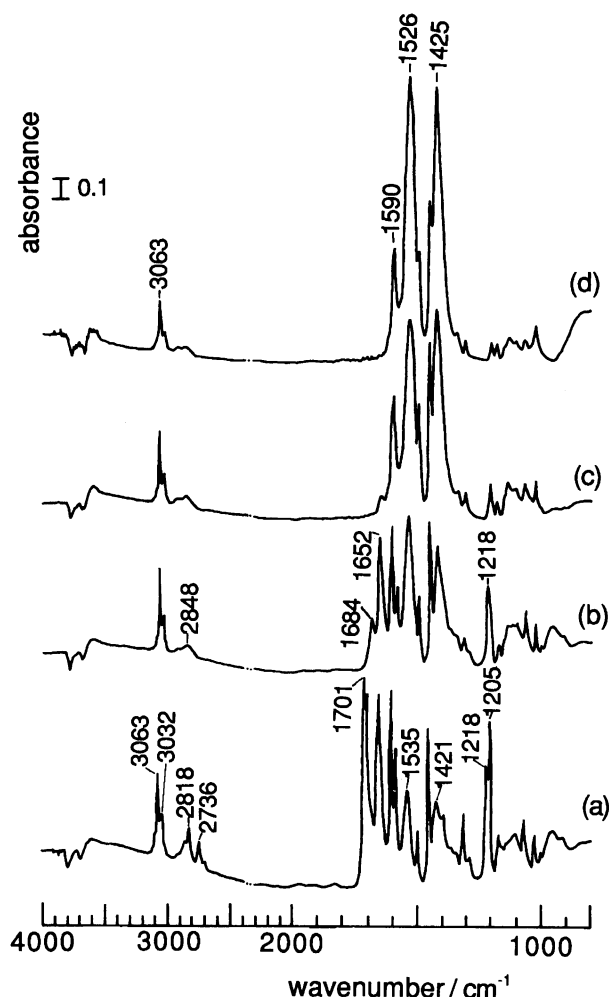


Fig. 5. FT-IR spectra of benzaldehyde adsorbed on  $\text{ZrO}_2$  at various temperatures: (a) 273 K, (b) 295 K, (c) 423 K, and (d) 573 K.

structure (6) seems to be preferable. The band at  $1218\text{ cm}^{-1}$  is assigned to the ph-C stretching mode.<sup>21–26,29</sup> The appearance of two bands at 1681 and  $1649\text{ cm}^{-1}$  may be regarded as being the adsorption of the intermediate species on two different sites.

For a further understanding, the role of the Cr adsorption of aldehyde on  $\text{ZrO}_2$  was compared with that on  $\text{Cr-ZrO}_2$ . Figure 5 shows the IR spectra obtained during the same procedure as those for Fig. 4. At 273 K, the physically adsorbed species and the intermediate were observed. It is also noted that a small amount of the benzoate species ( $1535$  and  $1421\text{ cm}^{-1}$ ) was already formed at this temperature. The same intermediate as that on  $\text{Cr-ZrO}_2$  was observed in Fig. 5 (a) and (b). In addition to the intermediate species ( $2848$ ,  $1684$ ,  $1652$ , and  $1218\text{ cm}^{-1}$ ), benzoate had already been observed at 295 K. The transformation from the intermediate to the benzoate species was similarly observed on both  $\text{Cr-ZrO}_2$  and  $\text{ZrO}_2$ . The essential property of the catalyst is therefore considered to be based on the nature of  $\text{ZrO}_2$ . These IR results are in good agreement with the

kinetic studies in which the selectivity of benzaldehyde formation is not affected by Cr doping (97% over  $\text{ZrO}_2$  and 96% over  $\text{Cr-ZrO}_2$  at 623 K), but only conversion is enhanced by Cr from 51 to 98% at 623 K.<sup>1–3)</sup>

### Summary

It was found that: 1) benzoic acid existed as benzoate species on both  $\text{ZrO}_2$  and  $\text{Cr-ZrO}_2$ ; 2) chemisorbed benzaldehyde described as (6) or (7) was formed by benzaldehyde adsorption at low temperature, which was expected to be the intermediate during the catalytic reduction of benzoate species by gaseous  $\text{H}_2$ ; and that 3) the role of the Cr is regarded as being to activate hydrogen, as well as to increase the surface area of the catalyst.

### References

- 1) T. Maki and T. Yokoyama, *J. Synth. Org. Chem. Jpn.*, **49**, 159 (1991).
- 2) T. Yokoyama, T. Setoyama, N. Fujita, M. Nakajima, T. Maki, and K. Fujii, *Appl. Catal.*, in press.
- 3) Mitsubishi Kasei Corporation, U.S. Patent 4613700 (1986).
- 4) T. Maki, T. Yokoyama, T. Setoyama, and N. Fujita, unpublished data.
- 5) N. Ding, J. Kondo, K. Maruya, K. Domen, T. Yokoyama, N. Fujita, and T. Maki, *Catal. Lett.*, **17**, 309 (1993).
- 6) C. G. Barraclough, J. Lewis, and R. S. Nyholm, *J. Chem. Soc.*, **1959**, 3552.
- 7) W. E. Hobbs, *J. Chem. Phys.*, **28**, 1220 (1958).
- 8) A. Zecchina, S. Coluccia, L. Cerruti, and E. Borello, *J. Phys. Chem.*, **75**, 2783 (1971).
- 9) I. E. Wachs and F. D. Hardcastle, "Proc. 9th Int. Congr. Catal.," Calgary, 1988, p. 1449.
- 10) C. J. Pouchert, "The Aldrich Library of FT-IR Spectra," 1st ed, Vol. 2, p. 1239B, (1985).
- 11) C. J. Pouchert, "The Aldrich Library of FT-IR Spectra," 1st ed, Vol. 2, p. 271B, (1985).
- 12) C. J. Pouchert, "The Aldrich Library of FT-IR Spectra," 1st ed, Vol. 2, p. 186B, (1985).
- 13) K. Nakamoto, "Infrared and Raman Spectra of Inorganic and Coordination Compounds," 4th ed, John Wiley and Sons, Inc., Canada (1986).
- 14) W. Lewandowski, *Can. J. Spectrosc.*, **32**, 41 (1987).
- 15) G. Varsanyi, "Vibrational Spectra of Benzene Derivatives," Academic Press, New York and London (1969).
- 16) D. H. Whiffen, *J. Chem. Soc.*, **1956**, 1350.
- 17) K. Machida, A. Kuwae, Y. Saito, and T. Uno, *Spectrochim. Acta, Part A*, **34A**, 793 (1978).
- 18) J. H. S. Green, *Spectrochim. Acta, Part A*, **33A**, 575 (1977).
- 19) W. Lewandowski, *Can. J. Spectrosc.*, **32**, 41 (1987).
- 20) R. P. Groff, *J. Catal.*, **79**, 259 (1983).
- 21) A. E. T. Kuiper, J. Medema, and J. J. G. M. Van Bokhoven, *J. Catal.*, **29**, 40 (1973).
- 22) R. Zwarich, J. Smolarek, and L. Goodman, *J. Mol. Spectrosc.*, **38**, 336 (1971).
- 23) J. H. S. Green and D. J. Harrison, *Spectrochim. Acta*

Part A, **32A**, 1265 (1976).

24) D. Ambrose, J. E. Connet, J. H. S. Green, J. L. Hales, A. J. Head, and J. F. Martin, *J. Chem. Thermodyn.*, **7**, 1143 (1975).

25) M. R. Padhye and B. G. Viladkar, *J. Sci. Ind. Res., Sect. B*, **19B**, 45 (1960).

26) C. Crrigou-Lagrange, N. Claverie, J. -M. Legas, and M. -L. Josien, *J. Chim. Phys.*, **58**, 559 (1961).

27) J. Kondo, Y. Sakata, K. Domen, K. Maruya, and T. Onishi, *J. Chem. Soc., Faraday Trans.*, **86**, 3021 (1990).

28) T. Yokoyama and T. Maki, to be published.

29) L. J. Bellamy, "Infra-red Spectra of Complex Molecules," Chapman and Hall Ltd., London (1975), Vol. 2, pp. 107—228.

30) J. A. Gladysz, *Adv. Organomet. Chem.*, **20**, 1 (1982), and the references therein.

---