

Review

Biofibres and biocomposites

Maya Jacob John, Sabu Thomas *

School of Chemical Sciences, Mahatma Gandhi University, Priyadarshini Hills P.O., Kottayam, Kerala 686 560, India

Received 14 February 2007; received in revised form 22 May 2007; accepted 24 May 2007

Available online 10 June 2007

Abstract

This review deals with a recent study of the literature on the various aspects of cellulosic fibres and biocomposites. Cellulosic fibre reinforced polymeric composites are finding applications in many fields ranging from construction industry to automotive industry. The pros and cons of using these fibres are enumerated in this review. The classification of composites into green composites, hybrid biocomposites and textile biocomposites are discussed. New developments dealing with cellulose based nanocomposites and electrospinning of nanofibres have also been presented. Recent studies pertaining to the above topics have also been cited. Finally, the applications of cellulosic fibre reinforced polymeric composites have been highlighted.

© 2007 Elsevier Ltd. All rights reserved.

Keywords: Biocomposite; Biofiber; Green composite; Textile; Hybrid**1. Lignocellulosic fibres/natural fibres**

Natural fibres are subdivided based on their origins, coming from plants, animals or minerals. All plant fibres are composed of cellulose while animal fibres consist of proteins (hair, silk, and wool). Plant fibres include bast (or stem or soft sclerenchyma) fibres, leaf or hard fibres, seed, fruit, wood, cereal straw, and other grass fibres. Over the last few years, a number of researchers have been involved in investigating the exploitation of natural fibres as load bearing constituents in composite materials. The use of such materials in composites has increased due to their relative cheapness, their ability to recycle and for the fact that they can compete well in terms of strength per weight of material. Natural fibres can be considered as naturally occurring composites consisting mainly of cellulose fibrils embedded in lignin matrix. The cellulose fibrils are aligned along the length of the fibre, which render maximum tensile and flexural strengths, in addition to providing rigidity. The reinforcing efficiency of natural fibre is related to the nature of cellulose and its crystallinity. The

main components of natural fibres are cellulose (α -cellulose), hemicellulose, lignin, pectins, and waxes.

Cellulose is a natural polymer consisting of D-anhydroglucose ($C_6H_{10}O_5$) repeating units joined by 1,4- β -D-glycosidic linkages at C₁ and C₄ position (Neveill & Zeronian, 1985). The degree of polymerization (DP) is around 10,000. Each repeating unit contains three hydroxyl groups. These hydroxyl groups and their ability to hydrogen bond play a major role in directing the crystalline packing and also govern the physical properties of cellulose. Solid cellulose forms a microcrystalline structure with regions of high order i.e. crystalline regions and regions of low order i.e. amorphous regions. Cellulose is also formed of slender rod like crystalline microfibrils. The crystal nature (monoclinic sphenoidic) of naturally occurring cellulose is known as cellulose I. Cellulose is resistant to strong alkali (17.5 wt%) but is easily hydrolyzed by acid to water-soluble sugars. Cellulose is relatively resistant to oxidizing agents.

Hemicellulose is not a form of cellulose and the name is a misnomer. They comprise a group of polysaccharides composed of a combination of 5- and 6-carbon ring sugars. Hemicellulose differs from cellulose in three aspects. Firstly, they contain several different sugar units whereas cellulose contains only 1,4- β -D-glucopyranose units.

* Corresponding author. Tel.: +91 481 2730003; fax: +91 481 2561190.

E-mail addresses: sabut@sancharnet.in, sabut552001@yahoo.com (S. Thomas).

Secondly, they exhibit a considerable degree of chain branching containing pendant side groups giving rise to its non crystalline nature, whereas cellulose is a linear polymer. Thirdly, the degree of polymerization of native cellulose is 10–100 times higher than that of hemicellulose. The degree of polymerization (DP) of hemicellulose is around 50–300. Hemicelluloses form the supportive matrix for cellulose microfibrils. Hemicellulose is very hydrophilic, soluble in alkali and easily hydrolyzed in acids.

Lignin is a complex hydrocarbon polymer with both aliphatic and aromatic constituents. They are totally insoluble in most solvents and cannot be broken down to monomeric units. Lignin is totally amorphous and hydrophobic in nature. It is the compound that gives rigidity to the plants. It is thought to be a complex, three-dimensional copolymer of aliphatic and aromatic constituents with very high molecular weight. Hydroxyl, methoxyl and carbonyl groups have been identified. Lignin has been found to contain five hydroxyl and five methoxyl groups per building unit. It is believed that the structural units of lignin molecule are derivatives of 4-hydroxy-3-methoxy phenylpropane. The main difficulty in lignin chemistry is that no method has been established by which it is possible to isolate lignin in its native state from the fibre. Lignin is considered to be a thermoplastic polymer exhibiting a glass transition temperature of around 90 °C and melting temperature of around 170 °C (Olesen & Plackett, 1999). It is not hydrolyzed by acids, but soluble in hot alkali, readily oxidized, and easily condensable with phenol (Bismarck, Mishra, & Lampke, 2005).

Pectins are a collective name for heteropolysaccharides. They give plants flexibility. Waxes make up the last part of fibres and they consist of different types of alcohols.

Biofibres can be considered to be composites of hollow cellulose fibrils held together by a lignin and hemicellulose matrix (Jayaraman, 2003). The cell wall in a fibre is not a homogenous membrane (Fig. 1). Each fibril has a complex, layered structure consisting of a thin primary wall that is the first layer deposited during cell growth encircling a secondary wall. The secondary wall is made up of three layers and the thick middle layer determines the mechanical properties of the fibre. The middle layer consists of a series of

helically wound cellular microfibrils formed from long chain cellulose molecules: the angle between the fibre axis and the microfibrils is called the microfibrillar angle. The characteristic value for this parameter varies from one fibre to another.

Such microfibrils have typically a diameter of about 10–30 nm and are made up of 30–100 cellulose molecules in extended chain conformation and provide mechanical strength to the fibre. The amorphous matrix phase in a cell wall is very complex and consists of hemicellulose, lignin, and in some cases pectin. The hemicellulose molecules are hydrogen bonded to cellulose and act as cementing matrix between the cellulose microfibrils, forming the cellulose–hemicellulose network, which is thought to be the main structural component of the fibre cell. The hydrophobic lignin network affects the properties of other network in a way that it acts as a coupling agent and increases the stiffness of the cellulose/hemicellulose composite.

The structure, microfibrillar angle, cell dimensions, defects, and the chemical composition of fibres are the most important variables that determine the overall properties of the fibres (Satyanarayana et al., 1986). Generally, tensile strength and Young's modulus of fibres increases with increasing cellulose content. The microfibrillar angle determines the stiffness of the fibres. Plant fibres are more ductile if the microfibrils have a spiral orientation to the fibre axis. If the microfibrils are oriented parallel to the fibre axis, the fibres will be rigid, inflexible and have high tensile strength. Some of the important biofibres are listed in Table 1.

1.1. Cellulosic fibres: advantages and disadvantages

The growing interest in lignocellulosic fibres is mainly due to their economical production with few requirements for equipment and low specific weight, which results in a higher specific strength and stiffness when compared to glass reinforced composites. They also present safer handling and working conditions compared to synthetic reinforcements. Biofibres are nonabrasive to mixing and molding equipment, which can contribute to significant cost reductions. The most interesting aspect about natural fibres is their positive environmental impact. Biofibres are a renewable resource with production requiring little energy. They are carbon dioxide neutral i.e. they do not return excess carbon dioxide into the atmosphere when they are composted or combusted. The processing atmosphere is friendly with better working conditions and therefore there will be reduced dermal and respiratory irritation. Biofibres possess high electrical resistance. Thermal recycling is also possible. The hollow cellular structure provides good acoustic insulating properties. The worldwide availability is an additional factor.

The inherent polar and hydrophilic nature of lignocellulosic fibres and the non-polar characteristics of most thermoplastics results in compounding difficulties leading to non-uniform dispersion of fibres within the matrix which

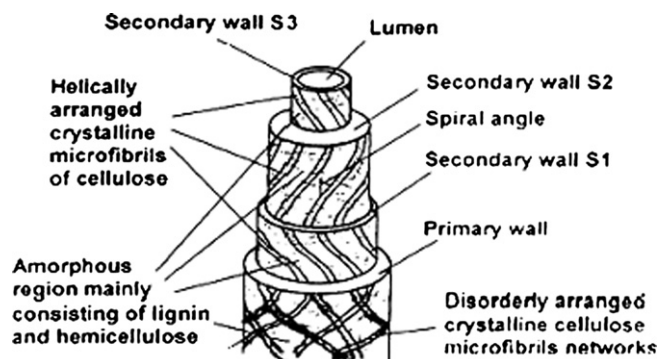


Fig. 1. Structure of biofibre.

Table 1
List of important biofibres

Fibre source	Species	Origin
Abaca	<i>Musa textilis</i>	Leaf
Bagasse	–	Grass
Bamboo	(>1250 species)	Grass
Banana	<i>Musa indica</i>	Leaf
Broom root	<i>Muhlenbergia macroura</i>	Root
Cantala	<i>Agave cantala</i>	Leaf
Caroa	<i>Neoglaziovia variegata</i>	Leaf
China jute	<i>Abutilon theophrasti</i>	Stem
Coir	<i>Cocos nucifera</i>	Fruit
Cotton	<i>Gossypium</i> sp.	Seed
Curaua	<i>Ananas erectifolius</i>	Leaf
Date palm	<i>Phoenix Dactylifera</i>	Leaf
Flax	<i>Linum usitatissimum</i>	Stem
Hemp	<i>Cannabis sativa</i>	Stem
Henequen	<i>Agave fourcroydes</i>	Leaf
Isora	<i>Helicteres isora</i>	Stem
Istle	<i>Samuela carnerosana</i>	Leaf
Jute	<i>Corchorus capsularis</i>	Stem
Kapok	<i>Ceiba pentrandia</i>	Fruit
Kenaf	<i>Hibiscus cannabinus</i>	Stem
Kudzu	<i>Pueraria thunbergiana</i>	Stem
Mauritius hemp	<i>Furcraea gigantea</i>	Leaf
Nettle	<i>Urtica dioica</i>	Stem
Oil palm	<i>Elaeis guineensis</i>	Fruit
Piassava	<i>Attalea funifera</i>	Leaf
Pineapple	<i>Ananus comosus</i>	Leaf
Phormium	<i>Phormium tenax</i>	Leaf
Roselle	<i>Hibiscus sabdariffa</i>	Stem
Ramie	<i>Boehmeria nivea</i>	Stem
Sansevieria (Bowstring hemp)	<i>Sansevieria</i>	Leaf
Sisal	<i>Agave sisilana</i>	Leaf
Sponge gourd	<i>Luffa cylindrica</i>	Fruit
Straw (Cereal)	–	Stalk
Sun hemp	<i>Crotalaria juncea</i>	Stem
Cadillo/urena	<i>Urena lobata</i>	Stem
Wood	(>10,000 species)	Stem

impairs the efficiency of the composite. This is a major disadvantage of natural fibre reinforced composites. Another problem is that the processing temperature of composites is restricted to 200 °C as vegetable fibres undergo degradation at higher temperatures; this restricts the choice of matrix material. Another setback is the high moisture absorption of natural fibres leading to swelling and presence of voids at the interface, which results in poor mechanical properties and reduces dimensional stability of composites. Another restriction to the successful exploitation of biofibres for durable composite application is low microbial resistance and susceptibility to rotting. These properties pose serious problems during shipping, storage and composite processing. The non-uniformity and variation of dimensions and of their mechanical properties (even between individual plants in the same cultivation) poses another serious problem.

It is quite clear that the advantages outweigh the disadvantages and most of the shortcomings have remedial measures in the form of chemical treatments. The lignocellulosic fibres have an advantage over synthetic ones since they buckle rather than break during processing and

fabrication. In addition, cellulose possesses a flattened oval cross section that enhances stress transfer by presenting an effectively higher aspect ratio.

Researchers (Kozłowski, Muzyczek, & Mieleniak, 2004) at the Institute of Natural Fibres, Poland have developed fire resistant upholstery using fire-retarded flax nonwoven (LinFR) FT. The non-woven used in the composites plays the role of fire barrier that reduces the vulnerability of filling material to the development and spread of fire. The softness of the upholstery system is also enhanced. In another interesting study, researchers (Zimniewska, Kozłowski, & Rawluk, 2004) investigated the influence of natural and synthetic fibres which covered the forearm muscles on the activity of motor units in these muscles. The electrophysiological parameters of motor units were measured with electromyographical methods. The results indicated that temporary covering of examined muscles in the forearm with the synthetic clothing changed the pattern of motor units activity of muscles. Clothing made of natural fibre did not evoke this kind of effect.

Recently, natural cellulose fibres having properties between cotton and linen and suitable for various industrial applications were extracted from cornhusks (Reddy & Yang, 2005a). High quality cellulosic fibres from cornhusks mean food, clothing and other major industrial products from the same source without the need for any additional natural resources. Using cornhusks for fibrous applications would save the land and other natural resources required to grow fibre crops and will conserve the non-renewable petroleum sources required to produce synthetic fibres. More than 9 million tons of natural cellulose fibres with a potential sale value of \$19 billion and with a value addition of at least \$12 billion could be produced from the cornhusks available every year. Utilizing cornhusks as a source for natural cellulose fibres will significantly benefit the agriculture, fibre, food and energy needs of the future and will also benefit the environment. The structure and composition of the natural cellulose fibres obtained from cornstalks were found to be different from that of the common bast fibres such as flax and kenaf. Cornstalk fibres were found to have relatively lower percentage of crystallinity but similar microfibrillar angle as that of the common bast fibres (Reddy & Yang, 2005a, 2005b). Another study reported on the production and characteristics of natural cellulose fibers obtained from the leaves and stems of switchgrass. The composition, structure and properties of fibers obtained from the leaves and stem of switchgrass were studied in comparison to the common natural cellulose cotton, linen and kenaf. The leaves and stems of switchgrass were found to have tensile properties intriguingly similar to that of linen and cotton, respectively. Fibers obtained from switchgrass leaves possessed crystallinity of 51%, breaking tenacity of 5.5 g per denier (715 MPa) and breaking elongation of 2.2% whereas the corresponding values for fibers obtained from switchgrass stems were 46%, 2.7 g per denier and 6.8%, respectively (Reddy & Yang, 2005a, 2005b). Shih (2007) studied

the fiber obtained from the water bamboo husks by CP/MAS C13 NMR, elemental analysis, and adiabatic calorimeter. The pyrolysis behavior of the fiber was also studied by TGA, TGA–GC–MS and Py–GC–MS. The fiber obtained from the water bamboo husks was found to be cellulose I.

2. Cellulosic fibre composites

The history of mankind has witnessed several surges in the field of research and development. The rampant use of petroleum products has created a twin dilemma; depletion of petroleum resources and entrapment of plastics in the food chain and environment. The increasing pollution caused by the use of plastics and emissions during incineration is affecting the food we eat, water we drink, air we breathe and threatening the greatest right of human beings, the right to live. The exhaustive use of petroleum based resources has initiated the efforts to develop biodegradable plastics. This is based on renewable biobased plant and agricultural products that can compete in the markets currently dominated by petroleum based products. The production of 100% biobased materials as substitute for petroleum based products is not an economical solution. A more viable solution would be to combine petroleum and biobased resources to develop a cost-effective product having immense applications. Biopolymers or synthetic polymers reinforced with natural or bio fibres (termed as biocomposites) are a viable alternative to glass fibre composites. Scientists are looking at the various possibilities of combining biofibres such as sisal, flax, hemp, jute, banana, wood and various grasses with polymer matrices from non-renewable and renewable resources to form composite materials to make the biocomposite revolution a reality (Mohanty, Drzal, & Misra, 2002).

Broadly defined, biocomposites are composite materials made from natural/bio fibre and petroleum derived non-biodegradable polymers (PP, PE) or biodegradable polymers (PLA, PHA). The latter category i.e. biocomposites derived from plant derived fibre (natural/biofibre) and crop/bio-derived plastic (biopolymer/bioplastic) are likely to be more eco-friendly and such composites are termed as green composites.

The best known renewable resources capable of making biodegradable plastics are starch and cellulose (Wilkinson, 2001). Starch is one of the least expensive biodegradable materials available in the world market today. It is a versatile polymer with immense potential for use in non-food industries. Cellulose from trees and cotton plants is a substitute for petroleum feedstocks to make cellulose plastics. Another aspect that has gained global attention is the development of biodegradable plastics from vegetable oils like soybean oil, peanut oil, walnut oil, sesame oil and sunflower oil. Green composites from soy protein based bioplastics and natural fibres show potential for rigid packing and housing and transportation applications (Tummala, Mohanty, Misra, & Drzal, 2003). Fish oil based

polymers have also attracted the attention of researchers due to their high degree of unsaturation. Fish oil based polymers also possess unique good damping and shape memory properties (Technology International Exchange, 1996).

The history of fibre reinforced plastics began in 1908 with cellulose fibre in phenolics, later extending to urea and melamine and reaching commodity status with glass fibre reinforced plastics. The fibre-reinforced composites market is now a multibillion-dollar business (Material Thoughts, 2002) (Fig. 2). Though hailed as a miraculous discovery long back, plastic products now enjoy an ambiguous reputation. Scientists at the BioComposites Centre at the University of Wales, Bangor are developing high-quality packaging of goods, using starch from corn and potatoes to tackle the problem of high cost waste disposal (Material Thoughts, 2005a, 2005b). Researchers (Material Thoughts, 2005a, 2005b) are also exploring the aspects of producing plastics from limonene which is extracted from citrus. After decades of obscurity, biofibre reinforced composites are being touted as the material of the millennium.

2.1. Classification of composites

2.1.1. Green composites

Research efforts are currently being harnessed in developing a new class of fully biodegradable ‘green’ composites by combining (natural/bio) fibres with biodegradable resins (Netravali & Chabba, 2003). The major attractions about green composites are that they are environmentally-friendly, fully degradable and sustainable, i.e. they are truly ‘green’ in every way. At the end of their life they can be easily disposed of or composted without harming the environment.

Fig. 3 shows a classification of biodegradable polymers in four families (Averous & Boquillon, 2004). Except the fourth family, which is of fossil origin, most polymers (family 1–3) are obtained from renewable resources (biomass). The first family is agro-polymers (e.g. polysaccharides) obtained from biomass by fractionation. The second and third families are polyesters, obtained, respectively by fermentation from biomass or from genetically modified plants (e.g. PHA, polyhydroxyalkanoate) and

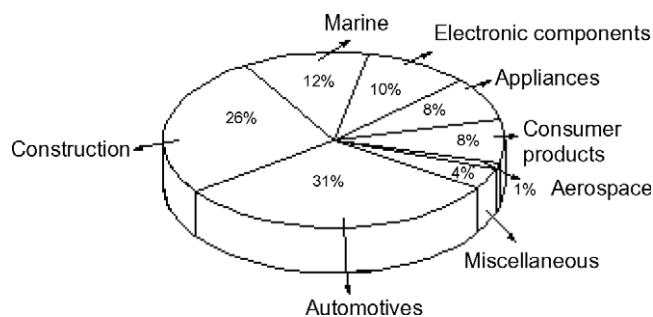


Fig. 2. Fibre reinforced plastic composites used in 2002.

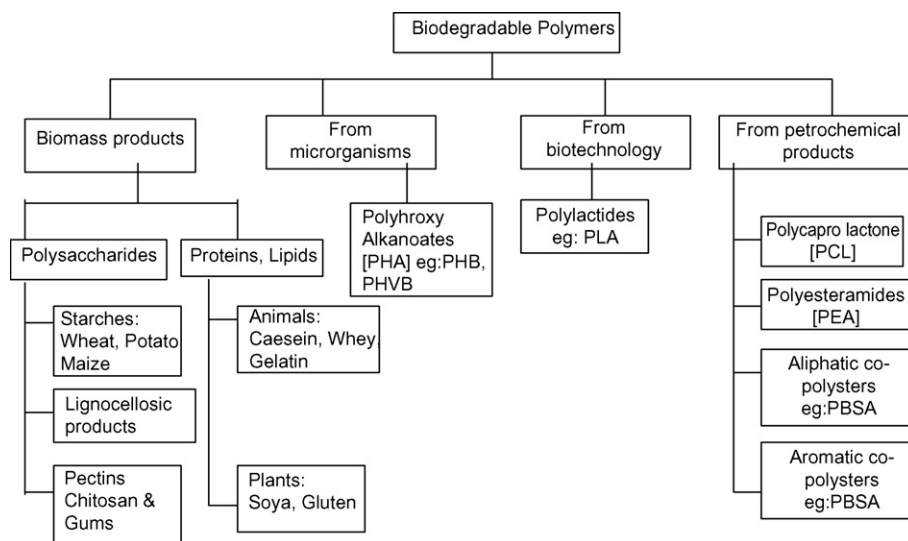


Fig. 3. Classification of biodegradable polymers.

by synthesis from monomers obtained from biomass (e.g. PLA, polylactic acid). The fourth family are polyesters, totally synthesized by the petrochemical process (e.g. PCL, polycaprolactone; PEA, polyesteramide; aliphatic or aromatic copolyesters). A large number of these biodegradable polymers (biopolymers) are commercially available. They show a large range of properties and they can compete with non-biodegradable polymers in different industrial fields (e.g. packaging).

Another important biocomposites category is based on agro-polymers matrixes, mainly focussed on starchy materials. Plasticized starch, the so-called 'thermoplastic starch' (TPS) is obtained after disruption and plasticization of native starch, with water and plasticizer (e.g. polyol) by applying thermomechanical energy in a continuous extrusion process. Unfortunately, TPS shows some drawbacks such as a strong hydrophilic character (water sensitive), rather poor mechanical properties compared to conventional polymers and an important post-processing variation of the properties. TPS properties reach equilibrium only after several weeks. To improve these material weaknesses, TPS is usually associated with other compounds.

The design and life cycle assessment of green composites have been exclusively dealt with by Baillie (2005). Green composites have been used effectively in many applications such as mass produced consumer products with short life cycles or products intended for one time or short time use before disposal. Green composites may also be used for indoor applications with a useful life of several years. The reinforcement of biofibres in green composites has been highlighted by Bismarck et al. (2005).

A number of natural and biodegradable matrices that are available for use in such green composites (Stevens, 2002) are listed in Table 2. The classification of green composites based upon the different types of biodegradable matrices is given below.

Table 2

Natural and biodegradable matrices

Biodegradable polymer matrices	
Natural	Synthetic
1. <i>Polysaccharides</i>	1. Poly(amides)
Starch	2. Poly(anhydrides)
Cellulose	3. Poly(amide-enamines)
Chitin	4. Poly(vinyl alcohol)
2. <i>Proteins</i>	5. Poly(vinyl acetate)
Collagen/gelatin	6. Polyesters
Casein, albumin, fibrogen, Silks	6.1 Poly(glycolic acid)
3. <i>Polyesters</i>	6.2 Poly(lactic acid)
Polyhydroxyalkanoates	6.3 Poly(caprolactone)
4. <i>Other polymers</i>	6.4 Poly(orthoesters)
Lignin	7. Poly(ethylene oxides)
Lipids	8. Poly(phosphazines)
Shellac	
Natural rubber	

2.1.1.1. Biofiber–plastic composites. Poly(a-hydroxy acid) such as poly(glycolic acid), PGA, or poly(lactic acid), PLA, are crystalline polymers with relatively high melting point. Recently PLA has been highlighted because of its availability from renewable resources like corn. PLA is a hydrophobic polymer because of the incorporation of the CH₃ side groups when compared to PGA. Poly(b-hydroxyalkanoate)s (PHAs), which are synthesized biochemically by microbial fermentation and which may be produced in the future by transgenic plants, represent natural polyesters. Bacteria came first and are still the only real source of these polyesters; it will still require some more years' research until transgenic plants will be available for production. Poly(b-hydroxybutyrate) (PHB) (commercial name Biopol) is a biotechnologically produced polyester that constitutes a carbon reserve in a wide variety of bacteria and has attracted much attention as a biodegradable thermoplastic polyester. It can be degraded to water and carbon dioxide under environmental conditions by a vari-

ety of bacteria and has much potential for applications of environmentally degradable plastics (Mohanty, Misra, & Hinrichsen, 2000).

In an interesting research Plackett, Andersen, Pederesen, and Nielsen (2003) used commercial L-poly(lactide) which was first converted to film and then used in combination with jute fibre mats to generate biodegradable composites by a film stacking technique. Degradation of the poly(lactide) during the process was investigated using size exclusion chromatography. The tensile properties of composites produced at temperatures in the 180–220 °C range were significantly higher than those of poly(lactide) alone. Examination of composite fracture surfaces using electron microscopy showed voids occurring between the jute fibre bundles and the poly(lactide) matrix in some cases. Size exclusion chromatography revealed that only minor changes in the molecular weight distribution of the poly(lactide) occurred during the process.

In an innovative study, novel biodegradable films were fabricated from chitosan and poly(lactic acid) by Sébastien, Stéphane, Copinet, and Coma (2006). It was found that composite films offered a great advantage in preventing the surface growth of mycotoxinogen strains because of their antifungal activity. However, the physico-chemical properties of such heterogeneous films, dramatically limit their further usage as packaging materials.

Lee and Wang (2006) investigated the effects of lysine-based diisocyanate (LDI) as a coupling agent on the properties of biocomposites from poly(lactic acid) (PLA), poly(butylene succinate) (PBS) and bamboo fiber (BF). They observed that the tensile properties, water resistance, and interfacial adhesion of both PLA/BF and PBS/BF composites were improved by the addition of LDI, but thermal flow (Ohkita & Lee, 2006) was hindered due to cross-linking between polymer matrix and BF. Enzymatic biodegradability of PLA/BF and PBS/BF composites was investigated by Proteinase K and Lipase PS, respectively. It was seen that the composites could be quickly decomposed by enzyme and the addition of LDI delayed the degradation. Fig. 4 shows the SEM micrographs of PLA or PBS/BF (70/30) composites with LDI degraded for different degradation time. It can be clearly seen that the matrix of both composites became reduced as enzymatic degradation proceeded.

Green composites composed of regenerated cellulose (lyocell) fabric and biodegradable polyesters [poly(3-hydroxybutyrate-co-3-hydroxyvalerate) (PHBV), poly(butylene succinate) (PBS), and poly(lactic acid) (PLA)] were prepared by Shibata, Oyamada, Kobayashi, and Yaginuma (2004) and properties studied. The tensile moduli and strength of all the biodegradable polyester/lyocell composites were found to increase with increasing fiber content. The biodegradation test revealed that the lyocell fabric in PLA/lyocell composite degraded, as shown in Fig. 5. Pure PLA film was found to be almost unchanged after 120 days.

The thermal stability of biodegradable composite films prepared from blends of poly(vinyl alcohol), cornstarch, and lignocellulosic fibre was investigated by Imam, Cinelli, Gordon, and Chiellini (2005). Thermogravimetric analysis (TGA) indicated the suitability of formulations for melt processing, and for application as mulch films in fields at much higher temperatures. The study also revealed that both starch and lignocellulosic fibre degraded much more rapidly than PVA. The addition of fibre to the formulations was found to enhance the PVA degradation. In another interesting study, the thermal behavior of green composites fabricated from bagasse fibre and poly(vinyl alcohol) was investigated by Fernandes, Cinelli, and Chiellini (2004). They observed an increase of thermal stability upon incorporation of bagasse fibre.

In another study biocomposites (Mehta, Mohanty, Misra, & Drzal, 2004) were fabricated using a non-woven fibre mat (90% hemp fibre with 10% thermoplastic polyester binder) as reinforcement, and unsaturated polyester (UPE) resin as well as blends of UPE and functionalized vegetable oils as the polymer matrix. All composites were made with 30% volume fraction of fibre, which was optimized earlier. The structure–property relationships of this system as well as the thermo-mechanical properties of these composites were measured. The notched Izod impact strength of biocomposites from bio-based resin blends of UPE and functionalized vegetable oil and industrial hemp fibre mat were enhanced by 90% as compared to that of the pure UPE-industrial hemp fibre mat composites. The tests also showed an improvement in the tensile properties of the composite as a result of the incorporation of the derivatized vegetable oil.

Researchers have also developed green composites from jute fabric and Biopol composites (Mohanty, Khan, Sahoo, & Hinrichsen, 2000). Chemical modification of the fabric was carried out to improve interfacial properties. A significant amount of research has been done at the German Aerospace Centre (DLR) in Braunschweig on biodegradable plastics and composites (Peijs, 2002). Starch and modified resins have also been used as matrix to form green composites (Goda, 2002).

Biodegradable composites were developed from poly(propylene carbonate) (PPC) reinforced with granular cornstarch by Ma, Yu, and Zhao (2006). The authors also investigated the effects of succinic anhydride (SA) on the morphology, thermal properties, as well as mechanical properties of the composites. The authors are of the opinion that SA enhances the properties of PPC/starch composites, which was ascribed to the improvement of the interaction between PPC and granular.

In another study (Ge, Xu, Meng, & Li, 2005) involving poly(propylene carbonate) (PPC), starch-g-poly(methyl acrylate) (S-g-PMA) copolymer was used to reinforce PPC. Starch-g-poly(methyl acrylate) (S-g-PMA) copolymer was prepared by ceric ammonium nitrate-initiated polymerization of methyl acrylate onto corn starch (CS). Tensile tests showed that the S-g-PMA incorporation

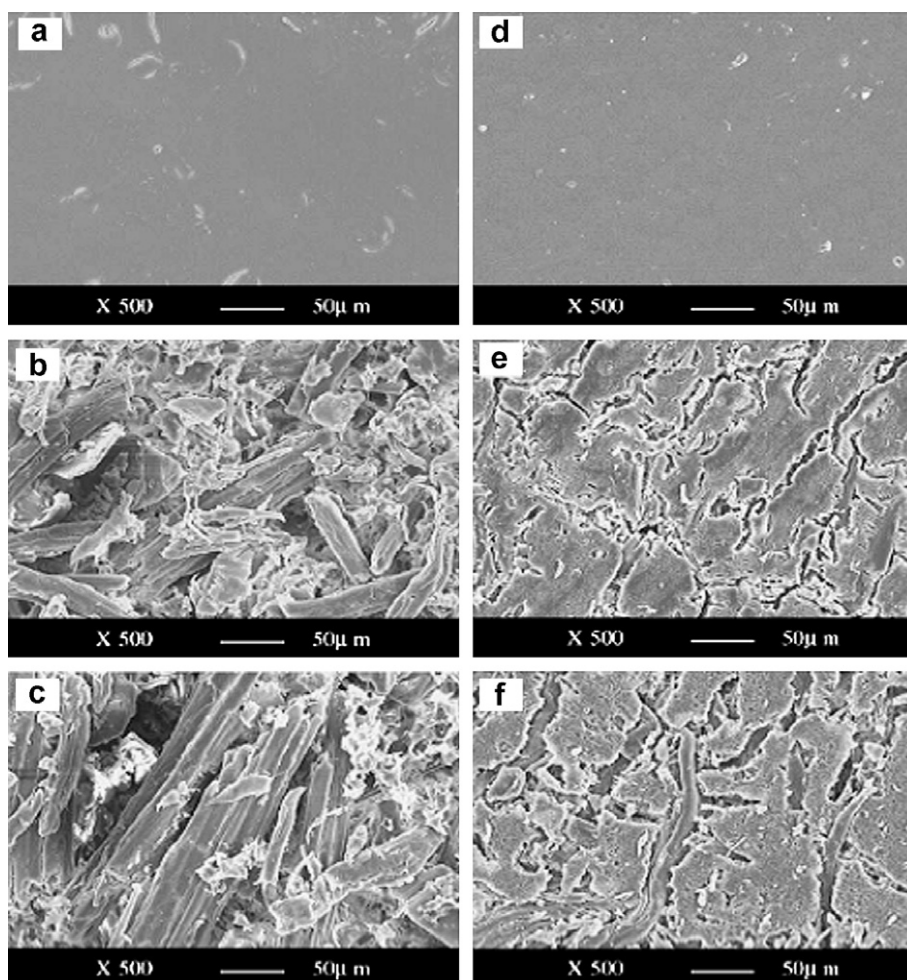


Fig. 4. SEM micrographs of PLA or PBS/BF composites with LDL (NCO content, 0.65%) after different enzymatic degradation time. (a) Control of PLA/BF composite, (b) after 7 days, (c) 9 days, (d) control of PBS/BF composite, (e) after 2 days, (f) 4 days.

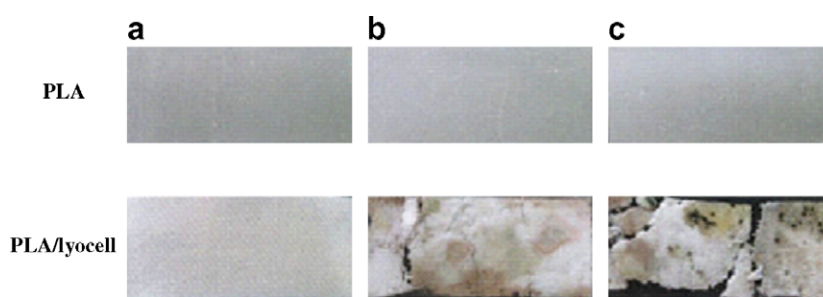


Fig. 5. Photographs of PLA (top) and PLA/lyocell composite (bottom) after the soil burial test: (a) before test, (b) at 60 days, and (c) at 120 days.

improved the stiffness and tensile strength of composites significantly. TG results indicated that the S-g-PMA addition led to an improvement in the thermal stability of resulting composites.

Bio-based polymer composite was from plant-derived kenaf fiber (KF) and biodegradable polyester, poly(L-lactide) (PLLA), by melt-mixing technique, by Pan et al. (2007). The effect of the KF weight contents (0, 10, 20, and 30 wt%) on crystallization behavior, composite morphology, mechanical, and dynamic mechanical properties

of PLLA/KF composites were investigated. It was found that the incorporation of KF significantly improves the crystallization rate and tensile and storage modulus. The crystallization of PLLA can be completed during the cooling process from the melt at 5 °C/min with the addition of 10 wt% KF. It was also observed that the nucleation density increases dramatically and the spherulite size drops greatly in the isothermal crystallization with the presence of KF. In addition, with the incorporation of 30 wt% KF, the half times of isothermal crystallization at 120

and 140 °C were reduced to 46.5% and 28.1% of the pure PLLA, respectively. Moreover, the tensile and storage modulus of the composite are improved by 30% and 28%, respectively, by the reinforcement with 30% KF. Scanning electron microscopy observation also showed that the crystallization rate and mechanical properties could be further improved by optimizing the interfacial interaction and compatibility between the KF and PLLA matrix.

The morphology, mechanical and thermal properties of composites of poly(L-lactide) with hemp fibers was investigated by Masirek, Kulinski, Chionna, Piorkowska, and Pracella (2007). The thermogravimetric analysis of the composites, carried out in both nitrogen and air, showed that the degradation process of fiber-filled systems started earlier than that of plain PLA, independently of the presence of the plasticizer. Mechanical tests showed that the modulus of elasticity of the composites markedly increased with the hemp content, reaching 5.2 GPa in the case of crystallized PLA reinforced with 20 wt% hemp, whereas the elongation and stress at break decreased with an increasing amount of fiber for all examined systems.

2.1.1.2. Biofiber–soy based composites. In US, soybeans provide over 60% of the fats and oils used for food and the majority of the feed protein. Soybeans typically contain about 20% oil and 40% protein. Protein levels as high as 55% have been observed in soybeans. Soybeans consist of discrete groups of proteins (polypeptides) that span a broad range of molecular sizes and are comprised of approximately 38% of non-polar, non-reactive amino acid residues, while 58% are polar and reactive. Modifications that take advantage of water solubility and reactivity are exploited in improving soy protein for use in plastics and other biomaterials (Thames, 1994). Soy protein plastics of different compositions have been prepared by injection moulding (Jane, 1996). Compression moulding is also used for soy plastic processing. Dried soy plastics display an extremely high modulus, 50% higher than that of currently used epoxy engineering plastics (Wang, Sue, & Jane, 1994). So with proper moisture-barrier, soy protein is a potential starting material for engineering plastics.

Researchers recently investigated the effect of stearic acid on tensile and thermal properties of ramie fibre reinforced soy protein isolate (SPI) resin green composites (Lodha & Netravali, 2005). It was observed that part of the stearic acid crystallized in SPI resin and that the crystallizability was affected by the addition of glycerol as a plasticizer. The fabricated green composite was found to have enormous potential for certain indoor applications.

The interfacial adhesion in the composites was apparent from SEM photomicrographs of the fracture tensile surfaces of the ramie/SPI and ramie/modified soy protein isolate (MSPI) composites tested in the axial direction is shown in Fig. 6a and b, respectively. Some of the fibres at the fracture surface do not show any resin, whereas a few other fibres clearly show resin sticking on the surface.

The presence of resin on some fibre surfaces for the SPI and MSPI resins clearly indicates good interfacial interaction between the fibre and the resins.

In an interesting study, researchers (Chabba, Mathews, & Netravali, 2005) modified soy flour (SF) by cross-linking it with glutaraldehyde (GA). The cross-linked soy flour (CSF) polymer was characterized for its tensile and thermal properties. The effect of glycerol on the mechanical properties of the soy flour was also characterized and optimized. CSF polymer showed improved tensile properties and thermal stability, compared to unmodified SF resin, for use as a resin to fabricate composites. Unidirectional green composites using flax yarn and CSF resin were fabricated and characterized for their tensile and flexural properties. The composite specimens exhibited fracture stress and Young's modulus of 259.5 MPa and 3.71 GPa, respectively, and flexural strength of 174 MPa, in the longitudinal direction.

Recently green composites were fabricated using pineapple leaf fibre and soy based plastic (Liu, Misra, Askeland, Drzal, & Mohanty, 2005). The addition of compatibilizer (polyester amide grafted glycidyl methacrylate (PEA-g-GMA)) was seen to increase the mechanical properties of composites. In another interesting study involving biocomposites, the effect of alkali treatment on the thermal properties of Indian grass fibre reinforced soy protein green composites was studied by the same group (Liu, Mohanty, Askeland, Drzal, & Misra, 2004).

The characterization of Phytigel[®] modified soy protein isolate (SPI) resin and unidirectional flax yarn reinforced green composites was undertaken by Lodha and Netravali (2005). The incorporation of Phytigel[®] in SPI resin led to an overall 10-fold increase in the tensile fracture stress and a 9-fold increase in the Young's moduli of the SPI resin along with a 7-fold decrease in fracture strain. The dynamic mechanical properties such as storage and loss modulus of the modified resin increased and the glass transition temperature also increased by about 56 °C.

2.1.1.3. Biofiber–natural rubber composites. The primary effects of bio-fibre reinforcement on the mechanical properties of natural rubber composites include increased modulus, increased strength with good bonding at high fibre concentrations, decreased elongation at failure, greatly improved creep resistance over particulate-filled rubber, increased hardness and a substantial improvement in cut, tear and puncture resistance. Biodegradation of vulcanized rubber material is possible, although it is difficult due to the interlinkages of the poly(*cis*-1,4-isoprene) chains, which result in reduced water absorption and gas permeability of the material (Seal & Morton, 1996). Certain *Streptomyces* strains were seen to degrade rubber samples after 12 months of incubation.

The reinforcement of coir fibre in natural rubber has been extensively studied (Geethamma, Joseph, & Thomas, 1995). Researchers have also investigated the reinforcement effects of a leaf fibre – sisal fibre – in natural rubber (Varghese, Kuriakose, Thomas, & Koshy, 1994).

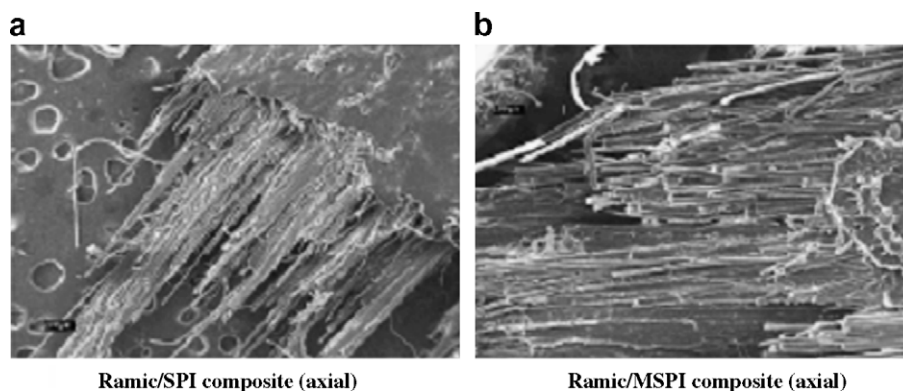


Fig. 6. (a, b) SEM photomicrographs of the fracture tensile surfaces of untreated and treated composites.

Attempts to incorporate oil palm fibre in rubber matrix have also been successful. The effect of fibre concentration on the mechanical properties of oil palm reinforced natural rubber composites was investigated by Ismail, Rosnah, and Ishiaku (1997). They observed the general trend of reduction in tensile and tear strength with increasing fibre concentration.

An interesting report on the reinforcement effect of grass fibre – bagasse – in natural rubber was presented by Nasar, Ashour, and Washid (1996). Aging experiments revealed tensile strength retention of 97%. Scientists have also developed composites comprising of kenaf fibre and natural rubber (El Sabbagh et al., 2000). An increase in rheometric and mechanical properties was observed. Pineapple (Bhattacharya, Biswas, Chatterjee, & Pramanick, 1986) and jute fibre (Arumugam, Tamareselvy, Venkata Rao, & Rajalingam, 1989) have also found their way as a potential reinforcement in natural rubber.

In an interesting study, researchers have used a novel fibre – isora fibre – in natural rubber (Mathew, Joseph, & Joseph, 2004). Isora fibres are present in the bark of the *Helicteres isora* plant and are separated by retting process. Isora fibre resembles jute in appearance but surpasses it in strength, durability and lustre. The effects of different chemical treatments, including mercerisation, acetylation, benzoylation and treatment with toluene diisocyanate and silane coupling agents, on isora fibre properties and mechanical properties were analyzed. Isora fibre was seen to have immense potential as reinforcement in natural rubber. The variation of tensile strength with chemical modification is given in Fig. 7.

Researchers have also designed novel rubber biocomposites by using a combination of leaf and fruit fibre in natural rubber (Haseena & Unnikrishnan, 2005). The incorporation of sisal and coir fibre in NR was seen to increase the dielectric constant of the composites. These hybrid biocomposites were found to have enormous applications as antistatic agents. In another interesting study, the preparation of composites comprising of waste paper in natural rubber along with boron carbide and paraffin wax, for radiation shielding applications, was investigated (Madani, Basta, Abdo, & El-Saied, 2004).

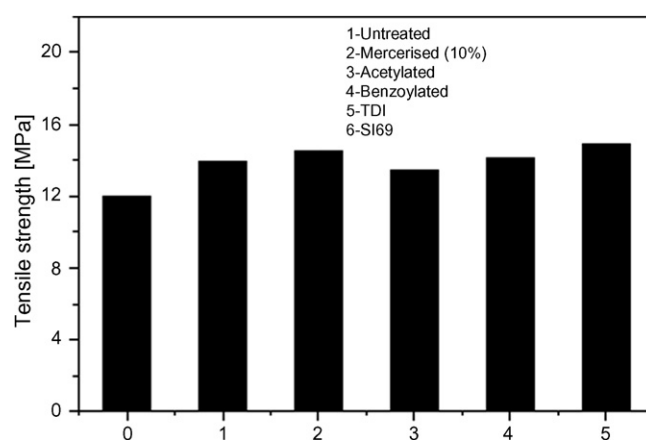


Fig. 7. Variation of tensile strength with chemical modification.

In an innovative study, a unique combination of sisal and oil palm fibres in natural rubber has been utilized to design hybrid biocomposites. It was seen that the incorporation of fibers resulted in increased modulus (Jacob, Varughese, & Thomas, 2004a, 2004b). Chemical modification of both sisal and oil palm fibres was imperative for increased interfacial adhesion and resulted in enhanced properties (Jacob et al., 2004a, 2004b). The viscoelastic (Jacob, Francis, Varughese, & Thomas, 2006), water sorption (Jacob, Varughese, & Thomas, 2005), dielectric (Jacob, Varughese, & Thomas, 2006a, 2006b) and stress relaxation (Jacob et al., 2006a, Jacob, Varughese, & Thomas, 2006b) characteristics were also studied.

A major hurdle to the commercialization of green composites is the high cost of biodegradable matrices. Most of the biodegradable resins cost significantly more than the commonly used resins. Inexpensive production of oils for resins through biotechnology would certainly be of help in expediting their commercialization. The manufacturing costs can also be reduced by faster, better and more efficient processing.

Efforts are on the anvil for the development of “advanced green composites” made out of high strength protein fibres (spider silk) and biodegradable matrices. Biotechnology is being used to increase the yield of specific tri-

glycerides and oils in beans for producing resins. These resins will be inexpensive compared to those available today and if suitably modified, could be biodegradable. Research is also being conducted to develop new pathways to synthesize inexpensive biodegradable resins (Allen, Moore, Lobkovsky, & Coates, 2002) with better mechanical properties and thermal stability using nanotechnology (Maiti & Giannelis, 2002).

2.1.2. Hybrid composites

The incorporation of several different types of fibres into a single matrix has led to the development of hybrid biocomposites. The behavior of hybrid composites is a weighed sum of the individual components in which there is a more favorable balance between the inherent advantages and disadvantages. Also, using a hybrid composite that contains two or more types of fibre, the advantages of one type of fibre could complement with what are lacking in the other. As a consequence, a balance in cost and performance could be achieved through proper material design (Thwe & Liao, 2003). The properties of a hybrid composite mainly depend upon the fibre content, length of individual fibres, orientation, extent of intermingling of fibres, fibre to matrix bonding and arrangement of both the fibres. The strength of the hybrid composite is also dependent on the failure strain of individual fibres. Maximum hybrid results are obtained when the fibres are highly strain compatible (Sreekala, George, Kumaran, & Thomas, 2002).

The properties of the hybrid system consisting of two components can be predicted by the rule of mixtures.

$$P_H = P_1 V_1 + P_2 V_2, \quad (1.1.1)$$

where P_H is the property to be investigated, P_1 the corresponding property of the first system and P_2 the corresponding property of the second system. V_1 and V_2 are the relative hybrid volume fractions of the first and second system and

$$V_1 + V_2 = 1. \quad (1.1.2)$$

A positive or negative hybrid effect is defined as a positive or negative deviation of a certain mechanical property from the rule of hybrid mixture.

The term hybrid effect has been used to describe the phenomenon of an apparent synergistic improvement in the properties of a composite containing two or more types of fibre. The selection of the components that make up the hybrid composite is determined by the purpose of hybridization, requirements imposed on the material or the construction being designed. The problem of selecting the type of compatible fibres and the level of their properties is of prime importance when designing and producing hybrid composites. The successful use of hybrid composites is determined by the chemical, mechanical and physical stability of the fibre/matrix system.

Hybrid biocomposites can be designed by the combination of a synthetic fibre and natural fibre (biofibre) in a matrix and a combination of two natural fibre/biofibre in

a matrix. Hybridization with glass fibre provides a method to improve the mechanical properties of natural fibre composites and its effect in different modes of stress depends on the design and construction of the composites. The effect of hybridization of glass fibre in thermoset biocomposites has been discussed in detail (Ray & Rout, 2005).

The tensile and impact behavior of oil palm fibre-glass fibre-reinforced epoxy resin was investigated by Bakar, Hariharan, and Abdul Khalil (2005). The hybridization of oil palm fibres with glass fibres increased the tensile strength, Young's modulus, and elongation at break of the hybrid composites. A negative hybrid effect was observed for the tensile strength and Young's modulus while a positive hybrid effect was observed for the elongation at break of the hybrid composites. The impact strength of the hybrid composites increased with the addition of glass fibres.

Cellular biocomposite cores fabricated from industrial hemp or flax fibres with unsaturated polyester were hybridized with woven jute, chopped glass, and unidirectional carbon fabrics (Burgueño et al., 2005). Material characterization showed improved stiffness, strength, and moisture-absorption stability, while flexural tests on laboratory-scale plates demonstrated enhanced structural behavior. These hybrid cellular biofibre-based composites were found to provide an economic and environmentally friendlier alternative to entry-level synthetic composites.

Hybridization also has a profound effect on the water absorption property of composites. An attempt to study the moisture uptake characteristics of hybrid systems was performed by Mishra et al. (2003). The composite systems chosen were sisal/glass and pineapple/glass fibre reinforced polyester composites. Composites were prepared by varying the concentration of glass fibre and by subjecting the bio-fibres to different chemical treatments. The authors observed that water uptake of hybrid composites were less than that of unhybridized composites.

A comparative study of the water absorption of the glass fibre (7 wt%)/natural biofibre (13 wt%) with that of non-hybrid composites is given in Table 3 where a lowering in water absorption is evident (Rout, Mishra, Tripathy, Nayak, & Mohanty, 2001).

The novel development of a photofabrication process of biofibre composites, based on oil palm empty fruit bunch fibres was recently reported (Kumar, Hee, & Rozman,

Table 3
Comparative study of the water absorption of the glass fibre/natural biofibre with that of non-hybrid composites

Sample	Water absorption (%)	
	Nonhybrid (coir–polyester composite) (20 wt%)	Hybrid [coir/glass–polyester composite]
Untreated	8.53	5.186
Alkali- treated (5%)	4.994	3.147
PMMA grafted (5%)	3.98	2.663
PAN grafted (10%)	4.119	2.997
Cyanoethylated	3.6	3.138
Bleached	5.8	3.718

2005). The process consisted of the following steps: (1) the preparation of nonwoven mat of biofibre, either alone or in combination with glass and nylon; (2) drying the mat; (3) preparation of photocurable resin matrix, consisting of vinyl ester and photoinitiator; (4) impregnation of the mat by photocurable resin; and (5) irradiation of the impregnated mat by UV radiation to effect the cure of the composite. Oil palm fibre, glass, and nylon fibres were mixed in different proportions. A “mixture experimental design” was used to generate experimental compositions of the reinforcing fibres and to model dependency of the response variables on the components through mathematical relationships.

The flexural behaviour of hybrid laminated composites (LC) with a hemp fibre/polypropylene core and two glass fibres/polypropylene surface layers at each side of the specimen were investigated by Reis, Ferreira, Antunes, and Costa (2007). When compared with full glass fibres reinforced polypropylene laminates, the hybrid composites were found to have economical, ecological and recycling advantages and also specific fatigue strength benefits. Static and fatigue tests were performed in three point bending for both laminates to evaluate flexural strength properties and fatigue behaviour. The major findings were that laminated composites (LC) exhibited an ultimate strength about 4% higher than the hybrid laminated composites (HLC) associated to changes in failure mechanisms, while the stiffness' modulus was also about 3.8% higher. Fatigue strength of hybrid laminated composites was also about 20% lower than the laminated composites as consequence of the change of the failure mechanisms and of the different static strengths.

Scientists (Morye & Wool, 2005) at the Affordable Composites from Renewable Resources (ACRES) program at the University of Delaware investigated the mechanical properties of glass/flax hybrid composites based on a novel modified soybean oil matrix material. Composites with different glass/flax ratios and different fibre arrangements were made using a modified soybean oil matrix material. The fibre arrangement was varied to make symmetric and unsymmetric composites. The latter were tested in different modes in flexural tests and drop weight impact tests. The mechanical properties of the composites were found to depend upon the glass/flax ratio and the arrangement of fibres in the composite. On proper selection of the arrangement of fibres in the composite, the glass fibres and flax fibres were found to act synergistically resulting in an improved flexural and impact performance.

The mechanical, water absorption, and thermal properties of injection-molded short hemp fiber/glass fiber-reinforced polypropylene hybrid composites was investigated by Panthapulakkal and Sain (2007). The authors observed that hybridization with glass fiber enhanced the performance properties. A value of 101 MPa for flexural strength and 5.5 GPa for the flexural modulus is achieved from hybrid composite containing 25 wt% of hemp and 15 wt% of glass. Notched Izod impact strength of the hybrid composites exhibited great enhancement (34%) compared to

unhybridized samples. Thermal properties and resistance to water absorption properties of the hemp fiber composites were improved by hybridization with glass fibers.

The ballistic properties of flax, hemp, and jute fabric-steel hybrid polypropylene composites processed by hot compression moulding were investigated by Wambua, Vangrimde, Lomov, and Verpoest (2007). The composites' ballistic limit (V_{50}) was determined by subjecting the material to ballistic impact loading by fragment simulating projectiles (FSPs) using a block manometric cannon interchangeable (BMCI) gun. Flax composites exhibited better energy absorption than hemp and jute composites. The composites failed by shear cut-out, delamination and fibre fracture. It was found that the ballistic properties of the hemp composites increased significantly when a mild steel plate was used as facing and backing.

The mechanical and thermal properties of hybrid bio-composites from oil palm empty fruit bunch (EFB) fibers and kaolinite in polyurethane was studied by Amin and Badri (2007). The occurrence of chemical interactions between the hydroxyl terminals in both fillers and the PU system was determined via FTIR spectroscopy. Hybrid bio-composites showed improved stiffness, strength, and better water resistance with the addition of kaolinite to an extent. At 15% of kaolinite loading, maximum flexural and impact strengths were observed. The interaction between kaolinite with PU matrix and EFB fibers enhanced the mechanical properties of the bio-composites.

The effect of the various layering patterns on the water absorption of the banana-glass hybrid composites was studied by Pothan, Cherian, Anandakutty, and Thomas (2007). It was found that water diffusion occurs in the composite depending on the layering pattern as well as the temperature. In all the experiments, it was found that composites with an intimate mixture of glass and banana show the maximum water uptake except for temperature of 90 °C. At 90 °C the maximum water uptake is found to be for composites where there is one layer of banana and another layer of glass. The water uptake follows the same trend as that in all other temperatures till a time span of 4900 min is reached. The kinetics of diffusion was found to be Fickian in nature.

Another innovative approach to hybrid composites is the incorporation of two natural fibres/biofibre in a matrix system. Recently, the mechanical performance of short randomly oriented banana and sisal hybrid fibre reinforced polyester composites was investigated with reference to the relative volume fraction of the two fibres at a constant total fibre loading of 0.40 volume fraction (V_f), keeping banana as the skin material and sisal as the core material. A positive hybrid effect was observed in the flexural strength (Fig. 8) and flexural modulus of the hybrid composites. The tensile strength of the composites showed a positive hybrid effect when the relative volume fraction of the two fibres was varied, and maximum tensile strength was found to be in the hybrid composite having a ratio of banana and sisal 4:1 (Idicula, Neelakantan, Oommen, Joseph, & Thomas, 2005).

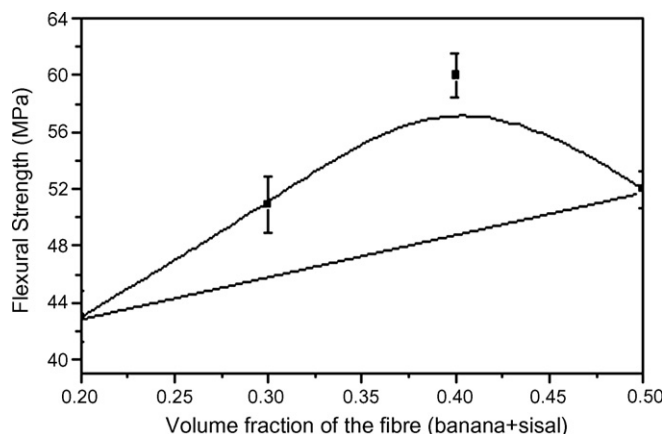


Fig. 8. Variation of flexural strength with volume fraction of fibre.

As a continuation to the above study the dynamic and static mechanical properties of randomly oriented intimately mixed banana and sisal hybrid fibre reinforced polyester composites were reported. Maximum stress transfer between the fibre and matrix was obtained in composites having volume ratio of banana and sisal as 3:1. The storage modulus was found to increase with fibre volume fraction above the glass transition temperature of the composites (Idicula, Malhotra, Joseph, & Thomas, 2005).

Idicula et al. (2006) investigated the thermophysical properties of banana-sisal hybrid reinforced composites as a function of chemical modification. Sisal and banana fibers were subjected to mercerization and polystyrene maleic anhydride treatments. The authors observed that chemical modification resulted in an increase of 43% in thermal conductivity when compared to untreated composites.

The tensile properties of wood flour/kenaf fiber polypropylene hybrid composites were investigated by Mirbagheri, Tajvidi, Hermanson, and Ghasemi (2007). The hybrid effect on the elastic modulus of the composites was also investigated using the rule of hybrid mixtures and Halpin–Tsai equations. The relationship between experimental and predicted values was evaluated and accuracy estimation of the models was performed. The results indicated that while nonhybrid composites of kenaf fiber and wood flour exhibited the highest and lowest modulus values respectively, the moduli of hybrid composites were closely related to the fiber to particle ratio of the reinforcements. Rule of hybrid mixtures equation was able to predict the elastic modulus of the composites better than Halpin–Tsai equation.

Researchers have also explored the incorporation of a fruit and leaf fibre in natural rubber (Haseena, Dasan, Namitha, Unnikrishnan, & Thomas, 2005). The addition of sisal and coir fibres offered good reinforcement and resulted in improvement of properties.

2.1.3. Textile composites

The development of textile technologies such as weaving, knitting and braiding has resulted in the formation of com-

posites that have superior mechanical properties, as continuous orientation of fibres is not restricted at any point.


In applications where more than one fibre orientation is required, a fabric combining 0° and 90° fibre orientations is useful. Woven fabrics are produced by the interlacing of warp (0°) fibres and weft (90°) fibres in a regular pattern or weave style. The fabric's integrity is maintained by the mechanical interlocking of the fibres. Drape (the ability of a fabric to conform to a complex surface), surface smoothness and stability of a fabric are controlled primarily by the weave style.

2.1.4. Common weave architectures

The following is a description of some of the more commonly found weave styles:


Plain

Each warp fibre passes alternately under and over each weft fibre. The fabric is symmetrical, with good stability and reasonable porosity. However, it is the most difficult of the weaves to drape, and the high level of fibre crimp imparts relatively low mechanical properties compared with the other weave styles. With large fibres (high tex) this weave style gives excessive crimp and therefore it is not generally used for very heavy fabrics.

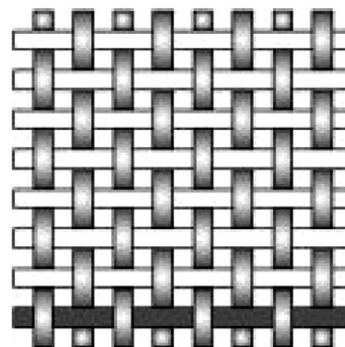


Twill

One or more warp fibres alternately weave over and under two or more weft fibres in a regular repeated manner. This produces the visual effect of a straight or broken diagonal 'rib' to the fabric. Superior wet out and drape is seen in the twill weave over the plain weave with only a small reduction in stability. With reduced crimp, the fabric also has a smoother surface and slightly higher mechanical properties.

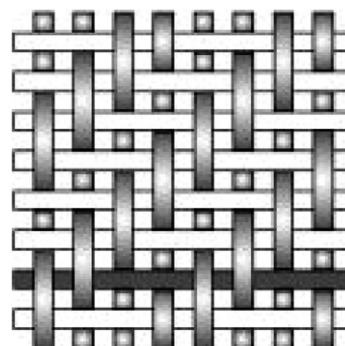


Satin

Satin weaves are fundamentally twill weaves modified to produce fewer intersections of warp and weft. The ‘harness’ number used in the designation (typically 4, 5, and 8) is the total number of fibres crossed and passed under, before the fibre repeats the pattern. A ‘crowsfoot’ weave is a form of satin weave with a different stagger in the repeat pattern. Satin weaves are very flat, have good wet out and a high degree of drape. The low crimp gives good mechanical properties. Satin weaves allow fibres to be woven in the closest proximity and can produce fabrics with a close ‘tight’ weave. However, the style’s low stability and asymmetry needs to be considered. The asymmetry causes one face of the fabric to have fibre running predominantly in the warp direction while the other face has fibres running predominantly in the weft direction.

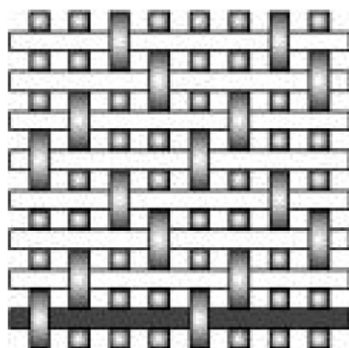

Basket


Basket weave is fundamentally the same as plain weave except that two or more warp fibres alternately interlace with two or more weft fibres. An arrangement of two warps crossing two wefts is designated 2×2 basket, but the arrangement of fibre need not be symmetrical. Therefore it is possible to have 8×2, 5×4, etc. Basket weave is flatter, and, though less crimp, stronger than a plain weave, but less stable. It must be used on heavy weight fabrics made with thick (high tex) fibres to avoid excessive crimping.

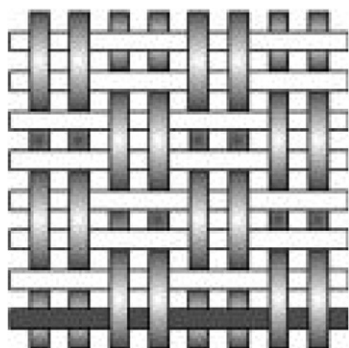

Leno


Leno weave improves the stability in ‘open’ fabrics which have a low fibre count. A form of plain weave in

which adjacent warp fibres are twisted around consecutive weft fibres to form a spiral pair, effectively ‘locking’ each weft in place. Fabrics in leno weave are normally used in conjunction with other weave styles because if used alone their openness could not produce an effective composite component.

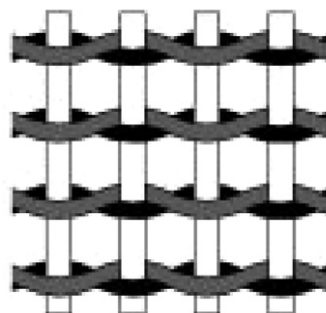

Mock leno

A version of plain weave in which occasional warp fibres, at regular intervals but usually several fibres apart, deviate from the alternate under-over interlacing and instead interlace every two or more fibres. This happens with similar frequency in the weft direction, and the overall effect is a fabric with increased thickness, rougher surface, and additional porosity.

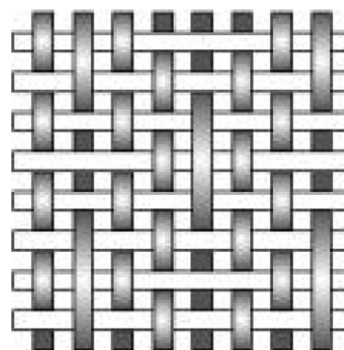

Researchers have looked into tensile strength of ramie-cotton hybrid fibre reinforced polyester composites (Junior, Carvalho, Fonseca, Monteiro, & Almeida, 2004). They observed that tensile behaviour was dominated by volume fraction of ramie fibres aligned in the test direction. The fabric and diameter of the thread did not play any role in tensile characteristics. Cotton fabric was found to have minor reinforcement effect due to weak cotton/polyester interface. Similar studies were performed by Mwaikambo and Bisanda (1999) on kapok-cotton fibre reinforced polyester composites.

Pothen, Thomas, Li, and Mai (2002) conducted tensile and impact studies of woven sisal fabric reinforced polyester composites prepared by RTM technique. It was found that the weave architecture was a crucial factor in deter-

mining the response of the composites. Researchers have studied the micromechanics of moisture diffusion in woven composites (Tang, Whitcomb, Li, & Sue, 2005). The weave pattern of the fabric was found to have a profound effect on the water uptake of the composites. They observed that woven composites exhibited quicker diffusion than that of a unidirectional laminate with the same overall fibre volume fraction. The plain weave with a lenticular tow and large waviness was seen to exhibit the quickest diffusion process.

The mechanical performance of isothalic polyester-based untreated woven jute-fabric composites was investigated by Ahmed and Vijayarangan (2007). It was found that the tensile strength and tensile modulus of jute-fabric composite are 83.96% and 118.97% greater than the tensile strength and modulus of unreinforced resin, respectively.

Novolac type phenolic composites reinforced with jute/cotton hybrid woven fabrics were fabricated and its properties were investigated as a function of fibre orientation and roving/fabric characteristics (De Medeiros, Agnelli, De Carvalho, & Mattoso, 2004). Results showed that the composite properties were strongly influenced by test direction and rovings/fabric characteristics. The anisotropy degree was shown to increase with test angle and to strongly depend on the type of architecture of fabric used, i.e. jute rovings diameter, relative fibre content, etc. The best overall mechanical properties were obtained for the composites tested along the jute rovings direction. Composites tested at 45° and 90° with respect to the jute roving direction exhibited a controlled brittle failure combined with a successive fibre pullout, while those tested in the longitudinal direction (0°) exhibited a catastrophic failure mode. The researchers are of the opinion that jute fibre promotes a higher reinforcing effect and cotton fibre avoids catastrophic failure. Therefore, this combination of natural fibres is suitable to produce composites for lightweight structural applications.

The thermal diffusivity, thermal conductivity and specific heat of jute/cotton, sisal/cotton and ramie/cotton hybrid fabric-reinforced unsaturated polyester composites were investigated by Alsina, Carvalho, Filho, and Almeida (2005). These properties were measured both parallel and perpendicular to the plane of the fabrics. The results obtained show that higher values were obtained parallel to the plane of the fibres. Sisal/cotton composites showed a particular behavior, with thermal properties very close to those of the resin matrix. The thermal properties of the fabrics, i.e. without any resin, were also evaluated and were used to predict the properties of the composites from the theoretical series and parallel model equations. The effect of fabric pre-drying on the thermal properties of the composites was also evaluated. The results showed that the drying procedure used did not bring any relevant change in the properties evaluated.

Textile biocomposites comprising of woven sisal fabric and natural rubber were fabricated by Jacob et al.

(2006a, 2006b). The mechanical properties of the textile composites were found to decrease after chemical modification which was contrary to the behaviour in short fiber composites. The solvent sorption (Jacob et al., 2006a, 2006b) characteristics of the composites were also investigated.

2.1.5. Applications of biocomposites

The use of biofibre reinforced composites has extended to almost all fields. Recently three-layer particleboards were produced from a mixture of sunflower stalks and poplar wood at certain ratios utilizing urea-formaldehyde (UF) adhesives. Panels with a density of 0.7 g/cm³ were manufactured with the ratios of 25, 50, and 75 percent particles from sunflower stalks or poplar. Panels were subjected to various tests for physical properties. Results show that all the panels provide properties required by the normal standards for general purpose-use particleboards (Bektas, Guler, Kalaycioglu, Mengeloglu, & Nacar, 2005).

Bio-based composite roof structures were successfully fabricated from soy oil-based resin and cellulose fibres in the form of paper sheets made from recycled cardboard boxes. This recycled paper was previously tested in composite sheets and structural unit beams and was found to give the required stiffness and strength required for roof construction (Dweib, Hu, Shenton, & Wool, 2006).

In a study encompassing many applications, the flame retardancy of biodegradable polymers and biocomposites was investigated (Matkó et al., 2005). For the comparison, flame retarded lignocellulosic filler reinforced biocomposites were prepared using polypropylene (PP), polyurethane (PUR) and fully biodegradable starch matrices. The compatibility of wood flake with PP was improved by application of an alkoxy silane based reactive surfactant. The silylation improved not only the compatibility but also the thermal stability of the wood flake according to TG measurements. Raman spectroscopic analysis of the silylated product showed that the improved thermal stability is the result of reduced ratio of the amorphous phase of cellulose. The phosphorus additives in flame retarded PUR biocomposites, comprising waste bio fillers and recycled polyol, proved to be very effective because both the matrix and the filler components participate in mechanism of flame retardancy.

Researchers (Hong & Wool, 2004) developed a new low dielectric constant material suited to electronic materials applications using hollow keratin fibres and chemically modified soybean oil. The unusual low value of dielectric constant was due to the air present in the hollow microcrystalline keratin fibres and the triglyceride molecules. The authors are of the opinion that the low cost composite made from avian sources and plant oil has the potential to replace the dielectrics in microchips and circuit boards in the ever growing electronics materials field. In an extension of the above study the authors have

also observed that the coefficient of thermal expansion (CTE) of the composite was low enough for electronic applications and similar to the value of silicon materials or polyimides used in printed circuit boards (Hong & Wool, 2005).

Plastic/wood fibre composites are being used in a large number of applications in decks, docks, window frames and molded panel components (Li & Matuana, 2003). It has been reported that 460 million pounds of plastic/wood fibre composites were produced in 1999. Statistics show that the production of these composites in 2001 has increased to 700 million pounds. Over the last three decades considerable research has been committed to finding an alternative fibre to replace asbestos in fibre cement products. Australian research was centred on natural fibres and ultimately it was a natural fibre, wood pulp fibre, which was responsible for the greatest replacement of asbestos in the beleaguered global fibre cement industry (Coutts, 2005). As these fibres are cheap and readily available the energy required for the processing of these composites is low; also the incorporation of random vegetable fibres in cement matrices requires only a small number of trained personnel in the construction industry. Recently, researchers (Ghavami, 2005) have explored the use of bamboo fibre as reinforcement in structural concrete elements. Pulp from eucalyptus waste and residual sisal and coir fibres have also been studied as a replacement for asbestos in roofing components (Agopyan, Savastano, John, & Cincotto, 2005). The use of cactus pulp as a stabilising agent to improve the behaviour of the sisal fibre reinforced soil has been studied (Mattone, 2005). Chopped barley straw has also been used as a suitable reinforcement for composite soil (Bouhicha, Aouissi, & Kenai, 2005).

Biocomposites also offer immense opportunities for an increasing role as alternate material, especially as wood substitutes in the furniture market. Yet biofibre as construction material for buildings were known long before. For centuries, mixtures of straw and loam, dried in the sun, were employed as construction composite in Egypt. Pipes, pultruded profiles and panels with polyester matrices are also quite popular. Large projects have been promoted where jute-reinforced polyester resins are used for buildings, e.g. the Madras House and grain elevators. Today, a renaissance in the use of natural fibres as reinforcement in technical applications is taking place, mainly in the automobile and packaging industries (e.g., egg boxes) (Singh & Gupta, 2005).

In the automotive industry (Suddell & Evans, 2005), cotton fibres embedded in polyester matrix was used in the body of the East German “Trabant” car. The use of flax fibres in car disk brakes to replace asbestos fibres is also another example. Daimler–Benz has been exploring the idea of replacing glass fibres with natural fibres in automotive components since 1991. A subsidiary of the company, Mercedes Benz pioneered this concept with the “Beleem project” based in Sao Paolo, Brazil. In this

case, coconut fibres were used in the commercial vehicles over a 9 year period. Mercedes also used jute-based door panels in its E-class vehicles in 1996. In September 2000, Daimler Chrysler began using natural fibres for their vehicle production. The bast fibres are primarily used in automotive applications because they exhibit greatest strength. The other advantages of using bast fibres in the automotive industry include weight savings of between 10% and 30% and corresponding cost savings. Recent studies have also indicated that hemp-based natural fibre mat thermoplastics are promising candidates in automotive applications where high specific stiffness is required (Pervaiz & Sain, 2003).

Virtually all the major car manufacturers in Germany (Daimler Chrysler, Mercedes, Volkswagen, Audi Group, BMW, Ford and Opel) now use biocomposites in various applications. Interior trim components such as dashboards and door panels using polypropylene and natural fibres are produced by Johnson Controls, Inc. for Daimler Chrysler. In 2000 Audi launched the A2 midrange car in which door trim panels were made of polyurethane reinforced with mixed flax/sisal mat. DaimlerChrysler has now increased its research and development in flax reinforced polyester composites for exterior applications (Automotive Industries, 2000).

Recent reports by Bledzki, Faruk, and Sperber (2006) point out the importance of biofibers and biocomposites in the automotive industry (Fig. 9a and b). The end of life vehicle (ELV) directive in Europe states that by 2015, vehicles must be constructed of 95% recyclable materials, with 85% recoverable through reuse or mechanical recycling and 10% through energy recovery or thermal recycling (Peijs, 2003). This will definitely lead to an increased use of biofibres. The diverse range of products utilizing biofibres and biobased resins derived from soy beans is giving life to a new generation of composites for a number of applications like hurricane-resistant housing and structures (Wool, 2002).

2.2. Designing biocomposites

Although biofibre reinforced polymer composites are gaining interest, the challenge is to replace conventional glass reinforced plastics with biocomposites that exhibit structural and functional stability during storage and use and yet are susceptible to environmental degradation upon disposal. An interesting approach in fabricating biocomposites of superior and desired properties include efficient and cost effective chemical modification of fibre, matrix modification by functionalizing and blending and efficient processing techniques. (Fig. 10)

Another interesting concept is that of “engineered natural fibres” to obtain superior strength biocomposites (Mohanty et al., 2002). This concept explores the suitable blending of bast (stem) and leaf fibres. The judicious selection of blends of biofibres is based on the fact that the correct blend achieves optimum balance in mechanical

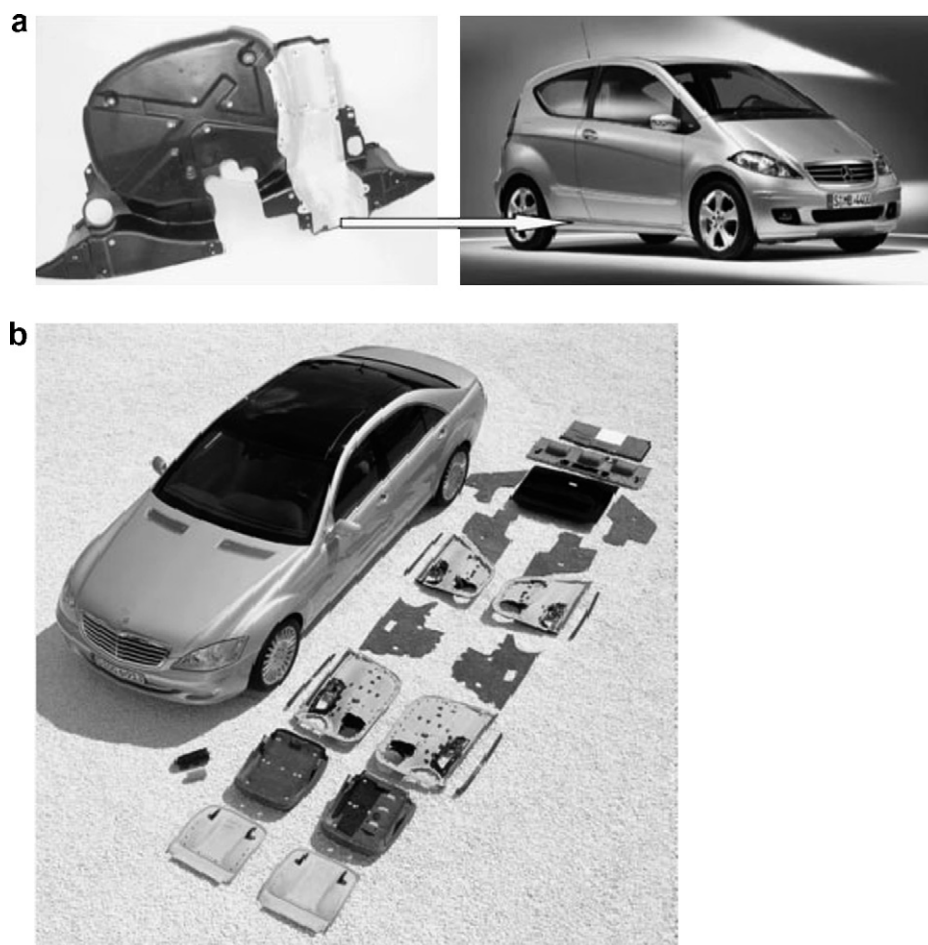


Fig. 9. (a) Under floor protection trim of Mercedes A class made from banana fibre reinforced composites. (b) Newest Mercedes S class automotive components made from different bio fibre reinforced composites.

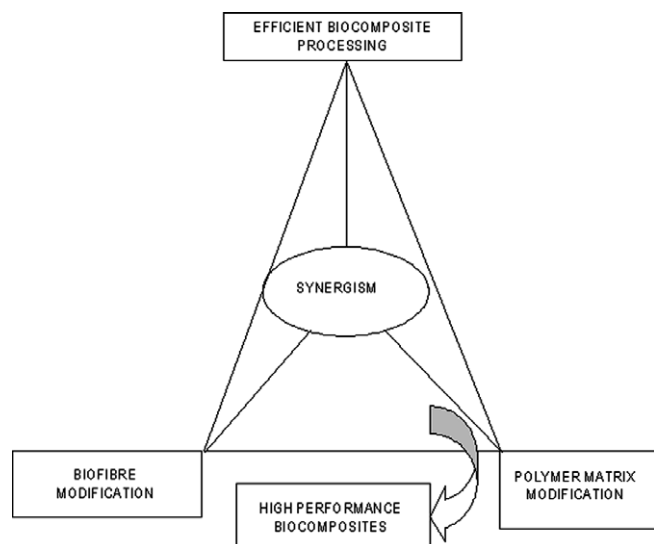


Fig. 10. Tricorner approach in designing of high performance biocomposites.

properties for e.g., the combination of bast and leaf fibre is expected to provide a stiffness–toughness balance in the resulting biocomposites.

3. Electrospinning (ELSP)

Electrospinning has been recognised as one of the most efficient techniques for the fabrication of nanopolymer fibres. When the diameter of polymer fibre is shrunk from micrometer to nanometre range, amazing new properties are exhibited in the nanopolymer fibres. The large surface area of the fibres contributes to various applications ranging from medical prosthesis to composite preparation. In addition, the electrospun fibres find applications in various other fields such as tissue template, protective clothing, cosmetics, drug delivery, conducting nanofibres, sensors, and optical shutters etc.

Electrospinning has recently drawn strong attention in biomedical engineering (Yoshimoto, Shin, Terai, & Vacanti, 2003), providing a basis for the fabrication of unique matrices and scaffolds for tissue engineering. ELSP is a spinning method that can produce polymer fibres with diameters ranging from several micros to 100 nm or less under a high-voltage electrostatic field operated between a metallic nozzle of a syringe and a metallic collector in air. The fibres are typically deposited in the form of a non-woven fabric onto a target metallic collector through

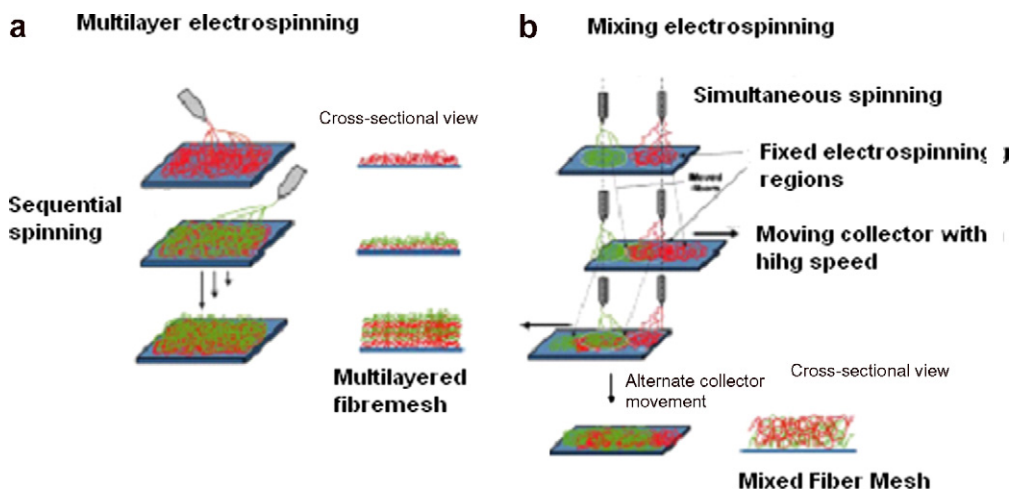


Fig. 11. Proposed electrospinning techniques (a) electrospinning (b) multilayer spinning.

a random projected jet of polymer solution, the so-called cone or instable jet. The accumulated charges on the polymer solution ejected from the nozzle induce the radial charge repulsion in the electric field, which induces the instable jet. If the random deposition process of fibres in the instability jet is appropriately controlled on the mesoscopic scale, the higher-ordered spatial placement of the nano- and microfibrils in the ELSP fabrics will be realized. In addition, the high-speed movement of the collector or nozzle may produce oriented meshes and more higher-ordered macroscopic devices.

Researchers recently developed two novel ELSP techniques: multilayering ELSP and (multicomponent) mixing ELSP, both of which are composed of different nano- and microfibrils (Kidoaki, Kwon, & Matsuda, 2005). In the multilayering ELSP, after electrospinning the first polymer, the second polymer is sequentially electrospun on the same target collector (See Fig. 11). Such a sequential spinning process can produce a multilayered fibre mesh, in which a hierarchically ordered structure composed of different kinds of polymer mesh could be obtained. For the mixing ELSP, two different polymers are simultaneously electrospun from different syringes under special conditions. The produced polymer fibres are mixed on the same target collector, resulting in the formation of a mixed fibre mesh.

Tremendous amount of studies are being undertaken in the field of electrospinning. The effect of molecular weight on fibrous PVA prepared by electrospinning has been reported by Koski, Yim, and Shivkumar (2004). Zarkoob et al. (2004) have reported on the structure and property of electrospun silk fibres. In the above work, fibres with diameter 50–200 nm could be obtained.

Recently scientists (Theron, Zussmann, & Yarin, 2004) have looked into the governing parameters in the electrospinning of polymer fibres. Researchers have studied the mechanical characterisation of electrospun gelatin nanofibres (Huang, Zhang, Ramakrishna, & Lim, 2004). Another innovative approach has been the preparation of blend bio-

degradable nanofibrous non-woven mats via multi jet electro spinning (Ding, Kimura, Sato, Fujita, & Shiratori, 2004).

Another interesting study was the electrospinning of chitosan nanofibres from aqueous chitosan solution using concentrated acetic acid solution as a solvent. A uniform nanofibrous mat of average fibre diameter of 130 nm was obtained from 7% chitosan solution in aqueous 90% acetic acid solution in an electric field of 4 kV/cm. An aqueous acetic acid concentration higher than 30% was prerequisite for chitosan nanofibre formation, because more concentrated acetic acid in water progressively decreased surface tension of the chitosan solution and concomitantly increased charge density of jet without significant effect on solution viscosity (Geng, Kwon, & Jang, 2005).

The fabrication and characterization of poly(vinyl alcohol)/chitosan blend nanofibers by electrospinning method was investigated by Yong-Tang et al. (2007). The results showed that the morphology and diameter of the nanofibers were mainly affected by concentration of the blend solution, weight ratio of the blend, respectively. It was also observed that there were strong intermolecular hydrogen bonds between the molecules of chitosan and poly(vinyl alcohol).

Recently researchers reported on the electrospinning and crosslinking of zein nanofibre mats (Yao, Li, & Song, 2007). Zein is a protein found in corn. The authors observed that crosslinked zein exhibited higher tensile properties than uncrosslinked zein.

4. Cellulose based nanocomposites

The concept of nanostructured materials design is gaining widespread importance among the scientific community (Berglund, 2005). The strong reinforcement effects at low volume fraction resulted in a tremendous interest from the industry and research circles. With this as an inspiration, the potential of nanoscale cellulose structures as reinforcement in novel composite materials was extre-

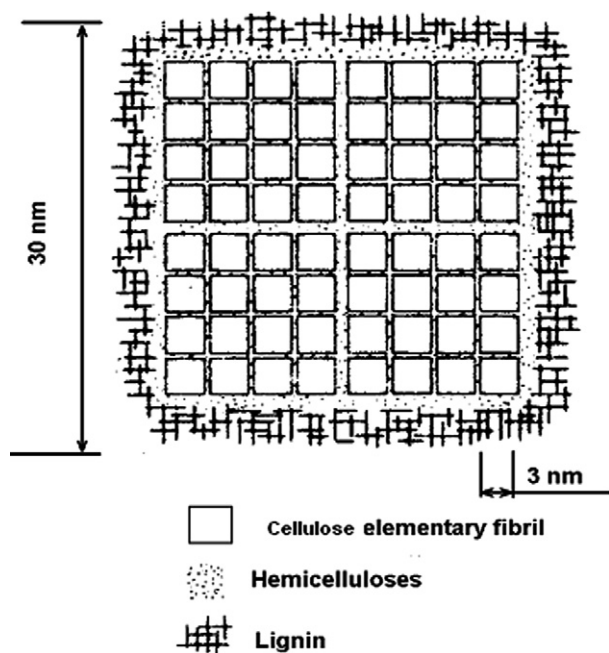


Fig. 12. Model of the cellulose microfibril structure.

mely interesting. The concept of cellulose nanocomposites for load bearing applications is fairly new. Property enhancements are expected due to higher Young's modulus of pure cellulose reinforcement and finely distributed reinforcing microfibrils. A major problem in the commercial use of cellulose microfibrils in structural materials is the disintegration of cellulose from plant cell wall at reasonable cost and without severe degradation. Another major problem is dispersion of cellulose microfibrils in a polymer matrix.

A simple model of the cellulose microfibril structure is presented in Fig. 12. Cellulose nanocomposites are usually fabricated by utilizing these microfibrils of 10–50 nm on width as reinforcement in a polymer matrix. Although many studies provide detailed knowledge regarding the morphology and crystallography of different types of cellulose, the Young's modulus of microfibrils from different sources and subjected to different types of hydrolysis is seldom discussed.

The research group at CERMAV-CNRS has presented numerous studies based on cellulose whiskers reinforced nanocomposites. The whiskers were disintegrated from an edible tunicate, a sea animal. Another area of interest is that of microfibrillated cellulose (MFC) nanocomposites. MFC based on parenchyma cells (i.e. sugar beet, potato tuber) tend to show small microfibril diameter and the fibrillar structures resemble swirled mats of connected, microfibrils rather than discrete rods (Dufresne, Cavaille, & Vignon, 1997). A review of the recent research into cellulosic whiskers, their properties and their application in nanocomposite field has been presented by the same group (Samir, Alloin, & Dufresne, 2005).

Recently scientists (Huang, Ichinose, & Kunitake, 2005) achieved uniform polypyrrole nanocoating on natural cel-

lulose fibres without disrupting the hierarchical network structures of individual cellulose fibres by means of polymerization-induced adsorption (Fig. 13).

High performance composites from low-cost plant primary cell walls were developed by Bruce, Hobson, Farrent, and Hepworth (2005). Purified cell wall fragments and cellulose microfibrils were developed from Swede root to form novel composite materials. The composites fabricated from purified cell wall fragments and acrylic matrix gave the best tensile properties. Researchers (Bokobza & Chauvin, 2005) have also reinforced natural rubber with nanofibres of sepiolite. The composites also contained silica particles generated in situ by the sol-gel process. The level of reinforcement was assessed from mechanical and orientation behaviour.

Algae are also a potential source of cellulose for use in composite materials. Researchers have concentrated on the morphology of cellulose powder from *Caldophora spatza* algae from the Baltic sea. The effective stiffness of the algae MFC (which is the combined effect of the microfibril modulus and its aspect ratio) was found to be higher than for the wheat straw cellulose. Bacterial or microbial cellulose (BC) have also found their way as reinforcement in composites. Cellulose can be produced from some bacteria such as *Acetobacter xylinum*, vinegar or acetic acid. Bacterial cellulose is an extracellular product which is excreted into the culture medium. Acetic acid bacteria are not photosynthetic but can convert glucose, sugar, glycerol to pure cellulose. Bacterial cellulose has been frequently studied to clarify the mechanism for biosynthesis (Tokoh, Takabe, Sugiyama, & Fujitha, 2002). Researchers have looked into the development of cellulose nanocomposites based on bacterial cellulose and cellulose acetate butyrate (Grunert & Winter, 2002). Though BC composites have evoked widespread interest, the industrial use of BC composites requires the development of efficient large-scale fermentation technology.

Nanoscale-modified plant structures such as paper or bast fibres also present a different approach to preparation of nanocomposite structures. An interesting study concentrated on the preserving the microfibril organization of wood veneer in composites (Yano, Hirose, Collins, & Yazaki, 2001). Pine veneer was used as the starting material.

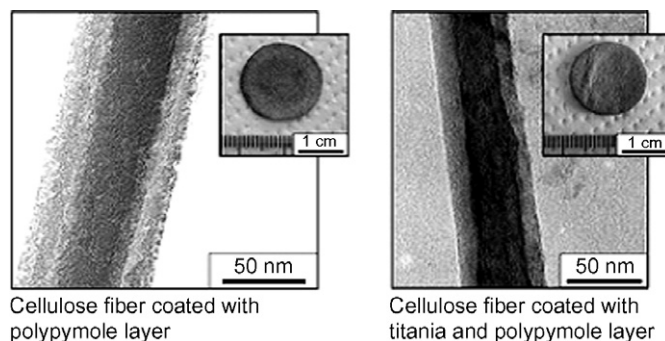


Fig. 13. Scanning electron micrographs of nanocoated cellulose fibres.

The basic idea was to increase the volume fraction of cellulose microfibrils by partially removing the lignin and hemicellulose wood polymers and by compressing the veneer. Phenol formaldehyde resin (PF) was used to preserve the compressed microstructure of the material and to bond microfibrils.

The orientation of cellulose nanowhiskers in polyvinyl alcohol was investigated by Kvien and Oksman (2007). Cellulose whiskers were incorporated in a polyvinyl alcohol matrix using solution casting with water as the solvent. The suspension was cast and the water was evaporated while a homogeneous magnetic field of 7 T was applied. Different microscopy investigations of prepared nanocomposites indicated that the cellulose whiskers were oriented perpendicular to the direction of the magnetic field. Dynamic mechanical thermal analysis further strengthened the idea of alignment because the results showed that the dynamic modulus of the nanocomposite was around 2 GPa higher at room temperature in the aligned direction compared to the transverse direction.

In an interesting study, nanocomposite materials reinforced with flax cellulose nanocrystals in waterborne polyurethane was reported by Xiaodong, Hua, and Chang (2007). The results indicated that the cellulose nanocrystals could disperse in the polyurethane uniformly and resulted in an improvement of microphase separation between the soft and hard segments of the WPU matrix. The films showed a significant increase in Young's modulus and tensile strength from 0.51 to 344 MPa and 4.27 to 14.96 MPa, respectively, with increasing filler content from 0 to 30 wt%.

5. Conclusions

The term biocomposite is now being applied to a staggering range of materials derived wholly or in part from renewable biomass resources. Keeping up with the developments in technology, it is compulsory that we stop developing materials, which are environmentally hazardous. This concept of bio-based materials has now become of key importance due to the need to preserve our environment. Biofibres like sisal, coir, hemp, oil palm are now finding applications in a wide range of industries. The field of bio-fibre research has experienced an explosion of interest, particularly with regard to its comparable properties to glass fibres within composites materials. The main area of increasing usage of these composites materials is the automotive industry, predominantly in interior applications.

Material revolution of this century may be provided by green composite materials. Sustainability, 'cradle-to-grave' design, industrial ecology, eco-efficiency, and green chemistry are not just newly coined buzz words, but form the principles that are guiding the development of a new generation of 'green' materials. Another promising area is that of nanocomposites and electrospinning of nanofibers.

References

- Agopyan, V., Jr., Savastano, H., John, V. M., & Cincotto, M. A. (2005). Developments on vegetable fibre-cement based materials in São Paulo, Brazil: An overview. *Cement and Concrete Composites*, 27, 527–536.
- Ahmed, K. S., & Vijayarangan, S. (2007). Experimental characterization of woven jute-fabric-reinforced isothalic polyester composites. *Journal of Applied Polymer Science*, 104, 2650–2662.
- Allen, S. D., Moore, D. R., Lobkovsky, E. B., & Coates, G. W. (2002). High-Activity, Single-Site Catalysts for the Alternating Copolymerization of CO₂ and Propylene Oxide. *Journal of the American Chemical Society*, 124, 14284–14285.
- Alsina, O. L. S., Carvalho, L. H. D., Filho, F. G. R., & Almeida, J. R. M. D. (2005). Thermal properties of hybrid lignocellulosic fabric-reinforced polyester matrix composites. *Polymer Testing*, 24, 81–85.
- Amin, K. A. M., & Badri, K. H. (2007). Palm-based biocomposites hybridized with kaolinite. *Journal of Applied Polymer Science*, 105, 2488–2496.
- Arumugam, N., Tamareselv, K., Venkata Rao, K., & Rajalingam, P. (1989). Coconut-fiber-reinforced rubber composites. *Journal of Applied Polymer Science*, 37, 2645–2659.
- Automotive Industries (2000), DaimlerChrysler "Goes Natural" for large body panel, p. 9.
- Averous, L., & Boquillon, N. (2004). Biocomposites based on plasticized starch: Thermal and mechanical behaviours. *Carbohydrate Polymers*, 56, 111–122.
- Baillie, C. (2005). *Green composites: Polymer composites and the environment*. CRC Press.
- Bakar, A., Hariharan, A., & Abdul Khalil, H. P. S. (2005). Lignocellulose-based hybrid bilayer laminate composite: Part I – studies on tensile and impact behavior of oil palm fiber-glass fiber-reinforced epoxy resin. *Journal of Composite Materials*, 39, 663–684.
- Bektas, I., Guler, C., Kalaycioglu, C., Mengeloglu, F., & Nacar, M. (2005). The Manufacture of Particleboards using Sunflower Stalks (*Helianthus annuus* L.) And Poplar Wood (*Populus alba* L.). *Journal of Composite Materials*, 39, 467–473.
- Berglund, L. (2005). In A. K. Mohanty, M. Misra, & L. T. Drzal (Eds.). *Natural fibres, Biopolymers and Biocomposites*. (pp. 808). CRC Press.
- Bhattacharya, T. B., Biswas, A. K., Chatterjee, J., & Pramanick, D. (1986). Short pineapple leaf fibre reinforced rubber composites. *Plastics, Rubbers and Processing Applications*, 6, 119–125.
- Bismarck, A., Mishra, S., & Lampke, T. (2005). In A. K. Mohanty, M. Misra, & L. T. Drzal (Eds.), *Natural fibres, biopolymers and biocomposites* (pp. 37). CRC Press.
- Bledzki, A. K., Faruk, O., & Sperber, V. E. (2006). Cars from bio-fibres. *Macromolecular Materials and Engineering*, 291, 449–457.
- Bokobza, L., & Chauvin, J-P. (2005). Reinforcement of natural rubber: Use of in situ generated silicas and nanofibres of sepiolite. *Polymer*, 46, 4144–4151.
- Bouhicha, M., Aouissi, F., & Kenai, S. (2005). Performance of composite soil reinforced with barley straw. *Cement and Concrete Composites*, 27, 617–621.
- Bruce, D. M., Hobson, R. N., Farrent, J. W., & Hepworth, D. G. (2005). High-performance composites from low-cost plant primary cell walls. *Composites Part A*, 36, 1486–1493.
- Burgueño, R., Quagliata, M. J., Mohanty, A. K., Mehta, G., Drzal, L. T., & Misra, M. (2005). Hybrid biofiber-based composites for structural cellular plates. *Composites: Part A*, 36, 581–593.
- Chabba, S., Mathews, G. F., & Netravali, A. N. (2005). Green composites using cross-linked soy flour and flax yarns. *Green Chemistry*, 8, 576–581.
- Coutts, R. S. P. (2005). A review of Australian research into natural fibre cement composites. *Cement and Concrete Composites*, 27, 518–526.
- De Medeiros, E. S., Agnelli, J. A. M., De Carvalho, L. H., & Mattoso, L. H. C. (2004). Mechanical properties of phenolic composites reinforced with jute/cotton hybrid fabrics. *Polymer Composites*, 26, 1–11.

- Ding, B., Kimura, E., Sato, T., Fujita, S., & Shiratori, S. (2004). Fabrication of blend biodegradable nanofibrous nonwoven mats via multi-jet electrospinning. *Polymer*, 45, 1895–1902.
- Dufresne, A., Cavaillie, J. Y., & Vignon, M. R. (1997). Mechanical behavior of sheets prepared from sugar beet cellulose microfibrils. *Journal of Applied Polymer Science*, 64, 1185–1194.
- Dweib, M. A., Hu, B., Shenton, H. W., III, & Wool, R. P. (2006). Bio-based composite roof structure: Manufacturing and processing issues. *Composite Structures*, 74, 379–388.
- El Sabbagh, S. H., El Hariri, D. M., & Abd. El Ghaffar, M. A., (2000). In *Proceedings from the third international symposium on natural polymers & composites* (pp. 469). ISNa Pol/May 14–17th.
- Fernandes, E. G., Cinelli, P., & Chiellini, E. (2004). Thermal behavior of composites based on poly(vinyl alcohol) and sugar cane bagasse. *Macromolecular Symposium*, 21, 231–240.
- Ge, X. C., Xu, Y., Meng, Y. Z., & Li, R. K. Y. (2005). Thermal and mechanical properties of biodegradable composites of poly(propylene carbonate) and starch–poly(methyl acrylate) graft copolymer. *Composites Science and Technology*, 65, 2219–2225.
- Geethamma, V. G., Joseph, R., & Thomas, S. (1995). Short coir fiber-reinforced natural rubber composites: Effects of fiber length, orientation, and alkali treatment. *Journal of Applied Polymer Science*, 55, 583–594.
- Geng, X., Kwon, O. H., & Jang, J. (2005). Electrospinning of chitosan dissolved in concentrated acetic acid solution. *Biomaterials*, 26, 5427–5432.
- Ghavam, K. (2005). Bamboo as reinforcement in structural concrete elements. *Cement and Concrete Composites*, 27, 637–649.
- Goda, K. (2002). *International workshop on green composites*.
- Grunert, M., & Winter, W. T. (2002). Nanocomposites of cellulose acetate butyrate reinforced with cellulose nanocrystals. *Journal of Polymers and the Environment*, 10, 27–30.
- Haseena, A. P., Dasan, K. P., Namitha, R., Unnikrishnan, G., & Thomas, S. (2005). Mechanical properties of sisal/coir hybrid fibre reinforced natural rubber. *Progress in Rubbers, Plastics and Recycling Technology*, 21, 155–181.
- Haseena, P., & Unnikrishnan, G., (2005). In *Proceedings from international conference on advances in polymer blends and composites* (ICBC 2005) (p. 51). March 21–23.
- Hong, C. K., & Wool, R. P. (2004). *Journal of Natural Fibres*, 2, 83.
- Hong, C. K., & Wool, R. P. (2005). Development of a bio-based composite material from soybean oil and keratin fibers. *Journal of Applied Polymer Science*, 95(6), 1524–1538.
- Huang, J., Ichinose, I., & Kunitake, T. (2005). Nanocoating of natural cellulose fibers with conjugated polymer: Hierarchical polypyrrole composite materials. *Chemical Communications*, 13, 1717–1719.
- Huang, Z. M., Zhang, Y. Z., Ramakrishna, S., & Lim, C. T. (2004). Electrospinning and mechanical characterization of gelatin nanofibers. *Polymer*, 45, 5361–5368.
- Idicula, M., Boudenne, A., Umadevi, L., Ibos, L., Candau, Y., & Thomas, S. (2006). Thermophysical properties of natural fibre reinforced polyester composites. *Composites Science and Technology*, 66, 2719–2725.
- Idicula, M., Malhotra, S. K., Joseph, K., & Thomas, S. (2005). Dynamic mechanical analysis of randomly oriented intimately mixed short banana/sisal hybrid fibre reinforced polyester composites. *Composites Science and Technology*, 65, 1077–1087.
- Idicula, M., Neelakantan, N. R., Oommen, Z., Joseph, K., & Thomas, S. (2005). A study of the mechanical properties of randomly oriented short banana and sisal hybrid fiber reinforced polyester composites. *Journal of Applied Polymer Science*, 96, 1699–1709.
- Imam, S. H., Cinelli, P., Gordon, S. H., & Chiellini, E. (2005). Characterization of biodegradable composite films prepared from blends of poly(vinyl alcohol), cornstarch, and lignocellulosic fiber. *Journal of Polymers and the Environment*, 13, 47–55.
- Ismail, H., Rosnah, N., & Ishiaku, U. S. (1997). Oil palm fibre-reinforced rubber composite: Effects of concentration and modification of fibre surface. *Polymer International*, 43, 223–230.
- Jacob, M., Francis, B., Varughese, K. T., & Thomas, S. (2006). Dynamical mechanical analysis of sisal/oil palm hybrid fiber-reinforced natural rubber composites. *Polymer Composites*, 27, 671–680.
- Jacob, M., Varughese, K. T., & Thomas, S. (2004a). Mechanical properties of sisal/oil palm hybrid fiber reinforced natural rubber composites. *Composites Science and Technology*, 64, 955–965.
- Jacob, M., Varughese, K. T., & Thomas, S. (2004b). Natural rubber composites reinforced with sisal/oil palm hybrid fiber: Tensile and cure characteristics. *Journal of Applied Polymer Science*, 93, 2305–2312.
- Jacob, M., Varughese, K. T., & Thomas, S. (2005). Water sorption studies of hybrid bio-fiber reinforced natural rubber biocomposites. *Biomacromolecules*, 6, 2969–2976.
- Jacob, M., Varughese, K. T., & Thomas, S. (2006a). Novel woven sisal fabric reinforced natural rubber composites: Tensile and swelling characteristics. *Journal of Composite Materials*, 40, 1471–1485.
- Jacob, M., Varughese, K. T., & Thomas, S. (2006b). Moisture sorption characteristics in woven sisal fabric reinforced natural rubber composites: A study. *Journal of Applied Polymer Science*, 102, 416–423.
- Jane, J., & Wang, S. (1996). US Patent 5,523,293.
- Jayaraman, K. (2003). Manufacturing sisal-polypropylene composites with minimum fibre degradation. *Composites Science and Technology*, 63, 367–374.
- Junior, C. Z. P., Carvalho, L. H., Fonseca, V. M., Monteiro, S. N., & Almeida, J. R. M. (2004). Analysis of the tensile strength of polyester/hybrid ramie-cotton fabric composites. *Polymer Testing*, 23, 131–135.
- Kidoaki, S., Kwon, K., & Matsuda, T. (2005). Mesoscopic spatial designs of nano- and microfiber meshes for tissue-engineering matrix and scaffold based on newly devised multilayering and mixing electrospinning techniques. *Biomaterials*, 26, 37–46.
- Koski, A., Yim, K., & Shivkumar, S. (2004). Effect of molecular weight on fibrous PVA produced by electrospinning. *Materials Letters*, 58, 493–497.
- Kozlowski, R., Muzyczek, M., & Mieleniak, B. (2004). Upholstery fire barriers based on natural fibres. *Journal of Natural Fibres*, 1, 85–92.
- Kumar, R. N., Hee, K. C., & Rozman, H. D. (2005). Photofabrication of biofiber-based polymer matrix composites. *Journal of Applied Polymer Science*, 95, 1493–1499.
- Kvien, I., & Oksman, K. (2007). Orientation of cellulose nanowhiskers in polyvinyl alcohol. *Applied Physics A: Materials Science and Processing*, 87, 641–643.
- Lee, S.-H., & Wang, S. (2006). Biodegradable polymers/bamboo fiber biocomposite with bio-based coupling agent. *Composites Part A*, 37, 80–91.
- Li, Q., & Matuana, L. M. (2003). Surface of cellulosic materials modified with functionalized polyethylene coupling agents. *Journal of Applied Polymer Science*, 88, 278–286.
- Liu, W., Mohanty, A. K., Askeland, P., Drzal, L. T., & Misra, M. (2004). Influence of fiber surface treatment on properties of Indian grass fiber reinforced soy protein based biocomposites. *Polymer*, 45, 7589–7596.
- Liu, W., Misra, M., Askeland, P., Drzal, L. T., & Mohanty, A. K. (2005). Green composites from soy based plastic and pineapple leaf fiber: Fabrication and properties evaluation. *Polymer*, 46, 2710–2721.
- Lodha, P., & Netravali, A. N. (2005). Characterization of stearic acid modified soy protein isolate resin and ramie fiber reinforced ‘green’ composites. *Composites Science and Technology*, 65, 1211–1215.
- Ma, X., Yu, J., & Zhao, A. (2006). Properties of biodegradable poly(propylene carbonate)/starch composites with succinic anhydride. *Composites Science and Technology*, 66, 2360–2366.
- Madani, M., Basta, A. H., Abdo, A. E.-S., & El-Saied, H. (2004). Utilization of waste paper in the manufacture of natural rubber composite for radiation shielding. *Progress in Rubbers, Plastics and Recycling Technology*, 20, 210–287.
- Maiti, P., & Giannelis, E. P. (2002). *Polymer Outreach Program* (19). NY: Cornell University.
- Masirek, R., Kulinski, Z., Chionna, D., Piorkowska, E., & Pracella, M. (2007). Composites of poly(L-lactide) with hemp fibers: Morphology and thermal and mechanical properties. *Journal of Applied Polymer Science*, 105, 255–268.

- Material Thoughts (2002). *Fiber reinforced plastics use*. Plastics News. August.
- Material Thoughts (2005a). *Plastics from citrus*.
- Material Thoughts (2005b). *Plants into plastic*.
- Mathew, L., Joseph, K. U., & Joseph, R. (2004). Isora fibres and their composites with natural rubber. *Progress in Rubber, Plastics and Recycling Technology*, 20, 337–349.
- Matkó, S., Toldy, A., Keszei, S., Anna, P., Bertalan, G., & Marosi, G. (2005). Flame retardancy of biodegradable polymers and biocomposites. *Polymer Degradation and Stability*, 88, 138–145.
- Mattone, R. (2005). *Cement and Concrete Composites*, 27, 611–616.
- Mehta, G., Mohanty, A. K., Misra, M., & Drzal, L. T. (2004). Biobased resin as a toughening agent for biocomposites. *Green Chemistry*, 6, 254–258.
- Mirbagheri, J., Tajvidi, M., Hermanson, J. C., & Ghasemi, I. (2007). Tensile properties of wood flour/kenaf fiber polypropylene hybrid composites. *Journal of Applied Polymer Science*, 105, 3054–3059.
- Mishra, S., Mohanty, A. K., Drzal, L. T., Misra, M., Parija, S., Nayak, S. K., et al. (2003). Studies on mechanical performance of biofiber/glass reinforced polyester hybrid composites. *Composites Science and Technology*, 63, 1377–1385.
- Mohanty, A. K., Drzal, L. T., & Misra, M. (2002). Engineered natural fiber reinforced polypropylene composites: Influence of surface modifications and novel powder impregnation processing. *Journal of Adhesion Science and Technology*, 16, 999–1015.
- Mohanty, A. K., Khan, M. A., Sahoo, S., & Hinrichsen, G. (2000). Effect of chemical modification on the performance of biodegradable jute yarn-Biopol® composites. *Journal of Materials Science*, 35, 2589–2595.
- Mohanty, A. K., Misra, M., & Hinrichsen, G. (2000). Biofibres, biodegradable polymers and biocomposites: An overview. *Macromolecular Materials and Engineering*, 276/277, 1–24.
- Morye, S. S., & Wool, R. P. (2005). Mechanical properties of glass/flax hybrid composites based on a novel modified soybean oil matrix material. *Polymer Composites*, 26, 407–416.
- Mwaikambo, L. Y., & Bisanda, E. T. N. (1999). The performance of cotton–kapok fabric–polyester composites. *Polymer Testing*, 18, 181–198.
- Nassar, M. M., Ashour, E. A., & Washid, S. S. (1996). Thermal characteristics of bagasse. *Journal of Applied Polymer Science*, 61, 885–890.
- Netravali, A. N., & Chabba, S. (2003). Composites get greener. *Materials Today*, 6, 22–29.
- Nevell, T. P., & Zeronian, S. H. (1985). *Cellulose chemistry and its applications*. New York: Wiley.
- Ohkita, T., & Lee, S.-H. (2006). Thermal degradation and biodegradability of poly(lactic acid)/corn starch biocomposites. *Journal of Applied Polymer Science*, 100, 3009–3017.
- Olesen, P. O., & Plackett, D. V. (1999). Perspectives on the performance of natural plant fibres presented at natural fibres performance forum, Copenhagen, May 27–28. <<http://www.ienica.net/fibreseminar/olesen.pdf>>.
- Pan, P., Zhu, B., Kai, W., Serizawa, S., Iji, M., & Inoue, Y. (2007). Crystallization behavior and mechanical properties of bio-based green composites based on poly(L-lactide) and kenaf fiber. *Journal of Applied Polymer Science*, 105, 1511–1520.
- Panthapulakkal, S., & Sain, M. (2007). Injection-molded short hemp fiber/glass fiber-reinforced polypropylene hybrid composites –Mechanical, water absorption and thermal properties. *Journal of Applied Polymer Science*, 103, 2432–2441.
- Peijs, T. (2002). *e-Polymers*, T.002 1.
- Peijs, T. (2003). Composites for recyclability. *Materials Today*.
- Pervaiz, M., & Sain, M. M. (2003). Sheet-molded polyolefin natural fiber composites for automotive applications. *Macromolecular Materials and Engineering*, 288(7), 553–557.
- Plackett, D., Andersen, T. L., Pedersen, W. B., & Nielsen, L. (2003). Biodegradable composites based on L-poly(lactide) and jute fibres. *Composites Science and Technology*, 63, 1287–1296.
- Pothan, L. A., Cherian, B. M., Anandakutty, B., & Thomas, S. (2007). Effect of layering pattern on the water absorption behavior of banana/glass hybrid composites. *Journal of Applied Polymer Science*, 105, 2540–2548.
- Pothen, L. A., Thomas, S., Li, R. K. Y., & Mai, Y. W. (2002). In *Proceedings of international conference on textile composites*. IIT Delhi.
- Ray, D., & Rout, J. (2005). In A. K. Mohanty, M. Misra, & L. T. Drzal (Eds.), *Natural fibers, biopolymers and biocomposites*. CRC Press.
- Reddy, N., & Yang, Y. (2005a). Properties and potential applications of natural cellulose fibers from cornhusks. *Green Chemistry*, 4, 190–195.
- Reddy, N., & Yang, Y. (2005b). Structure and properties of high quality natural cellulose fibers from cornstalks. *Polymer*, 46, 5494–5500.
- Reis, P. N. B., Ferreira, J. A. M., Antunes, F. V., & Costa, J. D. M. (2007). Flexural behaviour of hybrid laminated composites. *Composites Part A: Applied Science and Manufacturing*, 38, 1612–1620.
- Rout, J., Mishra, M., Tripathy, S. S., Nayak, S. K., & Mohanty, A. K. (2001). The influence of fibre treatment on the performance of coir-polyester composites. *Composites Science and Technology*, 61, 1303–1310.
- Thames, S. F. (1994). Soybean polypeptide polymers. In C. P. Baume, L. A. Johnson, C. A. Greiner (Eds.), *Identifying new industrial uses of soybean protein*. Special Rep 95. Iowa Agriculture and Home Economics Experiment Station, Iowa State University, Ames, IA, USA.
- Wang, S., Sue, H.-J., & Jane, J. (1994). *Journal of Macromolecular Science – Pure and Applied Chemistry*, 33, 557.
- Samir, M. A. S. A., Alloin, F., & Dufresne, A. (2005). Review of recent research into cellulosic whiskers, their properties and their application in nanocomposite field. *Biomacromolecules*, 6, 612–626.
- Satyanarayana, K. G., Ravikumar, K. K., Sukumaran, K., Mukherjee, P. S., Pillai, S. G. K., & Kulkarni, A. K. (1986). Structure and properties of some vegetable fibres. Part 3. Talipot and palmyrah fibres. *Journal of Material Science*, 21, 57.
- Seal, K. J., & Morton, L. H. G. (1996). Chemical materials. *Biotechnology*, 8, 583–590.
- Sébastien, F., Stéphane, G., Copinet, A., & Coma, V. (2006). Novel biodegradable films made from chitosan and poly(lactic acid) with antifungal properties against mycotoxinogen strains. *Carbohydrate Polymers*, 65, 185–193.
- Shibata, M., Oyamada, S., Kobayashi, S., & Yaginuma, D. (2004). Mechanical properties and biodegradability of green composites based on biodegradable polyesters and lyocell fabric. *Journal of Applied Polymer Science*, 92, 3857–3863.
- Shih, Y.-F. (2007). A study of the fiber obtained from the water bamboo husks. *Bioresource Technology*, 98, 819–828.
- Singh, B., & Gupta, M. (2005). Natural fiber composites for building applications. In A. K. Mohanty, M. Misra, & L. T. Drzal (Eds.), *Natural fibers, biopolymers and biocomposites* (pp. 261). CRC Press.
- Sreekala, M. S., George, J., Kumaran, M. G., & Thomas, S. (2002). The mechanical performance of hybrid phenol–formaldehyde-based composites reinforced with glass and oil palm fibres. *Composites Science and Technology*, 62, 339–353.
- Stevens, E. S. (2002). *Green plastics*. Princeton: Princeton University Press.
- Suddell, B. C., & Evans, W. J. (2005). In A. K. Mohanty, M. Misra, & L. T. Drzal (Eds.), *Natural fiber composites in automotive applications: Natural fibers. Biopolymers and Biocomposites* (pp. 231). CRC Press.
- Tang, X., Whitcomb, J. D., Li, Y., & Sue, H.-J. (2005). Micromechanics modeling of moisture diffusion in woven composites. *Composites Science and Technology*, 65, 817–826.
- Technology International Exchange Inc. (1996). *Certificate of analysis for pronova fish oil*, Pronoval Biocare, p. 6.
- Theron, S. A., Zussmann, E., & Yarin, A. L. (2004). Experimental investigation of the governing parameters in the electrospinning of polymer solutions. *Polymer*, 45, 2017–2030.
- Thwe, M. M., & Liao, K. (2003). Durability of bamboo-glass fiber reinforced polymer matrix hybrid composites. *Composites Science and Technology*, 63, 375–387.

- Tokoh, C., Takabe, K., Sugiyama, J., & Fujitha, M. (2002). Cp/mas ^{13}C NMR and electron diffraction study of bacterial cellulose structure affected by cell wall polysaccharides. *Cellulose*, 9, 351–360.
- Tummala, P., Mohanty, A. K., Misra, M., Drzal, L. T., (2003). *Proceedings of 14th international conference on composite materials (ICCM-14)*.
- Varghese, S., Kuriakose, B., Thomas, S., & Koshy, A. T. (1994). Mechanical and viscoelastic properties of short fiber reinforced natural rubber composites: Effects of interfacial adhesion, fiber loading, and orientation. *Journal of Adhesion Science and Technology*, 8, 235–248.
- Wambua, P., Vangrimde, B., Lomov, S., & Verpoest, I. (2007). The response of natural fibre composites to ballistic impact by fragment simulating projectiles. *Composite Structures*, 77, 232–240.
- Wilkinson, S. L. (2001). *Chemical and Engineering News*, 61.
- Wool, R. P. (2002). *Proceedings of the 10th European conference on composite materials (ECCM-10)*, Belgium.
- Xiaodong, C., Hua, D., & Chang, Ming L. (2007). New nanocomposite materials reinforced with flax cellulose nanocrystals in waterborne polyurethane. *Biomacromolecules*, 8, 899–904.
- Yano, H., Hirose, A., Collins, P. J., & Yazaki, Y. J. (2001). Effects of the removal of matrix substances as a pretreatment in the production of high strength resin impregnated wood based materials. *Journal of Material Science Letters*, 20, 1125–1126.
- Yao, C., Li, X., & Song, T. (2007). Electrospinning and crosslinking of zein nanofiber mats. *Journal of Applied Polymer Science*, 103, 380–385.
- Yong-Tang, J., Jian, G., Xiao-Hua, G., Hark-Yong, K., Jiong, D., & Xin-Yuan, S. (2007). Fabrication and characterization of poly(vinyl alcohol)/chitosan blend nanofibers produced by electrospinning method. *Carbohydrate Polymers*, 67, 403–409.
- Yoshimoto, H., Shin, Y. M., Terai, H., & Vacanti, J. P. (2003). A biodegradable nanofiber scaffold by electrospinning and its potential for bone tissue engineering. *Biomaterials*, 24, 2077–2082.
- Zarkoob, S., Eby, R. K., Reneker, D. H., Hudson, S. D., Ertley, D., & Adams, W. W. (2004). Structure and morphology of electrospun silk nanofibers. *Polymer*, 45, 3973–3977.
- Zimniewska, M., Kozłowski, R., & Rawluk, M. (2004). Natural vs. Man-made Fibres Physiological Viewpoint. *Journal of Natural Fibers*, 1(2), 69–81.