



Biodegradation of thermoplastic starch/eggshell powder composites



Munlika Bootklad, Kaewta Kaewtatip*

Department of Materials Science and Technology, Faculty of Science, Prince of Songkla University, Hat Yai, Songkhla 90112, Thailand

ARTICLE INFO

Article history:

Received 4 March 2013

Received in revised form 14 May 2013

Accepted 15 May 2013

Available online 23 May 2013

Keywords:

Eggshell

Starch

Calcium carbonate

Biodegradation

ABSTRACT

Thermoplastic starch (TPS) was prepared using compression molding and chicken eggshell was used as a filler. The effect of the eggshell powder (EP) on the properties of TPS was compared with the effect of commercial calcium carbonate (CC). The organic compound on the surface of the eggshell powder acted as a coupling agent that resulted in a strong adhesion between the eggshell powder and the TPS matrix, as confirmed by SEM micrographs. The biodegradation was determined by the soil burial test. The TPS/EP composites were more rapidly degraded than the TPS/CC composites. In addition, the eggshell powder improved the water resistance and thermal stability of the TPS.

© 2013 Elsevier Ltd. All rights reserved.

1. Introduction

In the last decade, thermoplastic starch (TPS) has been of interest as a polymer that could replace petroleum-derived plastics because it has a low production cost, is readily available, is fully biodegradable and is a renewable agricultural resource (Roz, Carvalho, Gandini, & Curvelo, 2006; Teixeira et al., 2009). Cassava roots have become economically important products of Thailand. Generally, cassava roots are processed as animal feed or are fermented for producing alcoholic beverages. Therefore, the preparation of TPS by using cassava starch not only increases the market value of cassava roots but also helps to solve the accumulation of petroleum-derived plastics in nature that have become a worldwide environmental problem. However, TPS has limitations including its poor long-term stability, poor mechanical properties and poor water resistance (Lopez, Mutje, Carvalho, Curvelo, & Girones, 2013; Roz, Zambon, Curvelo, & Carvalho, 2011). Several research groups have attempted to improve the properties of TPS. Many fillers have been used and some have been effective for improving some of the properties of TPS such as fiber (Gilfillan, Nguyen, Sopade, & Doherty, 2012; Kaewtatip & Thongmee, 2012), clay (Kaewtatip & Tanrattanakul, 2012; Wang, Zhang, Liu, & Wang, 2009), protein (Corradini, Marconcini, Agnelli, & Mattoso, 2011; Kaewtatip, Tanrattanakul, & Kaewtatip, 2013), brucite (Moreira, Pedro, Glenn, Marconcini, & Mattoso, 2013), fly ash (Ma, Yu, & Wang, 2007) and carbon nanotubes (Fama, Pettarin, Goyanes, &

Bernal, 2011). However, the hydrophilic characteristics of TPS can cause incompatibility with fillers and some of the fillers are non-biodegradable materials. Currently, most research has been focused on the development of a bio-filler for TPS that will not only improve the compatibility between the TPS and the filler but also can facilitate biodegradation by microorganisms.

Eggshell has been considered to be a good candidate for use as a bio-filler for preparing polymer composites because it is inexpensive, abundant, has low density, is environmentally friendly and is a renewable resource (Kang, Pal, Park, Bang, & Kim, 2010; Toro, Quijada, Arias, & Yazdani-Pedram, 2007). Eggshell is a major waste product of the food industry and is produced in large quantities. Eggshell contains about 95% of calcium carbonate and 5% of organic materials (Ji, Zhu, Qi, & Zeng, 2009; Kang et al., 2010). Eggshell has potential uses for many applications such as a fertilizer, animal feed, for coating pigments, as a catalyst and adsorbent (Cho & Seo, 2010; Tsai et al., 2006; Yoo, Hsieh, Zou, & Kokoszka, 2009). One of its most useful applications is as a filler for synthetic plastics e.g. poly(styrene-*b*-ethylene/butylene-*b*-styrene) (Kang et al., 2010), polypropylene (PP) (Toro, Quijada, Arias, et al., 2007; Toro, Quijada, Yazdani-Pedram, & Arias, 2007), epoxy resins (Ji et al., 2009) and low density polyethylene (LDPE) (Shuhadah & Supri, 2009). Toro, Quijada, Arias, et al. (2007) compared the effect of commercial calcium carbonate and eggshell on the properties of a PP composite. They found that eggshell disperses well in the PP matrix due to the higher surface/volume ratio for eggshell than that of commercial calcium carbonate. The toughness of the epoxy resin was improved by using eggshell (Ji et al., 2009). However, there have been few reports on the use of eggshell with starch-based materials. Takamine, Bhatnagar, and Hanna (1995) studied the effect of eggshell on the properties of corn starch extrudates. They suggested

* Corresponding author. Tel.: +66 74288365; fax: +66 74446925.

E-mail addresses: kaewta.k@psu.ac.th, jumpolymer@hotmail.com (K. Kaewtatip).

that eggshell brought about nucleation sites for water vaporization as the material exited the die of the extruder. Moreover, eggshell was used as a nucleating agent for preparing starch foam (Xu & Hanna, 2007). It was found that eggshells decreased the cell size and increased the cell population.

The aim of this work was to study the effect of eggshell on the properties of TPS and compare it with the use of commercial calcium carbonate. The morphology of their fractured surfaces, the thermal properties and water absorption of the composites was studied. The surface morphology and weight loss after burial in soil was also investigated.

2. Materials and methods

2.1. Materials

Pregelatinized cassava starch (PD 10370) was kindly supplied by Siam Modified Starch Co., Ltd. The starch was dried at 105 °C for 48 h in an oven and kept in a desiccator prior to use. The chicken eggshell was obtained from waste at a local market. Eggshells were washed in water to remove any impurities, dried in a hot air oven and ground by a Motar grinder, FRITSTSCH (Germany). After grinding, the eggshell powder was dried in a hot air oven until a constant weight was achieved and kept in a desiccator prior to use. The particle size of the eggshell powder was $26.26 \pm 9.48 \mu\text{m}$. Typical compositions of the eggshell powder was 95% by weight of calcium carbonate and 5% by weight of organic materials such as collagen, sulfated polysaccharides and other proteins (Kang et al., 2010). Commercial calcium carbonate was purchased from Kitpi boon Co., Ltd. The glycerol was from Ajax Finechem.

2.2. Preparation of the composites

Pregelatinized cassava starch, glycerol (45 parts per hundred of the total weight of the pregelatinized cassava starch) and filler (commercial calcium carbonate or eggshell powder) (0, 10, 20, 30, 40 and 50 wt.%, dry starch basis) were mixed in polyethylene bags until a homogeneous material was obtained. After that, TPS and the composites were prepared by using a compression molding machine at 160 °C for 10 min and a pressure of 200 kg/cm² was directly applied to the sample.

2.3. Characterization of the composites

Wide angle X-ray diffraction (XRD) studies were carried out using a Phillips diffractometer (Model PW 1830) with copper as a target material. The scanning regions of the diffraction angle 2θ were 5–90°. The samples were conditioned at $55 \pm 2\%$ RH and $25 \pm 3^\circ\text{C}$.

The morphology of the samples was examined using a scanning electron microscope (SEM) (Quanta 400, FEI). The TPS and composites were immersed in liquid nitrogen before fracturing. All specimens were first coated with a thin layer of gold.

The thermal decomposition temperatures of the TPS and the composites were obtained using a PerkinElmer® TGA 7. The thermogravimetric analyzer (TGA) was operated at a heating rate of 10 °C/min from 50 to 600 °C under a nitrogen atmosphere.

2.4. Soil burial degradation test

Soil burial degradation test was carried out according to Riyajan, Sasithornsonti, and Phinyocheep (2012). Small pieces of samples (dimensions 15 mm × 15 mm × 1 mm) were buried in natural soil at a depth of 7 cm in Hat Yai, Songkhla, Thailand. The average environmental temperature was $30 \pm 5^\circ\text{C}$ and the relative humidity (RH)

was 50–60%. After 15 days and 30 days, the samples were collected, washed with distilled water several times and dried in the oven at 105 °C for 24 h.

The weight loss was calculated using Eq. (1) (Franco, Cyras, Busalmen, Ruseckaite, & Vazquez, 2004; Phua, Lau, Sudesh, Chow, & Ishak, 2012):

$$\text{Weight loss (\%)} = \left[\frac{w_{\text{initial}} - w_{\text{final}}}{w_{\text{initial}}} \right] \times 100 \quad (1)$$

where w_{initial} and w_{final} was the weight of sample before and after soil burial degradation test, respectively.

2.5. Water absorption measurement

The samples were stored at 55%RH for 30 days before testing and were then dried in the oven at 105 °C for 24 h. These samples were weighed immediately after being removed from the oven. The water absorption was calculated as follows Eq. (2) (Huang, Yu, & Ma, 2004; Ma et al., 2007):

$$\text{Water absorption (\%)} = \left[\frac{w_1 - w_2}{w_2} \right] \times 100 \quad (2)$$

where w_1 was the weight of sample before drying and w_2 was the weight of sample after drying. All measurements were performed in triplicate.

3. Results and discussion

3.1. Characterization of fillers

The physical properties of commercial calcium carbonate and eggshell powder such as density, surface area and oil absorbent value has been reported in many articles (Ji et al., 2009; Toro, Quijada, Arias, et al., 2007; Tsai et al., 2006). Thus, the morphology and XRD patterns of commercial calcium carbonate and eggshell powder were studied. Fig. 1(a) presents the SEM micrograph of the commercial calcium carbonate. The shape of the commercial calcium carbonate was plate-like, whereas the morphology of the eggshell powder was similar to that of commercial calcium carbonate (Fig. 1(b)). A similar morphology of eggshell powders has been detected by other authors (Toro, Quijada, Arias, et al., 2007; Toro, Quijada, Yazdani-Pedram, et al., 2007). In contrast, the XRD diffraction pattern of the commercial calcium carbonate and eggshell powder are shown in Fig. 2(a) and (b), respectively. The XRD diffraction pattern of the eggshell powder was similar to the XRD diffraction pattern of the commercial calcium carbonate. The result was compared with previous reports (Ji et al., 2009; Kang et al., 2010) which showed that the main component of the eggshell powder was 95% calcium carbonate.

3.2. Morphology

SEM micrographs of the fractured surfaces of the TPS, TPS/CC composites and TPS/EP composites are presented in Fig. 3. TPS shows a clear and smooth surface (Fig. 3(a)). For the fractured surfaces of the composites, a coarse surface with cavities was observed (Fig. 3(b)–(e)). Although, TPS/CC composites seem to have similar morphology to that found in the TPS/EP composite there was some agglomerates of commercial calcium carbonate in the matrix. Moreover, large holes were present in the fractured surface of the TPS/CC composites due to the pull-out of the commercial calcium carbonate agglomerates. The TPS/EP composites showed good dispersion and the eggshell powder was embedded in the TPS matrix. The eggshell powder demonstrated a better adhesion to the TPS matrix than the commercial calcium carbonate due to the presence

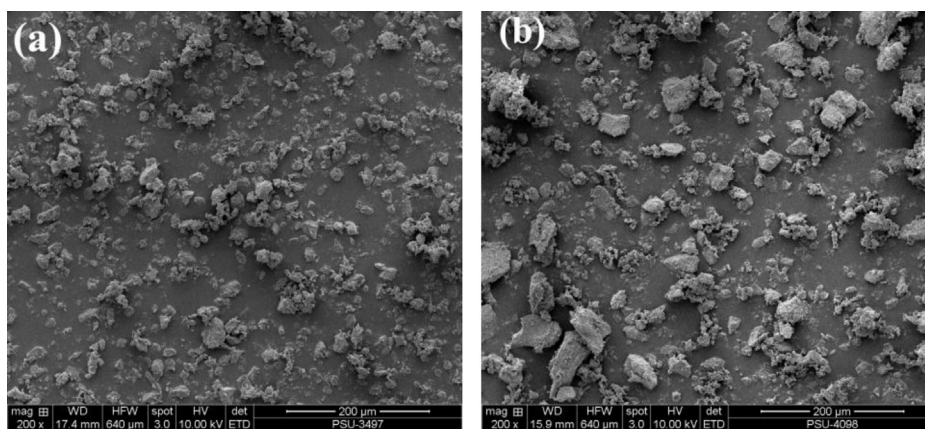


Fig. 1. SEM micrographs of the commercial calcium carbonate (a) and eggshell powder (b).

of organic components in the eggshell powder such as collagen, sulfated polysaccharides and other proteins that can act as coupling agents between the TPS matrix and the eggshell powder. This result is consistent with that of Ji et al. (2009) who presented an infrared (IR) spectrum that confirmed there are organic compounds on the surface of the eggshell powder.

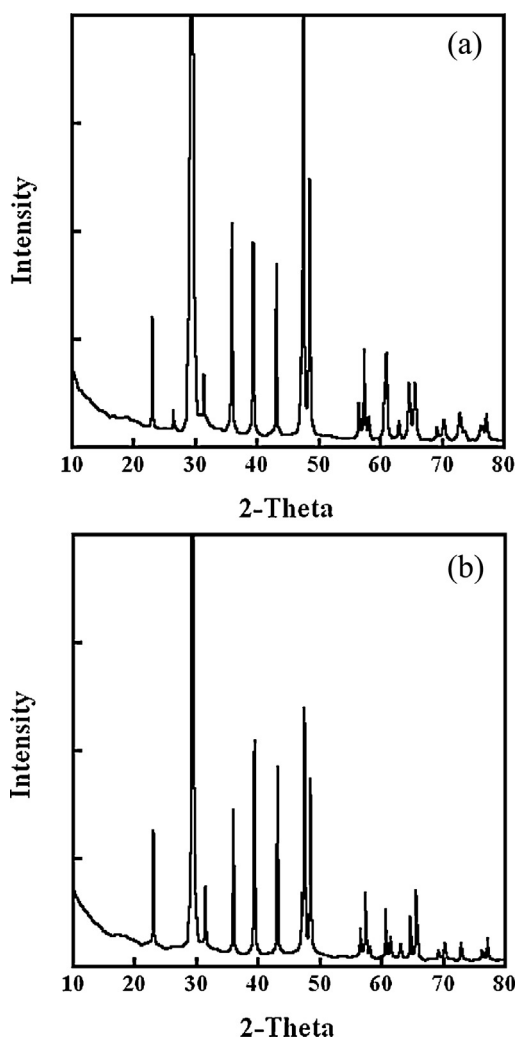


Fig. 2. XRD diffraction patterns of commercial calcium carbonate (a) and eggshell powder (b).

3.3. Water absorption

TPS has a strong ability to absorb water after storage for a long time. Therefore, it was necessary to improve the water resistance of TPS. The water absorption characteristics of the TPS and composites after being stored at 55%RH for 30 days are presented in Fig. 4. The water absorption of the TPS was 30.21%. For the composites, the water absorption decreased with increasing amounts of both commercial calcium carbonate and eggshell powder fillers. This was due to the hydrophobic characteristic of both the commercial calcium carbonate and the eggshell powder. Moreover, it was found that the water absorption of the TPS/EP composites was significantly lower than for the TPS/CC composites. For example, with a high amount of filler (40 wt.% and 50 wt.%), the water absorption was 11.73% and 11.37% for the TPS/EP composites and 14.02% and 13.82% for the TPS/CC composites, respectively. This was due to the good interaction between the eggshell powder and the TPS matrix that reduced the water absorption by the composites. These results can be related to the SEM micrographs in Fig. 3.

3.4. Biodegradation in soil

Fig. 5 presents the weight loss of the TPS, TPS/CC composites and TPS/EP composites during 15 days of soil burial. The weight loss is a reflection of the biodegradation process by the moisture and microorganism in the soil. The weight loss of TPS was 71.55% after 15 days of soil burial, whereas the weight loss of the TPS/EP composite was higher than for the TPS/CC composites. At 50 wt.% filler, the weight residue of the TPS/CC composite remained at 64.63% (35.37% weight loss) while the weight residue of the TPS/EP composite was only 47.72% (52.28% weight loss). The weight loss was accompanied by a change in the surface morphology of the samples. As can be observed in Fig. 6(a)–(e) the surface morphology of the TPS and the composites changed after the soil burial test for 15 days. The TPS had an irregular surface with large holes due to the high biodegradation rate of starch (Fig. 6(a)). On the other hand, the surface morphology of the composites also showed a rough surface with channels but they showed a more planar structure than for the TPS (Fig. 6(b)–(e)). This result indicated that both commercial calcium carbonate and eggshell powder hindered the penetration of water and microorganisms into the matrix. Moreover, the filler increased the hydrophobicity of the matrix that reduced the degradation rate. A similar result was reported by Wootthikanokkhan and Santayanon (2003) and Tang, Zou, Xiong, and Tang (2008). However, the TPS/EP composites showed more erosion than the TPS/CC composites. This phenomenon was again associated with the organic compounds in the eggshell powder and makes it easy

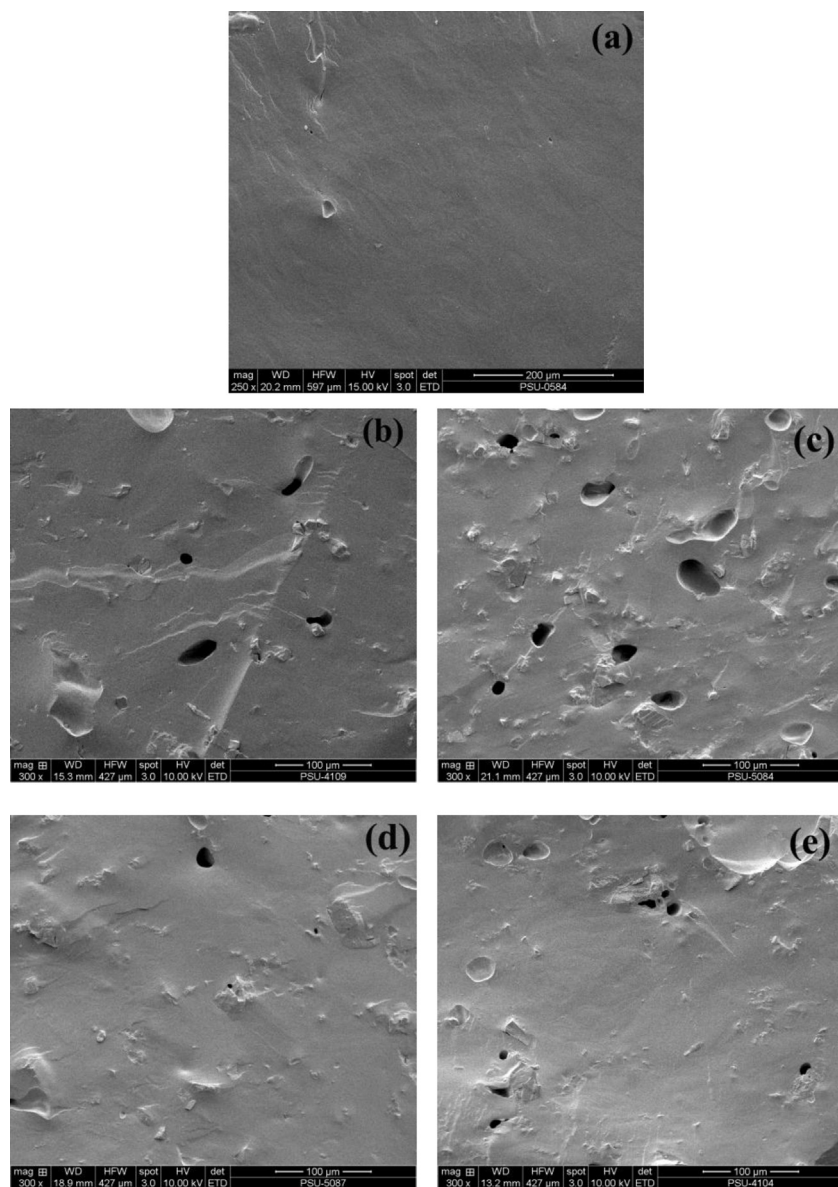


Fig. 3. SEM micrographs of TPS (a), TPS/CC composites with: 10 wt.%(b) and 30 wt.%(c) of commercial calcium carbonate and TPS/EP composites with: 10 wt.%(d) and 30 wt.%(e) of eggshell powder.

to attack by microorganisms. After the soil burial test for 30 days, the TPS, TPS/CC composites and TPS/EP composites at 10, 20, 30 and 40 wt.% fillers were completely degraded. However, the weight loss of the TPS/CC composite at 50 wt.% commercial calcium carbonate was 61.89% while TPS/EP composites at 50 wt.% eggshell powder was above 90%. It can be concluded that both commercial calcium carbonate and eggshell powder can retard the biodegradation rate of the TPS but the TPS/EP composites are more easily degraded by microorganism than the TPS/CC composites.

3.5. Thermal stability

Fig. 7 presents the thermogravimetric (TGA) curves of TPS, and the TPS/CC composites and TPS/EP composites with various filler content (10, 30 and 50 wt.%). There were two steps of weight loss in all samples. First, the weight loss from 50 °C to 200 °C, was assigned to the evaporation of water and glycerol (Amnuay, Katavut, Supranee, Pichan, & Claudio, 2011; Kaewtatip & Tanrattanakul, 2012) and the second step at the decomposition

temperature of 280–380 °C involved the decomposition of starch (Lopez et al., 2013; Teixeira et al., 2009). The thermal properties of the eggshell had been studied by Kang et al. (2010) who reported that the eggshell powder showed the first step of weight loss at 260–400 °C due to the CO₂ released after thermal degradation of the eggshell. However, it was difficult to observe an accurate position for this step because it overlapped with the major decomposition of starch. On the other hand, the temperature at the maximum rate of weight loss of the TPS was 333 °C. The addition of both commercial calcium carbonate and eggshell powder into the TPS matrix caused an increase in the thermal stability of the composites. For the TPS/CC composites, the temperature at the maximum rate of weight loss increased to 356 °C, 358 °C and 360 °C when the amount of the commercial calcium carbonate increased to 10, 30 and 50 wt.%, respectively, whereas the temperature at the maximum rate of weight loss of the TPS/EP composites was nearly identical to the TPS/CC composites that was 355 °C, 357 °C and 358 °C, respectively. It can be concluded that eggshell has similar properties to commercial calcium carbonate

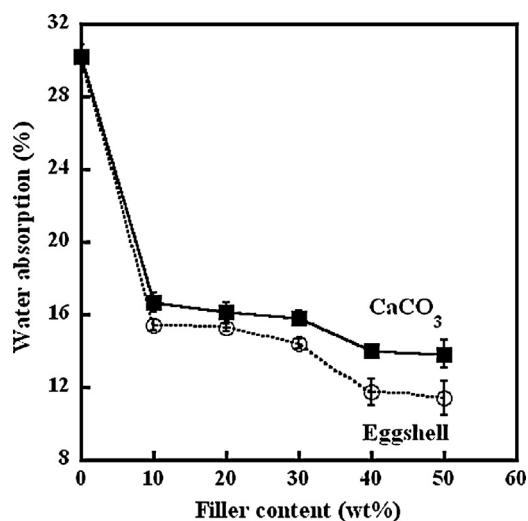


Fig. 4. Water absorption of TPS, TPS/CC composites and TPS/EP composites after being stored at 55%RH for 30 days.

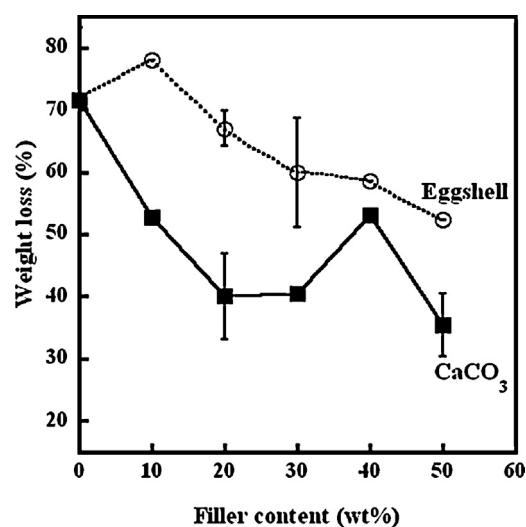


Fig. 5. Weight loss of TPS, TPS/CC composites and TPS/EP composites after the soil burial test for 15 days.

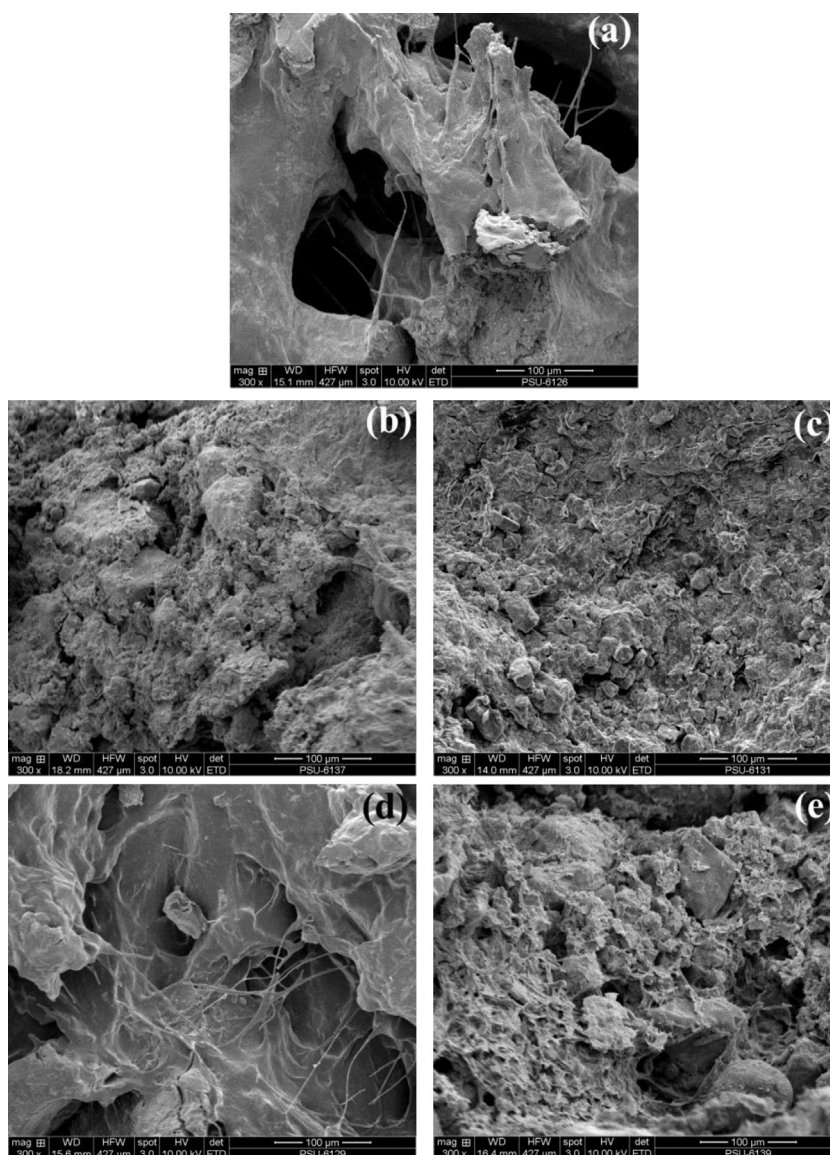


Fig. 6. SEM micrographs of TPS (a), TPS/CC composites with: 10 wt.% (b) and 30 wt.% (c) of commercial calcium carbonate and TPS/EP composites with: 10 wt.% (d) and 30 wt.% (e) of eggshell powder after the soil burial test for 15 days.

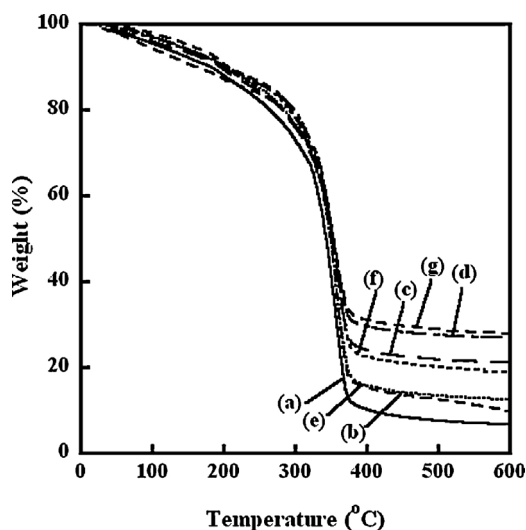


Fig. 7. TGA curves of TPS (a), TPS/CC composites with: 10 wt.% (b), 30 wt.% (c) and 50 wt.% (d) of commercial calcium carbonate and TPS/EP composites with: 10 wt.% (e), 30 wt.% (f) and 50 wt.% (g) of eggshell powder.

fillers that both show an improvement of the thermal stability of TPS.

4. Conclusions

In this study eggshell powder was used to improve the properties of TPS and was compared with adding commercial calcium carbonate. The results from the weight loss and surface morphology after the soil burial test for 15 days showed that both the eggshell powder and commercial calcium carbonate delayed the biodegradation of TPS. From the SEM micrographs, the eggshell powder was well dispersed and embedded in the TPS matrix, while the agglomeration of commercial calcium carbonate appeared to be due to the presence of organic compounds on the surface of the eggshell powder that improved the interaction between the eggshell powder and the TPS matrix. Moreover, the TPS/EP composites were degraded more quickly than the TPS/CC composites. The TPS/EP composites showed the lowest water absorption. TGA curves showed that the eggshell powder improved the thermal stability of TPS as well as the commercial calcium carbonate. Thus eggshell powder can be used as a filler for the TPS to replace commercial CaCO_3 and improve the properties of TPS.

Acknowledgements

We thank the Prince of Songkla University and the Faculty of Science for their financial support and Siam Modified Starch Co., Ltd. for their pregelatinized cassava starch. We would like to thank Dr. Apon Numnuam for suggestions about the chicken eggshell. Thanks also to Dr. Brian Hodgson for assistance with the English.

References

Amnuay, W., Katavut, P., Supranee, K., Pichan, S., & Claudio, M. (2011). Green composites of thermoplastic corn starch and recycled paper cellulose fibers. *Songklanakarin Journal of Science and Technology*, 33, 461–467.

Cho, Y., & Seo, G. (2010). High activity of acid-treated quail eggshell catalysts in the transesterification of palm oil with methanol. *Bioresource Technology*, 101, 8515–8519.

Corradini, E., Marconcini, J., Agnelli, J., & Mattoso, L. (2011). Thermoplastic blends of corn gluten meal/starch (CGM/Starch) and corn gluten meal/polyvinyl alcohol and corn gluten meal/poly (hydroxybutyrate-co-hydroxyvalerate) (CGM/PHB-V). *Carbohydrate Polymers*, 83, 959–965.

Fama, L., Pettarin, V., Goyanes, S., & Bernal, C. (2011). Starch/multi-walled carbon nanotubes composites with improved mechanical properties. *Carbohydrate Polymers*, 83, 1226–1231.

Franco, C., Cyran, V., Busalmen, J., Ruseckaite, R., & Vazquez, A. (2004). Degradation of polycaprolactone/starch blends and composites with sisal fibre. *Polymer Degradation and Stability*, 86, 95–103.

Gilfillan, W., Nguyen, D., Sopade, P., & Doherty, W. (2012). Preparation and characterisation of composites from starch and sugar cane fibre. *Industrial Crops and Products*, 40, 45–54.

Huang, M., Yu, J., & Ma, X. (2004). Studies on the properties of montmorillonite-reinforced thermoplastic starch composites. *Polymer*, 45, 7017–7023.

Ji, G., Zhu, H., Qi, C., & Zeng, M. (2009). Mechanism of interactions of eggshell microparticles with epoxy resins. *Polymer Engineering and Science*, 49, 1383–1388.

Kaewtatip, K., & Tanrattanakul, V. (2012). Structure and properties of pregelatinized cassava starch/kaolin composites. *Materials and Design*, 37, 423–428.

Kaewtatip, K., Tanrattanakul, V., & Kaewtatip, T. (2013). Preparation and characterization of thermoplastic starch/wheat gluten composites. *Key Engineering Materials*, 531–532, 321–324.

Kaewtatip, K., & Thongmee, J. (2012). Studies on the structure and properties of thermoplastic starch/luffa fiber composites. *Materials and Design*, 40, 314–318.

Kang, D., Pal, K., Park, S., Bang, D., & Kim, J. (2010). Effect of eggshell and silk fibroin on styrene-ethylene/butylene-styrene as bio-filler. *Materials and Design*, 31, 2216–2219.

Lopez, J., Mutje, P., Carvalho, A., Curvelo, A., & Giron, J. (2013). Newspaper fiber-reinforced thermoplastic starch biocomposites obtained by melt processing: Evaluation of the mechanical thermal and water sorption properties. *Industrial Crops and Products*, 44, 300–305.

Ma, X., Yu, J., & Wang, N. (2007). Fly ash-reinforced thermoplastic starch composites. *Carbohydrate Polymers*, 67, 32–39.

Moreira, F., Pedro, D., Glenn, G., Marconcini, J., & Mattoso, L. (2013). Brucite nanoplates reinforced starch bionanocomposites. *Carbohydrate Polymers*, 92, 1743–1751.

Phua, Y., Lau, N., Sudesh, K., Chow, W., & Ishak, Z. (2012). Biodegradability studies of poly(butylene succinate)/organo-montmorillonite nanocomposites under controlled compost soil conditions: Effects of clay loading and compatibiliser. *Polymer Degradation and Stability*, 97, 1345–1354.

Riyajan, S., Sasithornson, Y., & Phinyocheep, P. (2012). Green natural rubber-g-modified starch for controlling urea release. *Carbohydrate Polymers*, 89, 251–258.

Roz, A., Carvalho, A., Gandini, A., & Curvelo, A. (2006). The effect of plasticizers on thermoplastic starch compositions obtained by melt processing. *Carbohydrate Polymers*, 63, 417–424.

Roz, A., Zambon, M., Curvelo, A., & Carvalho, A. (2011). Thermoplastic starch modified during melt processing with organic acids: The effect of molar mass on thermal and mechanical properties. *Industrial Crops and Products*, 33, 152–157.

Shuhadah, S., & Supri, A. (2009). LDPE-Isophthalic acid-modified egg shell powder composites (LDPE/ESPI). *Journal of Physical Science*, 20(1), 87–98.

Takamine, K., Bhatnagar, S., & Hanna, M. (1995). Effect of eggshell on properties of corn starch extrudates. *Cereal Chemistry*, 72(4), 385–388.

Tang, S., Zou, P., Xiong, H., & Tang, H. (2008). Effect of nano- SiO_2 on the performance of starch/polyvinyl alcohol blend films. *Carbohydrate Polymers*, 72, 521–526.

Teixeira, E., Pasquini, D., Curvelo, A., Corradini, E., Belgacem, M., & Dufresne, A. (2009). Cassava bagasse cellulose nanofibrils reinforced thermoplastic cassava starch. *Carbohydrate Polymers*, 78, 422–431.

Toro, P., Quijada, R., Arias, J., & Yazdani-Pedram, M. (2007). Mechanical and morphological studies of poly(propylene)-filled eggshell composites. *Macromolecular Materials and Engineering*, 292, 1027–1034.

Toro, P., Quijada, R., Yazdani-Pedram, M., & Arias, J. (2007). Eggshell, a new bio-filler for polypropylene composites. *Materials Letters*, 61, 4347–4350.

Tsai, W., Yang, J., Lai, C., Cheng, Y., Lin, C., & Yeh, C. (2006). Characterization and adsorption properties of eggshells and eggshell membrane. *Bioresource Technology*, 97, 488–493.

Wang, X., Zhang, X., Liu, H., & Wang, N. (2009). Impact of pre-processing of montmorillonite on the properties of melt-extruded thermoplastic starch/montmorillonite nanocomposites. *Starch/Stärke*, 61, 489–494.

Wootthikanokkhan, J., & Santayanon, R. (2003). Modification of cassava starch by using propionic anhydride and properties of the starch-blended polyester polyurethane. *Carbohydrate Polymers*, 51, 17–24.

Xu, B., & Hanna, M. (2007). Effect of eggshell powder as nucleating agent on the structure, morphology and functional properties of normal corn starch foams. *Packaging Technology and Science*, 20, 165–172.

Yoo, S., Hsieh, J., Zou, P., & Kokoszka, J. (2009). Utilization of calcium carbonate particles from eggshell waste as coating pigments for ink-jet printing paper. *Bioresource Technology*, 100, 6416–6421.