

# Synthesis of Nanowire TiO<sub>2</sub> Thin Films by Hydrothermal Treatment and their Photoelectrochemical Properties

Masaaki Kitano · Ryo Mitsui · Diana Rakhmawaty Eddy ·  
Zeinhom M. A. El-Bahy · Masaya Matsuoka ·  
Michio Ueshima · Masakazu Anpo

Received: 19 June 2007 / Accepted: 5 August 2007 / Published online: 7 September 2007  
© Springer Science+Business Media, LLC 2007

**Abstract** Nanowire TiO<sub>2</sub> thin films were successfully prepared on Ti metal substrates by hydrothermal treatment of calcined Ti foils in 10 M NaOH. The nanowire TiO<sub>2</sub> thin films exhibited much larger surface area and higher photoelectrochemical performance than the TiO<sub>2</sub> thin films prepared on Ti metal substrates by the calcination of Ti foil. These nanowire films were shown to act as an efficient photoanodes for the photoelectrochemical water splitting reaction.

**Keywords** TiO<sub>2</sub> nanowire thin film · Photocatalyst · Hydrothermal synthesis · Water splitting

## 1 Introduction

Titanium oxide (TiO<sub>2</sub>) materials have been extensively investigated in areas such as photocatalysis and solar cells due to such advantages as their low cost, high photocatalytic reactivity and chemical stability [1–3]. It is known that various factors, such as its particle size [4–6], surface area [7], and crystallinity [7–10], affect the photocatalytic activity of TiO<sub>2</sub>. Therefore, the precise control of these parameters can be considered essential in obtaining highly active TiO<sub>2</sub> photocatalysts. Since the pioneering work of

Kasuga et al. [11, 12] in which TiO<sub>2</sub> nanotubes were prepared by the simple one-step hydrothermal treatment of TiO<sub>2</sub> crystals with a NaOH aqueous solution, various studies on the synthesis of nanostructured TiO<sub>2</sub>, such as nanotubes [13–15], nanowires [16, 17], and nanofibers [18], have been carried out. However, most of the nanostructured TiO<sub>2</sub> prepared by hydrothermal treatment are obtained in powder form of neither anatase nor rutile phase [13, 17, 18] and are difficult to handle for practical or industrial use [19, 20]. Therefore, these TiO<sub>2</sub> materials exhibit low photocatalytic activity. The development of nanostructured TiO<sub>2</sub> thin films with good crystallinity would, therefore, be of great importance not only as effective photocatalysts but also for such applications as gas sensors, photovoltaic cells, high surface area electrodes, etc. Along these lines, we have successfully prepared nanowire TiO<sub>2</sub> thin films by hydrothermal treatment of calcined Ti foil in NaOH aqueous solution. These films were shown to exhibit a remarkable enhancement in the photoelectrochemical oxidation of water under UV light irradiation [21]. Moreover, Yang et al. [22] have also reported the formation of rutile nanotube-like TiO<sub>2</sub> electrodes using a similar method.

In the present work, nanowire TiO<sub>2</sub> thin films have been prepared by a simple hydrothermal treatment and their characteristics, photoelectrochemical properties, and photocatalytic activities for the water splitting reaction have been investigated.

## 2 Experimental

### 2.1 Preparation of TiO<sub>2</sub> nanowire thin films

TiO<sub>2</sub> thin films (TiO<sub>2</sub>/Ti) were prepared on a Ti metal substrate by calcining Ti metal foil of 0.25 mm thickness at

M. Kitano · M. Ueshima  
Industry-University Cooperation Organization, Osaka Prefecture  
University, 1-2 Gakuen-cho, Naka-ku, Sakai,  
Osaka 599-8570, Japan

R. Mitsui · D. R. Eddy · Z. M. A. El-Bahy · M. Matsuoka ·  
M. Anpo (✉)  
Department of Applied Chemistry, Graduate School  
of Engineering, Osaka Prefecture University, 1-1 Gakuen-cho,  
Naka-ku, Sakai, Osaka 599-8531, Japan  
e-mail: anpo@chem.osakafu-u.ac.jp

873 K for 5 h in air. These TiO<sub>2</sub> thin films were then subjected to reactions with 10 M NaOH aqueous solution in a Teflon-lined stainless autoclave and kept for 12–72 h at 393 K. After cooling to room temperature (rt), the films were washed in 0.1 M HCl solution and nanowire TiO<sub>2</sub> thin films were obtained. These nanowire films were referred to as nw-TiO<sub>2</sub>(X)/Ti, where X is the time (h) of hydrothermal treatment.

## 2.2 Photoelectrochemical Measurements

The photoelectrochemical properties of the TiO<sub>2</sub> thin film electrodes were evaluated using a potentiostat (HZ3000, Hokuto Denko). The three-electrode cell consisted of the TiO<sub>2</sub> thin film electrode, a Pt electrode and a saturated calomel electrode (SCE) as the working, counter and reference electrodes, respectively. The working electrode was irradiated from the front side (light incident on the electrolyte/electrode interface) by a 500 W Xe lamp or 500 W high pressure Hg lamp in 0.25 M K<sub>2</sub>SO<sub>4</sub> solution which was mechanically stirred and purged with 99.99% pure Ar gas before and during the experiment. The area of the working electrode exposed to light was about 0.2 cm<sup>2</sup>. The incident photon to current conversion efficiency (IPCE), defined as the number of electrons collected per incident photon, was determined by measuring the photocurrent ( $I_{ph}$ ) of the electrodes at each excitation wavelength and by using the following equation [23, 24]:

$$\text{IPCE}(\%) = \left\{ \left[ 1240 \times I_{ph} (\text{A/cm}^2) \right] / \left[ \lambda (\text{nm}) \times I_{inc} (\text{W/cm}^2) \right] \right\} \times 100$$

where  $I_{inc}$  is the incident light intensity (W/cm<sup>2</sup>), and  $\lambda$  is the excitation wavelength (nm). Light irradiation was carried out using a 500 W Xe arc lamp with an interference filter ( $\lambda_{max}$  = 360 nm, half width: 22.9 nm). The incident light intensity ( $I_{inc}$ ) was measured by a laser power meter ( $I_{inc}$  = 435  $\mu\text{W/cm}^2$ ).

## 2.3 Photoelectrochemical Reactions

The separate evolution of H<sub>2</sub> and O<sub>2</sub> from water was investigated using an H-type Pyrex glass container connected to a vacuum system (10<sup>−3</sup> Pa) and the detailed experimental procedures are described in previous literature [25, 26]. The back side of TiO<sub>2</sub>/Ti or nw-TiO<sub>2</sub>(X)/Ti where the Ti metal surface is exposed was deposited with Pt by a radio frequency (RF) magnetron sputtering deposition method with an RF power of 70 W under a substrate temperature of 298 K. These Pt-loaded TiO<sub>2</sub> thin films were referred to as TiO<sub>2</sub>/Ti/Pt and nw-TiO<sub>2</sub>(X)/Ti/Pt. The

container consists of two water phases separated by a TiO<sub>2</sub> thin film and proton-exchange membrane (Nafion film). Prior to the reaction, the reaction cell was de-aerated by purging with 99.99% pure Ar gas for 3 h. Light irradiation was carried out with a 500 W Xe arc lamp through the reaction cell and the evolved H<sub>2</sub> and O<sub>2</sub> were analyzed by a gas chromatograph (GC, G2800-T, Yanaco) with a thermal conductivity detector (TCD).

## 2.4 Characterizations


The crystal structure of the TiO<sub>2</sub> thin films was investigated by X-ray diffractometer analysis (XRD, XRD-6100, Shimadzu). The morphologies of the TiO<sub>2</sub> thin films were observed by scanning electron microscopy (SEM, S-4500, Hitachi) and the surface compositions of the TiO<sub>2</sub> thin films were obtained by X-ray photoelectron spectroscopy (XPS, ESCA-3200, Shimadzu).

## 3 Results and Discussions

Figure 1 shows the SEM images of the TiO<sub>2</sub>/Ti thin films before and after hydrothermal treatment in 10 M NaOH aqueous solution. After 12 h hydrothermal treatment, the nanowire structures could be partially observed on the Ti substrate. The nw-TiO<sub>2</sub>(24)/Ti exhibited complicated surface structures consisting of the numerous stacking of nanowires having a diameter of around 30–50 nm and showing a remarkable contrast to TiO<sub>2</sub>/Ti which has a smooth flat surface. Furthermore, it was found that the XPS spectra of the nw-TiO<sub>2</sub>(X)/Ti thin films show only the peaks assigned to Ti 2p and O 1s and no peak assigned to Na 1s, showing that Na<sup>+</sup> ions are effectively removed by washing with HCl aqueous solution after hydrothermal treatment (data not shown).

The effect of hydrothermal treatment on the surface area of the TiO<sub>2</sub>/Ti thin films was investigated by BET surface measurements using krypton gas as the adsorbate. As summarized in Table 1, the surface area of the TiO<sub>2</sub>/Ti thin film increased as the time of hydrothermal treatment increased. The surface area of nw-TiO<sub>2</sub>(48)/Ti was 15 times larger than that of TiO<sub>2</sub>/Ti. Figure 2 shows the XRD patterns of the TiO<sub>2</sub>/Ti and nw-TiO<sub>2</sub>(X)/Ti thin films. The TiO<sub>2</sub>/Ti film shows XRD peaks due to the Ti metal and rutile phase, while the peak intensity of the rutile phase for the nw-TiO<sub>2</sub>(X)/Ti films decreased depending on the length of hydrothermal treatment. It has been reported that nanotube materials obtained by the reaction of TiO<sub>2</sub> powder with concentrated NaOH are composed of a layered titanate, such as Na<sub>x</sub>H<sub>2−x</sub>Ti<sub>3</sub>O<sub>7</sub>, H<sub>2</sub>Ti<sub>4</sub>O<sub>9</sub>·H<sub>2</sub>O, H<sub>2</sub>Ti<sub>2</sub>O<sub>4</sub>(OH)<sub>2</sub>, etc., rather than anatase or rutile phase TiO<sub>2</sub> [13, 17,

**Fig. 1** SEM images of (a) TiO<sub>2</sub>/Ti and (b–d) nw-TiO<sub>2</sub>(X)/Ti thin films. The (d) image shows a lower magnification image of (c)

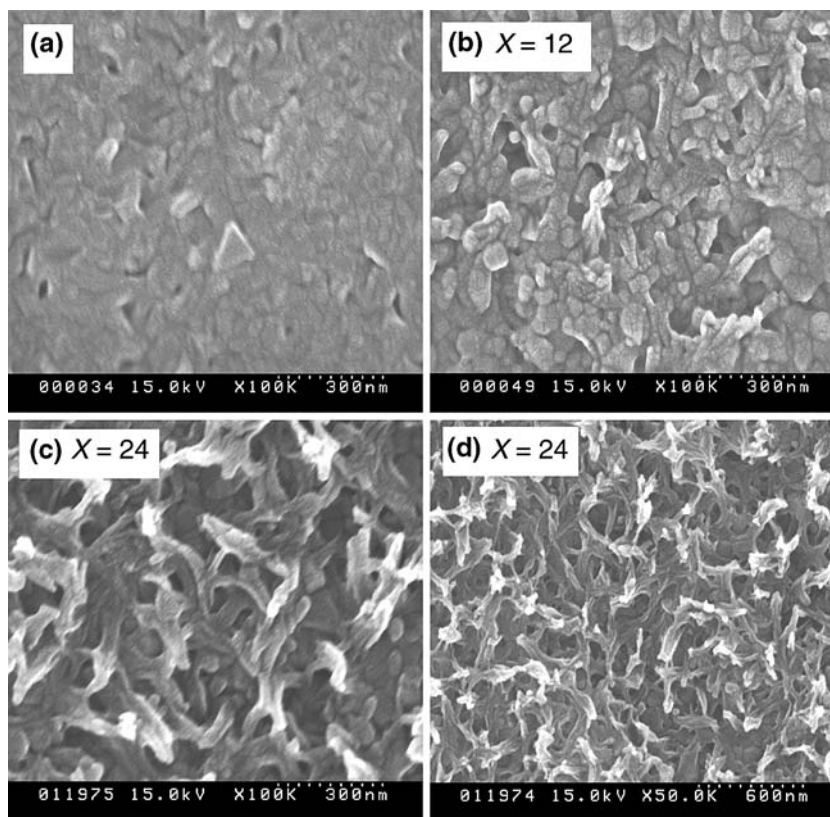

**Table 1** Surface areas of TiO<sub>2</sub>/Ti and nw-TiO<sub>2</sub>(X)/Ti thin films

| Sample                      | $A_{\text{bet}}^a (\text{cm}^2)$ |
|-----------------------------|----------------------------------|
| TiO <sub>2</sub> /Ti        | 26                               |
| nw-TiO <sub>2</sub> (12)/Ti | 80                               |
| nw-TiO <sub>2</sub> (24)/Ti | 167                              |
| nw-TiO <sub>2</sub> (48)/Ti | 414                              |
| nw-TiO <sub>2</sub> (72)/Ti | 428                              |


<sup>a</sup> Sample size: 5 × 20 mm<sup>2</sup>

18]. However, nw-TiO<sub>2</sub>(X)/Ti thin films show no XRD peak at around  $2\theta = 10^\circ$  due to the layered titanate.

Nanostructured TiO<sub>2</sub> films are photoactive as they undergo charge separation when subjected to the following band gap excitation (1):




where  $e_{\text{CB}}$  and  $h_{\text{VB}}$  represent the conduction band electrons and valence band holes, respectively. The photogenerated electrons can be readily collected at the conducting surface in a photoelectrochemical cell [23, 27]. Photoelectrochemical measurements were performed using a standard three-electrode system consisting of a working electrode (TiO<sub>2</sub>/Ti, nw-TiO<sub>2</sub>(X)/Ti), Pt wire counter electrode and SCE reference electrode in an Ar-purged 0.25 M K<sub>2</sub>SO<sub>4</sub> aqueous solution. Figure 3 shows the current–potential

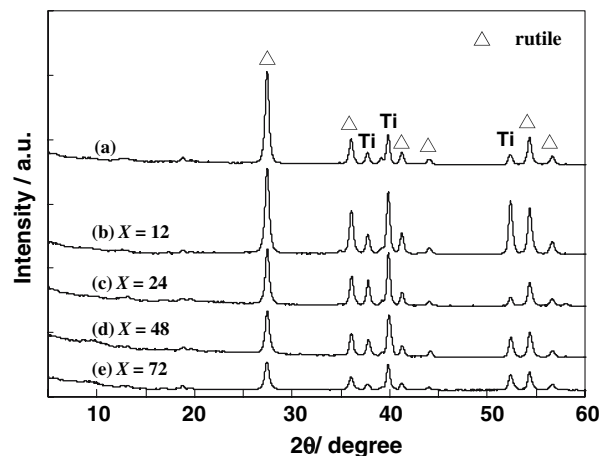


**Fig. 2** XRD patterns of (a) TiO<sub>2</sub>/Ti and (b–e) nw-TiO<sub>2</sub>(X)/Ti thin films

curves of the TiO<sub>2</sub>/Ti and nw-TiO<sub>2</sub>(X)/Ti electrodes. Dark currents were negligible under scanning potentials of −0.5 to +1.5 V vs. SCE, while the anodic photocurrent increased with an increase in the anodic bias. The observed photocurrent represents the anodic oxidation of water to oxygen by the photogenerated holes at the nw-TiO<sub>2</sub>(X)/Ti film electrode under UV light irradiation. Moreover, it can be seen that the photocurrent increased with an increase in the treatment time, reaching a plateau at 48 h and suggesting

that nw-TiO<sub>2</sub>(X)/Ti electrodes exhibit much higher photocurrent than the TiO<sub>2</sub>/Ti electrode. The nw-TiO<sub>2</sub>(X)/Ti films have the advantage of having a short diffusion length of the photoformed holes in the bulk to surface. Moreover, the electrolyte solution can penetrate into the interspaces throughout the film. The incident photons are also more efficiently absorbed on film having a rough surface than a flat one since light trapping through scattering at the surface of the structure is enhanced on a rough surface [28]. In order to investigate the stability of nw-TiO<sub>2</sub>(48)/Ti, current–potential curves were measured repeatedly under irradiation with the full arc of a 500 W high pressure Hg lamp. Although the anodic photocurrent slightly decreased with repeated scanning, it approached a saturated value of around 7.5 mA after 1 h. These results suggest that the nanowire structure is kept stable during the reaction and the photocurrent is not based on the oxidation of nw-TiO<sub>2</sub>(48)/Ti itself but on the oxidation of water. In fact, no noticeable changes in the SEM images nw-TiO<sub>2</sub>(48)/Ti before or after photoelectrochemical measurements could be observed. Figure 4 shows the photocurrents observed for the TiO<sub>2</sub>/Ti and nw-TiO<sub>2</sub>(48)/Ti electrode as a function of the wavelengths controlled by the cut-off filters. Light irradiation was carried out with a 500 W Xe arc lamp. As shown in Fig. 4, the nw-TiO<sub>2</sub>(48)/Ti electrode exhibited a higher photocurrent than the TiO<sub>2</sub>/Ti electrode and the onset of the photocurrent for both nw-TiO<sub>2</sub>(48)/Ti and TiO<sub>2</sub>/Ti electrode was observed at a wavelength of around 400–410 nm, corresponding to the energy gaps for rutile, 3.0 eV. The incident photon to current conversion efficiencies (IPCE) of TiO<sub>2</sub>/Ti and nw-TiO<sub>2</sub>(48)/Ti electrode under UV light irradiation ( $\lambda = 360$  nm) were determined to be 13.1 % and 23.7 %, respectively.

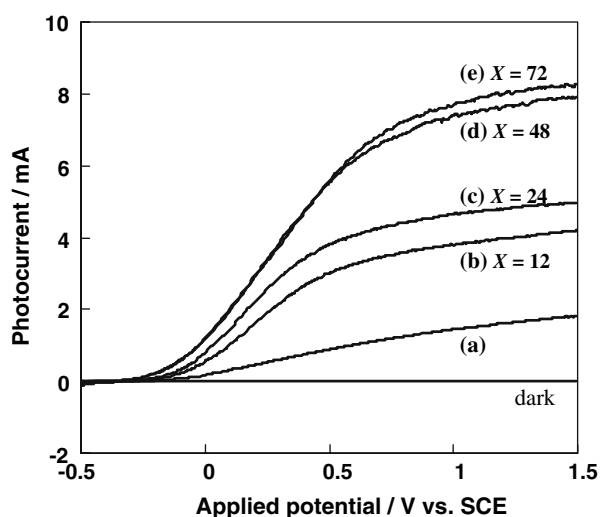


**Fig. 3** Current–potential curves of (a) TiO<sub>2</sub>/Ti and (b–e) nw-TiO<sub>2</sub>(X)/Ti thin films. Light source: 500 W high pressure Hg lamp

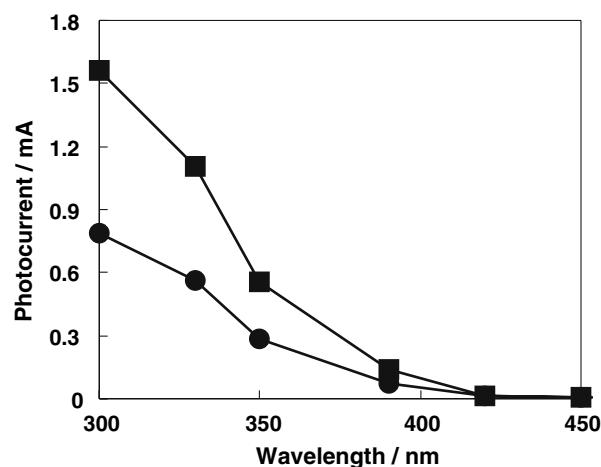


**Fig. 4** The relative photocurrent as a function of the cut-off wavelength of incident light for (●) TiO<sub>2</sub>/Ti and (■) nw-TiO<sub>2</sub>(48)/Ti measured in 0.25 M K<sub>2</sub>SO<sub>4</sub> aqueous solution at +1.0 V vs. SCE

The photocatalytic activity of TiO<sub>2</sub>/Ti/Pt and nw-TiO<sub>2</sub>(48)/Ti/Pt was investigated for the separate evolution of H<sub>2</sub> and O<sub>2</sub> from water under UV light irradiation. The TiO<sub>2</sub>/Ti/Pt or nw-TiO<sub>2</sub>(48)/Ti/Pt photocatalyst was mounted at the center of an H-type glass container, separating the two aqueous solutions, as shown in Fig. 5. A Nafion film was also mounted on the H-type glass container to provide the electrical connections which allowed the electron transfer between the two separated aqueous phases, playing the same role as a salt bridge between two aqueous phases. The TiO<sub>2</sub> side of the photocatalyst was immersed in 1.0 M NaOH and the Pt side was immersed in 0.5 M H<sub>2</sub>SO<sub>4</sub> aqueous solution in order to add a small chemical bias to assist the electron transfer from the TiO<sub>2</sub> to Pt side through the metal substrate. Figure 6 shows the separate evolution reaction of H<sub>2</sub> and O<sub>2</sub> under irradiation with the full arc of a 500 W Xe lamp. Water was decomposed into H<sub>2</sub> and O<sub>2</sub> separately with a good linearity against the irradiation time and nw-TiO<sub>2</sub>(48)/Ti/Pt exhibited much higher activity than TiO<sub>2</sub>/Ti/Pt. It was, thus, clearly shown that the observed photocurrent is attributed not to the irreversible oxidation of nw-TiO<sub>2</sub>(48)/Ti, but to the photoinduced oxidation of water to O<sub>2</sub>. Previously, we showed that TiO<sub>2</sub> thin films which act as efficient photoanodes for the photoelectrochemical water splitting reaction also exhibit high photocatalytic activity for such significant reactions as the purification of toxic compounds in polluted water and air as well as the decomposition of water [24–26]. These results indicate that the nanowire TiO<sub>2</sub> thin film can act as an efficient photocatalyst for the decomposition of water for the separate evolution of H<sub>2</sub> and O<sub>2</sub> from H<sub>2</sub>O under UV light irradiation. Highly active nanowire TiO<sub>2</sub> thin films could, thus, be easily prepared using low cost materials such as Ti foil.



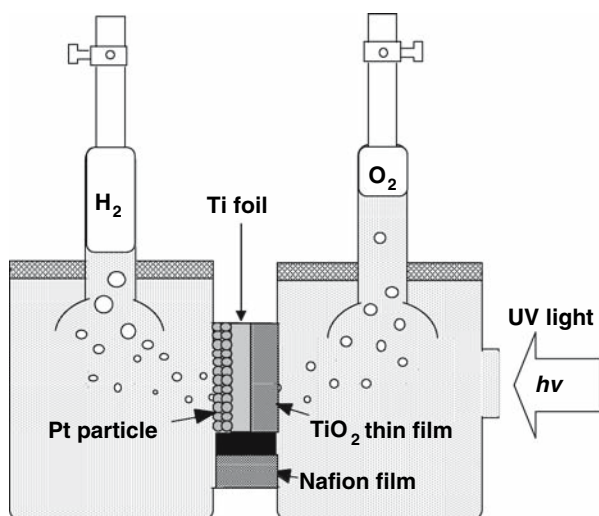

**Fig. 5** H-type glass container for the separate evolution of H<sub>2</sub> and O<sub>2</sub> using a TiO<sub>2</sub>/Ti/Pt thin film photocatalyst (TiO<sub>2</sub> side: 1.0 M NaOH aq; Pt side: 0.5 M H<sub>2</sub>SO<sub>4</sub> aq)

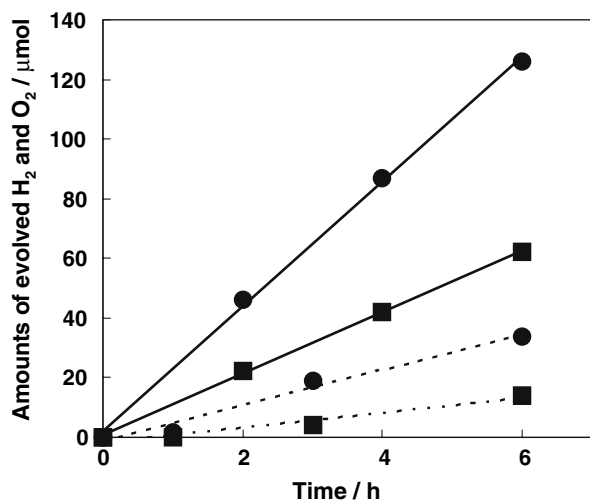

**Fig. 6** Reaction time profiles of the separate evolution of (●) H<sub>2</sub> and (■) O<sub>2</sub> under irradiation with the full arc of a 500 W Xe lamp on nw-TiO<sub>2</sub>(48)/Ti/Pt (solid line) and TiO<sub>2</sub>/Ti/Pt (broken line) in an H-type glass container. Irradiation area: 10 × 20 mm<sup>2</sup>

#### 4 Conclusions

Nanowire TiO<sub>2</sub> thin films (nw-TiO<sub>2</sub>/Ti) were synthesized by hydrothermal treatment of calcined Ti foil (TiO<sub>2</sub>/Ti) in 10 M NaOH aqueous solution at 393 K. The surface area of nw-TiO<sub>2</sub>/Ti was 15 times larger than that of TiO<sub>2</sub>/Ti. The nw-TiO<sub>2</sub>/Ti electrode was found to exhibit higher photocurrent than TiO<sub>2</sub>/Ti due to the short diffusion length of the photoformed holes from the bulk to surface. Moreover, the nw-TiO<sub>2</sub>/Ti photocatalyst exhibited higher photocatalytic reactivity for the separate evolution of H<sub>2</sub>

and O<sub>2</sub> under UV light irradiation than TiO<sub>2</sub>/Ti, thus, showing the potential for various applications as functional photocatalysts and photoelectrodes.

#### References

- Hoffmann MR, Martin ST, Choi WY, Bahnemann DW (1995) *Chem Rev* 95:69
- Anpo M (2004) *Bull Chem Soc Jpn* 77:1427
- Anpo M, Dohshi S, Kitano M, Hu Y, Takeuchi M, Matsuoka M (2005) *Annu Rev Mater Res* 35:1
- Anpo M, Shima T, Kodama S, Kubokawa Y (1987) *J Phys Chem* 91:4305
- Sclafani A, Palmisano L, Schiavello M (1990) *J Phys Chem* 94:829
- Zhang ZB, Wang CC, Zakaria R, Ying JY (1998) *J Phys Chem B* 102:10871
- Kominami H, Murakami S, Kato J, Kera Y, Ohtani B (2002) *J Phys Chem B* 106:10501
- Mills A, Porter G (1982) *J Chem Soc Faraday trans 1* 78:3659
- Stone VF, Davis RJ (1998) *Chem Mater* 10:1468
- Torimoto T, Nakamura N, Ikeda S, Ohtani B (2002) *Phys Chem Chem Phys* 4:5910
- Kasuga T, Hiramatsu M, Hoson A, Sekino T, Niihara K (1998) *Langmuir* 14:3163
- Kasuga T, Hiramatsu M, Hoson A, Sekino T, Niihara K (1999) *Adv Mater* 15:1307
- Du GH, Chen Q, Che RC, Yuan ZY, Peng LM (2001) *Appl Phys Lett* 79:3702
- Wang YQ, Hu GQ, Duan XF, Sun HL, Xue QK (2002) *Chem Phys Lett* 365:427
- Tsai CC, Teng H (2004) *Chem Mater* 16:4352
- Kavan L, Kalbac M, Zukalova M, Exnar I, Lorenzen V, Nesper R, Grätzel M (2004) *Chem Mater* 16:477
- Yoshida R, Suzuki Y, Yoshikawa S (2005) *J Solid State Chem* 178:2179
- Yuan ZY, Su BL (2004) *Colloid Surf A-Physicochem Eng Asp* 241:173
- Adachi M, Murata Y, Yoshikawa S (2000) *Chem Lett* 8:942
- Tian ZR, Voigt JA, Liu J, Mckenzie B, Xu H (2003) *J Am Chem Soc* 125:12384
- Kitano M, Ueshima M, Matsuoka M, Anpo M (2006) In: *Abstracts of spring meeting of Japan society of powder and powder metallurgy*. The Japan Society of Powder and Powder Metallurgy, Tokyo, p 147
- Yang SG, Quan X, Li XY, Sun C (2006) *Photochem Photobiol Sci* 5:808
- Kikuchi H, Kitano M, Takeuchi M, Matsuoka M, Anpo M, Kamat PV (2006) *J Phys Chem B* 110:5537
- Kitano M, Funatsu K, Matsuoka M, Ueshima M, Anpo M (2006) *J Phys Chem B* 110:25266
- Kitano M, Tsujimaru K, Anpo M (2006) *Appl Catal A Gen* 314:179
- Kitano M, Takeuchi M, Matsuoka M, Thomas JM, Anpo M (2007) *Catal Today* 120:133
- Kavan L, Grätzel M, Gillbert SE, Klemenz C, Scheel HJ (1996) *J Am Chem Soc* 118:6716
- Zhao JH, Wang AH, Green MA, Ferrazza F (1998) *Appl Phys Lett* 73:1991