

Preparation and Characterization of Porous Gold and Its Application as a Platform for Immobilization of Acetylcholine Esterase

Olga V. Shulga,^{†,‡} Kenise Jefferson,^{†,‡} Abdul R. Khan,[†] Valerian T. D'Souza,[†] Jingyue Liu,^{†,‡} Alexei V. Demchenko,^{†,‡} and Keith J. Stine^{*,†,‡}

Department of Chemistry and Biochemistry and Center for Nanoscience, University of Missouri–St. Louis, St. Louis, Missouri, 63121

Received January 25, 2007. Revised Manuscript Received June 4, 2007

We report a method for the fabrication of a free-standing porous gold material with a high surface area and well-defined, tunable pore morphology. Porous gold is formed via a simple procedure that involves acidic treatment of a commercially available complex white gold alloy. We used SEM and AFM techniques to characterize the surface morphology, size, and shape of the mesopores as well as the surface roughness of the prepared porous gold samples. Formation of self-assembled monolayers of a flavin sulfide on the gold surface was used to estimate the total surface area of the porous gold material. The monolayers were found to be electrochemically active by cyclic and square wave voltammetry. It was found that 24 h HNO₃ treatment gave a 12 400× surface enlargement and resulted in a surface area of 14.2 m²/g, whereas 72 h HNO₃ treatment resulted in a 6900× surface enlargement and a surface area of 8.2 m²/g. In addition, the enzyme acetylcholine esterase was immobilized on the different porous gold surfaces to demonstrate biocompatibility of the porous gold material. Kinetic parameters and the amount of the immobilized acetylcholine esterase were determined.

Introduction

Porous gold has attracted considerable attention in a wide range of applications including catalysis, fuel cells,^{1,2} cell imaging,³ energy storage,⁴ investigation of the critical behavior of liquid helium,⁵ and development of chemical sensors^{6–8} due to its high surface-to-volume ratio, stability, and biocompatibility.

Common methods for the preparation of porous gold include the formation of a gold/silver alloy used as a precursor followed by dealloying with concentrated nitric acid during which silver is removed, resulting in a highly porous structure of gold.⁹ Dealloying is frequently followed by thermal annealing to adjust the pore size. Gold/silver alloys can be prepared by electrodeposition from a solution

containing both Au(CN)₂[−] and Ag(CN)₂[−] at −1.2 V¹⁰, by arc melting of pure elements in an ampule under inert atmosphere^{11,12} or by sputtering pure gold and silver onto a substrate.¹³ Other methods of porous gold preparation include the use of templates,¹⁴ thermal decomposition of Au₂O₃, sublimation of iodine from Au–I₂ pressed powders,¹⁵ electrochemical treatment of polycrystalline gold,¹⁶ and dissolution of gold chloride in a dextran solution followed by heating to 600–800 °C.¹⁷ Porous gold also can be generated by applying a sufficiently positive electrochemical potential to Au-containing alloy films^{18,19} and by electrochemically dealloying Au–Zn films prepared on Au wires.²⁰

One of the most attractive avenues for the application of porous gold material is its use as a solid support for the immobilization of biomolecules such as enzymes and antibodies. Immobilization of enzymes on solid supports plays a major role in modern biosensor technology, while

* Corresponding author. Phone: (314) 516-5346; fax: (314) 516-5342; e-mail: kstine@umsl.edu.

[†] Department of Chemistry and Biochemistry.

[‡] Center of for Nanoscience.

- (1) West, J. L.; Hatas, N. J. *Ann. Rev. Biomed. Eng.* **2003**, *5*, 285–296.
- (2) Ding, Y.; Chen, M. W.; Erlebacher, J. J. *Am. Chem. Soc.* **2004**, *126*, 6876–6877.
- (3) Shukla, S.; Priscilla, A.; Banerjee, M.; Bhone, R.; Ghatak, J.; Satyam, P. V.; Sastry, M. *Chem. Mater.* **2005**, *17*, 5000–5005.
- (4) Gregory, S.; Torsten, R.; Burkhard, R. *J. Electroanal. Chem.* **2002**, *526*, 125–133.
- (5) Csathy, G. A.; Tulimieri, D.; Yoon, J.; Chan, M. H. W. *Phys. Rev. Lett.* **1998**, *80*, 4482–4485.
- (6) Bonroy, K.; Friedt, J.-M.; Frederix, F.; Laureyn, W. Langerock, S.; Campitelli, A.; Sara, M.; Borghs, G.; Goddeeris, B.; Declerck, P. *Anal. Chem.* **2004**, *76*, 4299–4306.
- (7) Wang, X.-Y.; Zhong, H.; Lv, Y.; Chen, H.-Y. *Chem. Lett.* **2003**, *32*, 1054–1055.
- (8) Noort, D.; Rani, R.; Mandenius, C.-F. *Microchim. Acta* **2001**, *136*, 49–53.
- (9) Erlebacher, J.; Aziz, M.; Karma, A.; Dimitrov, N.; Sieradzki, K. *Nature* **2001**, *410*, 450–453.

- (10) Ji, C.; Searson, P. C. *J. Phys. Chem. B* **2003**, *107*, 4494–4499.
- (11) Dursun, A.; Pugh, D. V.; Corcoran, S. G. *J. Electrochem. Soc.* **2005**, *152*, 65–72.
- (12) Parida, S.; Kramer, D.; Volkert, C. A.; Erlebacher, J.; Weissmüller, J. *Phys. Rev. Lett.* **2006**, *97*, 35504-1–35504-4.
- (13) Wagner, K.; Brankovic, S. R.; Dimitrov, N.; Sieradzki, K. *J. Electrochem. Soc.* **1997**, *144*, 3545–3555.
- (14) Attard, G. S.; Bartlett, P. N.; Coleman, N. R. B.; Elliot, J. M.; Owen, J.; Wang, J. H. *Science* **1997**, *278*, 838–840.
- (15) Jurczakowski, R.; Hitz, C.; Lasia, A. *J. Electroanal. Chem.* **2004**, *572*, 355–366.
- (16) Hoogvliet, J. C.; Dijkma, M.; Kamp, B.; Bennekomp, W. P. *Anal. Chem.* **2000**, *72*, 2016–2021.
- (17) Walsh, D.; Arcelli, L.; Ikoma, T.; Tanaka, J.; Mann, S. *Nat. Mater.* **2003**, *2*, 386–390.
- (18) Sieradzki, K.; Dimitrov, N.; Movrin, D.; McCall, C.; Vasiljevic, N.; Erlebacher, J. *J. Electrochem. Soc.* **2002**, *149*, 370–377.
- (19) Senior, N. A.; Newman, R. C. *Nanotechnology* **2006**, *17*, 2311–2316.
- (20) Haung, J.-F.; Sun, I.-W. *Adv. Funct. Mater.* **2005**, *15*, 989–994.

immobilized antibodies are often used to devise highly selective immunoassays for diagnostic purposes. Duan and Meyerhoff^{21,22} used gold coated porous nylon membranes to develop a colorimetric ELISA for human chorionic gonadotropin (hCG). Ducey and Meyerhoff²³ used microporous gold as an electrochemical biosensor for flow injection HPLC analysis and postcolumn detection of catechol and phenol. Jurica²⁴ and co-workers used porous gold electrodes prepared by potentiostatic or galvanostatic treatment of disposable porous working electrodes with solutions of HAuCl₄, for flow-through stripping coulometric detection of As(III) and total As in water samples. Noort and co-workers⁸ demonstrated the application of porous gold for the immobilization of human anti-myoglobin. A porous gold nanoparticle–CaCO₃ hybrid material was used by Cai and co-workers for the immobilization of horseradish peroxidase.²⁵ Thin films of porous gold of 20–100 nm thickness have been prepared on the surface of microcantilevers and then modified with a thiolated β -cyclodextrin derivative and shown to sensitively detect tetrachloroethylene vapor.²⁶ The modified cantilevers were also applied to detect biotin–avidin interactions in solution.²⁷

The activity of enzymes immobilized into porous materials has been extensively investigated. A large number of porous matrices such as polymers,²⁸ inorganic sol–gels,^{29,30} silica,^{31,32} and alumina³³ has been used for enzyme immobilization. A number of researchers has described the effect of entrapment or attachment of the enzyme to the porous solid support on the overall kinetics of the enzyme.^{32,34,35} It has been shown that kinetic parameters are affected by several factors. On one hand, the quaternary structure of the enzyme as well as the orientation of the tertiary structure is altered by immobilization, which may lead to insufficient exposure of the active site. On the other hand, when immobilization takes place in the porous material, other factors such as pore size and morphology, nature of porous material, and diffusion of the substrate in and the product out of the pores may contribute to much more complicated kinetic behavior.

The current paper describes the preparation of large and free-standing samples of porous gold from a convenient and

not previously used starting material, characterization of the resulting material by scanning electron and atomic force microscopies, and its application for the immobilization of the enzyme acetylcholine esterase. Efforts were made to estimate the total surface area of the material using solution depletion of a flavin sulfide, which forms self-assembled monolayers and is also a strong chromophore, with comparison of the results to classical BET adsorption data. The self-assembled monolayers were studied using cyclic and square wave voltammetry. The kinetics of the bulk and immobilized enzyme was investigated and compared, and the amount of enzyme adsorbed was estimated.

Materials and Methods

10 carat white gold (2 in. \times 2 in. piece, 30 GA, 0.25 mm thick) was purchased from Hoover and Strong (Richmond, VA). The stated atomic composition of this commercial alloy, used by jewelers, is 41.8% Au, 5% Ag, 30–35% Cu, 8–9% Zn, and 15–20% Ni. Acetylcholine esterase (AChE) type V-S from *Electrophorus electricus* as a lyophilized powder, 5,5'-dithiobis-(2-nitrobenzoic acid) (DTNB), and acetylthiocholine were purchased from Sigma-Aldrich (St. Louis, MO). Potassium dihydrogen phosphate, disodium hydrogen phosphate, and nitric acid were purchased from Fisher (Pittsburgh, PA). The synthetic flavin derivative (10-(3'-methylthiopropyl)-isoalloxazinyl-7-carboxylic acid) was synthesized in our lab, as previously reported.³⁶ Self-assembled monolayers of this compound were previously characterized using electrochemistry, X-ray photoelectron spectroscopy, and SEM.

Porous gold was prepared by cutting pieces with a size of 2 mm \times 2 mm \times 0.25 mm (geometrical surface area of 0.1 cm²) and placing them in concentrated nitric acid for different periods of time. A 1 day HNO₃ treatment resulted in what will be referred to as surface 1, and a 3 day treatment resulted in what will be referred to as surface 2. The sample size was specifically chosen for being able to place the piece of porous gold in the bottom corner of a standard cuvette, which left adequate room for a stir bar. The samples were weighed before and after HNO₃ treatment. After the HNO₃ acid treatment, the samples were rinsed thoroughly with water and were characterized by high-resolution SEM and AFM techniques. UV–vis spectroscopy and electrochemistry studies of the chemisorbed flavin derivative and of AChE were conducted on these samples. BET analysis was also applied to the samples.

Porous gold surfaces were characterized by SEM and AFM. High-resolution SEM images were acquired on a low-voltage field-emission JSM 6320F SEM (JEOL Inc., Peabody, MA). An electron beam voltage of 5 kV was used to obtain a good morphological contrast and high image resolution. Composition of the material obtained by dealloying of 10 carat gold was determined using the same instrument, which has the option of performing energy dispersed spectroscopy (EDS).

A Nanoscope IIIa atomic force microscope (Digital Instruments, Santa Barbara, CA) was used in tapping mode to determine the surface roughness. The surface was scanned using NP-20 silicon nitride tips (Veeco Metrology Group, Santa Barbara, CA).

Chemisorption of the synthetic flavin sulfide molecule onto the surface of porous gold was monitored by solution depletion using a UV–vis spectrophotometer (Cary UV 50, Varian, Palo Alto, CA). The porous gold piece was placed in the quartz cuvette containing a 0.2 mM solution of the synthetic flavin in 0.2 M phosphate buffer

- (21) Duan, C.; Meyerhoff, M. *Mikrochim. Acta* **1995**, 117, 195–206.
- (22) Duan, C.; Meyerhoff, M. *Anal. Chem.* **1994**, 66, 1369–1377.
- (23) Ducey, M.; Meyerhoff, M. *Electroanalysis* **1998**, 10, 157–162.
- (24) Jurica, L.; Manova, A.; Dzurov, J.; Beihrohr, E. *Fresenius J. Anal. Chem.* **2000**, 366, 260–266.
- (25) Cai, W.-Y.; Xu, Q.; Zhao, X.-N.; Zhu, J.-J.; Chen, H.-Y. *Chem. Mater.* **2006**, 18, 279–284.
- (26) Tipple, C. A.; Lavric, N. V.; Culha, M.; Datskos, P.; Sepaniak, M. J. *Anal. Chem.* **2002**, 74, 3118–3126.
- (27) Lavric, N. V.; Tipple, C. A.; Sepaniak, M. J.; Datskos, P. G. *Biomed. Microdevices* **2001**, 2, 35–44.
- (28) Berlin, P.; Klemm, D.; Jung, A.; Liebegott, H.; Rieseler, R.; Tiller, J. *Cellulose* **2003**, 10, 343–367.
- (29) Park, C.; Clark, D. S. *Biotechnol. Bioeng.* **2002**, 78, 229–235.
- (30) Lei, C.; Shin, Y.; Liu, J.; Ackerman, E. J. *J. Am. Chem. Soc.* **2002**, 124, 11242–11243.
- (31) DeLouise, L.; Miller, B. *Anal. Chem.* **2005**, 77, 1950–1956.
- (32) Drott, J.; Rosengren, L.; Lindstrom, K.; Laurell, T. *Thin Solid Films* **1998**, 330, 161–166.
- (33) Vasudevan, P. T.; Thakur, D. S. *Appl. Biochem. Biotechnol.* **1994**, 49, 173–189.
- (34) Blaedel, W. J.; Kissel, T. R.; Boguslaski, R. C. *Anal. Chem.* **1972**, 44, 2030–2037.
- (35) Kerby, M. B.; Legge, R. S.; Tripathi, A. *Anal. Chem.* **2006**, 78, 8273–8280.

- (36) Stine, K. J.; Andrauskas, D. M.; Khan, A. R.; Forgo, P.; D'Souza, V. T.; Liu, J.; Friedman, R. M. *J. Electroanal. Chem.* **1999**, 472, 147–156.

(pH 6.7). A control experiment was also conducted, in which the absorbance of a solution of the flavin sulfide in the absence of porous gold was monitored as a function of time. The variation of absorbance as a function of time was monitored between 300 and 600 nm for both experiments, with and without porous gold. Stirring of the flavin solution was initiated by a stirrer placed beneath the cuvette (Starna Spinette). The change in absorbance of flavin at 435 nm was used to calculate the remaining concentration of flavin in solution and to deduce the number of flavin molecules chemisorbed on the surface of porous gold. For our synthetic derivative, we determined the extinction coefficient for the absorbance at 435 nm to be $3150 \text{ M}^{-1} \text{ cm}^{-1}$. In their oxidized form, flavins are strong yellow chromophores. The ratio between the number of flavin molecules chemisorbed on the surfaces of porous gold and the number that would be chemisorbed onto a nonporous gold piece of the same size as the sample was calculated and used to estimate the degree of surface area enlargement.

Electrochemical behavior of the flavin derivative chemisorbed on the surface of porous gold was investigated by cyclic voltammetry (CV) and square wave voltammetry (SWV) techniques using a Parstat 2273 (Princeton Applied Research, Oak Ridge, CA). For this purpose, larger samples of porous gold ($4 \text{ mm} \times 4 \text{ mm} \times 0.25 \text{ mm}$) were prepared by the same method described previously. Both surface 1 and surface 2 were thoroughly rinsed with water and methanol and placed in a freshly prepared 0.2 mM methanol solution of flavin sulfide for 24 h followed by rinsing with methanol and drying. Flavin modified porous gold was then attached to a copper wire with Ag paste (Ted Pella, Inc., Redding, CA) producing flag electrodes for surfaces 1 and 2. Hot glue was used to insulate the connection of porous gold and copper wire as well as to block one side of the flag electrode. As a control, the redox behavior of a self-assembled monolayer of the flavin derivative chemisorbed on the surface of a standard gold electrode (CH Instruments, Austin, TX) for 24 h was investigated.

Surface area data for surfaces 1 and 2 were also obtained using a Quantachrome Autosorb-1 automated gas sorption system equipped with Autosorb software, version 1.24 at the Molecular and Nanoscale Analysis Laboratory at Washington University (Saint Louis, MO). Prior to N_2 adsorption, all samples were degassed at 100°C for 30 min. The surface area of surfaces 1 and 2 was calculated using the multipoint Brunauer–Emmett–Teller (BET) method. To carry out the BET analysis, 10 pieces of porous gold (individual size $2 \text{ mm} \times 2 \text{ mm} \times 0.25 \text{ mm}$) prepared and handled identically were weighted and used in the analysis, thus providing an appropriate mass for the analysis.

To immobilize AChE on the surface of the porous gold (surfaces 1 and 2), both surfaces were separately immersed in a 0.032 mg/mL solution of AChE (pH 8, 0.1 M phosphate buffer) at 4°C for 24 h. A similar procedure of 24 h adsorption was used for the experiments in which the concentration of the enzyme solution was varied. After immobilization of enzyme, both surfaces were rinsed with phosphate buffer to remove unbound enzyme. A series of experiments intended to assess the effect of diffusion of the substrate into the pores on the enzyme kinetics was performed. In these experiments, two pieces of porous gold (surface 1) were placed into two separate cuvettes, and AChE was added at a concentration of 0.032 mg/mL. One of the plates was crushed using a pipet tip immediately after addition of AChE, exposing the inner surfaces of the porous gold, followed by 24 h of immobilization. This produced plate A. Another plate was allowed to spend 24 h in the enzyme solution prior to crushing, producing plate B. Examination of the crushed pieces using an optical microscope and a calibration grid after completion of the experiment revealed fragments of size

0.05–1.0 mm, with almost all of the fragments smaller than 0.3 mm.

Surfaces 1 and 2 and plates A and B have been used to study the kinetics of immobilized AChE and to determine the Michaelis constant (K_m) and maximum velocity of the enzyme catalyzed reaction (V_{max}) as a function of sample treatment and storage time.

The standard Ellman assay³⁷ was used to study the kinetics of AChE. The principle of the method involves the measurement of the rate of production of thiocholine as acetylthiocholine is hydrolyzed. This is accomplished by reaction of thiocholine with DTNB to produce the yellow anion of 5-thio-2-nitrobenzoic acid. The rate of the anion color production is determined by measuring the absorbance at 412 nm. For continuous monitoring, a typical run used a porous gold plate with immobilized AChE, which was placed in a plastic cuvette, along with 2910 μL of 0.1 M phosphate buffer (pH 8), 20 μL of 0.01 M DTNB phosphate buffer solution, and 70 μL of 6 mM acetylthiocholine. The plot of absorbance at 412 nm versus time was generated and used to calculate the initial velocity. K_m and V_{max} values were calculated from a Michaelis plot and compared for bulk and immobilized enzyme for the entire range of substrate concentration that varied between 0.02 and 0.7 mM. For experiments that involved adsorption of enzyme onto gold from solutions containing different enzyme concentrations, the value of the initial velocity for the immobilized enzyme was determined at a fixed substrate concentration of 0.028 mM.

Results and Discussion

Preparation and Characterization of Porous Gold.

Dealloying is a common corrosion process during which one or more less-noble elements are removed from an alloy by treatment with concentrated nitric or perchloric acid.³⁸ Figure 1 shows a top view SEM analysis of porous gold prepared by 24 h (panel a) and 72 h (panel b) treatment in HNO_3 , which corresponds to surfaces 1 and 2, respectively. As it is seen from the figure, treatment of 10 carat gold with HNO_3 results in a highly porous structure. Surface 1 consists of interconnected ligaments, which form uniformly distributed pores that are 50–100 nm in diameter. A longer HNO_3 treatment (surface 2) produces larger ligaments, which are more separated from each other and with larger pores whose diameter is around 200 nm. EDS analysis revealed that these acid treatments removed all elements other than gold to an undetectable level. The formation mechanism of nanoporous structures during dealloying has been described in the literature.^{9,39} It has been shown that pores form due to an intrinsic dynamic pattern formation during which aggregation of chemically driven noble metal atoms occurs. Figure 2 shows a cross-sectional SEM analysis of surface 1; these images are similar to the top view images and show the formation of a sponge-like structure throughout the sample. Similar images of porous gold prepared by other methods such as sputter coating of a quartz crystal with a thin film of gold and silver followed by dealloying in HNO_3 ,⁴⁰ electrochemical deposition of a Au–Zn alloy followed by anodic stripping of Zn,⁴¹ and electrochemical deposition of

(37) Ellman, G.; Courtney, K.; Andres, V.; Featherstone, R. *Biochem. Pharmacol.* **1961**, 7, 88–95.

(38) Erlebacher, J.; Sieradzki, K. *Scr. Mater.* **2003**, 49, 991–996.

(39) Li, R.; Sieradzki, K. *Phys. Rev. Lett.* **1992**, 68, 1168–1171.

(40) Hieda, M.; Garcia, R.; Dixon, M.; Daniel, T.; Allara, D.; Chan, M. H. W. *Appl. Phys. Lett.* **2004**, 84, 628–630.

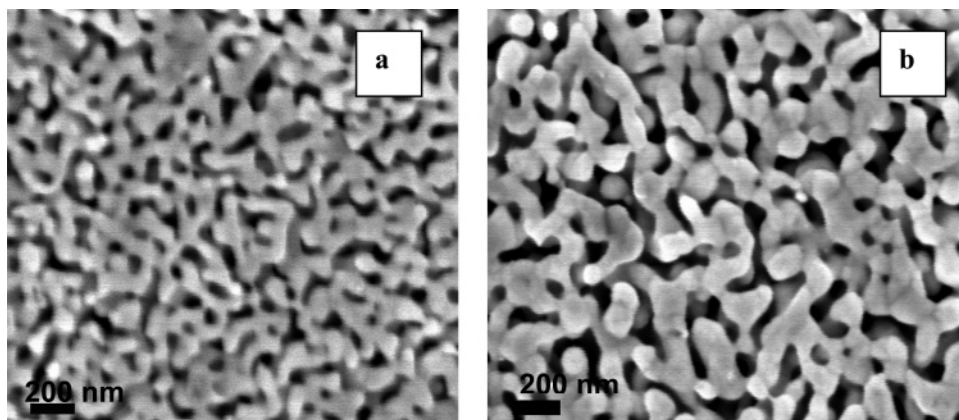


Figure 1. SEM of porous gold prepared by 24 h (a) and 72 h (b) HNO_3 treatments. Magnification is 100 000 \times .

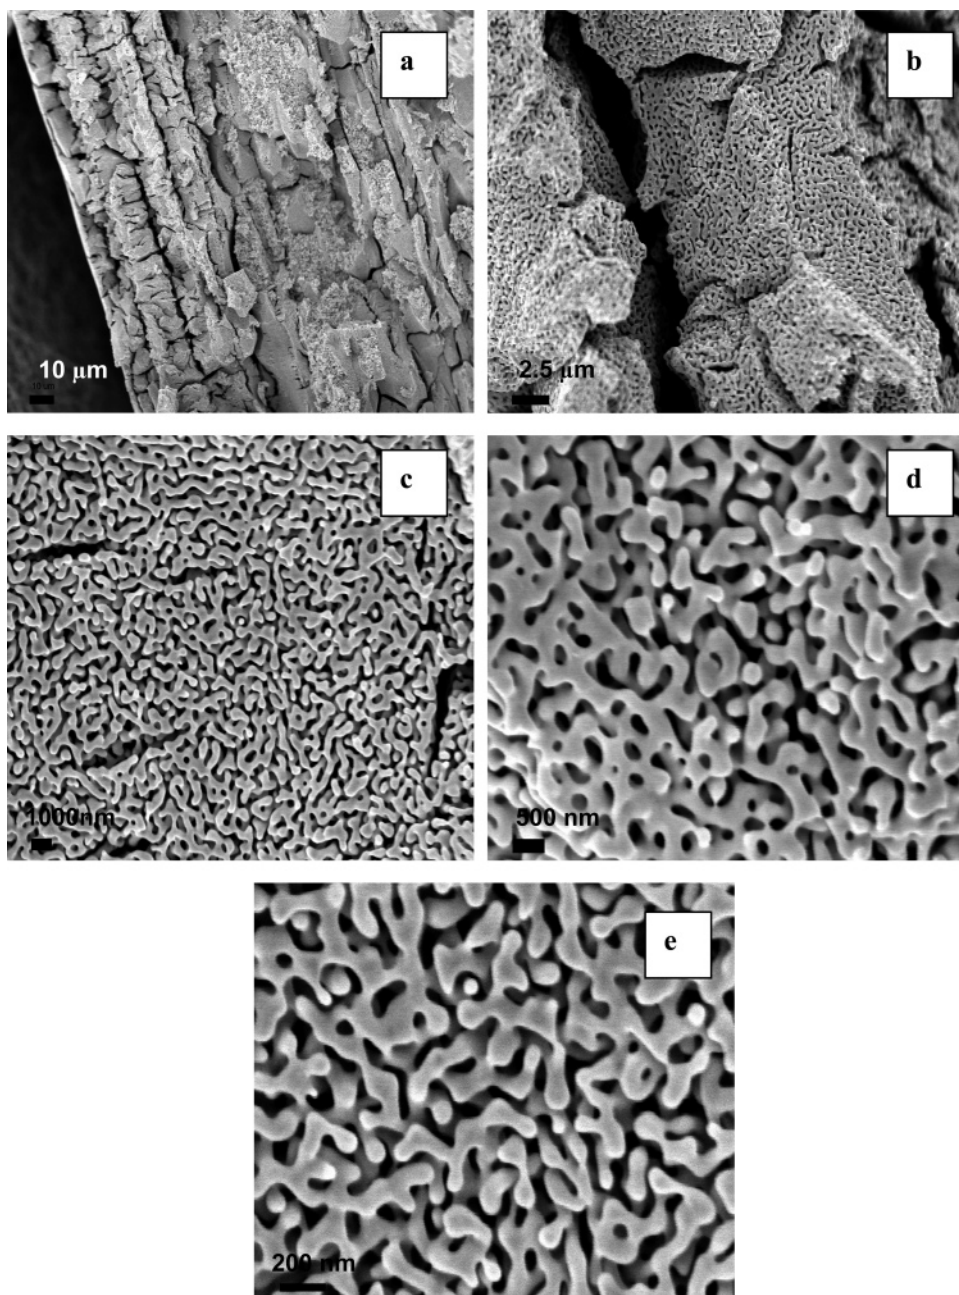


Figure 2. Cross-sectional SEM images of surface 1 at different magnifications: (a) 1000 \times , (b) 10 000 \times , (c) 20 000 \times , (d) 50 000 \times , and (e) 100 000 \times times.

Au–Ag alloys from the corresponding cyanide solutions followed by dealloying in HNO_3 ¹¹ have been obtained by

other authors. It is significant to note that the porous gold structure appears identical on the nanoscale/mesoscale level

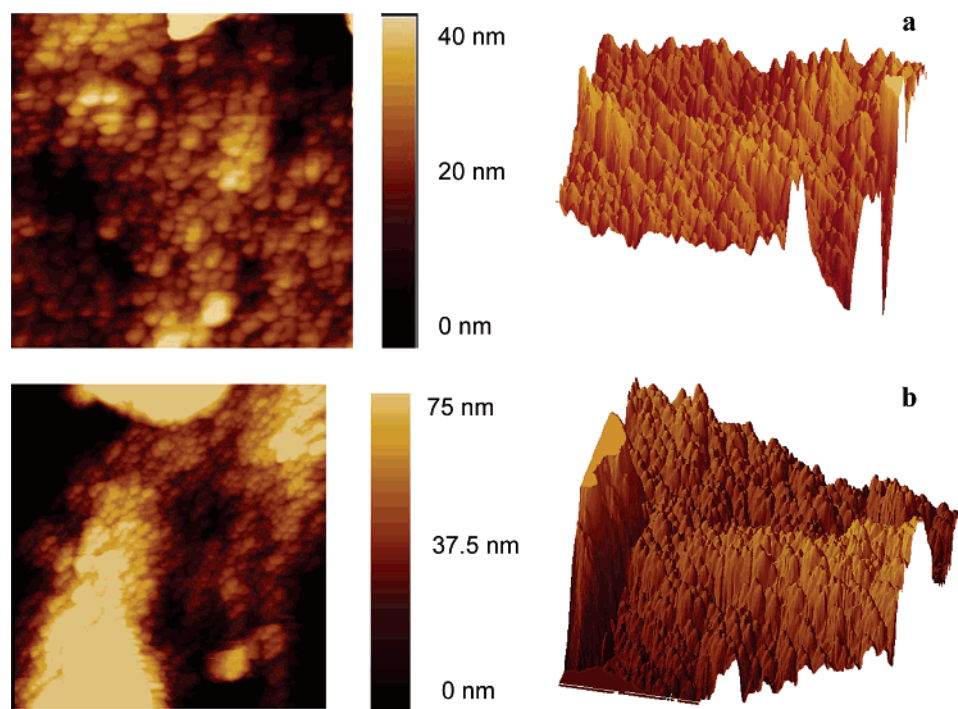


Figure 3. Typical AFM images of porous gold. (a) Surface 1, scan size $1\ \mu\text{m} \times 1\ \mu\text{m}$ and (b) surface 2, scan size $3\ \mu\text{m} \times 3\ \mu\text{m}$.

to that reported by other workers but has emerged from acid treatment of a more complex alloy mixture than typically used binary Au–Ag alloys. Au–Ag alloys form ideal metallic solutions due to their similar structure and almost identical lattice parameters of silver and gold. The alloy used here most likely has a more complex phase diagram and initial microstructure but has resulted in the same porous gold morphology reported from Au–Ag alloys. Ternary alloys of Au–Ni–Cu, the dominant elements in the alloy used in our experiments, are known to have a two-phase immiscibility gap.⁴² The cracks observed on the micrometer scale by SEM in a cross-section may be related to the initial microstructure of the alloy, a feature that warrants further investigation, or possibly to volume changes on dealloying.¹²

Figure 3 shows AFM images of surface 1 (panel a) and surface 2 (panel b). The generally spherical hills range from 50 to 70 nm in diameter for surface 1 and from 100 to 150 nm in diameter for surface 2. The presence of the spherical hills on the surface can be explained by the fact that every ligament seen in the SEM probably has higher and lower parts, so on the AFM image, the upper part appears as a particle-like hill. Three-dimensional topographic images of both surfaces are also presented in Figure 3. The roughness of each surface has been calculated as an arithmetic average of the absolute values of the surface height deviations measured from the mean plane. For surface 1, the roughness was found to be 6.6 nm, whereas for surface 2, it was 30 nm. It is seen that longer treatment of 10 carat gold with HNO_3 results in a rougher surface, which is due to the presence of large pores and thicker ligaments. These results are consistent with our SEM data and indicate the value of employing both methods of analysis.

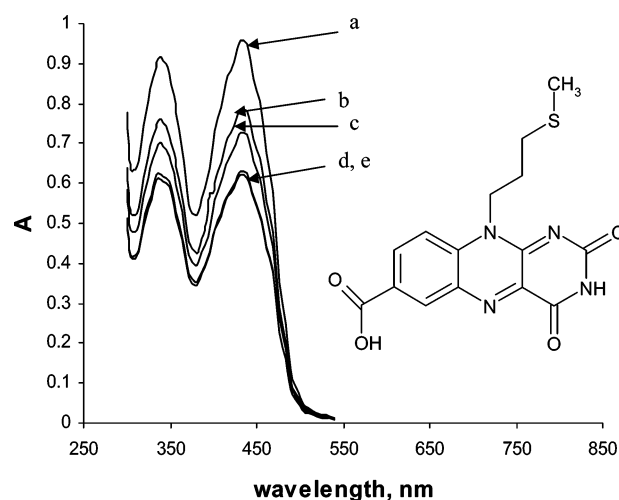


Figure 4. Spectrum of a 0.2 mM solution of flavin in phosphate buffer (pH 7) as it chemisorbs onto the surface of porous gold (surface 1, $2\ \text{mm} \times 2.1\ \text{mm} \times 0.25\ \text{mm}$) at different times: (a) initial spectrum, (b) after 3 h, (c) after 6 h, (d) after 24 h, and (e) after 30 h.

Surface Area Determination and Electrochemical Studies. Chemisorption of flavin sulfide monolayers on the surface of nonporous and porous gold (the porous gold resulted from HNO_3 treatment) was investigated by UV–vis spectroscopy and cyclic voltammetry to estimate the degree of surface enlargement caused by HNO_3 treatment. This approach was used as an alternate to the BET adsorption isotherm analysis and as a part of the study of the electrochemical behavior of the flavin sulfide monolayer in porous gold. Figure 4 shows the structural formula and UV–vis spectra of 0.2 mM flavin sulfide as it chemisorbs onto the surface of porous gold (surfaces 1 and 2) as a function of time. Flavin gives two peaks in the visible region, one at 339 nm and another at 435 nm. It is seen that as time progresses from zero hours to 24 h, the absorbance decreases for both peaks, which is due to the formation of a self-

(41) Huang, J.-F.; Sun, I.-W. *Adv. Funct. Mater.* **2005**, *15*, 989–994.

(42) Grimwade, M. *Gold Technol.* **2000**, *30*, 8–15.

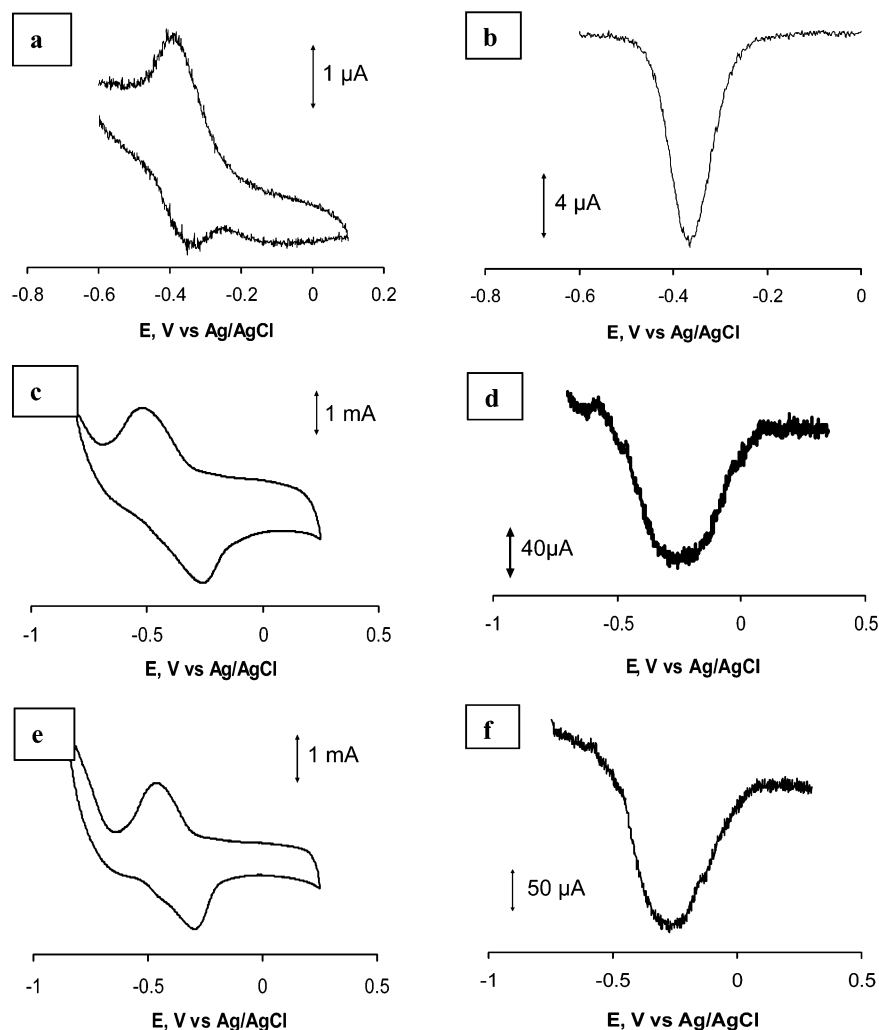


Figure 5. Cyclic voltammetric (a, c, and e) and square wave voltammetric (b, d, and f) responses of flavin modified standard gold electrode (a and b), porous gold flag electrode prepared of surface 1 (c and d), and porous gold flag electrode prepared of surface 2 (e and f) in 0.015 M phosphate buffer at pH 6.7. Scanning performed in positive direction at a rate of 10 mV/s.

assembled monolayer of flavin sulfide on the surface of porous gold. An additional spectrum was recorded at the 30 h period, in which a very small increase in the absorbance for both peaks was observed. The increase in absorbance value after the 30 h period is attributed to saturation of the porous gold sample and partial desorption of flavin disulfide molecules back into solution. A control experiment where the absorbance of flavin was monitored as a function of time in the absence of porous gold material was performed. A 0.2 mM methanol solution of flavin sulfide showed no detectable change in absorbance over 30 h, indicating that the molecule is stable in solution. Using the change in the absorbance of flavin sulfide at 435 nm, for which $\epsilon = 3150 \text{ M}^{-1} \text{ cm}^{-1}$, one can calculate the number of moles of flavin sulfide depleted from the solution by exposure to the porous gold surface after 24 h of treatment. After 24 h, the number of moles of flavin chemisorbed on the porous gold surface was found to be 3.6×10^{-7} and $2.0 \times 10^{-7} \text{ mol}$ for surfaces 1 and 2, respectively. To estimate the degree of surface area enlargement, one could consider measuring the amount of flavin chemisorbed on the surface of untreated 10 carat gold. However, UV-vis spectroscopy cannot be used for this purpose due to the undetectable change in absorbance with such a small surface area.

Cyclic voltammetry of a flavin sulfide monolayer chemisorbed on the surface of a standard gold electrode may be used to determine the average area occupied by a flavin sulfide in a SAM on gold. The electroactive part of flavin is the isoalloxazine ring system, which undergoes a $2e^-$, $2H^+$ reversible redox process. The curvature of the ligaments of diameter 50–200 nm is similar to that of the surfaces of large nanoparticles, which are routinely functionalized by thiol and sulfide derivatives. Under the assumption that equivalent SAMs form on porous gold and flat gold, the molecular area per flavin sulfide combined with the change in absorbance can provide an estimate of the surface area and thus the surface enlargement. Previous studies³⁶ show that the limiting coverage is reached after 6 h of exposure of a flat gold surface to a solution of flavin sulfide and that the resulting SAM exhibits quasi-reversible redox behavior. Figure 5a shows an example of a cyclic voltammogram measured for a monolayer of flavin. Integration of the area under the flavin reduction peaks for scanning rates between 0.1 and 0.4 V s^{-1} gives an average surface coverage of $2.9 \times 10^{-10} \text{ mol cm}^{-2}$. The maximum surface occupancy of the untreated (flat) surface will be equal to the product of the geometrical area of the untreated piece of white gold (considered as gold, 0.1 cm^2) and the average surface

coverage of untreated gold (2.9×10^{-10} mol cm^{-2}) and is equal to 2.9×10^{-11} mol for both surfaces 1 and 2. Our previous SEM and AFM studies showed that the 72 h HNO_3 treatment produced larger pores and a rougher surface, and therefore, less flavin can be accumulated on surface 2 than on surface 1. The amount of chemisorbed flavin sulfide determined from the UV-vis experiments was found to be 3.6×10^{-7} mol for surface 1 and 2.0×10^{-7} mol for surface 2. For surface 1, this would imply a total surface area of 1240 cm^2 ; for surface 2, the data imply a total surface area of 690 cm^2 . The ratio between the amounts of flavin adsorbed on treated and untreated gold surfaces suggests that the 24 h HNO_3 treatment of 10 carat white gold gives a $12\,400\times$ surface enlargement, whereas 72 h treatment enlarges the surface $6900\times$. Using the masses of the samples, we obtain 14.2 m^2/g for surface 1 and 8.2 m^2/g for surface 2.

The surface areas of surface 1 and of surface 2 were also determined by using the multipoint BET method where the adsorption/desorption of nitrogen was used. According to BET analysis, the surface areas of surfaces 1 and 2 were found to be 8.7 and 6.5 m^2/g , respectively. Ji and Searson previously determined the surface area of nanoporous gold nanowires by BET analysis.¹⁰ The reported surface area of nanoporous gold, prepared by electrochemical deposition of the Ag/Au alloy and followed by HNO_3 dealloying treatment, ranged from 3.7 to 6.9 m^2/g . The porous gold prepared by our method provided higher total surface areas. It is seen that our data obtained by solution depletion studies are in reasonable agreement with data obtained by BET analysis, especially in terms of comparing the two surfaces, which suggests that solution depletion studies can be used as an alternative approach for the determination of surface area. A possible explanation for the higher surface area obtained by solution depletion could be the presence of some additional flavin molecules inside the material that are not on the gold surface.

The electrochemical behavior of monolayers of flavin sulfide chemisorbed on the surface of porous gold was also investigated. Figure 5 shows typical cyclic voltammograms (panels a, c, and e) and square wave voltammograms (panels b, d, and f) for flavin chemisorbed on the surface of a standard gold electrode (panels a and b), an electrode prepared using surface 1 (panels c and d), and an electrode prepared using surface 2 (panels e and f). The cyclic voltammograms were stable over multiple cycles of scanning. As the structure of the electrode changes from nonporous (panels a and b) to porous (panels c, d, e, and f), the magnitude of the oxidation and reduction currents in the cyclic voltammograms and the magnitude of the oxidation current in the square wave voltammograms increase dramatically due to the significant increase in the electrode surface area. A shift in the oxidation and reduction potentials is also observed for porous electrodes as compared to standard gold electrodes. For example, the oxidation and reduction potentials for a monolayer of flavin chemisorbed on standard gold electrode are -360 and -380 mV, respectively, giving a ΔE value of 20 mV. These oxidation and reduction potentials are -250 and -520 mV for a porous gold electrode produced from surface 1 and -260 and -520 mV for a porous

electrode produced from surface 2, giving ΔE values of 270 and 260 mV, respectively. Such a large increase in the ΔE value could be explained by the porous nature of the material and the altered mass transport through the pores of different sizes, which may be located in the inner or outer parts of the electrode. Therefore, the nanoporous nature of the porous gold electrodes gives a rise to altered electrochemical behavior. The cyclic voltammograms on the porous gold electrode resemble those observed on flat gold at much higher scan rates.³⁶ Given the involvement of protons in the reduction and oxidation process, limitations on proton diffusion in the porous material might be responsible for slower electron-transfer kinetics. The average of the oxidation and reduction potential of flavin on the flat gold electrode is -370 mV, that on the surface 1 electrode is -385 mV, and on the surface 2 electrode is -390 mV. Given the sensitivity of the redox behavior of flavin to pH, these small shifts suggest that the pH inside the porous gold is close to that in the bulk solution. The area under the reduction peak in Figure 5c corresponds to a charge of 38 300 μC and that in Figure 5e corresponds to a charge of 24 000 μC , as compared to the charge under the reduction peak in Figure 5a of 2.21 μC . Accounting for the geometrical area of the electrodes (0.03 cm^2 for the standard electrode and 0.16 cm^2 for the porous gold flag electrodes), results are 56.6 $\mu\text{C cm}^{-2}$ for the standard electrode, $2.39 \times 10^5 \mu\text{C cm}^{-2}$ for surface 1, and $1.50 \times 10^5 \mu\text{C cm}^{-2}$ for surface 2. The ratios of the charges per unit area for the porous gold electrodes to the flat gold electrodes are 4220 and 2650, respectively. Although these ratios are somewhat smaller than the surface enlargement obtained by solution depletion or BET, it is clear that most of the flavin SAM is electrochemically active and accessible in the porous gold electrode.

Immobilization of Acetylcholine Esterase. One of the potential applications of porous gold material is its use as a solid support for the immobilization of biomolecules, which is a critical step in the development of new biosensors and assays. To investigate the effect of the new porous gold material on the catalytic properties of enzymes, acetylcholine esterase was chosen due to its high catalytic activity and robustness.⁴³ Acetylcholine esterase was immobilized on both surfaces of porous gold, and the kinetic parameters K_m and V_{max} were determined for the immobilized enzyme. The K_m values were compared between bulk and immobilized enzyme. The trend in V_{max} and K_m values as a function of storage time was used to assess enzyme stability on the surface. The K_m and V_{max} values of the bulk enzyme in a 0.04 $\mu\text{g/mL}$ solution in phosphate buffer, pH 8, were found to be 0.08 mM and $5.7 \times 10^{-6} \text{ M min}^{-1}$, respectively. The corresponding k_{cat} value is equal to 665 s^{-1} and comparable to those reported by Ramos and Techert,⁴⁴ who found that k_{cat} varied with ionic strength.

Figure 6 shows an example of a Michaelis-Menten plot obtained for acetylcholine esterase immobilized on surfaces 1 (Figure 6a) and 2 (Figure 6b). Immobilized acetylcholine esterase obeys Michaelis-Menten kinetics showing satura-

(43) Rosenberry, T. L. *Adv. Enzymol. Relat. Areas Mol. Biol.* **1975**, 43, 103-218.

(44) Ramos, A.; Techert, S. *Biophys. J.* **2005**, 89, 1990-2003.

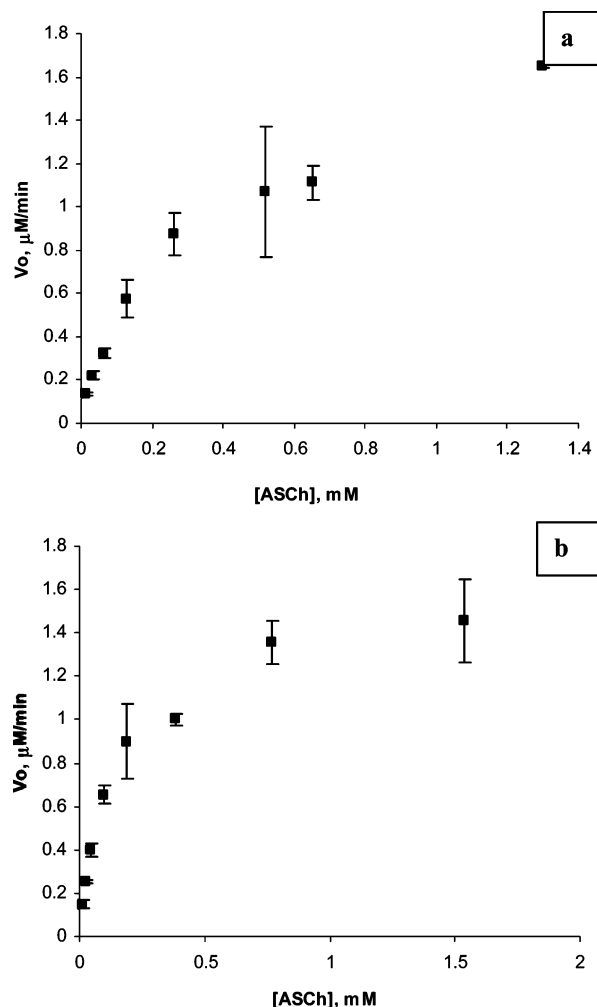


Figure 6. Example of a Michaelis–Menten plot for acetylcholine esterase immobilized on surface 1 (a) and surface 2 (b); both plots correspond to the first day after immobilization.

tion at about 2 and 1.5 $\mu\text{M min}^{-1}$ for surfaces 1 and 2, respectively. Acetylcholine esterase immobilized on surfaces 1 and 2 (Figure 6a,b) shows a slight decrease in the velocity of the enzyme catalyzed reaction when the concentration of acetylthiocholine is near 0.8 mM for surface 1 and near 0.4 mM for surface 2. This effect is more pronounced for acetylcholine esterase immobilized on surface 2 (Figure 6b). The reaction velocity goes back up as the concentration of substrate continues to increase. This could be attributed to the phenomenon known as inhibition by substrate. Inhibition by substrate for acetylcholine esterase has been studied and reported by a number of authors.^{45–47} In our case, acetylcholine esterase is immobilized on highly porous material, and there are several factors that might trigger inhibition by substrate. One of these factors is the effect of the environment around acetylcholine esterase (porous gold), which may trigger a conformational change in acetylcholine esterase and result in substrate inhibition. Another factor, which may be responsible for this phenomenon, is some retardation of the deacylation step when binding of a second substrate molecule occurs. This presumably could be due to steric hindrance

Table 1. Variation of Kinetic Parameters for Acetylcholine Esterase Immobilized on Porous Gold^a

| days | surface 1 | | surface 2 | |
|------|-------------|----------------------------------|-------------|----------------------------------|
| | K_m (mM) | V_{\max} ($\mu\text{M/min}$) | K_m (mM) | V_{\max} ($\mu\text{M/min}$) |
| 1 | 0.26 (0.05) | 1.85 (0.40) | 0.15 (0.04) | 1.56 (0.17) |
| 2 | 0.74 (0.1) | 3.0 (0.43) | 2.97 (0.9) | 1.18 (0.15) |
| 3 | 1.82 (0.3) | 4.23 (0.45) | 1.41 (0.56) | 3.73 (0.63) |
| 6 | 1.14 (0.3) | 2.03 (0.46) | 2.12 (0.33) | 2.75 (0.3) |

^a All experiments were repeated in triplicate. Standard deviations are given in parentheses.

created by other enzyme molecules immobilized on the highly porous material or by an unfavorable orientation.

Data obtained for K_m and V_{\max} values for acetylcholine esterase immobilized on surfaces 1 and 2 are presented in Table 1. Table 1 shows that upon immobilization of acetylcholine esterase on surfaces 1 and 2, the value of K_m increases as a function of time. During the first day of study, the increase in K_m is similar for both surfaces from 0.08 mM (bulk enzyme) to 0.26 mM (surface 1) and 0.15 mM (surface 2). During the second day of study, the value of K_m increases modestly for acetylcholine esterase immobilized on surface 1 (0.74 mM) but changes more dramatically for acetylcholine esterase immobilized on surface 2, where it reaches 2.97 mM. For the sixth day of study, the value of K_m reaches 1.14 mM for surface 1 and 2.12 mM for surface 2. The value of V_{\max} appears to be more stable for acetylcholine esterase immobilized on surface 2.

The kinetic parameters of enzymes immobilized inside porous materials may be strongly affected even without considering changes in enzyme structure due to interactions with the surface. Surface orientation upon adsorption or immobilization may restrict access to the active site. The surface charge and polarity may alter the substrate concentration near the surface relative to that in the bulk solution. If the substrate concentration is depleted relative to the bulk concentration, an apparent increase in the value of K_m will be observed. When the enzyme is immobilized within a porous material, both external mass transfer to the particle surface and internal mass transfer within the pores must be considered. The substrate concentration may be different from the bulk within the porous material, and there may also be a concentration gradient within the material dependent on its geometry. Diffusional restrictions within porous materials often result in higher K_m values. The internal diffusional effects are often described by an effectiveness factor η , which is a ratio of the reaction rate for the immobilized enzyme to that of the free enzyme.^{48,49} In the absence of diffusional restrictions, $\eta = 1$, and η increases as diffusional restrictions become more significant.⁵⁰ The pore structure and morphology of porous gold might be expected to play a role in the increase of K_m observed for the immobilized enzyme over the K_m measured in bulk solution. The mathematical modeling of enzyme kinetics within porous material is a challenging task.

(45) Gao, J.-R.; Rao, J. V.; Widle, G.; Zhu, K. Y. *Arch. Insect. Biochem. Physiol.* **1998**, *39*, 118–125.

(46) Krupka, R. M. *Biochem.* **1963**, *2*, 76–82.

(47) Radic, Z.; Reiner, E.; Taylor, P. *Mol. Pharmacol.* **1991**, *39*, 98–104.

(48) Gomez, J. L.; Bodalo, A.; Gomez, E.; Bastida, J.; Maximo, M. F. *Chem. Eng. Sci.* **2003**, *58*, 4287–4290.

(49) Ueyama, K.; Furusaki, S. *Chem. Eng. Commun.* **1985**, *36*, 299–316.

(50) Bailey, J. E.; Ollis, D. F. *Biochemical Engineering Fundamentals*; McGraw-Hill: New York, 1986.

Pore morphology and size also strongly affect kinetic parameters. Theoretical calculations suggest that maximum stabilization of proteins can be achieved in spherical cages with a diameter 2–6 times larger than the diameter of the native protein,⁵¹ and since the average diameter of hydrated protein is around 10 nm, a meso- to nanoporous material will provide maximum stabilization for the protein. The average pore sizes of surfaces 1 and 2 are 50–60 and 150–200 nm, respectively. Surface 1 is a nanoporous material, and the behavior of immobilized acetylcholine esterase changes less on this surface, as reflected by the overall lower K_m value after a 6 day period on surface 1 than on surface 2. A stabilization effect of genetically modified acetylcholine esterase on nanoporous silica beads and meso/nanoporous carbon was also observed by Sotiropoulou and co-workers.⁵²

The chemical nature of the porous material may also have an effect on enzyme kinetics. The behavior of proteins on metallic surfaces has been investigated by a number of authors. In particular, Leidbergh and co-workers^{53–55} studied the interactions of individual amino acids, L-cysteine, glycine, L-histidine, and L-phenylalanine with gold and copper surfaces, and they found that interactions between amino acids and metal surface occur via either NH_2 endgroups (glycine–gold) or through side groups of sulfur-containing amino acids (cysteine–gold). Thus, when a protein interacts with a porous material, it has enough degrees of freedom to take a preferred orientation. Furthermore, the pore size also plays an important role in the stabilization of the immobilized enzyme. Thus, it can be concluded that the activity of immobilized proteins may be affected by all or a group of the aforementioned parameters.

Experiments in which the porous gold plates were crushed before (plate A) and after (plate B) AChE immobilization have been performed to investigate the availability of the enzyme from the inner pores to the substrate as well as the access of the enzyme to the inner pores during adsorption. The K_m values for AChE immobilized on plates A and B were found to be 0.32 and 0.28 mM, respectively, after 24 h of adsorption. These values are essentially the same as for the intact plates of surface 1, for which $K_m = 0.26 \pm 0.05$ mM after 24 h of adsorption. Plate A, which was crushed prior to enzyme adsorption, exhibits a larger V_{\max} value of $9.0 \mu\text{M min}^{-1}$, which can be accounted for by the greater area of particle surface available through which the enzyme can adsorb into the material. The value of V_{\max} found for plate B, crushed after adsorption, is $5.7 \mu\text{M min}^{-1}$, which is also larger than that found for the intact plate of surface 1 of $1.85 \pm 0.40 \mu\text{M min}^{-1}$ and indicates that additional enzymes have been made available by exposure of inner surfaces by crushing. If limited diffusion of the substrate into pores was responsible for the observed increase in K_m

Table 2. Comparison of Initial Rates (V_o) of Acetylthiocholine Hydrolysis at 0.028 mM by Acetylcholine Esterase in the Supernatant Liquid (SNT) and on the Surface of the Porous Gold Plate

| enzyme concentration (mg/mL) | V_o ($\mu\text{M/min}$) at 0.028 mM acetylthiocholine | | amount of enzyme (mg) | |
|------------------------------|---|-------|--------------------------|---------------------------|
| | SNT | plate | $[\text{E}]_{\text{SN}}$ | $[\text{E}]_{\text{ads}}$ |
| 1.2×10^{-3} | 0.11 | 0.46 | 0.91×10^{-3} | 0.29×10^{-3} |
| 2.9×10^{-3} | 0.18 | 0.44 | 2.54×10^{-3} | 0.36×10^{-3} |
| 0.011 | 0.8 | 2.52 | 9.3×10^{-3} | 1.7×10^{-3} |
| 0.034 | 1.82 | 2.23 | 21×10^{-3} | 13×10^{-3} |
| 0.091 | 6.07 | 2.64 | 88×10^{-3} | 3×10^{-3} |

over the bulk value, then one might expect crushing to have resulted in a smaller observed increase in K_m ; however, this was not observed. While diffusion could play a role if the depletion of substrate concentration develops over a very short distance, the observed increase in K_m with storage time would not be consistent with diffusion being a sole factor. The increase in K_m with storage time suggests that the enzyme structure is slowly perturbed by its interaction with the surface over days of storage with the result being a slow decrease in substrate affinity. It is less clear why V_{\max} shows signs of increasing as well, although one can speculate that the structural changes are serving to expose more active sites to the substrate.

To estimate the amount of enzyme adsorbed on the surface of porous gold, the initial rate of acetylthiocholine hydrolysis at 0.028 mM was monitored as a function of enzyme concentration used for the immobilization of acetylcholine esterase on surface 2. The substrate concentration chosen is well below the value of K_m in the range where the initial rate (v_o) is linearly proportional to substrate concentration and where the rate at a fixed substrate concentration also should be linearly proportional to enzyme concentration. In these experiments, the supernatant liquid above the surface was removed, and v_o was determined separately. The value of v_o for the enzyme on the surface was also determined separately. Table 2 presents the variations of the initial rates determined in the supernatant liquid and on the porous gold surface at a constant concentration of acetylthiocholine for different concentrations of acetylcholine esterase. Each entry represents the average of results for two independently prepared plates. At a low enzyme concentration, the initial rate of acetylthiocholine hydrolysis is significantly higher for adsorbed enzyme than for the enzyme that remains in solution. However, as the initial concentration of the enzyme increases, the initial rate values become closer to each other and reach an almost identical value when 0.034 mg/mL enzyme was used for immobilization. As it is also seen from the table, a variation of enzyme concentration from 0.011 to 0.091 mg/mL has a less appreciable effect on the initial rate value, which varies between 2.2 and $2.6 \mu\text{M min}^{-1}$. Comparison of the initial rates determined for the supernatant liquid and porous gold plate can be used to study partitioning of the enzyme between the supernatant liquid and the porous gold plate and can also be used to determine the amounts of adsorbed enzyme assuming that the catalytic constant (k_{cat}) and K_m for bulk enzyme in the solution from which enzyme adsorption occurs and the enzyme contained in the super-

(51) Wie, Y.; Xu, J.; Feng, Q.; Dong, H.; Lin, M. *Mater. Lett.* **2000**, *44*, 6–11.

(52) Sotiropoulou, S.; Vamvakaki, V.; Chaniotakis, N. *Biosens. Bioelectron.* **2005**, *20*, 1674–1679.

(53) Leidbergh, B.; Lundstrom, I.; Wu, C. R.; Salanek, W. R. *J. Colloid Interface Sci.* **1985**, *108*, 123–131.

(54) Ihs, A.; Leidbergh, B. *J. Colloid Interface Sci.* **1991**, *144*, 282–292.

(55) Leidbergh, B.; Carlsson, C.; Lundstrom, I. *J. Colloid Interface Sci.* **1987**, *120*, 64–75.

natant liquid have the same values. Initial rates of acetylthiocholine hydrolysis by acetylcholine esterase before and after its adsorption on the porous gold surface can be written as follows:

$$v_{o,bulk} = (k_{cat,bulk}/K_{m,bulk})[E]_o[S] \quad (1)$$

$$v_{o,SN} = (k_{cat,SN}/K_{m,SN})[E]_{SN}[S] \quad (2)$$

where $v_{o,bulk}$ is the initial rate in the bulk enzyme solution prior to adsorption onto porous gold, $v_{o,SN}$ is the initial rate in the supernatant enzyme solution remaining after enzyme adsorption, $[E]_o$ is the initial enzyme concentration, $[E]_{SN}$ is the enzyme concentration in the supernatant, and $[S]$ is the concentration of substrate added to determine the initial rates. In our experiments, $[S] = 0.028$ mM was used to determine $v_{o,bulk}$ and $v_{o,SN}$. Assuming that $k_{cat,bulk} = k_{cat,SN}$ and $K_{m,bulk} = K_{m,SN}$, we can divide eq 2 by eq 1 to obtain

$$\frac{v_{o,SN}}{v_{o,bulk}} = \frac{[E]_{SN}}{[E]_o} \quad (3)$$

Using the ratio of initial rates and the known value of $[E]_o$, the value of $[E]_{SN}$ can be determined. The amount of adsorbed enzyme can be determined using

$$[E]_{ads} = [E]_o - [E]_{SN} \quad (4)$$

and then the amount of enzyme adsorbed can be calculated from $[E]_{ads}V_{bulk}$, where V_{bulk} is the volume of the solution from which enzyme adsorption occurred, in this case $V_{bulk} = 1$ mL. The calculated amounts of enzyme are presented in Table 2. The calculated amounts of adsorbed enzyme are seen to increase with enzyme concentration with the exception of the highest concentration; it is possible that some blockage of the pores on the surface of the material may have occurred.

The value of k_{cat} was calculated on the basis of the amount of adsorbed enzyme and the V_{max} value determined for surface 2 and was found to be 1.7 s^{-1} . This estimate of k_{cat} for the immobilized enzyme assumes that all of the immobilized enzyme is accessible and functioning at saturation. Given the increase in V_{max} observed for crushing after adsorption (plate B), this is unlikely, and the real value of k_{cat} for the immobilized enzyme is very likely to be higher by at least a factor of $3 \times$ this estimate. This value is much smaller as compared to bulk enzyme (665 s^{-1}), which means that the amount of the active sites that catalyze the hydrolysis of acetylthiocholine is significantly lower. However, other kinetic parameters (K_m and V_{max}) show that even with a reduced number of active sites, AChE immobilized on the surface of porous gold is fully functional and relatively stable.

The quantities of the enzyme adsorbed are in the submonolayer regime. The radius of gyration of type V-S acetylcholine esterase from *E. electricus* was determined by small-angle X-ray scattering to be 48.88 \AA including a 3 \AA wide hydration shell.⁴⁴ Assuming a footprint per enzyme molecule on the gold surface of 95 nm^2 , for surface 2, one would obtain a capacity of 7.3×10^{14} enzyme molecules in a ideally arranged monolayer. Acetylcholine esterase has a mass of 280 kDa. Thus, the number of enzyme molecules adsorbed, based on the results in Table 2, range from a low value of 6.2×10^{11} to a maximum value of 2.8×10^{13} . The coverage of enzyme on the surface obtained by physical adsorption thus falls in a submonolayer regime. Increasing the enzyme coverage would likely require either much longer adsorption times or the pursuit of covalent immobilization strategies. Covalent immobilization, such as to SAM modified porous gold, might result in more stable kinetic parameters and better behavior during storage.

Conclusion

In this paper, we reported the preparation, characterization, and application of a porous gold material. A simple approach to the fabrication of a large, free-standing, and high surface area porous gold material by dealloying commercially available 10 carat white gold with concentrated nitric acid is demonstrated. We have shown that the pore structure and morphology of the final porous gold sample can be altered by variation of the dealloying time: a 24 h HNO_3 treatment produces porous gold with a 12 400-fold surface enlargement, while a 72 h HNO_3 treatment yields porous gold with a 6900-fold surface enlargement. The nano- and mesoporous gold surfaces were used as a solid support for the enzyme acetylcholine esterase, which demonstrates the potential applicability of this material for biosensor development. The dependence of the activity of immobilized enzyme on the size and structure of pores in porous gold was studied. Our experimental data show that nanoporous gold, with average pore sizes of about 50 nm in diameter, is more suitable for the immobilization of acetylcholine esterase.

Acknowledgment. The authors are grateful to Prof. Cynthia Dupureur (University of Missouri—St. Louis, Department of Chemistry and Biochemistry) for discussions on some aspects of enzyme kinetics. This project was financially supported by the National Institutes of Health (NIH Grant 5R21GM072693-02).

Note Added after ASAP Publication. The Figure 5 caption that appeared in the version of this article published ASAP July 17, 2007, was modified; the corrected version was published July 19, 2007.

CM070238N