



The crystal structure of two new developers for high-performance thermo-sensitive paper: H-bonded network in urea–urethane derivatives

Shinya Matsumoto^{a,*}, Sakiko Takeshima^a, Saori Satoh^a, Kazuo Kabashima^{b,c}

^a Department of Environmental Sciences, Faculty of Education and Human Sciences, Yokohama National University, 79-2 Tokiwadai, Hodogaya-ku, Yokohama 240-8501, Japan

^b Fine Ace Corporation, 1-44-10, Higashi-ikebukuro, Toshima-ku, Tokyo 170-0013, Japan

^c Chemipro Kasei Kaisha, Ltd., 83 Kyomachi, Chuo-ku, Kobe 650-0034, Japan

ARTICLE INFO

Article history:

Received 6 August 2009

Received in revised form

15 October 2009

Accepted 22 October 2009

Available online 28 October 2009

Keywords:

Thermo-sensitive paper

Developer

Urea–urethane derivative

Crystal structure

Hydrogen-bond network

Fluoran dye

ABSTRACT

Crystal structure analysis was carried out on two novel, urea–urethane developers for high-performance thermo-sensitive paper. Crystals of the compounds displayed a multiple hydrogen-bonded network between the urea and urethane moieties, which stabilized the fluoran dyes, thereby imparting high fastness to printed images.

© 2009 Elsevier Ltd. All rights reserved.

1. Introduction

Direct thermal-printing technology is now widely used in facsimiles and many kinds of tickets owing to its simplicity and applicability in maintenance-free printing devices [1]. The application fields have expanded with the development of information technologies and therefore its market can be expected to increase. Thermo-sensitive paper is a key technology of this particular printing system, in which the paper contains a recording layer that comprises a leuco dye and developer. Fluoran dyes are typically used as the leuco dye, the spiro lactone ring being cleaved by the acidic developer, generating the desired colour. In order to obtain a black colour from one dye component, dichroic fluoran dyes were developed on the basis of molecular orbital calculations [2]. Such black dyes have two absorption maxima of almost identical molar absorption coefficient which are adjusted so as to provide complementary colours, thereby giving a “pure” black colour in a single component. This colouring process is the most important characteristic of this printing system.

Many potential developers have been examined; whilst acidic phenol derivatives are generally used. Recently, questions have been

raised about their effect on the environment [3,4]. In addition, the low stability of the ensuing coloured state gives problems in terms of the longevity of printed. Urea–urethane (UU) derivatives were developed as developers having no phenolic hydroxy group for high-performance thermo-sensitive paper [5,6]. The UU derivatives have no acidic protons, but promote ring cleavage of fluoran dyes; the coloured images that they produce display high stability compared to conventional acidic phenolic developers and enjoy low-environmental loading. These derivatives are already on the market, but the mechanism of their colour development is uncertain.

This paper concerns an investigation of the H-bonding ability of UU developers in the solid state, as the observed high fastness of colours obtained using these developers may be related to their H-bonding in the solid state.

2. Experimental

These UU derivatives were prepared using the previously reported procedure [5,6]. Single crystals of **1** and **2** were grown using the diffusion method employing the combination of good (1,4-dioxane for **1**, ethylacetate for **2**) and poor (*n*-hexane for **1**, benzene for **2**) solvents. Colourless platelet crystals were obtained for both compounds. Diffraction data were collected using a Rigaku R-Axis Rapid imaging plate area detector with graphite-monochromated Cu-K α radiation (50 kV, 40 mA). Both structures were

* Corresponding author. Tel.: +81 45 339 3366; fax: +81 45 339 3345.

E-mail address: smatsu@edhs.ynu.ac.jp (S. Matsumoto).

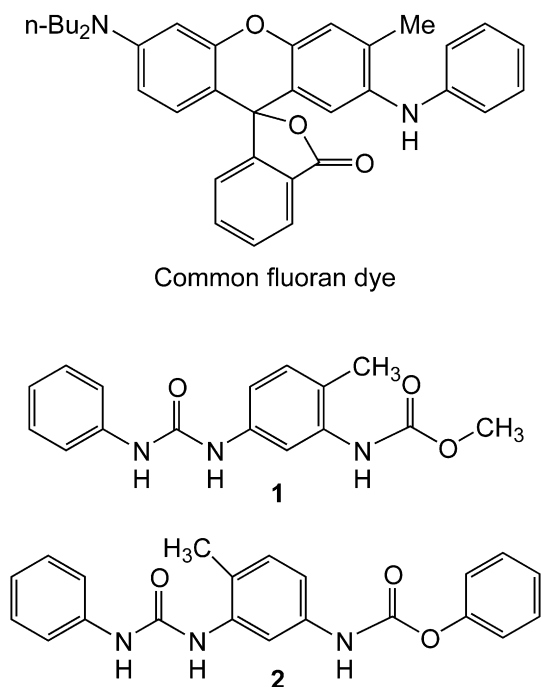


Fig. 1. Chemical structure of a common fluoran dye and UU derivatives.

solved by the direct method [7] and refined by least-squares calculation using the Crystal Structure 3.10 program package [8]. All non-hydrogen atoms were anisotropically refined except for the disordered benzene molecules in the solvate crystals of **2**. The benzene molecule was refined on the assumption that they are disordered into two conformations with a 50% occupancy sharing

of one C–C bond. All hydrogen atoms were located on the calculated positions and refined by the riding model. The crystallographic data have been deposited at the CCDC, 12 Union Road, Cambridge CB2 1EZ, UK, and copies can be obtained upon request, free of charge, by quoting the publication citation and the deposition number (**1**: CCDC294123 and **2**: CCDC294124). Crystal data for **1**: C₁₆H₁₇N₃O₃, *Mw* = 299.33, monoclinic, *P*2₁, *Z* = 4, *a* = 12.583 (7), *b* = 7.715 (3), *c* = 16.152 (8) Å, β = 99.43 (2)°, *D*_{calc} = 1.285 g/cm³, 13009 reflections were collected, 2845 unique (*R*_{int} = 0.044), 431 parameters, *R*₁ = 0.053, *wR*₂ = 0.081, GOF = 1.00, refinement on *F*; **2**: C₂₇H₂₅N₃O₃, *Mw* = 439.52, monoclinic, *C*2/c, *Z* = 8, *a* = 26.295 (5), *b* = 12.359 (3), *c* = 16.587 (4) Å, β = 118.07 (2)°, *D*_{calc} = 1.211 g/cm³, 21598 reflections were collected, 3932 unique (*R*_{int} = 0.048), 303 parameters, *R*₁ = 0.074, *wR*₂ = 0.097, GOF = 0.98, refinement on *F* (Fig. 1).

3. Results and discussion

As shown in Fig. 2, two unsymmetrical molecules were found in the crystal of compound **1**. They have different molecular conformations. In molecule A, two phenyl groups and the urea moiety are aligned in an almost planar manner. However, the urethane moiety is turned about its N–C bond to the central phenyl ring through an angle of about 97°. On the other hand, in molecule B, the central phenyl ring is twisted by about 47° against the almost planar arrangement of the terminal phenyl ring and the urea moiety. A further 48° torsion angle was recognized between the central phenyl ring and the urethane moiety. These two unsymmetrical molecules are located along the *c*-axis to form a complementary hydrogen bond between the carbonyl group of the urea moiety and the amino group of the urethane moiety (see Fig. 3). A hydrogen-bond network was also found along the *b*-axis. This is caused by a bifurcated (three-centered) hydrogen bond between the carbonyl group of the urethane moiety and two amino groups of the urea

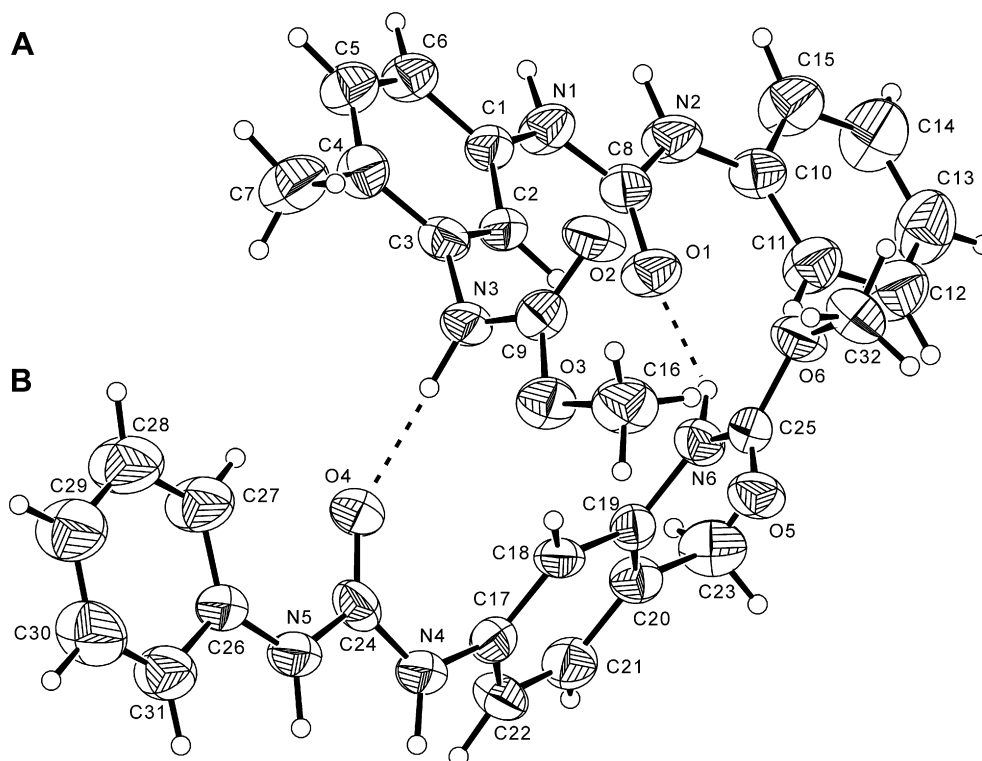


Fig. 2. Molecular structure of **1**. Two unsymmetrical units are depicted. A complementary hydrogen bond is indicated by the dotted line.

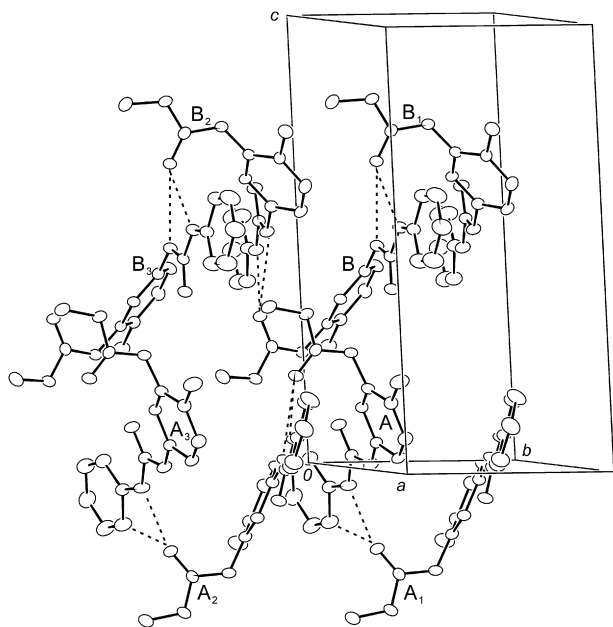


Fig. 3. Hydrogen-bond network of **1**. The hydrogen bonds are indicated by the dotted line. The molecules are given by the following symmetry operation; A_1 : $-x, y + 0.5, -z$, A_2 : $-x, y - 0.5, -z$, A_3 : $x, y - 1, z$, B_1 : $-x, y + 0.5, -z + 1$, B_2 : $-x, y - 0.5, -z + 1$, B_3 : $x, y - 1, z$.

moiety. This network is built between molecules associated with a 2-fold screw axis along the b -axis. The geometry of these hydrogen bonds is summarized in Table 1. These results indicate that compound **1** has the ability to form strong hydrogen bonds [9]. Compound **1** can be thus regarded as a multiple hydrogen-bond module. The colouration reaction based on the ring cleavage in fluoran dyes is an equilibrium reaction. The coloured form of the fluoran dyes has several donors and acceptors for hydrogen bonds [10]. If a hydrogen-bond network will form between the coloured fluoran dyes and the UU developers, this equilibrium should be displaced for production of the coloured state. The present

Table 1
Geometry of hydrogen bonds in **1**.

	Distance (N...O)/Å	Angle (N–H...O)/°
N3...O4	2.814 (8)	176.5 (3)
N6...O1	2.936 (8)	153.2 (2)
N1...O2 ¹⁾	3.072 (7)	145.4 (2)
N2...O2 ¹⁾	2.887 (8)	159.1 (3)
N4...O5 ²⁾	3.079 (7)	148.6 (2)
N5...O5 ²⁾	2.918 (7)	158.9 (2)

Symmetry operation, 1): $-x, y + 0.5, -z, 2)$: $-x, y + 0.5, -z + 1$.

hydrogen-bonding ability is therefore considered to be an important parameter affecting the fastness of the coloured images of the thermo-sensitive paper using **1**.

The strong hydrogen-bonding ability of **1** in the solid state can be explained by the bond lengths of the urea and urethane moieties from the viewpoint of its electrostatic nature. The bond lengths of C=O and C–N in the urea moiety for both unsymmetrical molecules are slightly short (1.21–1.22 Å) and long (1.36–1.37 Å), respectively, as compared to those of the unsubstituted urea and aliphatic urea derivatives [11]. This result also shows that the two amino-protons of the urea moiety can be expected to exhibit a slightly higher acidity as compared to that of the other urea derivatives. The bond lengths of the C=O in the urethane moiety for both unsymmetrical molecules are also found to be slightly shorter than that of the other urethane derivatives (1.21 Å) [11]. These relatively polarized carbonyl groups are considered to result in the formation of a strong hydrogen bond. Comparatively short aromatic C–C bonds were also observed in the terminal phenyl ring attached to the urea moiety. This can be ascribed to a ring-puckering motion.

Figs. 4 and 5 show the molecular and crystal structures of the inclusion crystals of **2** with benzene. Our group also found that compound **2** easily form similar inclusion crystals with solvent molecules such as THF and acetone. The included benzene molecules were found to be disordered in the two conformations sharing one aromatic C–C bond. These disordered benzene molecules are placed in such a way that the benzene molecules occupied

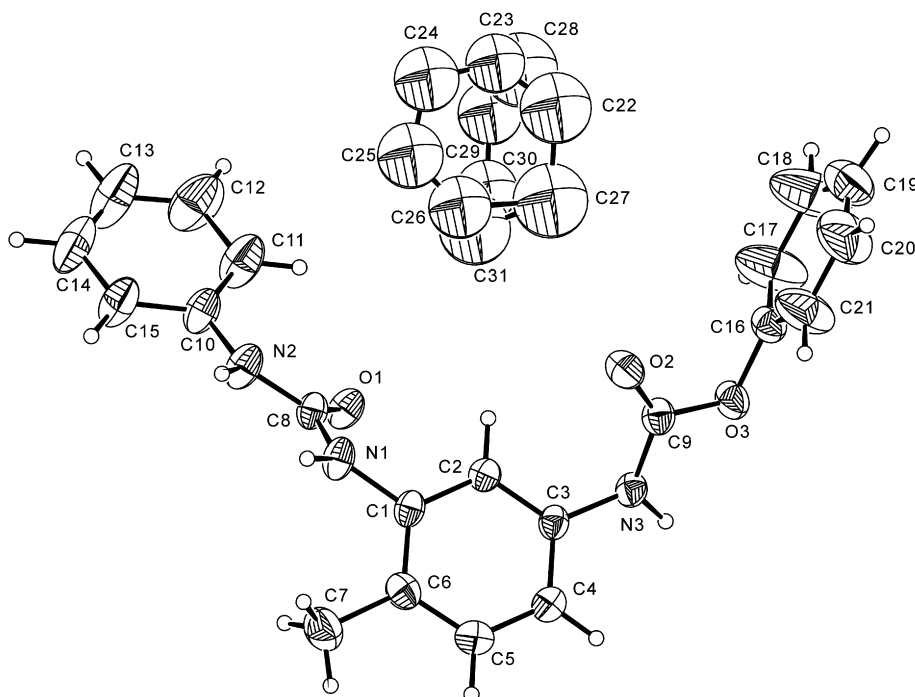


Fig. 4. Molecular structure of **2** with the disordered benzene.

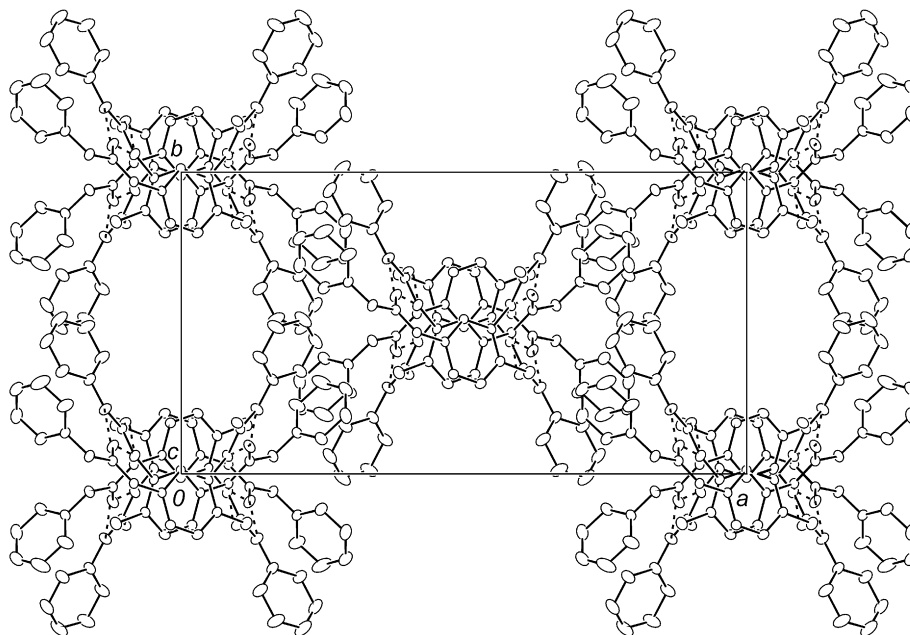


Fig. 5. Hydrogen-bond network of **2**. The disordered benzene molecules are omitted for clarity. The hydrogen bonds are indicated by the dotted line.

the voids between the hydrogen-bond network of **2**. The molecules of **2** have a non-planar conformation. The urea moiety and the attached terminal phenyl ring are arranged in almost planar fashion, but this unit is twisted against the central phenyl ring by about 53° . The urethane moiety is also twisted against the central phenyl ring by about 41° . The dihedral angle between the urethane moiety and the attached terminal phenyl ring is almost perpendicular. A hydrogen-bond network was also found in compound **2** along the *c*-axis as shown in Fig. 5. The network can be divided into two complementary hydrogen-bonded molecular pairs. In the first pair, two molecules form a complementary bifurcated hydrogen bond between the two amino groups of the urea moiety of one molecule and the carbonyl group of the urethane moiety of the molecule designated by the $(-x, -y, -z + 1)$ symmetry operation. Another complementary hydrogen bond is constructed in the second molecular pair in which the amino group of the urethane moiety of one molecule is bonded with the carbonyl group of the urea moiety of the molecule given by the $(-x, -y, -z + 1.5)$ symmetry operation to the first one. The geometry of these hydrogen bonds summarized in Table 2 indicates that compound **2** has the ability to form strong hydrogen bonds. Compound **2** is thus presumed to have the same property which affects the fastness of the thermo-sensitive papers like compound **1**.

The bond characteristics of the urea and urethane moieties in **2** were found to be almost similar to those of **1**. The bond lengths of C=O and C–N in the urea moiety are slightly short (1.21 Å) and long (1.36 Å), respectively, as compared to those of the other urea derivatives [11]. The C=O bond of the urethane moiety was also found to be relatively short (1.205 Å) as compared to those of the other urethane derivatives [11]. Comparatively short aromatic C–C bonds were also observed in the terminal phenyl ring attached to

the urethane moiety. This can be a result from the ring-puckering motion the same as those of **1**.

4. Conclusions

A crystal structure analysis was carried out on two new developers, the urea–urethane derivatives, for high-performance thermo-sensitive paper. These derivatives form a multiple hydrogen-bond network in crystals between their urea and urethane moieties. This hydrogen-bonding ability should be considered to stabilize the coloured state of the fluoran dyes in thermo-sensitive paper to achieve very high fastness of the printed images. A study of the colouration mechanism of these UU derivatives is also in progress and the result will be reported elsewhere.

References

- [1] Gregory P. High-technology applications of organic colorants. New York: Plenum Press; 1991. p. 123.
- [2] Matsuoka M, Ueda K, Kitao T. The PPP-MO method to the prediction of color in fluoran dyes. *Journal of the Japan Society of Colour Material* 1982;55(4):213–8 [in Japanese].
- [3] Krishnan AV, Stathis P, Permuth SF, Tokes L, Feldman D. Bisphenol-A: an estrogenic substance is released from polycarbonate flakes during autoclaving. *Endocrinology* 1993;132(6):2279–86.
- [4] Kitamura S, Suauki T, Sanoh S, Kohta R, Jinno N, Sugihara K, et al. Comparative study of the endocrine-disrupting activity of Bisphenol A and 19 related compounds. *Toxicological Sciences* 2005;84:249–59.
- [5] Kabashima K, Iwaya T. Color-developing compound having urea and urethane groups for thermal recording. Patent WO00/14058 A1.
- [6] Kabashima K, Kobayashi H, Iwaya T. Novel urethane-urea color former and recording material such as heat-sensitive recording material. Patent WO01/66515 A1.
- [7] Altomare A, Cascarano G, Giacovazzo C, Guagliardi A, Burla MC, Polidori G, et al. *SIR92-A* program for automatic solution of crystal structures by direct methods. *Journal of Applied Crystallography* 1994;27:435–6.
- [8] Crystal Structure 3.10: Crystal structure analysis package, Rigaku and Rigaku/MS; 2000–2002.
- [9] Kuleshova LN, Zorkii PM. Hydrogen bond length in homomolecular organic crystals. *Acta Crystallography Section B* 1981;37:1363–6.
- [10] Okada K, Okada S. X-ray crystal structure analysis and atomic charges of color former and developer: 5. Colored formers. *Journal of Molecular Structure* 1999;510:35–51.
- [11] Allen FH, Kennard O, Watson DG, Brammer L, Orpen AG, Taylor R. Tables of bond lengths determined by X-ray and neutron diffraction. Part 1. *Journal of the Chemical Society Perkin Transactions II* 1987:S1–19.

Table 2
Geometry of hydrogen bonds in **2**.

	Distance (N...O)/Å	Angle (N–H...O)/°
N1...O2 ¹⁾	2.960 (4)	155.5 (1)
N2...O2 ¹⁾	2.967 (4)	157.2 (1)
N3...O1 ²⁾	2.851 (4)	165.6 (1)

Symmetry operation, 1): $-x, y, -z + 1.5$, 2): $-x, -y, -z + 1$.