

This article was downloaded by:

On: 15 January 2011

Access details: Access Details: Free Access

Publisher Taylor & Francis

Informa Ltd Registered in England and Wales Registered Number: 1072954 Registered office: Mortimer House, 37-41 Mortimer Street, London W1T 3JH, UK



Green Chemistry Letters and Reviews

Publication details, including instructions for authors and subscription information:

<http://www.informaworld.com/smpp/title~content=t748292817>

Corrosion inhibition of Neem (*Azadirachta indica*) leaves extract as a green corrosion inhibitor for Zinc in H₂SO₄

Sanjay Kumar Sharma^a; Ackmez Mudhoo^b; Gargi Jain^a; Essam Khamis^c

^a Computational & Green Chemistry Research Laboratory, Institute of Engineering & Technology, Alwar, India ^b Department of Science, Chemistry Division, Universal College, Mauritius ^c Faculty of Science, Alexandria University, Mohram Bey, Egypt

To cite this Article Sharma, Sanjay Kumar , Mudhoo, Ackmez , Jain, Gargi and Khamis, Essam(2009) 'Corrosion inhibition of Neem (*Azadirachta indica*) leaves extract as a green corrosion inhibitor for Zinc in H₂SO₄', Green Chemistry Letters and Reviews, 2: 1, 47 – 51

To link to this Article: DOI: 10.1080/17518250903002335

URL: <http://dx.doi.org/10.1080/17518250903002335>

PLEASE SCROLL DOWN FOR ARTICLE

Full terms and conditions of use: <http://www.informaworld.com/terms-and-conditions-of-access.pdf>

This article may be used for research, teaching and private study purposes. Any substantial or systematic reproduction, re-distribution, re-selling, loan or sub-licensing, systematic supply or distribution in any form to anyone is expressly forbidden.

The publisher does not give any warranty express or implied or make any representation that the contents will be complete or accurate or up to date. The accuracy of any instructions, formulae and drug doses should be independently verified with primary sources. The publisher shall not be liable for any loss, actions, claims, proceedings, demand or costs or damages whatsoever or howsoever caused arising directly or indirectly in connection with or arising out of the use of this material.

RESEARCH LETTER

Corrosion inhibition of Neem (*Azadirachta indica*) leaves extract as a green corrosion inhibitor for Zinc in H₂SO₄

Sanjay Kumar Sharma^a, Ackmez Mudhoo^{b*}, Gargi Jain^a and Essam Khamis^c

^aComputational & Green Chemistry Research Laboratory, Institute of Engineering & Technology, Alwar, India; ^bDepartment of Science, Chemistry Division, Universal College, Mauritius; ^cFaculty of Science, Alexandria University, Mohram Bey, Egypt

(Received 5 January 2009; final version received 28 April 2009)

The corrosion inhibition of Neem (*Azadirachta indica* (AZI)) leaves extract as a green inhibitor of zinc corrosion in H₂SO₄ has been studied using the gravimetric method. The results of the study reveal that the different concentrations of the AZI extract inhibit zinc corrosion and that inhibition efficiency of the extract varies with concentration and temperature.

Keywords: corrosion; inhibitors; zinc; *Azadirachta indica*

Introduction

Corrosion is the destruction of material resulting from exposure and interaction with the environment. It is a major problem that must be confronted for safety, environment, and economic reasons (1). Several efforts have been made using corrosion preventive practices and the use of green corrosion inhibitors is one of them (2). The use of green inhibitors for the control of corrosion of metals (3) and alloys which are in contact with aggressive environment is an accepted and growing practice (4,5). Large numbers of organic compounds are under study to investigate their corrosion inhibition potential. All these studies have revealed that organic compounds, especially those with N, S, and O, show significant inhibition efficiency. However, most of these compounds are not only expensive, but also toxic to living beings (6). It is needless to point out the importance of cheap and safe inhibitors of corrosion.

Plant extracts and organic species have therefore become important as an environmentally acceptable, readily available, and renewable source for a wide range of inhibitors (7–12). They are the rich sources of ingredients which have very high inhibition efficiency (6) and are hence termed “Green Inhibitors” (10). Green corrosion inhibitors (13) are biodegradable and do not contain heavy metals or other toxic compounds. The successful use of naturally occurring substances to inhibit the corrosion of metals in acidic and alkaline environment have been reported by some research groups (14–20) to mention

but a few. Research efforts to find naturally organic substances or biodegradable organic materials to be used as effective corrosion inhibitors of a wide number of metals has been one of the key areas in our research group (21).

Azadirachta indica (AZI) – the Neem plant

Our focus in this paper is on Neem (*Azadirachta indica* (AZI)), which is more specifically the extract from Neem leaves. Several studies have been carried out and have remained focused on the Neem plant parts for their various pharmacological activities (anti-inflammatory, anti-pyretic, analgesic, immunostimulant, anti-fertility, anti-carcinogenic, anti-malarial, and hepatoprotective) (22–24) and medicinal properties (24) to mention but a few. The Neem extract has been only very occasionally involved in environmental engineering and environmental chemistry research with the analysis of the adsorption of Pb(II) from aqueous solution by AZI leaf powder by Bhattacharyya and Sharma (25), the adsorption and corrosion inhibitive properties of AZI in acid solutions (26) and the study of copper corrosion inhibition by AZI leaves extract in 0.5M sulfuric acid by (27). AZI has been well known in India and its neighboring countries for more than 2000 years as one of the most versatile medicinal plants having a wide spectrum of biological activity (24). Neem is an evergreen tree, cultivated in various parts of the Indian subcontinent. Neem has been extensively used in ayurveda (22), unani, and homoeopathic medicine and has become a

*Corresponding author. Email: ackmezchem@yahoo.co.uk

cynosure of modern medicine. The Sanskrit name of the Neem tree is "Arishta" meaning "reliever of sickness" and hence is considered as "Sarbarogani-barini" (24). The tree is still regarded as a "village dispensary" in India. The importance of the Neem tree has been recognized by the US National Academy of Sciences, which published a report in 1992 entitled "Neem – a tree for solving global problems."

Chemical investigation on the products of the Neem tree was extensively undertaken in the middle of the twentieth century. Nimbin was the first bitter compound isolated from Neem oil, and thereafter more than 135 compounds have been isolated from different parts of Neem and several reviews have also been published on the chemistry and structural diversity of these compounds which are divided into two major classes: isoprenoids (28) and others. Neem extracts contain significant amounts of water soluble, electrochemically active compounds, as well as high concentrations of alkaloids, fatty acids, and nitrogen and oxygen-containing compounds. Neem is bitter in taste. The bitterness is due to an array of complex compounds called "triterpenes" or more specifically "limonoids." Nearly 100 protolimonoids, limonoids or tetranortriterpenoids, pentanortriterpenoids, hexanortriterpenoids, and some non-terpenoid constituents have been isolated from various parts of the Neem tree (29,30); still more are being isolated. The most important bioactive principal is azadirachtin; at least 10 other limonoids possess insect growth in regulating activity (31,32). Neem fruits, seeds, oil, leaves, bark, and roots have such uses as general antiseptics, anti-microbials, treatment of urinary disorders, diarrhea, fever and bronchitis, skin diseases, septic sores, infected burns, hypertension, and inflammatory diseases. Neem oil and its isolates – nimbidin, nimbidol, and nimbin – inhibit fungal growth on humans and animals (33). Neem leaf extracts and teas can treat malaria and the anti-malarial action is attributable to gedunin, a limonoid. Given the wide spectrum of chemical species present in Neem leaves and their respective multifaceted chemical and biological properties, we therefore articulated that channeling Neem leaf extract for yet another use into green inhibition of corrosion studies may yield some interesting results. All the more, Neem extract has been only very occasionally involved in environmental engineering and environmental chemistry research with the analysis of the adsorption of Pb(II) from aqueous solution by Neem leaf powder by Bhattacharyya and Sharma (25), the adsorption and corrosion inhibitive properties of AZI in acid solutions (26) and the study of copper corrosion inhibition by AZI leaves extract in 0.5M sulfuric acid by Valek and Martinez (27).

Research objectives

Due to its position in the electrochemical series, zinc with an oxidation potential of 0.76 eV is much prone to corrosion, especially in acidic medium. The corrosion of Zn in acidic medium is believed to occur according to "Hydrogen evolution Mechanism." In the present study, we are trying to study corrosion of zinc and the inhibition of the corrosion process by AZI extract. To the best of our knowledge, nothing has been specifically reported on the use of AZI extract for the inhibition of zinc corrosion in acidic medium. AZI leaves are often used in the medicinal and pharmaceutical industry. An additional beneficial use of Neem leaves to curb corrosion of zinc would surely imply the successful utilization of this powerful and versatile natural resource in the metallurgical, materials science, and chemical engineering industries.

The present study therefore seeks to investigate the inhibitive properties of AZI leaves extract for zinc corrosion using a gravimetric technique in an acidic media (H_2SO_4 acid) with and without the extract at two temperatures. Any positive result would help reduce the economic cost of corrosion control as well as decrease the subsequent environmental threats from inhibitor usage because Neem leaves extract is non-toxic and biodegradable.

Results and discussion

Table 1 shows values of corrosion rate (CR) of zinc in all the concentrations of H_2SO_4 studied and it shows that CR increases with increase in H_2SO_4 concentration. Table 2 shows the CR for the corrosion of zinc at 2.0N H_2SO_4 in the absence and presence of AZI extract at 303 and 333 K. Addition of increasing concentration of the inhibitor generally retards the CR of zinc in the solutions. This is clearly seen from the decreasing change in mass loss taking place (Figure 1A and B) at a particular acid concentration corresponding with an increase in inhibitor concentration. Table 3 shows values of inhibition efficiency of the different concentrations of AZI extract at 303 and 333 K.

Table 1. Corrosion rate for the corrosion of zinc in H_2SO_4 at 303 K.

Concentration of H_2SO_4 (N)	CR (303 K)
0.5	1.18
1.0	1.32
2.0	1.48

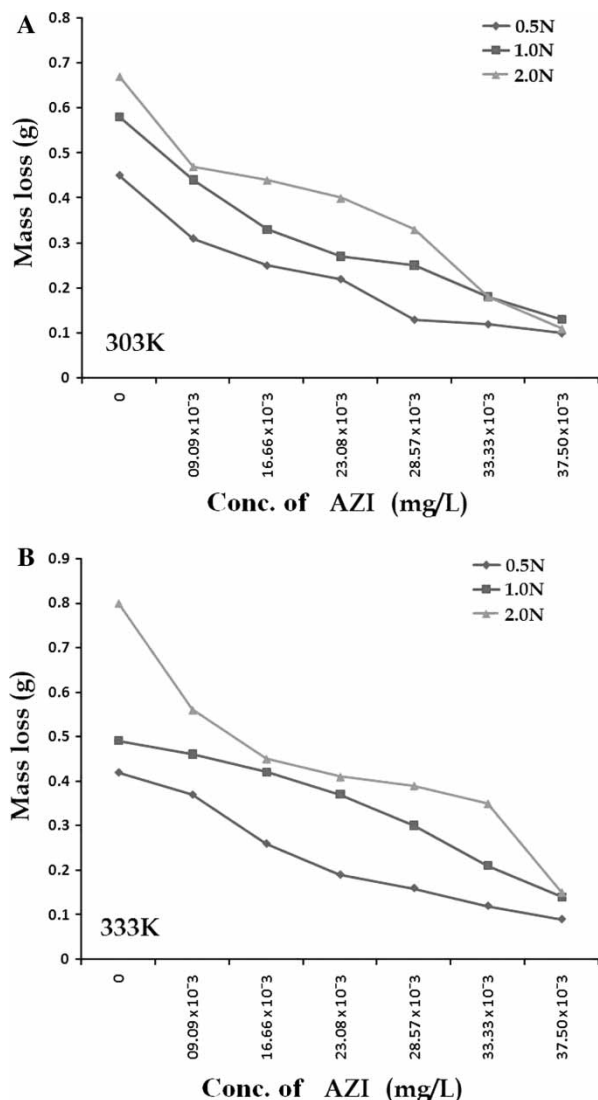


Figure 1. Variation of mass loss change with increase in concentration of AZI leaves extract for various acid concentrations at the two temperatures investigated.

Table 2. Corrosion rates for the corrosion of zinc in 2N H₂SO₄ solutions containing AZI extract.

Concentration of AZI extract in 2.0N H ₂ SO ₄ ($\times 10^{-3}$ g/L)	CR (mmpy) at 303 K	CR (mmpy) at 333 K
Uninhibited	1.48	1.73
9.09	0.87	1.21
16.66	0.83	0.87
23.08	0.78	0.86
28.57	0.68	0.83
33.33	0.48	0.81
37.50	0.31	0.62

Effect of concentration

From Tables 1 and 2, it is found that the rate of corrosion of zinc is affected by concentration of H₂SO₄, temperature, and concentration of AZI extract. The rate of zinc corrosion increases as the concentration of H₂SO₄ increases and also increases as the temperature is increased (Figure 1). Analysis and interpretation of trends in Figure 1 show that corrosion increases as the concentration of the acid increases confirming that the rate of corrosion of zinc in H₂SO₄ increases with concentration. The mass loss taking place and recorded at the different concentrations of the AZI extract are lower than that of the blank solution (for the 2.0N H₂SO₄) indicating that different concentrations of the AZI extract retard the corrosion of zinc. It is supposed to be due to adsorption of AZI extract on the surface of Zn. This hypothesis shall be verified in a future study with details of the electrochemical studies reported and discussed therein.

Effect of temperature

Figure 1 hence shows mass loss plots for the corrosion of zinc in the presence of different concentration of the AZI extract at 303 K (A) and 333 K (B), respectively. Comparing Figure 1A and B, it is found that at a fixed concentration of the inhibitor and a fixed acid concentration, the mass loss taking place at 333 K is in most of the instances higher than that occurring 303 K indicating that the inhibition efficiency of AZI extract decreases with increase in temperature. The decrease may be due to competition between forces of adsorption and desorption. These very same competing forces of adsorption and desorption may also actually explain the occasional discrepancies in mass loss change observed in Figure 1. From Table 3, it can also be seen that inhibition efficiency of AZI extract varies with its concentration. Optimum value of inhibition efficiency (83.58%) was obtained at an

Table 3. Inhibition efficiency (%I) for 2.0N H₂SO₄

Concentration of AZI extract ($\times 10^{-3}$ g/L)	Gravimetric	
	%I (303 K)	%I (333 K)
9.09	29.85	30.00
16.66	34.32	43.75
23.08	40.30	48.75
28.57	50.75	51.25
33.33	73.13	56.25
37.50	83.58	81.25

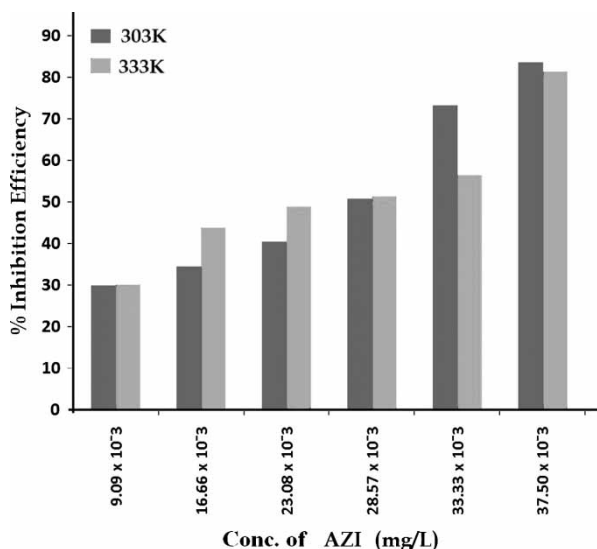


Figure 2. Variation of inhibition efficiency with concentration of AZI leaves extract.

extract concentration of 37.50 mg/L, while the least value was obtained at an extract concentration of 9.09 mg/L. Figure 2 shows the variation of inhibition efficiency against the different concentrations of AZI extract at both 303 and 333 K. The significant difference between values of inhibition efficiency of AZI extract obtained at 303 and 333 K for especially the higher concentrations of the extract suggests that the mechanism of adsorption of the inhibitor on the zinc surface is by physical adsorption. For a physical adsorption mechanism, inhibition efficiency of an inhibitor decreases with temperature while for a chemical adsorption mechanism, values of inhibition efficiency increase with temperature (34,35).

Experimental

Preparation of stock solution of *Neem Azadirachta indica* (AZI) leaves extract

Stock solution of the AZI leaves extract was prepared by boiling 0.5 kg of air-dried Neem leaves in deionized water and left overnight. The contents of the extraction process were then mixed in a graduated cylinder, filtered, and the resulting solution was kept in a refrigerator at low temperatures of 2°C in order to prevent the contents from being altered due to the chemical, physical, and biological reactions it might otherwise undergo (36).

Specimen preparation

Rectangular specimen sheets of zinc were mechanically pressed cut to form different coupons, each of dimension 5.0 × 2.5 × 0.04 cm. Each coupon was

degreased by washing with ethanol, dried in acetone, and preserved in a dessicator. All reagents used for the study were Analar grade and double distilled water was used for their preparation. Specimens containing a small hole of 2 mm diameter near the upper edge were used for the determination of CR. The working surfaces of the zinc coupons were carefully and lightly polished with grade P600 SiC polishing paper in order to remove the oxide layer and eliminate the reactions that would have otherwise taken place with the acid and this zinc oxide layer.

Calculation of inhibition efficiency (%I) and degree of surface coverage (θ)

The mass loss method was employed for a room temperature (303 K) and 333 K. The temperature for each run of the experiments was kept constant using a thermostat. In this procedure, the mass loss of the metal in uninhibited (with no AZI extract) and inhibited solutions were monitored and recorded. About 50 mL of test solutions were analyzed. From these data, the inhibition efficiency (%I) and degree of surface coverage (θ) were calculated (37) using Equations 1 and 2, respectively:

$$\%I = \left(1 - \frac{\Delta M_i}{\Delta M_u}\right) \times 100 \quad (1)$$

where ΔM_u and ΔM_i are the mass loss of zinc in uninhibited solution and inhibited solution, respectively.

$$\theta = \left(1 - \frac{\Delta M_i}{\Delta M_u}\right) \quad (2)$$

The CR in mmpy (millimetres per year) has been calculated from Equation 3.

$$CR = \frac{(MassLoss) \times 87.6}{(Area)(Time)(MetalDensity)} \quad (3)$$

where mass loss is expressed in mg, area is expressed in cm² of metal surface exposed, time is expressed in hours of exposure and metal density is expressed in g/cm³ and 87.6 is a conversion factor.

Conclusion

From the present study, it is found that AZI leaves extract can be used as an inhibitor for zinc corrosion in H₂SO₄ medium. While the green inhibitor molecule most supposedly acts by being adsorbed on zinc surface, the overall inhibition is provided by a synergistic effect. It has also been found that the inhibitive action of AZI leaves extract is basically controlled by temperature and the concentration of the inhibitor. A probable sequel to the present study

would be to perform in-depth chemical and analytical investigations using techniques like NMR or IR spectroscopy together with electrochemical studies so as to depict which are the active components of the AZI leaves extract involved in the corrosion inhibition reaction, and also elucidate the corrosion inhibition mechanism.

Acknowledgements

The authors are grateful to Dr. V.K. Agarwal (Chairman) of the Institute of Engineering and Technology (IET) Group of Institutions, Alwar, India, for providing us the opportunity to establish a Computational and Green Chemistry Research Laboratory at IET whereat burgeoned the idea to carry out the present work. Special thanks also go to Ms Vanessa Jumnoodo (Department of Chemical & Environmental Engineering, University of Mauritius) for her insight into the further chemical and analytical tests that have to be done to elucidate the corrosion inhibition reaction mechanisms.

References

- Thompson, N.G.; Yunovich, M.; Dunmire, D. *Corrosion Rev.* **2007**, *25*, 247–262.
- Anuradha, K.; Vimala, R.; Narayanasamy, B.; Arcockia Selvi, J.; Rajendran, S. *Linn. Chem. Eng. Comm.* **2008**, *195*, 352–366.
- Valdez, B.; Cheng, J.; Flores, F.; Schorr, M.; Veleva, L. *Corrosion Rev.* **2003**, *21*, 445–458.
- Taylor, S.R.; Chambers, B.D. *Corrosion Rev.* **2007**, *25*, 571–590.
- Khaled, K.F. *Int. J. Electrochem. Sci.* **2008**, *3*, 462–475.
- Bothi Raja, P.; Sethuraman, M.G. *Mater Lett.* **2008**, *62*, 113–116.
- Rajendran, S.; Amalraj, A.J.; Joice, M.J.; Anthony, N.; Trivedi, D.C.; Sundaravadivelu, M. *Corrosion Rev.* **2004**, *22*, 233–248.
- Mesbah, A.; Juers, C.; Lacouture, F.; Mathieu, S.; Rocca, E.; François, M.; Steinmetz, J. *Solid State Sci.* **2007**, *9*, 322–328.
- Okafor, P.C.; Osabor, V.I.; Ebenso, E.E. *Pigment and Resin Technol.* **2007**, *36*, 299–305.
- Lebrini, M.; Traisnel, M.; Lagrenée, M.; Mernari, B.; Bentiss, F. *Corrosion Sci.* **2008**, *50*, 473–479.
- Radojčić, I.; Berković, K.; Kovač, S.; Vorkapić-Furač, J. *Corrosion Sci.* **2008**, *50*, 1498–1504.
- Refaey, S.A.M.; Abd El Malak, A.M.; Taha, F.; Abdel-Fatah, H.T.M. *Int. J. Electrochem. Sci.* **2008**, *3*, 167–176.
- Sharma, S.K.; Mudhoo, A.; Khamis, E. *J. Corrosion Sci. Eng. (Electronic Journal)* **2009**, *11*, 1–25.
- Abdel-Gaber, A.M.; Khamis, E.; Abo-Eldahab, H.; Adeel, S. *Mater. Chemistry and Phys.* **2008**, *109*, 297–305.
- Khamis, E.; Hefnawy, A.; El-Demerdash, A.M. *Materialwissenschaft und Werkstofftechnik* **2007**, *38*, 227–232.
- Umoren, S.A.; Ebenso, E.E. *Pigment and Resin Technol.* **2008**, *37*, 173–182.
- Okafor, P.C.; Ebenso, E.E. *Pigment and Resin Technol.* **2007**, *36*, 134–140.
- El-Etre, A.Y. *Appl. Surf. Sci.* **2006**, *252*, 8521–8525.
- Umoren, S.A.; Ogbobe, O.; Ebenso, E.E.; Ekpe, U.J. *Pigment and Resin Technol.* **2006**, *35*, 284–292.
- Bendahou, M.A.; Benadallah, M.B.E.; Hammouti, B.B. *Pigment and Resin Technol.* **2006**, *35*, 95–100.
- Sharma, S.K.; Chaudhary, A.; Singh, R.V. *RASA-YAN J. Chem.* **2008**, *1*, 68–92.
- Subapriya, R.; Nagini, S. *Curr. Med. Chem. Anti Can. Agents.* **2005**, *5*, 149–156.
- Dasgupta, T.; Banerjee, S.; Yadava, P.K.; Rao, A.R. *J. Ethnopharmacol.* **2004**, *92*, 23–36.
- Biswas, K.; Chattopadhyay, I.; Banerjee, R.K.; Bandyopadhyay, U. *Curr. Sci.* **2002**, *82*, 1336–1345.
- Bhattacharyya, K.G.; Sharma, A. *J. Hazard. Mater.* **2004**, *113*, 97–109.
- Oguzie, E.E. *Pigment and Resin Tech.* **2006**, *35*, 334–340.
- Valek, L.; Martinez, S. *Mater. Lett.* **2007**, *61*, 148–151.
- Roy, M.K.; Kobori, M.; Takenaka, M.; Nakahara, K.; Shinmoto, H.; Isobe, S.; Tsushida, T. *Phytother. Res.* **2007**, *21*, 245–250.
- Sawchuk, M.J. An environmentally friendly insecticide for conifer seed orchards. MS Thesis, Department of Biological Sciences, Simon Fraser University, 1994, 1–58.
- Koul, O.; Isman, M.B.; Ketkar, C.M. *Can. J. Bot.* **1990**, *68*, 1–11.
- Saxena, R.C.; Kidiavai, E.L. *Phytoparasitica.* **1997**, *25*, 99–110.
- Schmutterer, H. *The Neem Tree Azadirachta Indica A. Juss. and Other Meliaceous Plants: Source of Unique Natural Products for Integrated Pest Management, Medicine, Industry and Other Purposes*; Germany: VCH, Weinheim, 1995.
- Suresh, G.V.; Gopalakrishnan, G.; Masilamani, S. *Neem for Plant Pathogenic Fungal Control: The Outlook in the New Millennium. Neem: Today and in the New Millennium*. Springer: The Netherlands, 2007; pp 183–207.
- Ebenso, E.E. *Bull Electrochem.* **2003**, *19*, 209–216.
- Ebenso, E.E. *Bull Electrochem.* **2004**, *20*, 551–559.
- Sliwka-Kaszynska, M.; Kot-Wasik, A.; Namiesnik, J. *Crit. Rev. Environ. Sci. Tech.* **2003**, *33*, 31–44.
- Eddy, N.O.; Ebenso, E.E. *AJPAC.* **2008**, *2*, 46–54.