

Crystal structure and synthesis of a novel tetranuclear iron(III) complex with a defective double-cubane core†

Hui Li,^a Zhuang Jin Zhong,^{*,a} Wei Chen^b and Xiao-Zeng You^a

^a Coordination Chemistry Institute, State Key Laboratory of Coordination Chemistry, Nanjing University, Nanjing, 210093, P. R. China

^b Department of Chemistry, University of Malaya, Lambah Pautai, 59100 Kuala, Malaysia

A novel tetranuclear iron(III) complex $[\text{Fe}_4(\text{OCH}_3)_6(\text{acac})_4(\text{N}_3)_2]$ (acac = acetylacetonate) has been synthesized and shown by X-ray crystallography to contain an unusual defective double-cubane core connected by μ -OCH₃ and μ_3 -OCH₃ bridges; it also shows an antiferromagnetic interaction.

One-dimensional magnetic compounds as important precursors of molecular magnets have aroused wide interest.^{1–3} The azide group is a versatile bridging ligand and useful for generating this kind of system. A series of one- and two-dimensional μ -azide nickel(II) complexes has been synthesized and characterized.^{4–6} A few manganese(III) chain complexes have also been synthesized.⁷ However, no μ -azide Fe^{III} chain complexes have been reported until now. To obtain such a complex we have attempted the reaction of $[\text{Fe}(\text{acac})_2\text{NO}_3]$ with NaN_3 in methanol. To our surprise, a methoxo-bridged tetranuclear iron(III) complex $[\text{Fe}_4(\text{OCH}_3)_6(\text{acac})_4(\text{N}_3)_2]$ (acac = acetylacetonate) was obtained instead in which the azide ion acts as a terminal ligand. There has been a growing interest in the synthesis of polynuclear iron complexes due to the discovery that the catalytic sites of a number of non-haem iron proteins contain oxo- or hydroxo-bridged diiron units and the relevance of large polyiron(II,III)-oxo aggregates to the ferritin core.^{8–10} And a large number of polynuclear oxo-, hydroxo- and alkoxo-bridged iron complexes have been synthesized and characterized so far.^{11–14} However, no tetranuclear $[\text{Fe}^{\text{III}}_4(\text{OR})_6]^{6+}$ complex has been reported. In this view, $[\text{Fe}_4(\text{OCH}_3)_6(\text{acac})_4(\text{N}_3)_2]$ is a novel example. In this communication, the synthesis, crystal structure and magnetic properties of this tetranuclear iron(III) complex are presented.

The complex $[\text{Fe}_4(\text{OCH}_3)_6(\text{acac})_4(\text{N}_3)_2]$ was prepared by the reaction of equimolar amounts of $[\text{Fe}(\text{acac})_2\text{NO}_3]$ ¹⁵ (0.315 g, 1 mmol) and NaN_3 (0.065 g, 1 mmol) in methanol and acetone (1 : 2; 30 cm³) with stirring for 0.5 h at room temperature. A red crystalline solid suitable for X-ray structure analysis was obtained after slow evaporation of this solution (Found: C, 34.90; H, 5.45; N, 9.75. Calc. for $\text{C}_{26}\text{H}_{46}\text{Fe}_4\text{N}_6\text{O}_{14}$: C, 35.10; H, 5.20; N, 9.45%). The structure of the entire molecule is illustrated in Fig. 1.†

The structure consists of a centrosymmetric tetranuclear Fe^{III} complex. The four Fe atoms are located at four corners of a defective double cubane and bridged by four μ -OCH₃ and two μ_3 -OCH₃ groups. The intramolecular Fe...Fe distances range from 3.193(6) [Fe(1)...Fe(2')] to 5.514(5) Å [Fe(1)...Fe(1')]. The asymmetric unit consists of $\text{Fe}_2(\text{acac})_2\text{N}_3(\text{OCH}_3)_3$. Within the asymmetric unit, the geometrical environment of Fe(1) and

Fe(2) are roughly similar. Atom Fe(1) has a NO₃ distorted octahedral ligand donor set in which the O-donor atoms are supplied by an acac ligand [O(1), O(2)], two μ -OCH₃ [O(6), O(7')] and a μ_3 -OCH₃ [O(5)]. The N-donor atom comes from a terminal azide. However, Fe(2) has an O₆ donor set in a distorted octahedron, where five of the oxygen-donor atoms are the same as those of Fe(1) and the remainder is supplied by another μ_3 -OCH₃ [O(5')]. The average Fe– μ -OR bond length in $[\text{Fe}_4(\text{OCH}_3)_6(\text{acac})_4(\text{N}_3)_2]$ (1.99 Å) is close to those in other μ -alkoxo iron(III) complexes [2.06 Å].¹² The longest bond distance is Fe(1)–O(5) [2.196(5) Å], the μ_3 -OCH₃ ligand bridge being slightly asymmetric. The Fe(2)–O(5) bond distance [2.100(5) and 2.077(5) Å] is slightly shorter than Fe(1)–O(5) [2.196(5) Å] and the Fe(2')–O(5)–Fe(2) bond angle [100.6(2)°] is slightly larger than those of Fe(2)–O(5)–Fe(1) [96.8(2)°] and Fe(2')–O(5)–Fe(1) [96.7(2)°]. This is the first example of a structurally characterized tetranuclear iron(III) complex with a defective double cubane to our knowledge, although a pentanuclear one has been reported.¹⁸


The effective magnetic moment per iron ion in $[\text{Fe}_4(\text{OCH}_3)_6(\text{acac})_4(\text{N}_3)_2]$ varies gradually from 4.26 μ_B at 300 K down to 2.75 μ_B at 80 K, indicative of an antiferromagnetic interaction between the metal ions. This behaviour is similar to another tetranuclear iron(III) complex, $[\text{Fe}_4\text{O}_2(\text{O}_2\text{CCH}_3)_7(\text{bipy})_2][\text{ClO}_4]$ (bipy = 2,2'-bipyridine).¹³ Further investigation into the magnetic behaviour of $[\text{Fe}_4(\text{OCH}_3)_6(\text{acac})_4(\text{N}_3)_2]$ is in progress.

Acknowledgements

This work was supported by grants from the State Science and Technology Commission, the State Education Commission and the National Nature Science Foundation of China.

† Crystal data. $\text{C}_{26}\text{H}_{46}\text{Fe}_4\text{N}_6\text{O}_{14}$, red cubic crystal of dimension $0.25 \times 0.14 \times 0.05$ mm, $M = 890.08$, monoclinic, space group $P2_1/c$, $Z = 4$, $a = 11.500(1)$, $b = 8.515(1)$, $c = 20.385(2)$ Å, $\beta = 99.26(1)^\circ$, $U = 1970.1$ Å³, $D_c = 1.500$ g cm^{−3}, $T = 300(2)$ K, $F(000) = 920$, Mo-K α radiation ($\lambda = 0.71073$ Å), $\mu = 1.509$ mm^{−1}. The structure was solved by the direct methods and refined by full-matrix least-squares methods using 3445 observed reflections. Absorption correction was not applied owing to the small size of the crystal. A total of 3617 unique data were measured on a four-circle Enraf-Nonius CAD4 diffractometer using ω – 2θ scans. The final $R1$ and $wR2$ values were 0.0697 and 0.1488 respectively for 226 parameters and $[\sigma^2(F_o)]^{-1}$ weights, goodness of fit = 0.871 on F^2 for all data. All non-H atoms were refined with anisotropic displacement parameters, whereas H atoms were located from the difference map.^{16,17} Atomic coordinates, thermal parameters, and bond lengths and angles have been deposited at the Cambridge Crystallographic Data Centre (CCDC). See Instructions for Authors, *J. Chem. Soc., Dalton Trans.*, 1997, Issue 1. Any request to the CCDC for this material should quote the full literature citation and the reference number 186/394.

† Non-SI unit employed: $\mu_B \approx 9.274 \times 10^{-24}$ J T^{−1}.

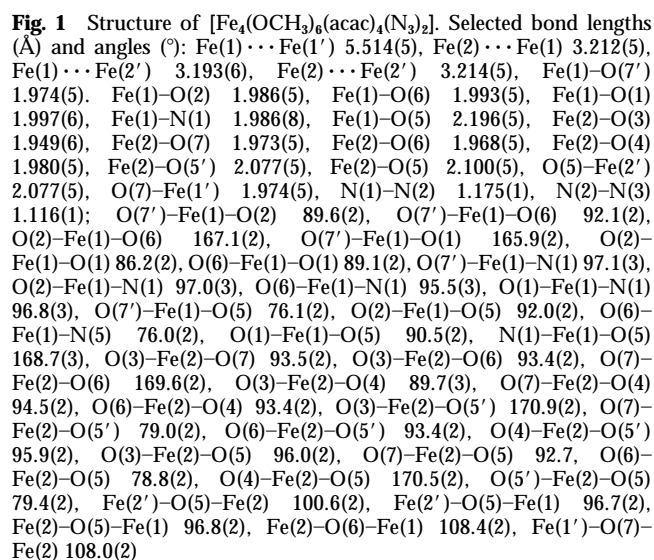

- 1 C.-T. Chen and K. S. Suslick, *Coord. Chem. Rev.*, 1993, **128**, 293.
- 2 E. Coronado, M. Drillon, A. Fuertes, D. Beltran, A. Mosset and J. Galy, *J. Am. Chem. Soc.*, 1986, **108**, 900.
- 3 R. Soules, F. Dahan and J.-P. Laurent *J. Chem. Soc., Dalton Trans.*, 1988, 587.
- 4 R. Cortes, K. Urtiaga, L. Lezama, J. L. Pizarro, A. Goni, M. I. Arriortua and T. Rojo, *Inorg. Chem.*, 1994, **33**, 4009.
- 5 R. Vicente, A. Escuer, J. Ribas and X. Solans, *Inorg. Chem.*, 1992, **31**, 1726.
- 6 J. Ribas, M. Monfort, X. Solans and M. Drillon, *Inorg. Chem.*, 1994, **33**, 724.
- 7 B. J. Kennedy and K. S. Murray, *Inorg. Chem.*, 1985, **24**, 1552; A. Escuer, R. Vicente, M. A. S. Goher and F. A. Mautner, *Inorg. Chem.*, 1995, **34**, 5707 and refs. therein.
- 8 S. J. Lippard, *Angew. Chem., Int. Ed. Engl.*, 1988, **27**, 344.
- 9 W. Micklitz, V. McKee, R. L. Rardin, L. E. Pence, G. C. Papaefthymiou, S. G. Bott and S. J. Lippard, *J. Am. Chem. Soc.*, 1994, **116**, 8061.
- 10 W. Micklitz and S. J. Lippard, *J. Am. Chem. Soc.*, 1989, **111**, 6856.
- 11 S. Drudke, K. Wieghardt, B. Nuber, J. Weiss, E. L. Bommar, A. Sawaryn, H. Winkler and A. X. Trautwein, *Inorg. Chem.*, 1989, **28**, 4477.
- 12 A. Caneschi, A. Cornia, A. C. Fabretti, D. Gatteschi and W. Malavasi, *Inorg. Chem.*, 1995, **34**, 4660.
- 13 J. K. MacCusker, J. B. Vincent, E. A. Schmitt, M. L. Mino, K. Shin, D. K. Coggin, P. M. Hagen, J. C. Huffman, G. Christou and D. N. Hendrickson, *J. Am. Chem. Soc.*, 1991, **113**, 3012 and refs. therein.
- 14 K. L. Taft, A. Caneschi, L. E. Pence, C. D. Delfs, G. C. Papaefthymiou and S. J. Lippard, *J. Am. Chem. Soc.*, 1993, **115**, 11 753 and refs. therein.
- 15 D. Laroque, I. Morgen Stern-Badarau, H. Winkler, E. Bill, A. X. Trautwein and M. Julve, *Inorg. Chim. Acta*, 1992, **192**, 107.
- 16 G. M. Sheldrick, SHELXS 86, *Acta Crystallogr., Sect. A*, 1990, **46**, 467.
- 17 G. M. Sheldrick, SHELXL 93, A Program for Crystal Structure Determination, University of Göttingen, 1993.
- 18 M. Mikuriya, Y. Hashimoto and S. Nakashima, *Chem. Commun.*, 1996, 295.

464 *J. Chem. Soc., Dalton Trans.*, 1997, Pages 463–464