

# A new layered aluminophosphate $[\text{Al}_2\text{P}_4\text{O}_{16}][\text{C}_6\text{H}_{22}\text{N}_4][\text{C}_2\text{H}_{10}\text{N}_2]$ with 4.12-net porous sheets

Bo Wei, Jihong Yu,\* Zhan Shi, Shilun Qiu\* and Jiyang Li

Key Laboratory of Inorganic Synthesis and Preparative Chemistry, Department of Chemistry, Jilin University, Changchun 130023, P. R. China. E-mail: jihong@mail.jlu.edu.cn; sqiu@mail.jlu.edu.cn

Received 19th April 2000, Accepted 23rd May 2000

Published on the Web 12th June 2000

Employing phenol, an aromatic and acidic organic solid, as the solvent, and triethylene tetramine as the template, a new two-dimensional layered aluminophosphate  $[\text{Al}_2\text{P}_4\text{O}_{16}][\text{C}_6\text{H}_{22}\text{N}_4][\text{C}_2\text{H}_{10}\text{N}_2]$  has been solvothermally synthesized for the first time, which contains novel 4.12-net porous sheets.

Since the first report of microporous aluminophosphates ( $\text{AlPO}_4\text{-}n$ ) in 1982,<sup>1</sup> much study has been focused on the exploration of new microporous aluminophosphate (AlPO) compounds. This is not only for their potential applications in sorption, catalysis, and host-guest assembly chemistry,<sup>2-4</sup> but also for the diversity of their arrangements of  $\text{AlO}_4$  (and/or  $\text{AlO}_5$ ,  $\text{AlO}_6$ ) and  $\text{PO}_4$  tetrahedral building units forming one-dimensional (1-D) chain, two-dimensional (2-D) layer, and three-dimensional (3-D) open-framework structures with Al/P ratios of 1/1, 1/2, 2/3, 3/5, 3/4, 4/5, 5/6, etc.<sup>5-7</sup>


So far, three distinct aluminophosphate networks have been found to have a stoichiometry of  $[\text{AlP}_2\text{O}_8]^{3-}$  with an Al/P ratio of 1/2. Two of them are based upon a chain network built up by corner-sharing and edge-sharing  $\text{Al}_2\text{P}_2$  4-membered rings (MRs), respectively.<sup>8-11</sup> The third one is based upon a 2-D sheet built up solely by 8-MRs.<sup>12,13</sup> Here, we report a new layered aluminophosphate  $[\text{Al}_2\text{P}_4\text{O}_{16}][\text{C}_6\text{H}_{22}\text{N}_4][\text{C}_2\text{H}_{10}\text{N}_2]$  (denoted **1**) with an Al/P ratio of 1/2. Compared to previous layered AlPOs

with 4.6-, 4.8-, 4.6.8-, 4.6.12-, and 8-nets,<sup>7</sup> **1** is the first 2-D layered AlPO constructed of 4.12-net porous sheets.


In this work, we employ phenol (melting point is 41°C) as an aromatic and acidic solvent in the synthesis, and use triethylene tetramine (TETA) as the template. Large platelike single crystals were formed from a gel mixture with the molar ratio  $1.0\text{Al}_2\text{O}_3:1.8\text{P}_2\text{O}_5:10.0\text{TETA}:65\text{PhOH}$  heated at 185°C for 12 days.<sup>14</sup> The experimental powder X-ray diffraction pattern of **1** is in agreement with the simulated one, proving that the as-synthesized product is a single phase. Inductively coupled plasma (ICP) analysis gives the Al and P content as 8.6 and 19.7 wt%, respectively, showing an Al/P molar ratio of 1/2. A suitable single crystal with dimensions of  $0.3 \times 0.3 \times 0.2\text{ mm}$  was selected for single-crystal X-ray diffraction analysis.<sup>15</sup> Single crystal analysis showed that **1** crystallizes in the monoclinic space group  $P2(1)/n$  (no. 14) with lattice parameters  $a = 10.826(1)\text{ \AA}$ ,  $b = 8.143(8)\text{ \AA}$ ,  $c = 13.770(1)\text{ \AA}$ , and  $\beta = 95.104(2)^\circ$ .

Each asymmetric unit of **1** contains one crystallographically distinct Al atom and two crystallographically distinct P atoms. All  $\text{AlO}_4$  tetrahedra are vertex linked with  $\text{PO}_4$  tetrahedra with the Al–O bond lengths in the range of 1.7277–1.7415 Å, but only two vertices of the  $\text{PO}_4$  tetrahedra are linked with adjacent  $\text{AlO}_4$  tetrahedra with P–O bond lengths in the range of 1.5142–1.5512 Å, with the remaining vertex being a terminal P=O group. The bond lengths of P(1)=O(2) and P(2)=O(8) are 1.505 and 1.508 Å, respectively.

The structure of **1** consists of macroanion  $[\text{AlP}_2\text{O}_8]^{3-}$ , which is charge balanced by the tetraprotonated TETA molecule  $^+\text{H}_3\text{N}(\text{CH}_2)_2\text{NH}_2^+(\text{CH}_2)_2\text{NH}_2^+(\text{CH}_2)_2\text{NH}_3^+$ , and diprotonated ethylenediamine  $^+\text{H}_3\text{N}(\text{CH}_2)_2\text{NH}_3^+$ . The ethylenediamine

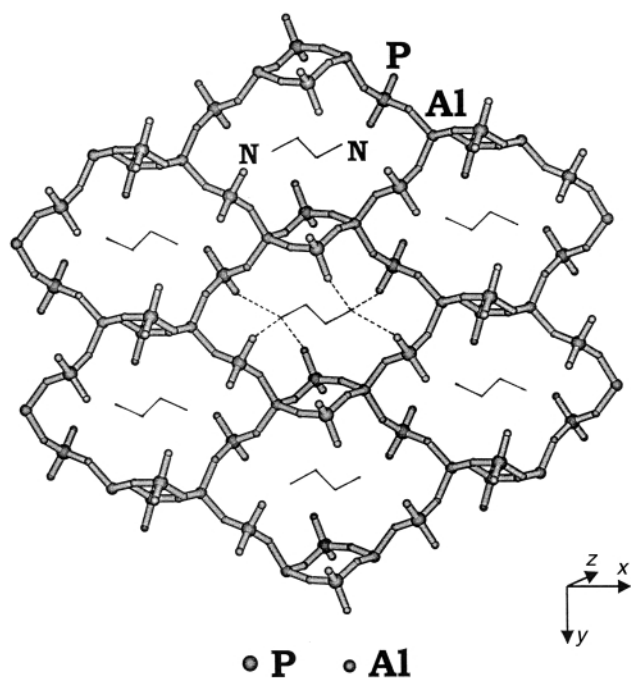

**Fig. 1** The 4.12-net porous sheet of **1** parallel to the  $[-101]$  plane, with ethylene diammonium cations located inside the 12-MR openings (H-bonds are represented by dotted lines).

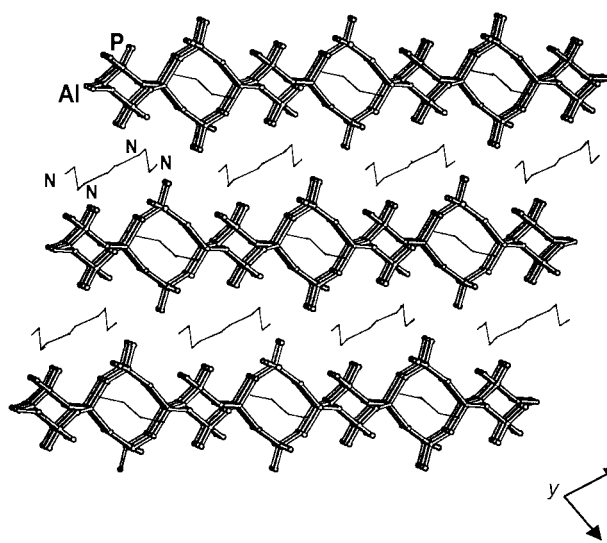


**Fig. 2** Packing of the sheets along the  $[-101]$  direction in an AAAA sequence, with TETA molecules intercalated in the interlayer region.

DOI: 10.1039/b003153o

J. Chem. Soc., Dalton Trans., 2000, 1979–1980

1979

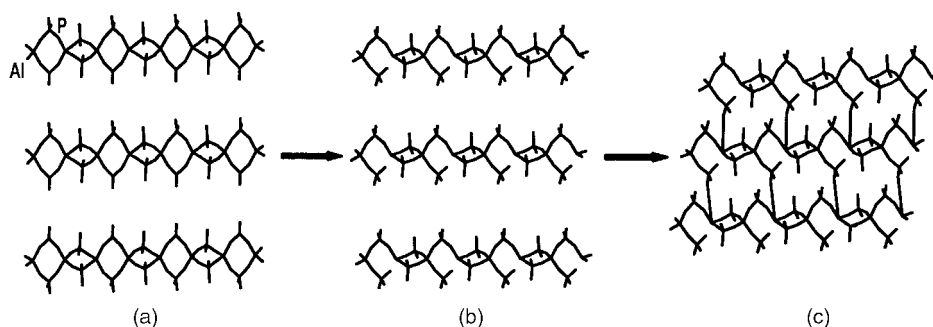

**Fig. 3** Structural relationship between the 1-D  $\text{AlP}_2\text{O}_8^{3-}$  chain and the 2-D  $\text{AlP}_2\text{O}_8^{3-}$  sheet in **1**, (a) 1-D  $\text{AlP}_2\text{O}_8^{3-}$  chain with corner-sharing 4-MRs; (b) breaking the  $\text{P}-\text{O}\cdots\text{Al}$  bond in the 1-D chain; (c) relinking the  $\text{P}-\text{O}\cdots\text{Al}$  bond with adjacent chains to form a 4.12-net sheet as in **1**.

molecules are believed to be generated during the course of solvothermal synthesis through fragmentation of the TETA molecules, as in the case of the previously reported 1-D chain  $[\text{Al}_2\text{P}_4\text{O}_{16}][\text{NH}_3(\text{CH}_2)_2\text{NH}_3][\text{NH}_3(\text{CH}_2)_3\text{NH}_3]_2$ .<sup>16</sup> The network of **1**, as shown in Fig. 1, is constructed of 4.12-net porous sheets parallel to the  $(-101)$  plane. This novel 4.12-net was first found in layered AIPO compounds.

Diprotinated ethylenediammonium cations  $^+\text{H}_3\text{N}(\text{CH}_2)_2\text{NH}_3^+$  exist in the 12-MR openings. Each 12-MR traps one ethylenediamine molecule, which interacts with six adjacent terminal  $\text{P}=\text{O}$  groups through strong  $\text{H}-\text{bonds}$  with  $\text{N}\cdots\text{O}$  separation in the range of 2.757–2.859 Å. Energy calculation by Cerius<sup>2</sup> using a Burchart1.01-Dreiding 2.21 force field<sup>17,18</sup> gives the the H-bonding interaction energy between the sheets and occluded ethylenediamine molecules as  $-10.25 \text{ kcal mol}^{-1}$  per unit of  $[\text{AlP}_2\text{O}_8]^{3-}$ . It is believed that the ethylenediamine molecules play an important role in the stabilization of the 12-MR in the porous sheet.

The macroanionic sheets are stacked in an AAAA sequence along the  $[-101]$  direction (Fig. 2), and intercalated by tetraprotonated  $^+\text{H}_3\text{NCH}_2\text{CH}_2^+\text{NH}_2\text{CH}_2\text{CH}_2\text{NH}_2^+\text{CH}_2\text{CH}_2\text{NH}_3^+$  cations. The distance between two layers is *ca.* 9.13 Å (atom to atom). Each tetraprotonated TETA cation provides a total of ten H-bonds to terminal  $\text{P}=\text{O}$  groups protruding into the inter-layer region, with both  $^+\text{H}_3\text{N}$ -groups each providing three H-bonds, and the middle  $\text{H}_2\text{N}^+$ -groups each providing two H-bonds.

Thermogravimetric analysis shows that the template molecules decompose in the region 280–430 °C with a weight loss of 30.2% (theoretical value: 32.8%), which is correlated to the decomposition of occluded TETA and ethylenediamine molecules. Elemental analysis gives the C, H and N content as 15.3, 5.2 and 13.6%, respectively, which is in agreement with the theoretical values of 14.9, 4.95 and 13.0%, respectively.

Further insight into the sheet structure of **1**, a structural relationship between **1** and a corner-sharing  $\text{AlP}_2\text{O}_8^{3-}$  1-D chain<sup>9</sup> (Fig. 3a) can be found. This 1-D  $\text{AlP}_2\text{O}_8^{3-}$  chain is proposed to be a parent chain for the formation of a family of 1-D chain, 2-D layer and 3-D open-framework AIPOs through an hydrolysis–condensation self-assembly pathway by Ozin and co-workers.<sup>19</sup> As shown in Fig. 3b,c, through breaking the  $\text{P}-\text{O}\cdots\text{Al}$  bonds in the 1-D chain, and relinking the  $\text{Al}-\text{O}\cdots$  group with the dangling P atoms in the adjacent chain, the 4.12-net sheet of **1** can be transformed from the 1-D  $\text{AlP}_2\text{O}_8^{3-}$  chain (Fig. 3c). It is noteworthy that both the 1-D  $\text{AlP}_2\text{O}_8^{3-}$  chain and the 4.12-net  $\text{AlP}_2\text{O}_8^{3-}$  sheets of **1** can be stabilized by the ethylenediamine cations. Further investigation of the crystallization of **1** might yield some information on the formation of this 2-D layer compound.

## Acknowledgements

We are grateful for financial support from National Natural Science Foundation and Pandeng Project of China.

## Notes and references

- S. T. Wilson, B. M. Lok, C. A. Messian, T. R. Cannan and E. M. Flanigen, *J. Am. Chem. Soc.*, 1982, **104**, 1146; S. T. Wilson, B. M. Lok and E. M. Flanigen, US Pat. 4 310 440, 1982.
- O. Terasaki, *J. Phys. Condens. Matter*, 1990, **2**, 5209.
- G. A. Ozin, *Adv. Mater.*, 1992, **4**, 612.
- J. Chen and J. M. Thomas, *J. Chem. Soc., Chem. Commun.*, 1994, 603; Z. K. Tang, M. M. T. Loy, J. Chen and R. Xu, *Appl. Phys. Lett.*, 1997, **70**, 34.
- J. M. Bennett, W. J. Dytrych, J. J. Pluth, J. W. Richardson Jr. and J. V. Smith, *Zeolites*, 1986, **6**, 349.
- J. Chen, W. Pang and R. Xu, *Top. Catal.*, 1999, **9**, 93.
- J. Yu, R. Xu and J. Li, *Solid State Sci.*, 2000, **2**, 181.
- R. H. Jones, J. M. Thomas, R. Xu, Q. Huo, Y. Xu, A. K. Cheetham and D. Bieber, *J. Chem. Soc., Chem. Commun.*, 1990, 1170.
- Q. Gao, J. Chen, S. Li and R. Xu, *J. Solid State Chem.*, 1996, **127**, 145.
- I. D. Williams, J. Yu, Q. Gao, J. Chen and R. Xu, *Chem. Commun.*, 1997, 1273.
- A. M. Chippindale and C. Turner, *J. Solid State Chem.*, 1997, **128**, 318.
- J. Yu and I. D. Williams, *J. Solid State Chem.*, 1998, **136**, 141.
- M. A. Leech, A. R. Cowley, K. Prout and A. M. Chippindale, *Chem. Mater.*, 1998, **10**, 451.
- In a typical experiment, 1.0 g of aluminium triisopropoxide was first dispersed into 30 g of phenol at 50 °C under reflux conditions with stirring, and then 0.6 mL of  $\text{H}_3\text{PO}_4$  (85wt% in water) was added dropwise to form a gel. Finally, 4.0 mL of TETA was added to the above mixture. The reaction mixture was further stirred until homogenous and then was sealed in a Teflon-lined stainless steel autoclave and heated at 185 °C for 12 days under autogenous pressure. The resulting product containing pure large platelike single crystals of up to 1 mm was filtered and washed thoroughly with ethanol and deionized water, and dried at ambient temperature.
- Crystal structure data:  $F_w = 323.12$ , monoclinic, space group  $P2(1)/n$  (no. 14),  $a = 10.826(1) \text{ Å}$ ,  $b = 8.143(8) \text{ Å}$ ,  $c = 13.770(1) \text{ Å}$ , and  $\beta = 95.104(2)^\circ$ ,  $V = 1029.2(2) \text{ Å}^3$ ,  $T = 293(2) \text{ K}$ ,  $Z = 4$ ,  $\rho_{\text{calcd}} = 1.775 \text{ Mg m}^{-3}$ ,  $F(000) = 672$ ,  $\mu(\text{Mo-K}\alpha) = 0.471 \text{ mm}^{-1}$ ,  $\theta_{\text{max}} = 23.26^\circ$ . Goodness-of-fit on  $F^2$  was 1.083,  $R_1[\text{for } I > 2\sigma(I)] = 0.0285$ ,  $wR_2 = 0.0836$ , Data/restraints/parameters = 1679/0/227. Structural analysis was performed on a Siemens SMART CCD diffractometer using graphite-monochromated Mo-K $\alpha$  radiation ( $\lambda(\text{Mo-K}\alpha) = 0.71073 \text{ Å}$ ). The data were collected at  $20 \pm 2^\circ \text{C}$ . Data processing was accomplished with the SAINT processing program (SMART and SAINT (software packages), Siemens Analytical X-ray Instruments, Inc., Madison, WI, 1996.). Direct methods were used to solve the structure using the SHELXTL crystallographic software package (SHELXL, version 5.1; Siemens Industrial Automation, Inc., 1997.). Hydrogen atoms were located by a difference Fourier map, and were added to the structure factor calculation. All non-hydrogen atoms were refined anisotropically. CCDC reference number 186/2002. See <http://www.rsc.org/suppdata/ft/b0/b003153o/> for crystallographic files in .cif format.
- K. Sugiyama, K. Hiraga, J. Yu, S. Zheng, S. Qiu and O. Terasaki, *Acta Crystallogr., Sect. C*, 1999, **55**, 1615.
- Cerius2, Molecular simulations/Biosym corporation, San Diego, CA, 1995.
- J. Li, J. Yu, W. Yan, Y. Xu, W. Xu, S. Qiu and R. Xu, *Chem. Mater.*, 1999, **11**, 2600.
- S. Oliver, A. Kuperman and G. A. Ozin, *Angew. Chem., Int. Ed.*, 1998, **37**, 46.