

## Water Tolerance of DeNO<sub>x</sub> SCR Catalysts Using Hydrocarbons: Findings, Improvements and Challenges

Moon Hyeon Kim and In-Sik Nam <sup>\*\*†</sup>

Department of Environmental Engineering, Taegu University, 15 Naeri, Jinryang,  
Kyungsan 712-714, Rep. of Korea

<sup>\*</sup>Department of Chemical Engineering/School of Environmental Science and Engineering,  
Pohang University of Science and Technology (POSTECH),  
P.O. Box 125, Pohang 790-600, Rep. of Korea

(Received 8 August 2001 • accepted 7 September 2001)

**Abstract**—The recent developments on the effect of H<sub>2</sub>O on deNO<sub>x</sub> performance of a variety of SCR catalysts selectively removing NO<sub>x</sub> by hydrocarbons in excess oxygen have been reviewed. In particular, the water tolerance of the catalyst is summarized to illustrate a common deactivation behavior of SCR catalyst for the reduction of NO by hydrocarbons under wet feed gas mixture. Earlier proposals elucidating the possible cause of the catalyst deactivation under wet conditions are discussed, focusing mainly on the catalyst characteristics. A promising way, which can improve the water tolerance and the hydrothermal stability of zeolite-based SCR catalyst, is also described.

Key words: NO<sub>x</sub> Reduction, Water Tolerance, Hydrocarbon, Deactivation, SCR, DeNO<sub>x</sub> Catalyst, Zeolite, Mordenite, Ferrierite

### INTRODUCTION

Selective catalytic reduction (SCR) is one of the most effective technologies for lowering NO<sub>x</sub> from a high temperature combustion process. With strict emission standards for NO<sub>x</sub> emissions from stationary and mobile sources, combustion measure and modification technology will be no longer appropriate for reducing NO<sub>x</sub>; therefore, post-treatment deNO<sub>x</sub> technology will be unavoidable. Commercially proven deNO<sub>x</sub> technology including NH<sub>3</sub>-SCR for catalytic NO<sub>x</sub> removal and the purification of automotive exhausts using three-way catalytic converter are currently available; however, there are a few limitations in their commercial application. The deNO<sub>x</sub> SCR using NH<sub>3</sub> over a V<sub>2</sub>O<sub>5</sub>-WO<sub>3</sub>/TiO<sub>2</sub> may be the most technically advanced technology for effectively removing NO<sub>x</sub> from large and small scale combustion processes, but still contains disadvantages such as NH<sub>3</sub>-slip by unreacted and/or excess NH<sub>3</sub> and high cost of facilities and operation. A Pt-Pd-Rh system is capable of reducing NO<sub>x</sub> from gasoline engines. This technology, however, may hardly reduce NO<sub>x</sub> from diesel and lean burn gasoline engines due to huge amounts of excess O<sub>2</sub>, which can easily transfer the rhodium to an inactive phase, rhodium oxide during the course of the reaction.

This would be the reason why a new catalytic system is required for removing diluted NO<sub>x</sub> from stationary and oxygen-rich mobile sources. Catalytic decomposition is essentially the simplest and best approach for NO<sub>x</sub> removal, and an ultimate goal in the development of deNO<sub>x</sub> technology. Up to now, Cu-exchanged zeolite-based catalyst is known as the best catalyst for NO decomposition; however, a catalyst containing consistently high removal activity for the decomposition has not been developed yet. Since the selective re-

duction of NO<sub>x</sub> by hydrocarbons (HC) in the presence of excess oxygen was successfully established with Cu-zeolites [Held et al., 1990; Iwamoto, 1990], the use of HCs as an alternative reductant to NH<sub>3</sub> has received great attention as the most promising deNO<sub>x</sub> technology for stationary and oxygen-rich mobile sources. There have been numerous investigations on the selective reduction of NO<sub>x</sub> by HCs with excess oxygen. Based on the earlier works, the SO<sub>2</sub> effect on NO removal activity was moderate, whereas H<sub>2</sub>O resulted in serious catalyst deactivation even with small amounts. Not only would high catalytic activity be essential for a commercial application, but water and sulfur tolerances of the catalyst must also be required from the view of catalyst life.

In the early 1990s, an extensive review of research in this area mainly concerning the catalysts and their activity for the reduction had been made [Truex et al., 1992; Iwamoto and Mizuno, 1993]. The reaction mechanism for the reduction of NO by HCs, has been reviewed by Iwamoto and Yahiro [1994], Smits and Iwasawa [1995], and Adelman et al. [1996]. More than 200 patents and their applications in the present deNO<sub>x</sub> technology have been summarized by Tabata et al. [1994]. Recently, Parvulescu et al. [1998] published an extensive review of catalytic NO<sub>x</sub> removal where the catalysts and their catalytic property were covered in a part. The present review will focus on the issues, particularly relating to the effect of H<sub>2</sub>O on the catalytic reduction of NO<sub>x</sub> by HCs over a variety of catalysts, an approach to improve the water tolerance and the hydrothermal stability from knowledge-based understandings on predominant factors in determining it. For this purpose, recent studies, efforts and attempts on the present topic in the literature will be mainly covered in the present review.

### 1. Advent of NO<sub>x</sub> SCR by HCs

There have been earlier studies investigating the use of HCs for replacing NH<sub>3</sub> in the SCR process. Representative examples can be found from the work to clean up the tail gas from nitric acid pro-

<sup>†</sup>To whom correspondence should be addressed.

E-mail: isnam@postech.ac.kr

duction plant *via* ammonia oxidation. The tail gas stream generally contains 0.1 to 0.5%  $\text{NO}_x$  and 3 to 4%  $\text{O}_2$  [Cohn et al., 1961; Adlhart et al., 1971]. A major fraction of  $\text{NO}_x$  exists in the form of  $\text{NO}_2$ , so that the stack plume from nitric acid plants is associated with yellow to red color. The color of the stack gas is distinctive compared to the colorless one including the equivalent amounts of other pollutants without  $\text{NO}_2$ ; therefore, initial efforts were mainly directed toward eliminating the color of the flue gas rather than  $\text{NO}_2$  itself. One of the most frequently employed methods removing  $\text{NO}_2$  was to convert it into colorless NO through a commercial decolorizing process for "purely public relations purposes" [Adlhart et al., 1971]. The catalytic decolorization of such tail gases over alumina-supported Pt, Pd and Rh can be typically described as:



Reaction (1) is easily accomplished by introducing an excessive stoichiometric amount of fuel, referred to as  $\text{CH}_4$ , to the feed gas stream. During the decolorizing reaction, the combustion of fuel should also occur:



Subsequently, NO removal can take place by Reaction (3).



This reaction might provide a conceptual guideline for the development of  $\text{NO}_x$  by HCs, although methane is one of the most difficult molecules to activate.

An earlier attempt to establish the catalytic technology for removing  $\text{NO}_x$  by using HCs was made mainly with metal oxides and supported-noble metals. Ault and Ayen [1971] utilized a barium-promoted copper chromite for the reduction of NO by  $\text{C}_1\text{-C}_8$  hydrocarbons including alkenes and alkanes. Numerous metal oxides including  $\text{MnO}_2$ ,  $\text{Fe}_2\text{O}_3$ ,  $\text{V}_2\text{O}_5$ ,  $\text{Cr}_2\text{O}_3$ ,  $\text{WO}_3$ ,  $\text{ZnO}$ ,  $\text{SnO}_2$ ,  $\text{Co}_3\text{O}_4$ ,  $\text{CdO}$ ,  $\text{MoO}_3$ ,  $\text{NiO}$ ,  $\text{Cu}_2\text{O}$  and  $\text{TiO}_2$  have been examined for NO reduction using  $\text{C}_3\text{H}_6$  [Murakami et al., 1977]. Among them,  $\text{Fe}_2\text{O}_3$  and  $\text{MnO}_2$  were the most active catalyst for this reaction system. Few, if any, kinetic and mechanistic studies have been made on the catalytic NO reduction by HCs. The catalytic reduction of NO by  $\text{CH}_4$  over an alumina-supported Rh could be well illustrated by a Langmuir-Hinshelwood mechanism [Hardee and Hightower, 1984]. These earlier studies, however, may not be so attractive from the view of commercial application, since they have been mainly examined in oxygen-free streams and/or excess NO and HCs feed concentrations.

#### 1-1. Initial Efforts in Germany

In the middle of the 1980s, a number of zeolite catalysts were developed to catalytically reduce  $\text{NO}_x$  by using hydrocarbons in an exhaust gas containing excess oxygen through a cooperative research with Volkswagen AG and Bayer AG in Germany [Held and Konig, 1987]. Transition metal ion-exchanged zeolites such as MOR, MFI and FAU (X and Y) structures were quite active for NO reduction at 100 to 700 °C of the reaction temperature and 10,000 to 50,000  $\text{h}^{-1}$  of the reactor space time [Held and Konig, 1987; Held et al., 1988], where the MOR, MFI and FAU represent mordenite, ZSM-5 and faujasite zeolites, respectively. Cu-MOR catalyst exhibited 66% of NO conversion within the temperature range from 150 to

230 °C when  $\text{C}_2\text{H}_4$  was used as a reducing agent in the absence of  $\text{H}_2\text{O}$ . The catalytic activity of 50% in terms of NO conversion at 350 °C was observed for Cu-MFI catalyst, but other metal-exchanged MFI catalysts were relatively less active [Held and Konig, 1987]. The capability of MFI zeolite to reduce NO at 300 °C strongly depends on metal ions exchanged in the zeolite; for example, Ir-, Pt-, Rh-, Ni- and Co-MFI catalysts revealed lower activity than Cu-MFI. FAU type zeolite exchanged with Cu, Fe, Mn, Ni, Co, Ag, V and Cr also revealed the de $\text{NO}_x$  performance with  $\text{C}_2\text{H}_4$  and  $\text{C}_3\text{H}_6$  but their NO removal activity was mainly less than 20% of NO conversion in the range of the reaction temperature from 300 to 600 °C. In a wet condition, the activity maintenance of Cu-MFI catalyst for NO reduction with  $\text{C}_2\text{H}_4$  was stronger than Cu-MOR catalyst. These findings have been mainly observed over a conventional monolith coated with Cu-MFI to remove NO from a lean-burn engine [Held and Konig, 1987; Held et al., 1988]. It has been believed that Held and coworkers at Volkswagen AG in Germany were first aware of the present selective reduction technology to remove NO by HCs.

#### 1-2. Pioneering Work in Japan

In the research undertaken by Toyota Motor Corporation and Iwamoto and coworkers in Japan, an extensive screening test for the effective catalytic decomposition of  $\text{NO}_x$  contained in automotive engine exhausts was conducted at the end of 1980s [Fujitani et al., 1988; Tanaka et al., 1989; Iwamoto, 1990]. Among the catalysts examined, Iwamoto and coworkers found that Cu-MFI was the most active catalyst for the decomposition [Iwamoto, 1990; Iwamoto et al., 1991]; for example, the activity of Cu-MFI catalyst was 80% of NO conversion at 500 °C and 3,000  $\text{h}^{-1}$ , depending on the Si/Al ratio and copper loading of the catalyst. After this pioneering finding, the subsequent effect of  $\text{O}_2$ ,  $\text{CO}_2$ ,  $\text{SO}_2$ ,  $\text{H}_2\text{O}$ , CO and HCs on the removal of NO was systematically examined to confirm if any change in the catalytic activity could be accompanied, since automotive engine exhaust also contains gas components besides NO [Fujitani et al., 1988; Tanaka et al., 1989; Iwamoto et al., 1991; Iwamoto and Hamada, 1991].

In the presence of  $\text{O}_2$ , the catalytic removal activity of NO decreased and a similar trend was also observed by the addition of either  $\text{SO}_2$  or  $\text{H}_2\text{O}$  in the feed gas stream. However, it dramatically increased according to the presence of either CO or HCs. It has been believed that the significant enhancement should be mainly related to the role of HCs similar to the result observed for the decolorizing reaction described before [Fujitani et al., 1988; Tanaka et al., 1989]. The decomposition of NO over Cu-MFI catalyst in the presence of stoichiometric amounts of HCs as well as of excess  $\text{O}_2$  could occur [Fujitani et al., 1988; Tanaka et al., 1989]. In addition, this NO removal reaction was later designated as not "Decomposition" but "Selective Catalytic Reduction" [Iwamoto, 1990]. From this history for  $\text{NO}_x$  SCR by HCs, the advent of SCR technology came coincidentally into the world "during the survey of the effect of coexisting gases on the catalytic activity of copper ion-exchanged zeolites for the decomposition of NO" as Iwamoto and Mizuno [1993] described.

#### 2. Catalyst and Reductant

##### 2-1. HC-SCR De $\text{NO}_x$ Catalyst

Since Held and Konig [1987], Held et al. [1988, 1990] and Iwamoto [1990] independently reported the selective catalytic reduction of  $\text{NO}_x$  by HCs over Cu-MFI catalyst on which the ppm level

**Table 1. Literature-based catalysts for selective reduction of NO<sub>x</sub> by hydrocarbons**

<i>Zeolites and related materials</i>
(1) Bare zeolites: MFI, MOR, FER, FAU, CLI
(2) Metal ion-exchanged zeolites:
MFI with Cu, Fe, Co, Ce, Ga, Ag, Na, Zn, Ni, Mn, Mg, Mo, V, Cr, Ca, La, Pr, Nd, Ln, In, Ir, Pb, Pt, Rh, Ru and Pd
MOR with Cu, Fe, Co, Pt, Rh, Ru, Pd, Ti, W, Mo, Ce, Mg, Zr, Sn, Na, V, Cr, Ni, Zn, Ca, Ga, Sr, Ba and La
FER with Cu, Fe, Co, Cr, V, Zn, Pt, Pd, Mn and Ni
FAU with Cu, Co, Fe, Ce and Ga
LTL with Cu, Co and Fe
BEA with Cu and Co
CLI with Fe, Cr, Ni and Mn
(3) Metallosilicates: Cu-, Fe-, Ga-, Al-, Co-, Ni-, Mn-, Mo-, Ti-silicate
(4) Silicoaluminophosphates: Cu-, H-, Ca-, Pd-SAPO, H-MAPO, ALPO
(5) Cordierites
(6) Mullites
<i>Metal oxides and related materials</i>
(1) Single metal oxides: Al <sub>2</sub> O <sub>3</sub> , SnO <sub>2</sub> , TiO <sub>2</sub> , ZrO <sub>2</sub> , La <sub>2</sub> O <sub>3</sub> , Fe <sub>2</sub> O <sub>3</sub> and Ag <sub>2</sub> O
(2) Mixed metal oxides: Al <sub>2</sub> O <sub>3</sub> -BaO, Al <sub>2</sub> O <sub>3</sub> -La <sub>2</sub> O <sub>3</sub> , ZnO-SiO <sub>2</sub> , TiO <sub>2</sub> -Al <sub>2</sub> O <sub>3</sub> , SiO <sub>2</sub> -Al <sub>2</sub> O <sub>3</sub> , ZrO <sub>2</sub> -TiO <sub>2</sub> and ZrO <sub>2</sub> -Al <sub>2</sub> O <sub>3</sub>
(3) Sulfate-promoted single and mixed metal oxides: Al <sub>2</sub> O <sub>3</sub> , TiO <sub>2</sub> , ZrO <sub>2</sub> , Fe <sub>2</sub> O <sub>3</sub> , ZrO <sub>2</sub> -Al <sub>2</sub> O <sub>3</sub> and ZrO <sub>2</sub> -TiO <sub>2</sub>
(4) Metal oxides supported on (1) to (3): Cu, Co, Ag, V, Ni, La, Mn, Ga, Cr, Ba, Ca, Sr, Mg, Zr, Cs, Sm, Mo, Ce and Fe
(5) Perovskites
<i>Noble metals</i>
(1) On zeolites: MFI, MOR, FER and FAU
(2) On metal oxides: Al <sub>2</sub> O <sub>3</sub> , SiO <sub>2</sub> , TiO <sub>2</sub> , ZrO <sub>2</sub> , La <sub>2</sub> O <sub>3</sub> , CeO <sub>2</sub> , Cr <sub>2</sub> O <sub>3</sub> , ZnO, TiO <sub>2</sub> -Al <sub>2</sub> O <sub>3</sub> , ZrO <sub>2</sub> -TiO <sub>2</sub> , TiO <sub>2</sub> -ZrO <sub>2</sub> -Al <sub>2</sub> O <sub>3</sub> , AlPO <sub>4</sub> and AlBO <sub>3</sub>

of NO<sub>x</sub> concentration is readily reduced by HCs even in the presence of excess oxygen, numerous catalysts listed in Table 1 have been reported in the literature. Representative, transition metal ion-exchanged zeolites [Iwamoto et al., 1991; Sato et al., 1991, 1992; Teraoka et al., 1992; Li et al., 1993; Kim et al., 1994, 1995; Ohtsuka and Tabata, 1999; Lee et al., 2001], H-zeolites [Hamada et al., 1990, 1991; Sato et al., 1991, 1992; Kim et al., 1994, 1995], supported noble metals [Hamada et al., 1991; Hamada, 1994], supported metals [Hamada et al., 1991; Hosose et al., 1991; Sato et al., 1992; Torikai et al., 1991], metal oxides [Hamada, 1994; Kintaichi et al., 1990; Sato et al., 1992; Maurula et al., 1998, 2000], solid acids [Hamada et al., 1991; Hamada, 1994; Hosose et al., 1991; Kintaichi et al., 1990; Torikai et al., 1991; Sato et al., 1992] and perovskites [Sato et al., 1992; Hong et al., 1997], have been suggested to be active for SCR reaction using HCs.

NO removal activity significantly depends on the catalyst and reductant, except the reaction condition including the concentrations of NO, HCs and O<sub>2</sub>. Generally, transition metal-exchanged zeolites such as MFI, MOR, FER (ferrierite), LTL (L-zeolite) and

FAU contain higher deNO<sub>x</sub> efficiency than the other type of the catalyst. It is widely accepted that MFI and MOR type zeolite catalysts are currently the best support material for NO reduction by HCs in the presence of oxygen [Sato et al., 1992]. Note that FER zeolite is the best catalyst support for the reduction of NO when reduced by CH<sub>4</sub> [Li and Armor, 1994; Witzel et al., 1994; Lee et al., 2001].

## 2-2. Hydrocarbons and Related Compounds

Hydrocarbons could be a useful reducing agent and replace NH<sub>3</sub>, regarded as the best reductant for commercial SCR process. A variety of hydrocarbons and related compounds have been employed for the reduction of NO<sub>x</sub>, as summarized in Table 2. Iwamoto and Hamada [1991] have classified the reductant into two categories, selective (C<sub>2</sub>H<sub>4</sub>, C<sub>3</sub>H<sub>6</sub>, C<sub>3</sub>H<sub>8</sub> and C<sub>4</sub>H<sub>8</sub>) and non-selective (CH<sub>4</sub> and C<sub>2</sub>H<sub>6</sub>), based upon the amount of the consumption of the reductant during the course of the reaction, and a similar result has been also observed for light hydrocarbons [Truex et al., 1992]. It is of interest to note that such a classification may be valid for the non-selective reduction of NO<sub>x</sub> by CH<sub>4</sub> and C<sub>2</sub>H<sub>6</sub> over Cu-MFI and Al<sub>2</sub>O<sub>3</sub>. How-

**Table 2. Literature-based hydrocarbons and related compounds for selective reduction of NO<sub>x</sub> over SCR catalysts**

<i>Hydrocarbons</i>
(1) Saturated hydrocarbons: CH <sub>4</sub> , C <sub>2</sub> H <sub>6</sub> , C <sub>3</sub> H <sub>8</sub> , C <sub>4</sub> H <sub>10</sub> , C <sub>5</sub> H <sub>12</sub> , C <sub>6</sub> H <sub>14</sub> , C <sub>7</sub> H <sub>16</sub> , C <sub>8</sub> H <sub>18</sub> , C <sub>9</sub> H <sub>20</sub> , C <sub>10</sub> H <sub>22</sub> and C <sub>16</sub> H <sub>34</sub>
(2) Unsaturated hydrocarbons: C <sub>2</sub> H <sub>4</sub> , C <sub>3</sub> H <sub>6</sub> and C <sub>4</sub> H <sub>8</sub>
<i>Related compounds</i>
(1) Alcohols: CH <sub>3</sub> OH, C <sub>2</sub> H <sub>5</sub> OH, C <sub>3</sub> H <sub>7</sub> OH and C <sub>4</sub> H <sub>9</sub> OH
(2) Common fuels: liquified petroleum gas, natural gas, diesel oil and gasoline
(3) Others: acetone, kerosene, dioxane, methylethylketone, toluene, benzene, xylene, ether, ether acetone, dimethylether, diethylether, formaldehyde, acetoaldehyde, formic acid, acetic acid and methyl formate

**Table 3. Water tolerance of numerous catalysts for the selective reduction of NO<sub>x</sub> by HCs**

Catalyst <sup>a</sup>	HC	H <sub>2</sub> O (%)	Conversion of NO <sub>x</sub> (%) <sup>b</sup>						Reference	
			Reaction temperature (°C)							
			300	350	400	450	500	550	600	
Cu-MFI	C <sub>2</sub> H <sub>4</sub>	10		50 (37)						[Held et al., 1990]
		16		50 (23)						
Cu-MOR	C <sub>2</sub> H <sub>4</sub>	10		37 (17)						[Held et al., 1990]
Cu-MFI-157	C <sub>3</sub> H <sub>6</sub>	3.9				75 (40)				[Iwamoto et al., 1992]
Co-MFI-98	CH <sub>4</sub>	2.0				40 (29)	27 (28)	21 (22)		[Li and Armor, 1993]
Co-FER-78	CH <sub>4</sub>	2.0				60 (28)	50 (40)	40 (32)		[Li and Armor, 1993]
Co-MFI-140	CH <sub>4</sub>	2.0			47 (23)	33 (31)				[Li et al., 1993]
Co-MOR-94	CH <sub>4</sub>	2.0			33 (25)	28 (25)				[Li et al., 1993]
Mn-MFI-106	CH <sub>4</sub>	2.0			31 (23)	39 (36)				[Li et al., 1993]
Ni-MFI-140	CH <sub>4</sub>	2.0			26 (19)	21 (19)				[Li et al., 1993]
H-MFI	CH <sub>4</sub>	2.0			16 (5)	24 (2)				[Li et al., 1993]
Cu-MOR-46	C <sub>3</sub> H <sub>8</sub>	3.0			24 (10)					[Mabilon and Durand, 1993]
		5.0			24 (2)					
Cu-MFI-87	C <sub>3</sub> H <sub>8</sub>	14		61 (19)	77 (45)	78 (55)				[Gopalakrishnan et al., 1993]
Al <sub>2</sub> O <sub>3</sub>	C <sub>3</sub> H <sub>6</sub>	10		42 (4)	71 (9)	79 (24)				[Miyadera, 1993]
CoO <sub>x</sub> /Al <sub>2</sub> O <sub>3</sub>	C <sub>3</sub> H <sub>6</sub>	10		76 (20)	60 (42)	43 (44)				[Miyadera, 1993]
AgO <sub>x</sub> /Al <sub>2</sub> O <sub>3</sub>	C <sub>3</sub> H <sub>6</sub>	10		81 (40)	77 (71)	62 (62)				[Miyadera, 1993]
CuO <sub>x</sub> /Al <sub>2</sub> O <sub>3</sub>	C <sub>3</sub> H <sub>6</sub>	10		31 (13)	23 (10)	14 (5)				[Miyadera, 1993]
Ga-MFI-162	CH <sub>4</sub>	2.0				40 (13)				[Li and Armor, 1994]
Co-MFI	C <sub>2</sub> H <sub>6</sub>	2.0			50 (22)					[Burch and Scire, 1994]
H-MOR	C <sub>3</sub> H <sub>6</sub>	6.5		84 (66)						[Kim et al., 1995, 1997, 1998]
		7.3		66 (17) <sup>c</sup>						[Kim et al., 1995, 1997, 1998]
Cu-MOR-48	C <sub>3</sub> H <sub>6</sub>	7.3		78 (28)						[Kim et al., 1995, 1997, 1998]
		7.3		65 (21) <sup>c</sup>						[Kim et al., 1995, 1997, 1998]
Cu-NZA <sup>d</sup> -44	C <sub>3</sub> H <sub>6</sub>	7.3		91 (85)						[Kim et al., 1995, 1997, 1998]
		7.3		58 (34) <sup>c</sup>						[Kim et al., 1995, 1997, 1998]
Ag/Al <sub>2</sub> O <sub>3</sub>	C <sub>3</sub> H <sub>6</sub>	1.5				43 (34)				[Bethke and Kung, 1997]
Cu-Pillared Clays	C <sub>2</sub> H <sub>4</sub>	5.0		55 (32)	71 (50)	81 (76)				[Li et al., 1997]
AuO <sub>x</sub> /Al <sub>2</sub> O <sub>3</sub>	C <sub>3</sub> H <sub>6</sub>	9.8		30 (42)	57 (72)	45 (52)				[Ueda et al., 1997]
Cu-saponite	C <sub>3</sub> H <sub>6</sub>	8.0		41 (32)	35 (27)	27 (20)				[Sato et al., 1997]
Ag-saponite	C <sub>3</sub> H <sub>6</sub>	8.0		37 (51)	45 (45)	51 (37)				[Sato et al., 1997]
Mn <sub>2</sub> O <sub>3</sub> +Sn-MFI	C <sub>3</sub> H <sub>6</sub>	5.7	12 (65)	41 (74)	27 (45)		3 (10)			[Misono et al., 1997]
InO <sub>x</sub> /Al <sub>2</sub> O <sub>3</sub>	C <sub>3</sub> H <sub>6</sub>	8.0		73 (26)	95 (55)	87 (57)	78 (42)	58 (25)		[Maunula et al., 1998]
InO <sub>x</sub> /Al <sub>2</sub> O <sub>3</sub> +Mn <sub>3</sub> O <sub>4</sub>	C <sub>3</sub> H <sub>6</sub>	8.0		78 (72)	90 (83)	79 (73)	68 (58)	49 (46)		[Maunula et al., 1998]
Ga <sub>2</sub> O <sub>3</sub> /Al <sub>2</sub> O <sub>3</sub>	CH <sub>4</sub>	2.5			6 (0)	13 (2)	28 (7)	70 (21)	62 (29)	[Shimizu et al., 1998]
Cu-aluminate	C <sub>3</sub> H <sub>6</sub>	10			37 (24)	25 (11)	14 (6)			[Shimizu et al., 1998]
Co-aluminate	C <sub>3</sub> H <sub>6</sub>	10			47 (28)	55 (47)	54 (44)			[Shimizu et al., 1998]
Ni-aluminate	C <sub>3</sub> H <sub>6</sub>	10			32 (22)	68 (52)	67 (51)			[Shimizu et al., 1998]
Pd-MOR	CH <sub>4</sub>	9.0			87 (44)	91 (69)	76 (55)			[Ohtsuka and Tabata, 1999]
Pd-MFI	CH <sub>4</sub>	9.0			62 (32)	69 (33)				[Ohtsuka and Tabata, 1999]
CoO <sub>x</sub> /Al <sub>2</sub> O <sub>3</sub>	C <sub>3</sub> H <sub>6</sub>	8.0			88 (16)	81 (49)	62 (66)	23 (54)		[Maunula et al., 2000]
InO <sub>x</sub> /Fe <sub>2</sub> O <sub>3</sub> +H-MFI	CH <sub>4</sub>	3.3			84 (41)	100 (80)	100 (91)	100 (83)	100 (71)	[Wang et al., 2000]
In-FER	CH <sub>4</sub>	2.0			60 (14)	58 (32)	56 (30)	41 (27)		[Ramallo-Lopez et al., 2001]
Co-FER-98	CH <sub>4</sub>	5.0			83 (1)	88 (39)	70 (56)	47 (35)	27 (23)	[Lee et al., 2001]

<sup>a</sup>Numbers next to the zeolite structure designate the exchange percentage of each metal ion.<sup>b</sup>Numbers in parentheses indicate NO<sub>x</sub> conversion at wet condition.<sup>c</sup>At 360 °C.<sup>d</sup>Natural zeolite consisting mainly of a MOR structure.

ever, they are selective reductants with Co-MFI, Co-FER [Li and Armor, 1992; Li et al., 1993, 1994; Lee et al., 2001], Ga-MFI [Yogo et al., 1993; Tabata et al., 1994], H-zeolite [Yogo et al., 1993], Pt/Al<sub>2</sub>O<sub>3</sub> [Demicheli et al., 1993], Li-promoted MgO [Zhang et al., 1994], Pd-MOR [Ohtsuka and Tabata, 1999] and In-FER [Ramallo-Lopez et al., 2001]. Although the SCR activity is mainly related to the catalyst, the other variable may be the selectivity of the reductant for the present reaction system containing excess O<sub>2</sub> and water. The selectivity can be determined by the consumption of the reductant according to the reaction stoichiometry.

### 3. Catalyst Deactivation by Water

Although less than 1% of H<sub>2</sub>O is commonly included in the exhaust stream of nitric acid plant [Adlhart et al., 1971], most of NO<sub>x</sub> emission sources contain H<sub>2</sub>O in the concentration ranges of 2 to 18% [Li et al., 1993]; therefore, the strong water tolerance of deNO<sub>x</sub> catalyst is essential for its practical use besides the sulfur tolerance of the catalyst in the presence of SO<sub>x</sub> contained in the flue gas. There have been efforts not only to demonstrate the effect of H<sub>2</sub>O on the NO<sub>x</sub> SCR, but also to elucidate the reason why most SCR catalysts significantly lose catalytic activity under wet conditions [Iwamoto and Mizuno, 1993; Li et al., 1993; Kharas et al., 1993; Kim et al., 1995, 1997; Ohtsuka and Tabata, 1999; Lee et al., 2001]. A few of the representative investigations in this topic have focused on how to improve the water tolerance of zeolite catalysts for the reduction [Chung et al., 1999; Lee et al., 2001]. Based upon the earlier studies on the role of H<sub>2</sub>O in reducing NO<sub>x</sub> by HCs, the present review will focus on improving the water tolerance of zeolite catalysts for the present NO reduction technology intensively developed over the last decade. It is not intended to cover the application of the present technology, particularly to NO<sub>x</sub> reduction under actual lean-burn and diesel engine conditions.

#### 3-1. Effect of Water on NO Removal Activity

##### 3-1-1. Metal Ion-Exchanged Zeolites

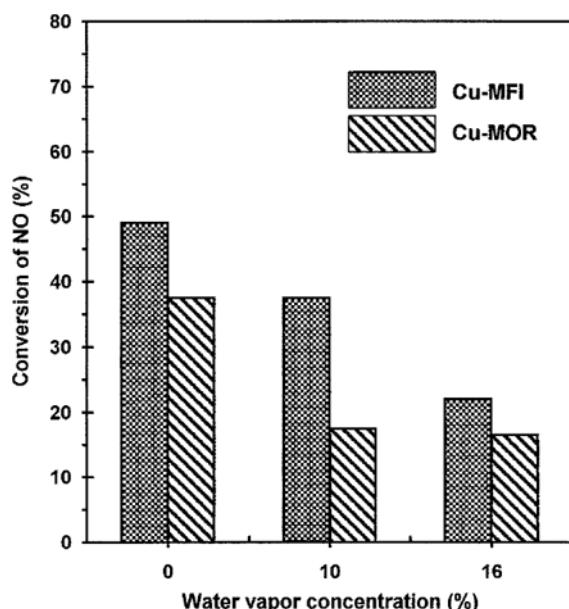


Fig. 1. Effect of water on NO<sub>x</sub> conversion with zeolites. Reaction condition: NO<sub>x</sub> 1,000 ppm, C<sub>2</sub>H<sub>4</sub> 40 ppm, O<sub>2</sub> 1.5%, GHSV=13,000 and T=350 °C [Held et al., 1990].

Up to now, the effect of H<sub>2</sub>O on the catalytic activity for NO<sub>x</sub> reduction by hydrocarbons and the cause of the activity loss in the presence of H<sub>2</sub>O have been among the most important topics in this area of research, as extensively summarized in Table 3. Held and coworkers [Held and Konig, 1987; Held et al., 1988, 1990] first published illustrative results for the effect of H<sub>2</sub>O on the selective reduction of NO<sub>x</sub> by C<sub>2</sub>H<sub>4</sub> over Cu ion-exchanged zeolite catalysts with excess oxygen. Using Cu-MOR, 37% of NO<sub>x</sub> was removed at 350 °C when the feed gas stream contained 1,000 ppm of NO<sub>x</sub> in the presence of 40 ppm of C<sub>2</sub>H<sub>4</sub> and 1.5% O<sub>2</sub>, but the NO<sub>x</sub> conversion dropped down to 17% when 10% H<sub>2</sub>O was subsequently included in the feed gas stream, as shown in Fig. 1. For Cu-MFI catalyst, the initial NO<sub>x</sub> conversion of 50% decreased to 37% in the presence of 10% H<sub>2</sub>O and further decrease was observed when the feed concentration of water increased to 16%. The degree of the loss of NO removal activity for Cu-MFI catalyst in the presence of H<sub>2</sub>O is somewhat milder than that over Cu-MOR. This may be associated with the distinction of Si/Al ratio of both zeolites, although they were not specifically provided in the literature.

Significant effect of H<sub>2</sub>O vapor on NO<sub>x</sub> reduction activity by C<sub>2</sub>H<sub>6</sub> was again examined for Cu-MFI-157 catalyst [Iwamoto et al., 1992]. Hereafter, the numbers next to zeolite structure codes will indicate an ion exchange rate. Introducing 3.9% of H<sub>2</sub>O to the feed gas stream containing 250 ppm of SO<sub>2</sub>, the catalytic activity at 500 °C suddenly decreased from 73% of NO conversion to 45%, as illustrated in Fig. 2. The wet activity remained unchanged even for 1.5 h under the identical reactor operating conditions and could be immediately restored to its initial conversion when H<sub>2</sub>O was eliminated from the feed stream. This implies that the effect of H<sub>2</sub>O is fully reversible and presumably suggests that the major active reaction sites on the catalyst surface, *i.e.*, Cu ions, may not be chemically altered by H<sub>2</sub>O. Among a variety of zeolite structures including MFI, MOR and FAU (X and Y), significant NO removal ac-

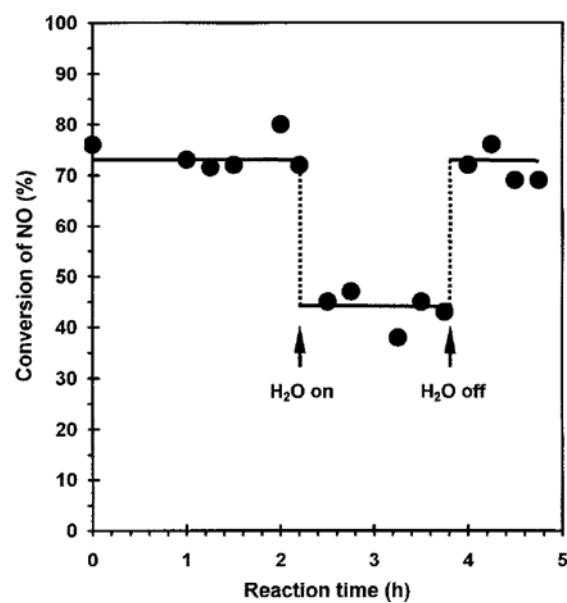


Fig. 2. Effect of H<sub>2</sub>O on the catalytic activity of Cu-MFI-157 for the selective reduction of NO. [NO]=600 ppm; [O<sub>2</sub>]=1.5%; [C<sub>2</sub>H<sub>6</sub>]=940 ppm; [SO<sub>2</sub>]=250 ppm; [H<sub>2</sub>O]=3.9%; W/F=0.1 g·s·cm<sup>-3</sup>; T=500 °C [Iwamoto et al., 1992].

tivity by  $C_3H_8$  was observed over Cu-exchanged MFI and MOR zeolites, but not over FAU type zeolite [Gopalakrishnan et al., 1993]. In a wet stream with 14%  $H_2O$ , the de $NO_x$  conversion of Cu-MFI-87 was reduced by 20% at both 350 and 500 °C and 40% at 400 °C, as listed in Table 3. The dry activity was not restored even after  $H_2O$  was fed into the reactor system off, implying an irreversible activity loss by water. This differs from the earlier result [Iwamoto et al., 1992] but is in good agreement with the irreversible catalyst deactivation of Cu-MFI-104 catalyst to remove NO from an actual diesel engine in the presence of 7%  $H_2O$  at 400 °C [Konno et al., 1992].

The water tolerance of transition metal ion-exchanged MFI, FER and MOR type zeolites for selectively reducing NO by  $CH_4$  was examined by Armor and coworkers [Li and Armor, 1993; Li et al., 1993, 1994]. Both Co-MFI-98 and Co-FER-78 catalysts were highly active for NO removal reaction by  $CH_4$ , compared to Co-MOR-94, Mn-MFI-106, Ni-MFI-140 and H-MFI catalysts. However, the catalytic activity was severely suppressed in the presence of water vapor, regardless of metal ion exchanged on the catalyst surface (Table 3). As an example, Co-MFI-140 catalyst revealed 47% of NO conversion without  $H_2O$ , but the presence of 2%  $H_2O$  in a gas mixture resulted in the activity loss more than 30% at the reaction temperatures below 450 °C, as shown in Fig. 3. The effect of water on NO removal activity was reversible [Li and Armor, 1993], which was quite consistent with the earlier observation over Cu-MFI-157 catalyst by Iwamoto et al. [1992]. The alteration of cobalt state and zeolite structure might not be suspicious for the present catalytic system, since the activity in the wet condition was quite stable within the observation over 12 hours at the given reaction temperatures.

Based upon the comparison of Co-MFI-98 catalyst with Co-FER-78 for  $NO_x$  reduction by  $CH_4$ , Li and Armor [1993] observed that

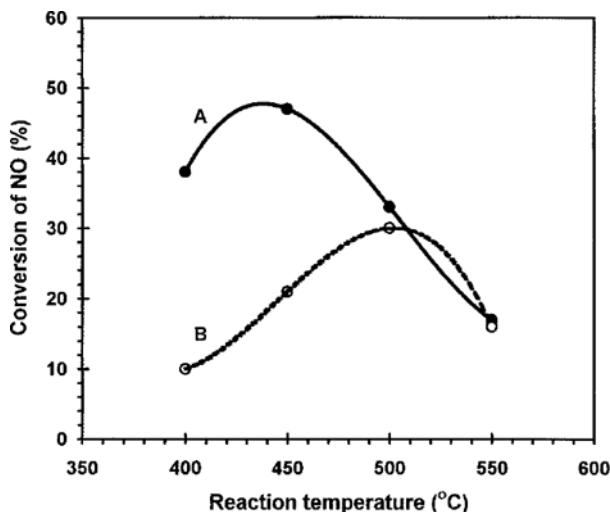


Fig. 3. Effect of water on the NO conversion over Co-MFI-140 as a function of reaction temperature. The reaction was run at  $GHSV=30,000$ ,  $[NO]=820$  ppm,  $[CH_4]=1,015$  ppm, and  $[O_2]=2.5\%$  ( $[H_2O]=2\%$  for the wet feed). The reaction was run first with the dry feed with increasing temperature (line A), then 2% water vapor was added at 560 °C and the reaction was run with decreasing temperature (line B). Data were collected at each temperature for a period 1 to 2 h, and only stable, average data are shown [Li et al., 1993].

FER structure zeolite revealed the best NO removal activity even in a wet stream containing 2% of  $H_2O$ , as indicated in Table 3; however, this only occurs when  $CH_4$  as a reducing agent is employed, since the de $NO_x$  activity of Co-BEA ( $\beta$ -zeolite)-80 catalyst under a wet stream with  $C_3H_8$  was much greater than that of Co-FER catalyst [Tabata et al., 1998]. The overall conversion of  $CH_4$  significantly decreased under the wet condition as well, regardless of zeolite structure. A complete reversible catalyst deactivation due to water was again observed for both Co-exchanged zeolites during a cyclic inclusion of water into the feed gas stream. Ga-zeolites have been highly active for the reduction of NO by  $CH_4$  [Li and Armor, 1994; Tabata et al., 1994] and  $C_3H_8$  [Yogo et al., 1993]. In a comparative study with Co-MFI catalyst for the reduction of NO by  $CH_4$ , Ga-MFI-162 with  $CH_4$  revealed high performance of NO removal activity and was more selective than Co-MFI catalyst, but it showed a severer activity loss by  $H_2O$ ; the respective de $NO_x$  conversions for Ga-MFI-162 and Co-MFI at 500 °C decreased from 40 to 13% and from 40 to 35% in the presence of 2%  $H_2O$  [Li and Armor, 1994].

An extensive study to elucidate the loss of NO removal activity by  $H_2O$  was conducted for Cu-exchanged MOR type zeolites by  $C_2H_4$  and  $C_3H_8$  [Kim et al., 1995, 1997, 1998]. Fig. 4 shows the water tolerance of Cu-exchanged synthetic MOR (H-MOR and Cu-MOR-48) and natural zeolite (Cu-NZA-44) by  $C_2H_4$  as a function of the feed concentration of  $H_2O$ . The activity of the synthetic MOR without Cu ions decreased from 66 to 17% under the wet stream containing 7.3% of  $H_2O$ ; however, the water tolerance could be appreciably improved as Cu ions were exchanged in the catalyst. Cu-NZA-44 reveals better water tolerance than the synthetic MOR containing copper ions. If  $C_3H_8$  is employed as a reductant, the activity loss of Cu-NZA-44 catalyst is less than 5% even at 16% of  $H_2O$  in the feed gas stream, as illustrated in Fig. 5. The deactivation has been improved for the synthetic MOR catalysts when  $C_3H_8$  is employed as a reductant instead of  $C_2H_4$ , regardless of the presence of Cu ions on the catalyst surface. It may imply that  $C_3H_8$  is a better reductant than  $C_2H_4$  in the presence of  $H_2O$ . The Cu-exchanged MOR type

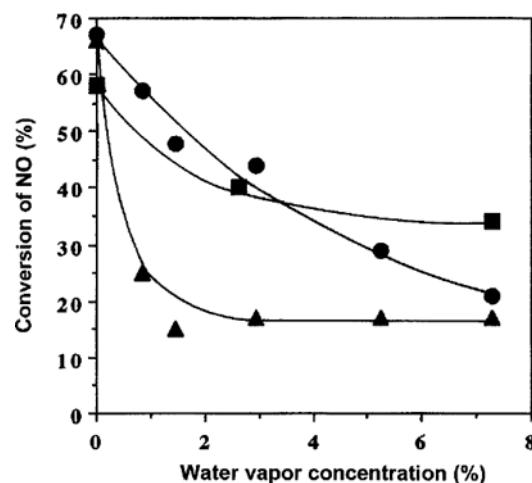


Fig. 4. Water tolerance of mordenite type zeolite catalysts for the reduction of NO by  $C_2H_4$ : (●) Cu-MOR-48; (▲) H-MOR; (■) Cu-NZA-44. Reaction condition: NO 500 ppm,  $C_2H_4$  1,000 ppm,  $O_2$  4.2% and  $T=360$  °C [Kim et al., 1997].

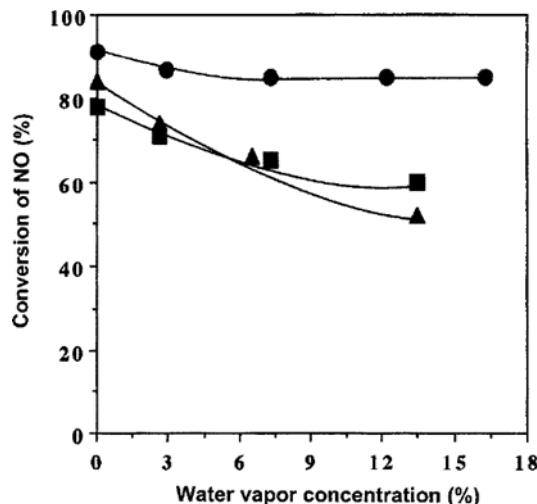


Fig. 5. Water tolerance of mordenite type zeolite catalysts for the reduction of NO by C<sub>3</sub>H<sub>6</sub> : (■) Cu-MOR-48; (▲) H-MOR; (●) Cu-NZA-44. Reaction condition: NO 500 ppm, C<sub>3</sub>H<sub>6</sub> 2,000 ppm, O<sub>2</sub> 4.2% and T=400 °C [Kim et al., 1997].

zeolite shows milder catalyst deactivation by water than the copper-free catalyst, and the natural MOR type catalyst particularly contains stronger water tolerance than the synthetic MOR-based zeolites. It indicates that the zeolite structures and the existence of the copper ions are mainly associated with the distinctive water tolerance of the catalyst.

The NO removal activity of Cu-MOR-48 in the presence and absence of H<sub>2</sub>O was completely reversible. The reversibility of NO conversion has been also observed for H-MOR and Cu-NZA-44 catalysts [Kim et al., 1996, 1997, 1998], regardless of reductant, which is consistent with the earlier studies for Cu-MFI-157 [Iwamoto et al., 1992] as well as for Co-FER-78 and Co-MFI-140 [Li and Armor, 1993; Li et al., 1993]. It is common for the oxidation of HCs into CO by the cyclic injection of water into the feed gas stream. It suggests that the deterioration of the catalytic activity is probably due to the adsorption characteristics of reactant and water, rather than due to the structural alteration of the catalyst by water.

Recently, NO removal activity by CH<sub>4</sub> has been examined over Co-exchanged FER, MOR, BEA and MFI type zeolites [Lee et al., 2001]. Co-FER-98 catalyst exhibited deNO<sub>x</sub> conversion of 88% at 450 °C under a dry condition but 50-60% for the other type of Co-zeolites, which is also consistent with the activity dependence on zeolite structure for the reduction by CH<sub>4</sub> [Li and Armor, 1993]. In a wet stream with 10% H<sub>2</sub>O, only 30% of NO conversion has been achieved for Co-FER catalyst at 450 °C [Lee et al., 2001]. In addition, metal ions on the surface of FER structure may be another important catalyst variable for the high performance of NO removal, as revealed in Fig. 6. Although In-FER catalyst contains a wide operating temperature window with the maximum NO conversion of 60% at 400-500 °C, Co-FER is the most active catalyst from the view of the operating condition. The catalytic activity could be enhanced as the content of Co on the catalyst surface increases [Lee et al., 2001; Lamello-Lopez et al., 2001].

### 3-1-2. Supported Metal Oxides

A mixture of transition metal oxides and zirconium oxide catalyst prepared by co-precipitation method has been employed for

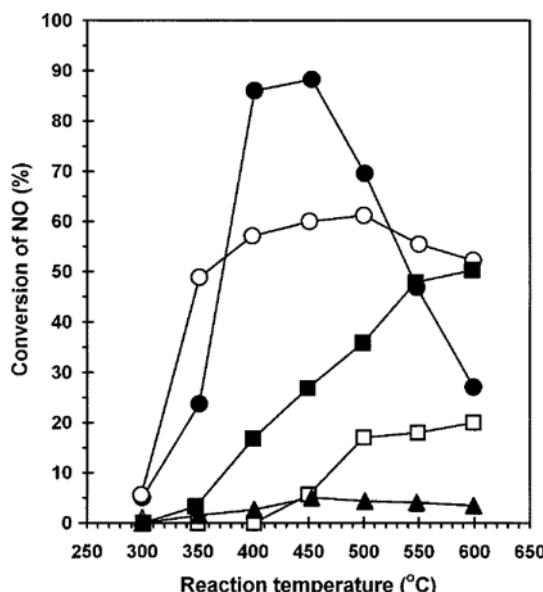


Fig. 6. Dry activity of metal-exchanged FER structure zeolite catalysts for NO reduction by CH<sub>4</sub> : (●) Co; (○) In; (■) Mn; (□) Ni; (▲) Cu. Reaction condition: NO 1,200 ppm, CH<sub>4</sub> 1,600 ppm and O<sub>2</sub> 3.2% [Lee et al., 2001].

NO reduction by either C<sub>3</sub>H<sub>6</sub> or C<sub>3</sub>H<sub>8</sub> [Bethke et al., 1994]. Cu-Zr-O was particularly active for the reaction, but the deNO<sub>x</sub> performance dramatically decreased mainly due to 2.4% of H<sub>2</sub>O contained in the feed gas stream. Miyadera [1993] has reported high performance of AgO<sub>x</sub>/Al<sub>2</sub>O<sub>3</sub> for the reduction of NO with C<sub>3</sub>H<sub>6</sub> in the absence of water. Although most of the metal oxide catalysts suffered from activity loss by H<sub>2</sub>O, the supported AgO<sub>x</sub> catalyst exhibited strong water tolerance (Table 3). This may be related to the weak adsorption of H<sub>2</sub>O on the surface of silver. The water tolerance of alumina-supported InO<sub>x</sub> and CoO<sub>x</sub> catalysts for NO removal reaction with C<sub>3</sub>H<sub>6</sub> was also examined by Maunula et al. [1998, 2000]. InO<sub>x</sub>/Al<sub>2</sub>O<sub>3</sub> catalyst in a dry stream revealed 95% of NO conversion at 400 °C [Maunula et al., 1998]. If 8% of H<sub>2</sub>O was subsequently included in the feed gas stream, the catalytic performance notably dropped to 55% of NO conversion at the identical reaction temperature, as listed in Table 3. As Mn<sub>3</sub>O<sub>4</sub> was physically added to the catalyst (unknown weight ratio), the water tolerance became stronger so as to be less than 10% of the decrease in NO conversion within the range of the reaction temperatures covered (Table 3). A similar enhanced water resistance was observed for NO reduction with CH<sub>4</sub> over a physical mixture of InO<sub>x</sub>/Fe<sub>2</sub>O<sub>3</sub> and H-MFI [Wang et al., 2000], as also included in Table 3.

The deNO<sub>x</sub> activity of CoO<sub>x</sub> catalysts in the dry condition significantly varied with respect to the phase of alumina employed as a catalyst support, the Co precursor and the calcination temperature. The catalyst calcined at 700 °C contained 90 to 60% of NO conversion without water at reaction temperatures ranging from 350 to 550 °C. With the addition of 8% H<sub>2</sub>O to the dry gas mixture, the NO removal activity below 450 °C significantly decreased, while that above 500 °C increased, as shown in Table 3. This catalytic behavior of deNO<sub>x</sub> catalyst in the presence of water vapor is in good agreement with that of a mechanical mixture of Mn<sub>3</sub>O<sub>4</sub> and Sn-MFI (weight ratio of 1 : 1) [Misono et al., 1997], Au/Al<sub>2</sub>O<sub>3</sub> [Ueda et al.,

1997] and Ag-saponite [Sato et al., 1997] on which their wet deNO<sub>x</sub> performance within either certain or wider temperature regions was higher than the dry activities. 3.2% GaO<sub>x</sub>/Al<sub>2</sub>O<sub>3</sub> catalyst exhibited poor activity less than 15% of NO conversion within the reaction temperatures covered [Li and Armor, 1994]. The catalytic activity was a strong function of the amount of GaO<sub>x</sub> dispersed on the surface of alumina support. NO conversion of 65% at 500 °C was obtained over 35% GaO<sub>x</sub>/Al<sub>2</sub>O<sub>3</sub> catalyst [Shimizu et al., 1998]; however, the catalyst contained weak water tolerance, as shown in Table 3. Besides the catalytic systems discussed in the present review, Cu-pillared clay [Bethke and Kung, 1997] and metal-incorporated aluminates [Shimizu et al., 1998] have been also suggested as a deNO<sub>x</sub> catalyst with HCs, as listed in Table 3.

### 3-2. Cause of the Activity Loss by H<sub>2</sub>O

#### 3-2-1. Chemical State of Metal Ions

Most HC-SCR DeNO<sub>x</sub> catalysts experience severe deactivation in their catalytic activity when H<sub>2</sub>O exists in the feed gas stream, as summarized in Table 3; however, the extent of the catalyst deactivation under a wet stream seriously depends on catalyst, hydrocarbon, reaction temperature and water content employed for the reaction system. Few, if any, studies focusing on the reason why the performance of deNO<sub>x</sub> catalyst is too sensitive to water vapor in the feed gas stream could be found in the literature so far.

At the initial stage to understand the catalyst deactivation by H<sub>2</sub>O, the earlier work by Kharas et al. [1993] should be cited. Using a simulated Air/Fuel feed ratio of 18 to the reactor system where 10% of H<sub>2</sub>O is included, deNO<sub>x</sub> performance of Cu-MFI-387 was examined for 1 h at reaction temperatures from 600 to 800 °C. The primary cause of the catalyst deactivation is the alteration of Cu ions on the catalyst surface to CuO and Cu<sub>2</sub>O based on the analysis of the catalyst surface before and after reaction by EXAFS and XRD. A substantial loss in initial micropore volume of the catalyst compared to fresh catalyst has been observed. The sintering of the copper ions could lead to the destruction of the zeolite structure along with the loss of catalytic activity during the course of reaction at the lean burn condition. A similar result has been also observed for Cu-MFI-106 and Cu-MFI-678 catalysts on which Cu ions are transferred to small CuO clusters through a durability test at 500°C for 500 h under a simulated lean burn exhaust containing 9% H<sub>2</sub>O [Tabata et al., 1994]. The dealumination of the catalyst, the carbon deposition on the catalyst surface and the loss of the catalyst micropore volume have not been observed, as confirmed by the catalyst characterization including BET surface area, CO chemisorption, NMR and elemental carbon measurements.

Electronic and local structures of Cu-MOR-48 and Cu-NZA-44 catalysts after reaction at 400 °C for 1 h in the presence of 7.3% H<sub>2</sub>O have been determined by XANES and EXAFS spectra along with those for the references including Cu foil, CuO, Cu<sub>2</sub>O and Cu(OH)<sub>2</sub> [Kim et al., 1997]. Cu K-edge XANES spectra for both catalysts even after the reaction were basically similar to those of each fresh catalyst, indicating that no change in the electronic structure of the Cu ions occurs during the catalytic reaction with water. The spectra were quite distinctive compared with the reference samples even for the catalysts exposed to the wet stream, revealing that the copper species are neither Cu<sub>2</sub>O, CuO nor Cu(OH)<sub>2</sub>. A multiple scattering did not appear, therefore no formation of copper oxide clusters on the catalyst surface.

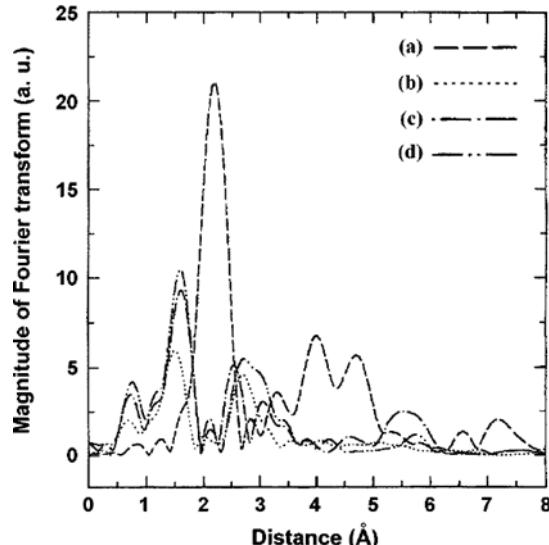


Fig. 7. Cu K-edge EXAFS spectra for (a) Cu foil, (b) Cu<sub>2</sub>O, (c) CuO and (d) Cu(OH)<sub>2</sub> [Kim et al., 1997].

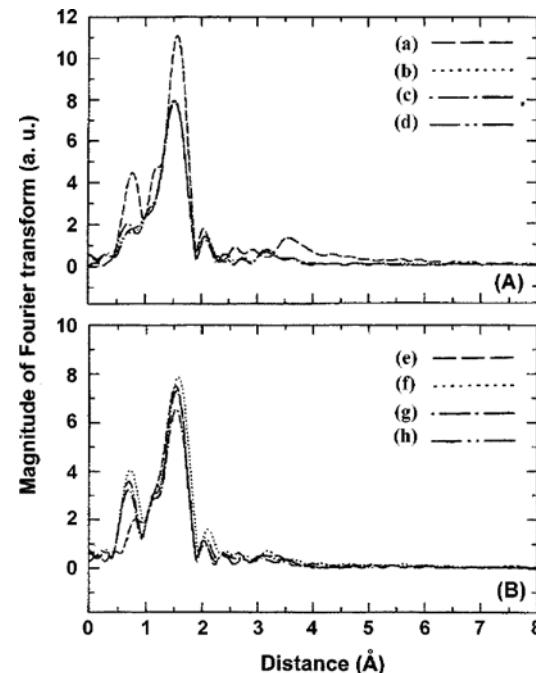


Fig. 8. Cu K-edge EXAFS spectra for (A) Cu-MOR-48 and (B) Cu-NZA-44 catalysts. (a) and (e) fresh; (b) and (f) after reaction with water at 400 °C for 1 h; (c) and (g) after reaction with water at 700 °C for 1 h; (d) and (h) after reaction with water at 400 °C for 1 h following reaction without water for 1 h. Reaction condition: NO 500 ppm, C<sub>3</sub>H<sub>6</sub> 2,000 ppm and O<sub>2</sub> 4.2% [Kim et al., 1997].

Cu K-edge k<sup>3</sup>-weighted EXAFS spectra could lead to the same conclusion for the two kinds of Cu-exchanged catalysts before and after the reaction compared to the references in Figs. 7 and 8. Cupric oxide shows the predominant peak at 1.62 Å due to the nearest Cu-O, as compared to 1.50 Å in Cu<sub>2</sub>O (1.95 Å in CuO [Asbrink and Norrby, 1970] and 1.85 Å in Cu<sub>2</sub>O [Wells, 1984]). Either one or two neighbor peaks appear at a longer distance: 2.73 Å for Cu<sub>2</sub>O,

and 2.55 and 3.08 Å for CuO. In the case of Cu(OH)<sub>2</sub>, three prominent peaks are at 1.60 and 2.73, and 3.01 Å, corresponding to Cu-O and Cu-Cu distances. Both Cu-zeolite catalysts before and after the reaction exhibit only a single peak at 1.54 Å, as shown in Fig. 8, representing that the copper species are in the form neither of CuO and Cu<sub>2</sub>O nor of Cu(OH)<sub>2</sub>. The 1.54 Å peak is associated with the local structure between the Cu ions and the nearest zeolite framework oxygen, as well known for Cu-FAU [Matsumoto and Tanabe, 1990; Piffer et al., 1991] and Cu-MFI [Hamada et al., 1990; Kharas et al., 1993; Nakayama et al., 1993; Tabata et al., 1994]. These EXAFS spectra clearly indicate that the loss of the catalytic activity in the wet condition does not result from the transformation of copper ions to copper oxides, CuO and Cu<sub>2</sub>O on the catalyst surface.

From an earlier work by Auger spectroscopy for the two catalysts hydrothermally aged at 800 °C during a few hours (>4 h) under flowing either 7.3 or 10% of H<sub>2</sub>O in He [Kim, 1996], the formation of CuO had been observed as confirmed by a Cu L<sub>3</sub>VV Auger line. This may be in good agreement with the earlier observations for Cu-MFI catalyst [Kharas et al., 1993; Tabata et al., 1994]; however, the sintering may not be directly related with the immediate decrease in catalytic activity at low temperatures with water and the complete restoration of the catalytic activity upon switching the feed of water to the reactor periodically.

### 3-2-2. Competitive Adsorption of NO, HCs and H<sub>2</sub>O

Temperature programmed desorption of H<sub>2</sub>O was conducted on H-MOR, Cu-MOR-48 and Cu-NZA-44 to provide the major reason for the catalyst deactivation under a wet stream [Kim et al., 1997]. Large amounts of H<sub>2</sub>O were adsorbed on H-MOR and desorbed continuously up to 500 °C, as shown in Fig. 9, and on Cu-MOR-48 up to 380 °C. Much less hydrophobic surface is evident for the natural zeolite-based catalyst on which H<sub>2</sub>O desorption peaks at 150, 210, 250 and 460 °C appear, but the total amount of water desorbed is significantly small. Based upon the present result from H<sub>2</sub>O TPD, the adsorption capacity and strength of water on H-MOR is much higher than that on Cu-MOR-48 catalyst. The synthetic

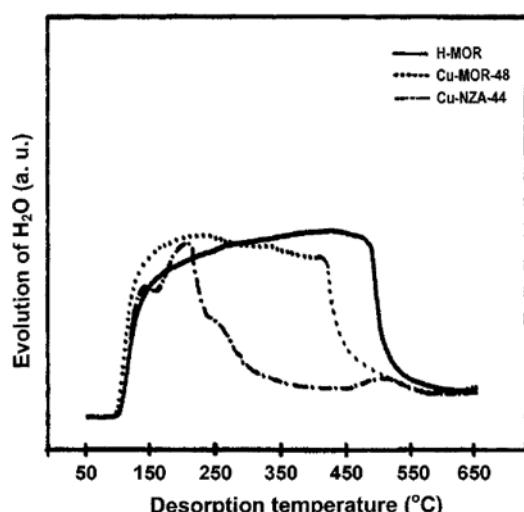


Fig. 9. Temperature-programmed desorption (TPD) of water for the catalysts. The ramping rate was 10 °C/min, and the carrier (He) flow rate was 40 cm<sup>3</sup>/min [Kim et al., 1997].

and natural zeolites contain the respective Si/Al ratios of 5.2 and 9.2; therefore, this distinction may bring Cu-NZA-44 to exhibit the greatest surface hydrophobicity. A similar result has also been observed for MFI type zeolite; the surface hydrophobicity of the catalyst is a strong function of Si/Al ratio of the zeolite [Flanigen et al., 1978]. The Kubelka-Munk spectra indicated that water molecules bounded on the Cu ions, depending on the adsorption temperature of water on the catalyst surface [Kim et al., 1997]. This was in good agreement with the relative hydrophobicity of both Cu-exchanged zeolites by H<sub>2</sub>O TPD. Water coordinated to the copper ions may inhibit the adsorption of NO on the catalyst surface. It may well be correlated with the competitive adsorption of NO, HCs and H<sub>2</sub>O on the catalytic reaction sites.

A close relationship of the catalyst hydrophobicity with the competitive adsorption has been confirmed by the simultaneous adsorption of NO and HC on the catalyst surface with and without H<sub>2</sub>O [Kim et al., 1997]. For Cu-MOR-48 catalyst shown in Fig. 10, the desorption peaks of NO<sub>x</sub> at 110, 160, 210 and 280 °C have been observed, regardless of the presence of H<sub>2</sub>O in the feed gas stream; however, the adsorption capacity considerably decreases upon the simultaneous adsorption of NO and H<sub>2</sub>O on the catalyst surface. Since NO adsorption on H-MOR catalyst contains only the three desorption peaks at 110, 160, and 210 °C obtained for Cu-MOR, the last one shown for Cu-exchanged catalyst at 280 °C may be assigned to Cu<sup>2+</sup>-NO<sub>x</sub> species, indicating that the copper sites could

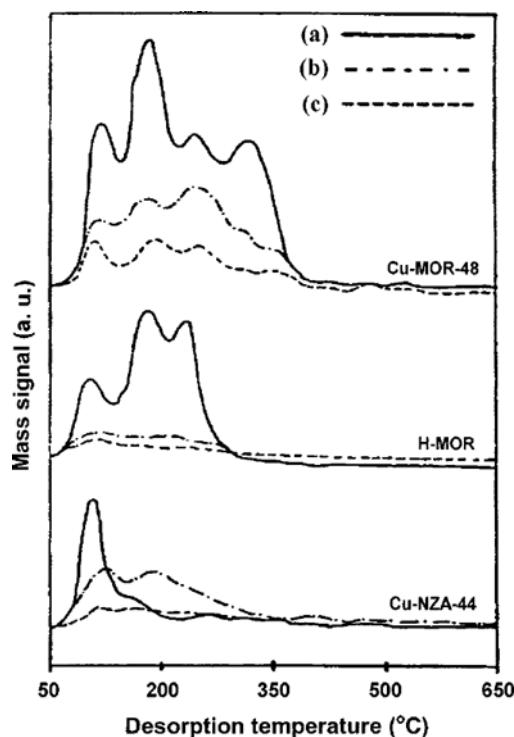


Fig. 10. Temperature-programmed desorption (TPD) of the catalysts adsorbing NO in the absence and presence of H<sub>2</sub>O. (a) NO adsorption in the absence of H<sub>2</sub>O; (b) summation of nitrogen compounds formed during NO adsorption in the presence of H<sub>2</sub>O; (c) NO desorption after simultaneous adsorption of NO and H<sub>2</sub>O. The ramping rate was 10 °C/min, and the carrier (He) flow rate was 40 cm<sup>3</sup>/min [Kim et al., 1997].

be strongly inhibited by  $H_2O$  during NO adsorption with  $H_2O$ . The capability of H-MOR to adsorb NO in a wet stream is significantly low compared to that of Cu-MOR-48 catalyst.

Cu-NZA-44 catalyst contains three desorption peaks at 100, 146 and 230 °C when NO is only adsorbed on the catalyst surface, as also observed in Fig. 10. By the competitive adsorption of NO and  $H_2O$ , the amount of NO desorption from the catalyst surface severely decreases. However, the amount of total nitrogen compounds desorbed remains unchanged, implying that the adsorption sites on Cu-exchanged natural zeolite catalyst are still active even in the wet condition. The extent of the decrease of NO adsorption by  $H_2O$  well illustrates the water tolerance of the catalyst employed. It also agrees with the hydrophobicity of the catalyst surface. The complete reversibility of NO removal activity in dry and wet streams may be another evidence for the competitive adsorption of NO and water on the catalyst surface, which is consistent with the earlier results on Co-MFI-140, Co-MFI-98, Co-FER-78 and Co-MOR-94 [Li and Armor, 1993; Li et al., 1993], Cu-MFI-157 [Iwamoto et al., 1992], Pd-MOR [Uchida et al., 1996] and Co-FER-98 [Lee et al., 2001].

Water could also affect the adsorption of hydrocarbon on the surface of the catalyst [Kim, 1996; Kim et al., 1997]. In a representative experiment for  $C_3H_6$  TPD over Cu-NZA-44 catalyst, the adsorption of  $C_3H_6$  without  $H_2O$  allowed two prominent desorption peaks at 100 and 350 °C [Kim et al., 1997]. Although the simultaneous adsorption of  $C_3H_6$  and  $H_2O$  on the catalyst surface leads a significant decrease in the amounts of the desorption of  $C_3H_6$  at the temperatures ranging from 130 to 250 °C, the amount of chemisorbed  $C_3H_6$  on the catalyst surface at 350 °C maintains even in a wet stream. For the adsorption of  $C_2H_4$  on the catalyst without  $H_2O$ , a doublet peak for its desorption below 200 °C has been observed with a broad one and centered at 370 °C. However, the intensity of the peaks decreases for the simultaneous adsorption of  $C_2H_4$  and  $H_2O$ .

By a comparison of the desorption amounts of both HCs on the catalyst surface from 200 to 500 °C, it is evident that the adsorption capacity of  $C_3H_6$  on the surface of Cu-NZA-44 is much greater than that of  $C_2H_4$ , irrespective of the presence of  $H_2O$ , and  $C_3H_6$  is predominantly chemisorbed on the catalyst surface even under the wet condition, thereby providing an excellent activity maintenance in a catalytic system using Cu-NZA-44 with  $C_3H_6$ . This is quite consistent with the large amount of chemisorption and the high heat of adsorption of  $C_3H_6$  compared to those of  $C_2H_4$  [Kim, 1996; Kim et al., 1997]. The competitive adsorption of NO, HCs and  $H_2O$  leads to lower coverage on the catalyst surface for the chemisorption of NO and HCs, thus causing the loss of the catalytic activity in the presence of  $H_2O$ . This is also in good agreement with the observation in which smaller amounts of NO and HCs could be adsorbed on wet surfaces of Cu-MFI-111, Co-MFI-117 and Co-BEA-80 [Tabata et al., 1996] as well as of Pd-MFI catalyst [Ogura et al., 1999]. In addition, further reaction of HCs with  $H_2O$  could be a minor reason for the catalyst deactivation for SCR by HCs in a wet feed gas stream [Kim et al., 1997].

### 3-3. An Approach to Improve Water Tolerance

The water tolerance of zeolite-based deNO<sub>x</sub> catalysts for NO reduction by HCs strongly depends on the surface hydrophobicity of the catalyst which could be closely related to the competitive adsorption among NO, HCs and  $H_2O$ , as proposed by Kim et al. [1997].

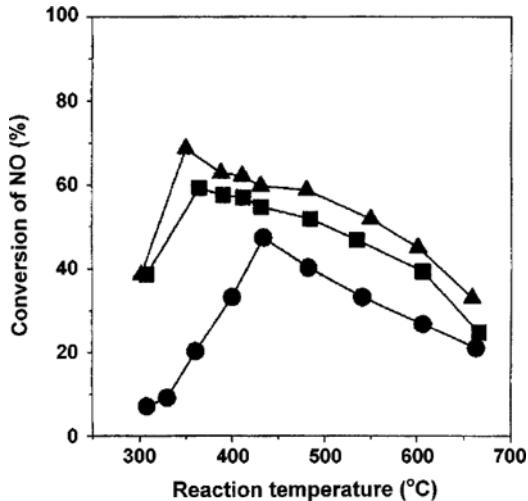


Fig. 11. NO removal activity of dealuminated Cu-MOR catalysts: (●) Cu-MOR-32 (6); (■) Cu-MOR-68 (12); (▲) Cu-MOR-90 (22). Reaction condition: NO 1,200 ppm,  $C_3H_6$  1,600 ppm,  $O_2$  3.2%,  $H_2O$  10%, CO 3,000 ppm,  $H_2$  1,000 ppm and  $CO_2$  10% [Chung et al., 1999].

It is widely accepted that the hydrophobicity is associated with the ratio of silicon to aluminum in the structure of zeolite [Flanigen et al., 1978], anticipating that the surface of zeolite-based catalysts becomes hydrophobic as the Si/Al ratio of zeolite increases. Under a simulated lean NO<sub>x</sub> wet condition, the water tolerance of synthetic and natural MOR type zeolites containing a variety of Si/Al ratios, prepared by a common dealumination procedure, has been investigated, as shown in Fig. 11 [Chung et al., 1999]. Cu-MOR-32 (6) catalyst revealed 45% of NO conversion at 450 °C. Note that hereafter the Si/Al ratio of each catalyst is expressed in parenthesis followed by the exchanging ratio of the metal. Through the progressive dealumination of H-MOR from the Si/Al ratio of 5 to 22, the deNO<sub>x</sub> activity within the wide range of the reaction temperature significantly improves as the ratio increases.

The enhancement of the catalyst water tolerance is mainly attributed to the increase in the Si/Al ratio of zeolite, which has been also confirmed by the comparison of NO removal activity for Cu-MOR catalyst containing a variety of Cu/Al ratios at the given Si/Al ratio. NO removal activity of Cu-MOR-60 (5) catalyst is almost identical to that of Cu-MOR-32 (6) [Chung et al., 1999], although the maximum conversion of NO for the catalyst containing the low ratio of Cu/Al, shifts slightly to the high reaction temperature. A similar observation has also been made for the catalysts containing identical Si/Al ratio, such as Cu-MOR-28 (12) and Cu-MOR-68 (12) at the reaction temperature higher than 350 °C. However, the wet activity of Cu-MOR-28 (12) is much higher than that of Cu-MOR-32 (6) and this trend is also observed for Cu-MOR-60 (5) and the Cu-MOR-68 (12) [Chung et al., 1999].

The dependence of the water tolerance of zeolite catalyst on the Si/Al ratio was quite peculiar for Cu-MOR type catalyst as shown in Fig. 12. Three kinds of Cu-NZA catalyst in which the Cu/Al ratio of the catalysts is basically equal reveal the distinctive activity maintenances with respect to the Si/Al ratio of the catalysts. This clearly shows that the water tolerance is a strong function of the Si/Al ratio. It is also in good agreement with an earlier study on the deNO<sub>x</sub> ac-

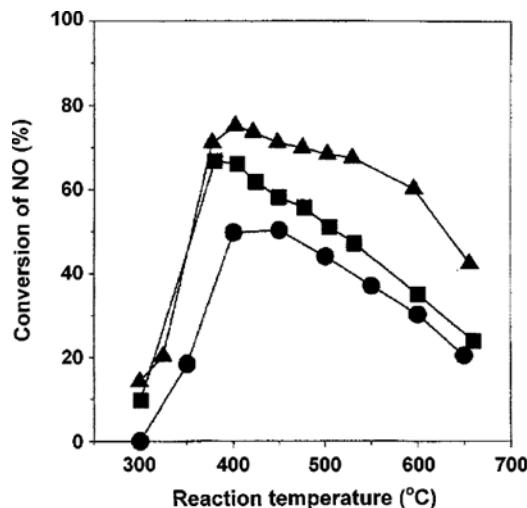


Fig. 12. NO removal activity of dealuminated Cu-NZA catalysts: (●) Cu-NZA-50 (4); (■) Cu-NZA-48 (10); (▲) Cu-NZA-56 (14). Reaction condition: NO 1,200 ppm, C<sub>3</sub>H<sub>6</sub> 1,600 ppm, O<sub>2</sub> 3.2%, H<sub>2</sub>O 10%, CO 3,000 ppm, H<sub>2</sub> 1,000 ppm and CO<sub>2</sub> 10% [Chung et al., 1999].

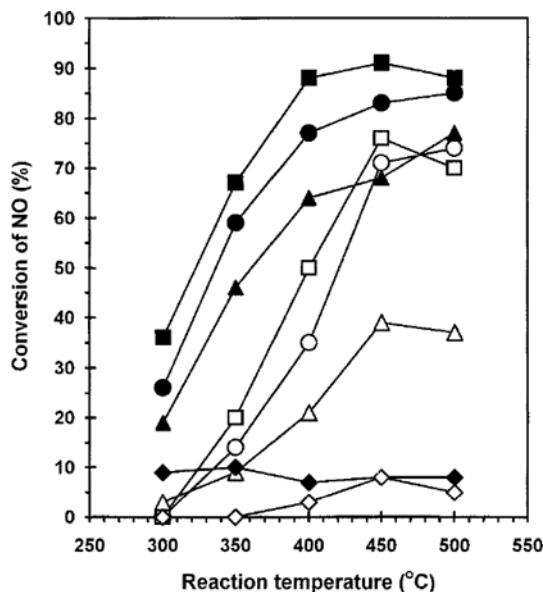


Fig. 13. Activity of Pd-MFI catalysts for the reduction of NO by CH<sub>4</sub> with and without H<sub>2</sub>O: (●, ○) Pd-MFI-6 (15); (■, □) Pd-MFI-10 (15); (▲, △) Pd-MFI-10 (25); (◆, ◇) Pd-MFI-22 (75). Reaction condition: NO 150 ppm, CH<sub>4</sub> 2,000 ppm, O<sub>2</sub> 10% and H<sub>2</sub>O 0 (closed symbols) or 9% (open symbols) [Ohtsuka and Tabata, 2000].

tivity of Cu-MFI-80 (27) and (11) by C<sub>3</sub>H<sub>6</sub> with 2% of H<sub>2</sub>O at temperatures below 400 °C [Torre-Abreu et al., 1997]. Recently, the influence of Si/Al ratio on the wet activity of Pd-MFI catalysts with respect to the ratio of Pd/Al has also been examined by Ohtsuka and Tabata [2000], as illustrated in Fig. 13. Pd-MFI-6 (15) catalyst reveals 78% of dry activity for NO reduction by CH<sub>4</sub> at 400 °C, while the presence of 9% H<sub>2</sub>O decreases NO conversion to 34%, indicating that Pd ions are active reaction sites for the removal reaction but too sensitive to maintain its dry activity. When the Pd/Al ratio

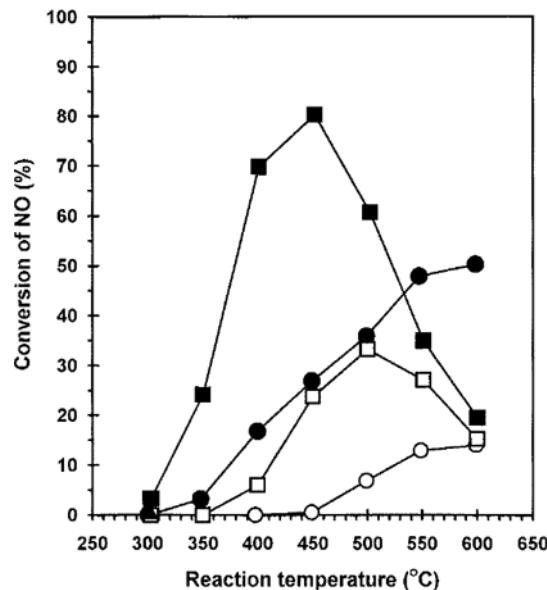


Fig. 14. NO removal activity of PdCo-FER catalyst for the reduction of NO by CH<sub>4</sub>: (●, ○) Co-FER-44; (■, □) PdCo-FER-54. Reaction condition: NO 1,200 ppm, CH<sub>4</sub> 1,600 ppm, O<sub>2</sub> 3.2% and H<sub>2</sub>O 0 (closed symbols) or 10% (open symbols) [Lee et al., 2001].

increases, the catalytic activity becomes higher in the absence of H<sub>2</sub>O but the water tolerance is not improved. If parent MFI zeolite containing a high Si/Al ratio of 25 is employed for preparing Pd-MFI-10 catalyst, the dry performance is not improved at all. As the Si/Al ratio increases, the catalytic activity decreases and the higher Si/Al ratio cannot improve the water tolerance, either. It implies that the dealumination of zeolites, thereby increasing the Si/Al ratio, is a useful way for improving the water tolerance of the catalyst; however, optimal Si/Al and metal/Al ratio depending on zeolite structures should be selected to obtain the best performance of the catalyst in a wet stream.

Another approach for improving the water tolerance of zeolite catalysts is to introduce second metal ions into single metal-exchanged zeolite. In a such attempt with Co-FER-44 catalyst for reducing NO by CH<sub>4</sub> in the presence and absence of H<sub>2</sub>O [Lee et al., 2001], the NO removal activity was about 27% in terms of NO conversion at 450 °C over the catalyst without H<sub>2</sub>O but dropped to less than 1% under a wet condition with 10% of H<sub>2</sub>O, as shown in Fig. 14. If a small amount of Pd (Pd/Al=0.04) is exchanged into H-FER after which Co ions at the ratio of Co/Al=0.23 are subsequently introduced into the Pd-FER sample, 80% of NO conversion at 450 °C is obtained with a dry feed gas stream and the presence of 10% H<sub>2</sub>O allows the NO conversion of 24%. It is interesting to note that the degree of dry activity loss by H<sub>2</sub>O is in the range of 27% of NO conversion for Co-FER-44 catalyst in which the Co/Al ratio is similar to the total metal to aluminum ratio, (Pd+Co)/Al=0.27. Not only could the pre-exchanged Pd ions play an important role in improving the water tolerance, but they can also enhance the dry performance of the catalyst. Other cocations, *i.e.*, In and La, are also useful in improving the water tolerance of Co-FER catalyst [Lee et al., 2001]. This result is also quite consistent with earlier and recent developments in this area of research.

**Table 4. Physicochemical properties of MOR structure zeolite catalysts with and without a hydrothermal aging**

Catalyst <sup>a</sup>	Cu content (wt%) <sup>b</sup>	Si/Al <sup>b</sup>	Cu/Al <sup>b</sup>	Surface area (m <sup>2</sup> /g)	
				Fresh	Hydrothermally-aged <sup>c</sup>
H-MOR (5)		5		449	
H-MOR (10)		10			
H-MOR (20)		20		449	
Cu-MOR-32 (6)	2.02	6	0.16	368	22
Cu-MOR-60 (5)	4.20	5	0.30		
Cu-MOR-68 (12)	2.55	12	0.34	434	154
Cu-MOR-28 (12)	1.03	12	0.14		
Cu-MOR-90 (22)	1.73	22	0.45	450	330
Cu-NZA <sup>d</sup> -50 (4)	4.37	4	0.25	179	
Cu-NZA <sup>d</sup> -48 (10)	1.84	10	0.24	232	26
Cu-NZA <sup>d</sup> -56 (14)	1.75	14	0.28		
Cu-NZA <sup>d</sup> -62 (19)	1.64	19	0.31	128	
Cu-MFI-162 (26)	2.90	26	0.81	344	249
					27 <sup>e</sup>

Note. This table was prepared using data published by Chung et al. [1999].

<sup>a</sup>Numbers next to the zeolite structure designate the exchange percentage of each metal ion.

<sup>b</sup>Based on fresh samples.

<sup>c</sup>Under flowing 10% H<sub>2</sub>O in He 800 °C for 24 h.

<sup>d</sup>Natural zeolite consisting mainly of a MOR structure.

<sup>e</sup>At 900 °C.


By adding small amounts of Na and Ba to Cu-based MOR catalyst at the given ratio of Cu/Al (0.10), improved performance of the catalyst for NO reduction by C<sub>3</sub>H<sub>6</sub> in the presence of 2% H<sub>2</sub>O was obtained compared to Cu-MOR-20, but all the catalysts in the presence of H<sub>2</sub>O were deactivated in the range of NO conversion less than 20% [Torre-Abreu et al., 1997]. For Pd (0.4 wt%)-MFI catalyst without Co ions, the conversion of NO at 500 °C was in the range of 5% when 10% of H<sub>2</sub>O existed in the feed gas stream, while 64% of NO conversion was attained for Pd-MFI catalyst containing 3.3 wt% of Co ions. A similar role of second metals in improving the water tolerance of deNO<sub>x</sub> catalysts has also been observed for Pd/Ag/H-MOR [Masuda et al., 1998], Ce-Ag-MFI [Li and Flytzani-Stephanopoulos, 1999], Pt-In-FER [Ramallo-Lopez et al., 2001], Pt-Co-MOR [Gutierrez et al., 2001] and Pt-Co-MFI [Maisuls et al., 2001] for NO reduction by HCs in a wet condition.

#### 4. Hydrothermal Stability of HC-SCR DeNO<sub>x</sub> Catalysts

Few investigations concerning the hydrothermal stability of deNO<sub>x</sub> catalyst for NO removal reaction with HCs could be found in the literature. Hydrothermal stability has been examined for Cu-SAPO-75 and Cu-MFI (unknown Cu content) [Ishihara et al., 1997]. The catalyst samples have been aged under flowing of 3% H<sub>2</sub>O in air for 2 h at the temperatures 500, 700 and 800 °C to examine the hydrothermal stability of the catalyst. Although Cu-SAPO catalyst revealed strong hydrothermal stability, both catalysts after the aging at 800 °C showed the catalyst deactivation within the reaction temperatures covered. The dependence of the stability on the aging temperature has been also observed for Ce-Ag-MFI catalyst aged in He containing 14% of water for 24 h with respect to the temperatures [Li and Flytzani-Stephanopoulos, 1999]. In an earlier attempt to investigate the effect of Si/Al ratio of zeolite on the stability of Cu-MFI [Torre-Abreu et al., 1997], the activity maintenance of the

catalyst containing high Si/Al ratio was stable according to the comparison of the catalyst deactivation of Cu-MFI-40 (11) and Cu-MFI-80 (27) catalysts, indicating that hydrothermal stability can be improved by an increase of the Si/Al ratio of the catalyst.

A systematic study to provide the dominant parameter in determining the hydrothermal stability of zeolites has been postulated for MOR type zeolites. Chung et al. [1999] have attempted to illustrate the main role of Si/Al ratio in improving the hydrothermal

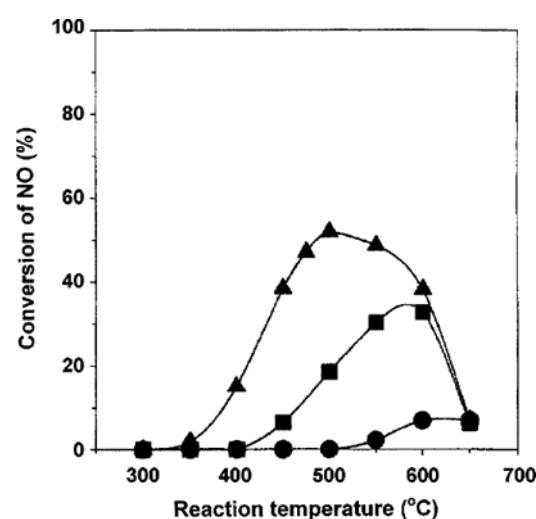

**Fig. 15. Hydrothermal stability of dealuminated Cu-MOR catalysts: (●) Cu-MOR-32 (6); (■) Cu-MOR-68 (12); (▲) Cu-MOR-90 (22). Reaction condition: NO 1,200 ppm, C<sub>3</sub>H<sub>6</sub> 1,600 ppm, O<sub>2</sub> 3.2%, H<sub>2</sub>O 10%, CO 3,000 ppm, H<sub>2</sub> 1,000 ppm and CO<sub>2</sub> 10% [Chung et al., 1999].**

stability of synthetic Cu-MOR catalysts containing the variety of the Si/Al ratios, as listed in Table 4. The catalyst was prepared by using a typical dealumination technique of zeolite with hydrochloric acid. As shown in Fig. 15, zero activity at the temperatures below 550 °C under a simulated lean NO<sub>x</sub> condition has been observed for Cu-MOR-32 (6) catalyst hydrothermally aged at 800 °C in a flowing mixture of 10% H<sub>2</sub>O/90% He for 24 h. The dealuminated Cu-MOR catalysts exhibit strong activity maintenance with respect to the Si/Al ratio of the catalysts; the NO conversions after aging are 50, 20 and 0% for Cu-MOR-90 (22), Cu-MOR-68 (12) and Cu-MOR-32 (6) at 500 °C, respectively. It clearly presents that hydrothermal stability could be improved by dealumination, thereby increasing the Si/Al ratio of the catalyst.

The dependence of hydrothermal stability on the Si/Al ratio for MOR type Cu-NZA catalyst has been also examined [Chung et al., 1999]. Essentially, the same trend in the hydrothermal stability has been observed as the Si/Al ratio increases. It may be a typical example presenting the close relationship of the Si/Al ratio of zeolites with the hydrothermal durability of the catalyst in the present reaction system. Although the catalyst deactivation by sintering can be improved by the modification of the Si/Al ratio of zeolite, the catalyst still reveals the loss of NO removal activity compared to that of the fresh catalyst. This could be mainly due to the destruction of zeolite structure during the hydrothermal aging, thus resulting in the sintering of active reaction site, Cu<sup>2+</sup> ions on the catalyst surface to CuO species, as extensively observed by BET, XRD and ESR studies [Chung et al., 1999]. A typical evidence for the zeolite structure destruction upon the hydrothermal aging could be provided by BET surface area measurements, as listed in Table 4. It is also in good agreement with the formation of CuO on the surface of Cu-MOR-48 catalyst when hydrothermally aged under the similar sintering condition, as illustrated by AES [Kim, 1996].

In addition, the hydrothermal stability of Pd-MFI-14 (25) and Pd-silicellite-40 (131) aged at 800 °C for 6 h under N<sub>2</sub> flow with 10% H<sub>2</sub>O has been also examined, and they are seriously deactivated even in dry stream probably due to the agglomeration of active Pd ions and their transformation to PdO species, as confirmed from XRD, TEM and NMR studies [Descomme et al., 1997]. It has been observed that the hydrothermal durability of zeolite mainly depends on both exchanged metal and its type [Ohtsuka and Tabata, 1999].

## 5. General Remarks

Inhibiting NO and HC adsorption sites on the catalyst surface by water is one of the main reasons for the loss of catalytic activity for the reduction of NO by HCs over zeolite catalyst. It well elucidates the cause of the catalyst deactivation by water, regardless of the degree of the activity loss. Surface hydrophobicity of zeolite catalyst may play a critical role in determining the extent of the catalyst deactivation in a wet stream. The reversibility of the catalyst deactivation by the existence of water in the feed gas stream may be an experimental evidence for the competitive adsorption of the reactants including water during the course of the reaction. It has also been observed for the decomposition of NO over excessively ion-exchanged Cu-zeolite. However, it becomes complicated due to the chemical alteration of metal ions to metal oxides after aging in a wet stream, as extensively discussed. This implies that no single cause can elucidate the catalyst deactivation by water for the re-

duction of NO by HCs. It varies with the catalyst, the reductant and the operating condition employed for the reduction.

No HC-SCR catalyst without the catalyst deactivation by water has been proposed so far. The extent of the activity loss for the reduction of NO<sub>x</sub> by NH<sub>3</sub> in a wet stream strongly depends on the catalyst employed. In general, negligible activity decrease in the reduction even with H<sub>2</sub>O has been observed for V<sub>2</sub>O<sub>5</sub>/TiO<sub>2</sub> catalyst, a commercial deNO<sub>x</sub> catalyst by NH<sub>3</sub>; NO removal activity simply shifts to the region of the high reaction temperature where the effect of water becomes negligible. This may be due to the distinction of the reaction mechanism depending upon the catalyst. Earlier studies indicate that NO removal reaction of V<sub>2</sub>O<sub>5</sub>/TiO<sub>2</sub> proceeds on the basis of Eley-Rideal (ER) kinetic mechanism, while that for Cu-MOR catalyst occurs by Langmuir-Hinshelwood Hougen Watson (LHHW) mechanism. This leads to the fact that the reaction mechanism can vary with the catalysts employed. If the catalytic deNO<sub>x</sub> reaction with NH<sub>3</sub> over V<sub>2</sub>O<sub>5</sub>/TiO<sub>2</sub> catalyst was governed by the latter mechanism, significant activity loss at low reaction temperatures in the presence of H<sub>2</sub>O should be unavoidable. The major distinction of the reaction mechanisms described may be the adsorption of NO on the catalyst surface along with NH<sub>3</sub> and water. No adsorption of NO is generally known for SCR of NO by NH<sub>3</sub> based upon ER mechanism. Since the catalytic reduction of NO<sub>x</sub> by HCs takes place by LHHW mechanism, a future approach for developing the catalyst containing strong water tolerance may be first directed to understand the reaction mechanism of the reduction of NO by HCs.

## ACKNOWLEDGEMENT

One (M. H. Kim) of the authors is grateful to Taek-Jeong Lee and Chan Hee Park for preparing a part of the figures and processing a hard copy of a few references.

## REFERENCES

- Adelman, B. J., Beutel, T., Lei, G. D. and Sachtler, W. M. H., "On the Mechanism of Selective NO<sub>x</sub> Reduction with Alkanes over Cu/ZSM-5," *Appl. Catal. B*, **11**, L1 (1996).
- Adlhart, O. J., Hindin, S. G. and Kenson, R. E., "Processing Nitric Acid Tail Gas," *Chem. Eng. Prog.*, **67**, 73 (1971).
- Asbrink, S. and Norby, L. J., "A Refinement of the Crystal Structure of Copper (II) Oxide with a Discussion of Some Experimental E.s.d.s," *Acta Crystallogr. B*, **26**, 8 (1970).
- Ault, J. W. and Ayen, R. J., "Catalytic Reduction of Nitric Oxide with Various Hydrocarbons," *AIChE J.*, **17**, 265 (1971).
- Bethke, K. A., Alt, D. and Kung, M. C., "NO Reduction by Hydrocarbons in an Oxidizing Atmosphere over Transition Metal-Zirconium Mixed Oxides," *Catal. Lett.*, **25**, 37 (1994).
- Bethke, K. A. and Kung, M. C., "Supported Ag Catalysts for the Lean Reduction of NO with C<sub>3</sub>H<sub>6</sub>," *J. Catal.*, **172**, 93 (1997).
- Burch, R. and Scire, S., "Selective Catalytic Reduction of Nitric Oxide with Ethane and Methane on Some Metal Exchanged ZSM-5 Zeolites," *Appl. Catal. B*, **3**, 295 (1994).
- Chung, S. Y., Oh, S.-H., Kim, M. H., Nam, I.-S. and Kim, Y. G., "Hydrothermal Stability of Dealuminated Mordenite Type Zeolite Catalysts for the Reduction of NO by C<sub>3</sub>H<sub>6</sub> under Lean-Burn Condition,"

*Catal. Today*, **54**, 521 (1999).

Cohn, J. G. E., Orange, W., Steele, D. R. and Anderson, H. C., "Method of Selectively Removing Oxides of Nitrogen from Oxygen Containing Gases," US 2975025 (1961).

Demichelis, M. C., Hoang, L. C., Menezo, J. C. and Barbier, J., "Influence of Metal Particle Size and Effect of Gold Addition on the Activity and Selectivity of Pt/Al<sub>2</sub>O<sub>3</sub> Catalysts in the Reduction of Nitric Oxide by Methane," *Appl. Catal. A*, **97**, L11 (1993).

Descomme, C., Gelin, P., Lecuyer, C. and Primet, M., "Palladium-Exchanged MFI-Type Zeolites in the Catalytic Reduction of Nitrogen Monoxide by Methane: Influence of the Si/Al Ratio on the Activity and the Hydrothermal Stability," *Appl. Catal. B*, **13**, 185 (1997).

Flanigen, E. M., Bennett, J. M., Grose, R. W., Cohen, J. P., Patton, R. L., Kirchner, R. M. and Smith, J. V., "Silicalite, A New Hydrophobic Crystalline Silica Molecular Sieve," *Nature*, **271**, 512 (1978).

Fujitani, Y., Muraki, H., Kondo, S. and Fukui, M., "Method of Purifying Exhaust Gases," JP 63100919 A (1988); DE 3735151 A1 (1988).

Gutierrez, L. B., Boix, A. V., Lombardo, E. A. and Fierro, J. L. G., "Study of the Co-Pt Synergism for the Selective Catalytic Reduction of NO<sub>x</sub> with CH<sub>4</sub>," *J. Catal.*, **199**, 60 (2001).

Gopalakrishnan, R., Stafford, P. R., Davidson, J. E., Hecker, W. C. and Bartholomew, C. H., "Selective Catalytic Reduction of Nitric Oxide by Propane in Oxidizing Atmosphere over Copper-Exchanged Zeolites," *Appl. Catal. B*, **2**, 165 (1993).

Hamada, H., "Selective Reduction of NO by Hydrocarbons and Oxygenated Hydrocarbons over Metal Oxide Catalysts," *Catal. Today*, **22**, 21 (1994).

Hamada, H., Kintaichi, Y., Sasaki, M., Ito, T. and Tabata, M., "Highly Selective Reduction of Nitrogen Oxides with Hydrocarbons over H-Form Zeolite Catalysts in Oxygen-Rich Atmosphere," *Appl. Catal.*, **64**, L1 (1990).

Hamada, H., Kintaichi, Y., Sasaki, M., Ito, T. and Tabata, M., "Transition Metal-Promoted Silica and Alumina Catalysts for the Selective Reduction of Nitrogen Monoxide with Propane," *Appl. Catal.*, **75**, L1 (1991).

Hamada, H., Matsubayashi, N., Shimada, H., Kintaichi, Y., Ito, T. and Nishijima, A., "XANES and EXAFS Analysis of Copper Ion-Exchanged ZSM-5 Zeolite Catalyst Used for Nitrogen Monoxide Decomposition," *Catal. Lett.*, **5**, 189 (1990).

Hardee, J. R. and Hightower, J. W., "Nitric Oxide Reduction by Methane over Rh/Al<sub>2</sub>O<sub>3</sub> Catalysts," *J. Catal.*, **86**, 137 (1984).

Held, W. and Konig, A., "Process and Apparatus for the Reduction of Nitrogen Oxides," DE 3642018 A1 (1987).

Held, W., Konig, A. and Puppe, L., "Method and Apparatus for Reducing Nitrogen Oxides," JP 63283727 A (1988).

Held, W., Konig, A. and Puppe, L., "Process and Device for Reducing Nitrogen Oxides," DE 3713169 A1 (1988); EP 0286967 A2 (1988).

Held, W., Konig, A., Richter, T. and Puppe, L., "Catalytic NO<sub>x</sub> Reduction in Net Oxidizing Exhaust Gas," SAE Paper 900496 (1990).

Hong, S.-S., Lee, G.-D., Park, J.-W., Park, D.-W., Cho, K.-M. and Oh, K.-J., "Catalytic Reduction of NO over Perovskite-Type Catalyst," *Korean J. Chem. Eng.*, **14**, 491 (1997).

Hosose, H., Yahiru, H., Mizuno, N. and Iwamoto, M., "Catalytic Activity of Cu/SiO<sub>2</sub>-Al<sub>2</sub>O<sub>3</sub> Catalyst for Selective Reduction of Nitrogen Monoxide by Ethene in Oxidizing Atmosphere," *Chem. Lett.*, 1859 (1991).

Ishihara, T., Kagawa, M., Hadama, F. and Takita, Y., "Copper Ion-Exchanged SAPO-34 as a Thermostable Catalyst for Selective Reduction of NO with C<sub>3</sub>H<sub>6</sub>," *J. Catal.*, **169**, 93 (1997).

Iwamoto, M., "Decomposition of NO on Copper Ion-Exchanged Zeolite Catalysts," in Proceedings of Meeting on Catalytic Technology for Removal of Nitrogen Monoxide, Tokyo, Japan (1990).

Iwamoto, M., "Catalytic Decomposition of Nitrogen Monoxide," *Stud. Surf. Sci. Catal.*, **54**, 121 (1990).

Iwamoto, M. and Hamada, H., "Removal of Nitrogen Monoxide from Exhaust Gases through Novel Catalytic Processes," *Catal. Today*, **10**, 57 (1991).

Iwamoto, M. and Mizuno, N., "NO<sub>x</sub> Emission Control in Oxygen-Rich Exhaust through Selective Catalytic Reduction by Hydrocarbon," *J. Auto. Eng.*, **207**, 23 (1993).

Iwamoto, M. and Mizuno, N. and Yahiru, H., "Selective Catalytic Reduction of NO by Hydrocarbon in Oxidizing Atmosphere," in Proceedings of 10<sup>th</sup> International Congress on Catalysis, Budapest, Hungary (1992).

Iwamoto, M. and Yahiru, H., "Novel Catalytic Decomposition and Reduction of NO," *Catal. Today*, **22**, 5 (1994).

Iwamoto, M., Yahiru, H., Shundo, S., Yu-u, Y. and Mizuno, N., "Influence of Sulfur Dioxide on Catalytic Removal of Nitric Oxide over Copper Ion-Exchanged ZSM-5 Zeolite," *Appl. Catal.*, **69**, L15 (1991).

Iwamoto, M., Yahiru, H., Tanda, K., Mizuno, N., Mine, Y. and Kagawa, S., "Decomposition on Excessively Copper Ion-Exchanged ZSM-5 Zeolites," *J. Phys. Chem.*, **95**, 3727 (1991).

Kharas, K. C. C., Robota, H. J. and Liu, D. J., "Deactivation in Cu-ZSM-5 Lean-Burn Catalysts," *Appl. Catal. B*, **2**, 225 (1993).

Kim, M. H., "Effect of Water Vapor and SO<sub>2</sub> on the Selective Reduction of NO<sub>x</sub> over Mordenite-Type Zeolite Catalysts by Hydrocarbons," PhD Dissertation, Pohang University of Science and Technology (1996).

Kim, M. H., Nam, I.-S. and Kim, Y. G., "Selective Catalytic Reduction of NO by Hydrocarbons over Mordenite-Type Zeolite Catalysts," *HWAHAK KONGHAK (in Korean)*, **32**, 402 (1994).

Kim, M. H., Nam, I.-S. and Kim, Y. G., "Selective Catalytic Reduction of Nitrogen Oxide by Hydrocarbons over Mordenite-Type Zeolite Catalysts," *Appl. Catal. B*, **6**, 297 (1995).

Kim, M. H., Nam, I.-S. and Kim, Y. G., "The Role of Water for NO Reduction by Hydrocarbons over Copper Ion-Exchanged Mordenite-Type Zeolite Catalysts," *Stud. Surf. Sci. Catal.*, **105**, 1493 (1997).

Kim, M. H., Nam, I.-S. and Kim, Y. G., "Water Tolerance of Mordenite-Type Zeolite Catalysts for Selective Reduction of Nitric Oxide by Hydrocarbons," *Appl. Catal. B*, **12**, 125 (1997).

Kim, M. H., Nam, I.-S. and Kim, Y. G., "Sulfur Tolerance of Cu- and H-Mordenite Zeolite Catalysts for the Reduction of NO by Hydrocarbons," *Stud. Surf. Sci. Catal.*, **111**, 213 (1997).

Kim, M. H., Nam, I.-S. and Kim, Y. G., "Formation of Isocyanate Species on the Surface of Mordenite-Type Zeolite Catalysts for the Reduction of NO by Hydrocarbons with H<sub>2</sub>O," *J. Chem. Soc., Chem. Commun.*, 1771 (1998).

Kim, M. H., Nam, I.-S. and Kim, Y. G., "Characteristics of Mordenite-Type Zeolite Catalysts Deactivated by SO<sub>2</sub> for the Reduction of NO with Hydrocarbons," *J. Catal.*, **179**, 350 (1998).

Kim, M. H., Hwang, U.-C., Nam, I.-S. and Kim, Y. G., "The Characteristics of a Copper-Exchanged Natural Zeolite for NO Reduction by NH<sub>3</sub> and C<sub>3</sub>H<sub>6</sub>," *Catal. Today*, **44**, 57 (1998).

Kim, M. H., Nam, I.-S. and Kim, Y. G., "Reaction Intermediate over Mordenite-Type Zeolite Catalysts for NO Reduction by Hydrocarbons," *Korean J. Chem. Eng.*, **16**, 139 (1999).

Kintaichi, Y., Hamada, H., Tabata, M., Sasaki, M. and Ito, T., "Selective Reduction of Nitrogen Oxides with Hydrocarbons over Solid Acid Catalysts in Oxygen-Rich Atmosphere," *Catal. Lett.*, **6**, 239 (1990).

Konno, M., Chikahisa, T., Murayama, T. and Iwamoto, M., "Catalytic Reduction of NO<sub>x</sub> in Actual Diesel Engine Exhaust," SAE Paper 920091 (1992).

Lee, D. I., Lee, T. J., Ham, S. W., Nam, I. S., Oh, Y. S. and Baek, Y. S., "Characteristics of Cobalt-Exchanged Ferrierite Catalysts for the Reduction of NO by Methane," *Theor. Appl. Chem. Eng. (in Korean)*, **7**, 225 (2001).

Li, Y. and Armor, J. N., "Catalytic Reduction of Nitrogen Oxides with Methane in the Presence of Excess Oxygen," *Appl. Catal. B*, **1**, L31 (1992).

Li, Y. and Armor, J. N., "Selective Catalytic Reduction of NO with Methane on Gallium Catalysts," *J. Catal.*, **145**, 1 (1994).

Li, Y. and Armor, J. N., "Selective Reduction of NO<sub>x</sub> by Methane on Co-Ferrierites," *J. Catal.*, **150**, 376 (1994).

Li, Y., Battavio, P. J. and Armor, J. N., "Effect of Water Vapor on the Selective Reduction of NO by Methane over Cobalt-Exchanged ZSM-5," *J. Catal.*, **142**, 561 (1993).

Li, Z. and Flytzani-Stephanopoulos, M., "Effect of Water Vapor and Sulfur Dioxide on the Performance of Ce-Ag-ZSM-5 for the SCR of NO with CH<sub>4</sub>," *Appl. Catal. B*, **22**, 35 (1999).

Li, W., Sirilumpen, M. and Yang, R. T., "Selective Catalytic Reduction of Nitric Oxide by Ethylene in the Presence of Oxygen over Cu<sup>2+</sup>-Exchanged Pillared Clays," *Appl. Catal. B*, **11**, 347 (1997).

Maisuls, S. E., Seshan, K., Feast, S. and Lercher, J. A., "Selective Catalytic Reduction of NO<sub>x</sub> to Nitrogen over Co-Pt/ZSM-5: Part A. Characterization and Kinetic Studies," *Appl. Catal. B*, **29**, 69 (2001).

Masuda, K., Shinoda, K., Kato, T. and Tsujimura, K., "Activity Enhancement of Ag/Mordenite Catalysts by Addition of Palladium for the Removal of Nitrogen Oxides from Diesel Engine Exhaust Gas," *Appl. Catal. B*, **15**, 29 (1998).

Matsumoto, H. and Tanabe, S., "Catalytic Behavior and Structure of Active Species of Cu-Y Zeolite in Oxidation of Carbon Monoxide," *J. Phys. Chem.*, **94**, 4207 (1990).

Maunula, T., Ahola, J. and Hamada, H., "Reaction Mechanism and Kinetics of NO<sub>x</sub> Reduction by Propene on CoO<sub>x</sub>/Alumina Catalysts in Lean Conditions," *Appl. Catal. B*, **26**, 173 (2000).

Misono, M., Hirao, Y. and Yokoyama, C., "Reduction of Nitrogen Oxides with Hydrocarbons Catalyzed by Bifunctional Catalysts," *Catal. Today*, **38**, 157 (1997).

Miyadera, T., "Alumina-Supported Silver Catalysts for the Selective Reduction of Nitric Oxide with Propene and Oxygen-Containing Organic Compounds," *Appl. Catal. B*, **2**, 199 (1993).

Murakami, Y., Hayashi, K., Yasuda, K., Ito, T., Minami, T. and Miyamoto, A., "Catalytic Reduction of Nitrogen Oxides by Hydrocarbons over Metal Oxide Catalysts," *Nippon Kagaku Kaishi*, 173 (1977).

Nakayama, T., Yasumatsu, T., Kokitsu, M., Tabata, T. and Sakane, H., "XAFS Studies of Copper/Zeolite Catalysts for NO<sub>x</sub> Reduction," *Jpn. J. Appl. Phys.*, **32**, 487 (1993).

Ogura, M., Hayashi, M., Kage, S., Matsukata, M. and Kikuchi, E., "Determination of Active Palladium Species in ZSM-5 Zeolite for Selective Reduction of Nitric Oxide with Methane," *Appl. Catal. B*, **23**, 247 (1999).

Ogura, M., Kage, S., Hayashi, M., Matsukata, M. and Kikuchi, E., "Remarkable Enhancement in Durability of Pd/H-ZSM-5 Zeolite Catalysts for CH<sub>4</sub>-SCR," *Appl. Catal. B*, **27**, L213 (2000).

Ohtsuka, H. and Tabata, T., "Effect of Water Vapor on the Deactivation of Pd-Zeolite Catalysts for Selective Catalytic Reduction of Nitrogen Monoxide by Methane," *Appl. Catal. B*, **21**, 133 (1999).

Ohtsuka, H. and Tabata, T., "Influence of Si/Al Ratio on the Activity and Durability of Pd-ZSM-5 Catalysts for Nitrogen Oxide Reduction by Methane," *Appl. Catal. B*, **26**, 275 (2000).

Parvulescu, V. I., Grange, P. and Delmon, B., "Catalytic Removal of NO," *Catal. Today*, **46**, 233 (1998).

Piffer, R., Forster, H. and Niemann, W., "IR and XAS Investigations on the Interaction of Butadiene with Zeolite CuY," *Catal. Today*, **8**, 491 (1991).

Ramallo-Lopez, J. M., Requejo, F. G., Gutierrez, L. B. and Miro, E. E., "EXAFS, TDPAC and TPR Characterization of PtInFerrierite: The Role of Surface Species in the SCR of NO<sub>x</sub> with CH<sub>4</sub>," *Appl. Catal. B*, **29**, 35 (2001).

Sato, K., Fujimoto, T., Kanai, S., Kintaichi, Y., Inaba, M., Haneda, M. and Hamada, H., "Catalytic Performance of Silver Ion-Exchanged Saponite for the Selective Reduction of Nitrogen Monoxide in the Presence of Excess Oxygen," *Appl. Catal. B*, **13**, 27 (1997).

Sato, S., Hirabayashi, H., Yahiro, H., Mizuno, N. and Iwamoto, M., "Iron Ion-Exchanged Zeolite: The Most Active Catalyst at 473 K for Selective Reduction of Nitrogen Monoxide by Ethene in Oxidizing Atmosphere," *Catal. Lett.*, **12**, 193 (1992).

Sato, S., Yu-u, Y., Yahiro, H., Mizuno, N. and Iwamoto, M., "Cu-ZSM-5 Zeolite as Highly Active Catalyst for Removal of Nitric Oxide from Emission of Diesel Engines," *Appl. Catal.*, **70**, L1 (1991).

Shimizu, K.-I., Satsuma, A. and Hattori, T., "Selective Catalytic Reduction of NO by Hydrocarbons on Ga<sub>2</sub>O<sub>3</sub>/Al<sub>2</sub>O<sub>3</sub> Catalysts," *Appl. Catal. B*, **16**, 319 (1998).

Shimizu, K.-I., Maeshima, H., Satsuma, A. and Hattori, T., "Transition Metal-Aluminate Catalysts for NO Reduction by C<sub>3</sub>H<sub>6</sub>," *Appl. Catal. B*, **18**, 163 (1998).

Smits, R. H. H. and Iwasawa, Y., "Reaction Mechanisms for the Reduction of Nitric Oxide by Hydrocarbons on Cu-ZSM-5 and Related Catalysts," *Appl. Catal. B*, **6**, L201 (1995).

Tabata, T., Kokitsu, M., Ohtsuka, H., Okada, O., Sabatino, L. M. F. and Bellussi, G., "Study on Catalysts of Selective Reduction of NO<sub>x</sub> Using Hydrocarbons for Natural Gas Engines," *Catal. Today*, **27**, 91 (1996).

Tabata, T., Kokitsu, M. and Okada, O., "Adsorption Properties of Oxygen and Methane on Ga-ZSM-5: The Origin of Selectivity of NO<sub>x</sub> Reduction Using Methane," *Catal. Lett.*, **25**, 393 (1994).

Tabata, T., Kokitsu, M. and Okada, O., "Study on Patent Literature of Catalysts for a New NO<sub>x</sub> Removal Process," *Catal. Today*, **22**, 147 (1994).

Tabata, T., Kokitsu, M., Okada, O., Nakayama, T., Yasumatsu, T. and Sakane, H., "Deterioration Mechanism of Cu/ZSM-5 as a Catalyst of Selective Reduction of NO<sub>x</sub> by Hydrocarbons from the Exhaust of Stationary Natural Gas-fueled Engine," *Catalyst Deactivation 1994*, Delmon, B. and Froment, G. F., eds, Elsevier, Amsterdam (1994).

Tabata, T., Ohtsuka, H., Okada, O., Sabatino, L. M. F. and Bellussi, G., "Selective Catalytic Reduction of NO<sub>x</sub> by Propane on Co-Loaded

Zeolites," *Micropor. Mesopor. Mat.*, **21**, 517 (1998).

Tanaka, T., Matsumoto, S., Muraki, H. and Kondo, S., "Catalyst for Purifying Exhaust Gas," JP 1130735 A (1989).

Teraoka, Y., Ogawa, H., Furukawa, H. and Kagawa, S., "Influence of Co-cations on Catalytic Activity of Copper Ion-Exchanged ZSM-5 Zeolite for Reduction of Nitric Oxide with Ethene in the Presence of Oxygen," *Catal. Lett.*, **12**, 361 (1992).

Torikai, Y., Yahiro, H., Mizuno, N. and Iwamoto, M., "Enhancement of Catalytic Activity of Alumina by Copper Addition for Selective Reduction of Nitrogen Monoxide by Ethene in Oxidizing Atmosphere," *Catal. Lett.*, **9**, 91 (1991).

Torre-Abreu, C., Ribeiro, M. F., Henriques, C. and Ribeiro, F. R., "Influence of Cocation on Catalytic Activity of CuMOR Catalysts for NO SCR by Propene. Effect of Water Presence," *Catal. Lett.*, **43**, 25 (1997).

Torre-Abreu, C., Ribeiro, M. F., Henriques, C., Ribeiro, F. R. and Delahay, G., "Deactivation of CuMFI Catalysts under NO Selective Catalytic Reduction by Propene: Influence of Zeolite Form, Si/Al Ratio and Copper Content," *Catal. Lett.*, **43**, 31 (1997).

Truex, T. J., Searles, R. A. and Sun, D. C., "Catalysts for Nitrogen Oxides Control under Lean Burn Conditions: The Opportunity for New Technology to Complement Platinum Group Metal Autocatalysts," *Platinum Metals Rev.*, **36**, 2 (1992).

Uchida, H., Yamaseki, K.-I. and Takahashi, I., "NO<sub>x</sub> Reduction with Methane over Mordenite Supported Palladium Catalyst," *Catal. Today*, **29**, 99 (1996).

Ueda, A., Oshima, T. and Haruta, M., "Reduction of Nitrogen Monoxide with Propene in the Presence of Oxygen and Moisture over Gold Supported on Metal Oxides," *Appl. Catal. B*, **12**, 81 (1997).

Wang, X., Zhang, T., Sun, X., Guan, W., Liang, D. and Lin, L., "Enhanced Activity of an In-Fe<sub>2</sub>O<sub>3</sub>/H-ZSM-5 Catalyst for NO Reduction with Methane," *Appl. Catal. B*, **24**, 169 (2000).

Wells, A. F., "Structural Inorganic Chemistry," 5th edn, Clarendon, Oxford (1984).

Witzel, F., Sill, G. A. and Hall, W. K., "Reaction Studies of the Selective Reduction of NO by Various Hydrocarbons," *J. Catal.*, **149**, 229 (1994).

Yogo, K., Ihara, M., Terasaki, I. and Kikuchi, E., "Gallium Ion-Exchanged Zeolite as a Selective Catalyst for Reduction of Nitric Oxide with Hydrocarbons under Oxygen-Rich Conditions," *Catal. Lett.*, **17**, 303 (1993).

Yogo, K., Ihara, M., Umeno, M., Terasaki, I., Watanabe, H. and Kikuchi, E., "Selective Reduction of NO by Methane on Zeolite Catalysts," *Shokubai*, **35**, 126 (1993).

Yogo, K., Umeno, M., Watanabe, H. and Kikuchi, E., "Selective Reduction of Nitric Oxide by Methane on H-Form Zeolite Catalysts in Oxygen-Rich Atmosphere," *Catal. Lett.*, **19**, 131 (1993).

Zhang, X., Walters, A. B. and Vannice, M. A., "Catalytic Reduction of NO by CH<sub>4</sub> over Li-Promoted MgO," *J. Catal.*, **146**, 568 (1994).