

Reactivity of Bio-sorbent Prepared by Waste Shells of Shellfish in Acid Gas Cleaning Reaction

Jong-Hyeon Jung, Young-Soo Lee*, Kyung-Seun Yoo*, Hyung-Keun Lee**,
Kwang-Joong Oh*** and Byung-Hyun Shon****,†

Department of Environmental Engineering, Sorabol College, 165 Chunghyo-dong, Kyungju, Kyungbuk 78-711, Korea

*Department of Environmental Engineering, Kwangwoon University, 447-1 Wolge-dong, Nowon-gu, Seoul 139-701, Korea

**Energy and Environmental Research Department, Korea Institute of Energy Research,
71-2 Jang-dong, Yuseong-gu, Daejeon 305-343, Korea

***Department of Environmental Engineering, Pusan National University,
30 Changjeon-dong, Kumjeong-gu, Busan 609-735, Korea

****Department of Environmental Engineering, Hanseo University, Haemi-myun, Seosan, Chungnam 356-820, Korea
(Received 23 December 2004 • accepted 1 April 2005)

Abstract—Acid gas cleaning activity of bio-adsorbent prepared by waste shell of different shellfish species was investigated in a fixed bed reactor to evaluate its feasibility as an acid gas cleaning agent. The physicochemical properties of prepared adsorbents were measured using ICP, BET, SEM-EDX and XRD. The results showed that active chemical species of bio-sorbent are comparable to that of commercial limestone and lime. SO_2/NO_x removal capacity of waste shell of shellfish was higher than that of commercial limestone due to the enhanced physical properties. In particular, the desulfurization activity of clam based adsorbent was the best among the tested waste shells because of both higher calcium content and more specific surface area. These lead to the conclusion that commercial limestone can be substituted for bio-sorbent prepared by waste shell of clam.

Key words: Waste Shell, Bio-Sorbent, DeSO_x , DeNO_x

INTRODUCTION

Recently, marine pollution by waste shellfish shells has become a serious problem for the mariculture industry in Korea. Annually, hundreds of thousand tons of waste oyster-shells are dumped into public waters and reclaimed lands, which causes a foul smell as a consequence of the decomposition of fresh remnants attached to shellfish shells [Yoon et al., 2003]. As a physical recycling process, studies on the application of waste oyster-shell to construction materials had been carried out, and physical properties and processing methods were reported. However, a large scale application as construction materials was limited due to a lower mechanical strength of oyster-shell.

Another method to recycle the waste shells of shellfish can be found in acid gas cleaning processes such as flue gas desulfurization systems which can be categorized into three groups, such as dry adsorption [Yoo et al., 1994; Garea et al., 2001], wet scrubbing [Ukawa et al., 1993; Chu et al., 1997], and wet/dry system [O'Dowd et al., 1994; Karlsson et al., 1983]. In spite of the differences in the processes, calcium based alkali sorbents are widely used to remove SO_2 . This is because calcium based sorbents have good reactivity toward acidic gases and lower cost compared to other sodium based alkali adsorbents such as sodium bicarbonate [Keener and Davis, 1984]. However, experimental results using waste shells of different shellfish species are scarce in literature.

The objective of this study is to evaluate the feasibility of waste

shells of different shellfish species as an acid gas cleaning agent.

MATERIALS AND METHODS

The waste shell of clams, oysters, mussels, and sea-shells from Tongyeong province around the South Sea of Korea were chosen as the main materials. Limestone from Danyang province, which is commercially used in flue gas desulfurization systems, was selected for the comparison of acid gas cleaning reactivity of waste shell. These materials were crushed twice by jaw crusher and ball mill, and then sieved to prepare a sample size of 48-60 Tyler meshes (0.295-0.25 mm). Calcinations of these calcium based sorbents were carried out at 800 °C in a Lindberg furnace under N_2 flow and then hydrated in a hydration reactor. Physicochemical properties of waste shell of shellfish were analyzed by ICP (ICPS-7500 Shimadzu, Japan), XRD (SIMENS, Deutsche), BET (Micromeritics Co., USA), and SEM (JEOL superprobe JSM-5400, Japan). ICP was applied to analyze the atomic properties of the materials. SEM was used to observe the micro-tissue of the surface of waste shells and surface area of the adsorbent was measured by BET technique after pretreating to remove vapor in vacuum and 180 °C for 2 hours. The crystal state of shell adsorbent and the products before and after reaction was assured by X-ray diffractometer under the condition of 30 kV and 20 mA. To evaluate the acid gas cleaning reactivity of the samples (Fig. 1), a fixed bed quartz reactor (0.025 m in diameter, 0.25 m in height) was placed in a hot air bath and the temperature was controlled by PID type controller with a precision of ± 1.0 °C. After the sample was put on the reactor and the temperature was stabilized in N_2 flow, reacting gas containing SO_2 and NO_x was injected into

†To whom correspondence should be addressed.

E-mail: bhshon@hanseo.ac.kr



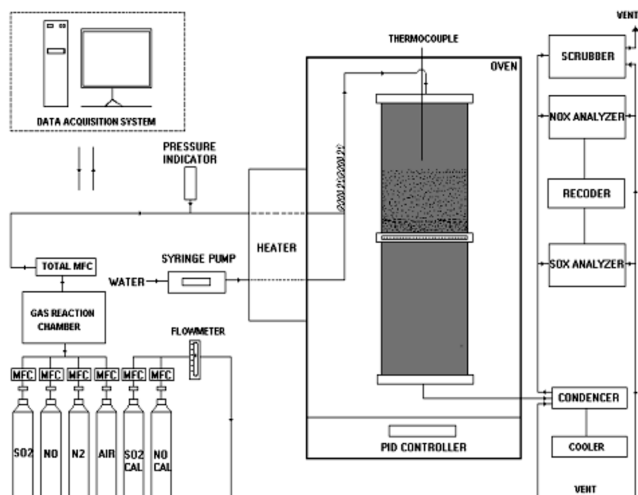


Fig. 1. Schematic diagram of packed-bed experimental apparatus.

the reactor by using mass flow controllers. The water was also injected into the reactor by Syringe pump to keep a steady H_2O concentration in the simulated gas. A hygrometer and SO_2/NO_x analyzer were used to measure the gas concentration, and signals from the measuring instrument were recorded at a personal computer with RS-232C interface.

Combining the following equation we can derive the overall reactivity of each absorbent with SO_2 and NO_x [Nakamura, 1995].



RESULTS AND DISCUSSION

Physical properties and chemical compositions of waste shells of shellfish are summarized in Table 1 along with the data of commercial limestone. The concentration of CaO of waste shell was around 53–54 wt%, which is comparable to that of commercial Danyang limestone, and was in good agreement with the results of Yoon et al. [2003] reporting the CaO content of oyster was about 53.7 wt%. MgO content of oyster and SiO_2 content of limestone are slightly higher than other samples. However, other compositions of the

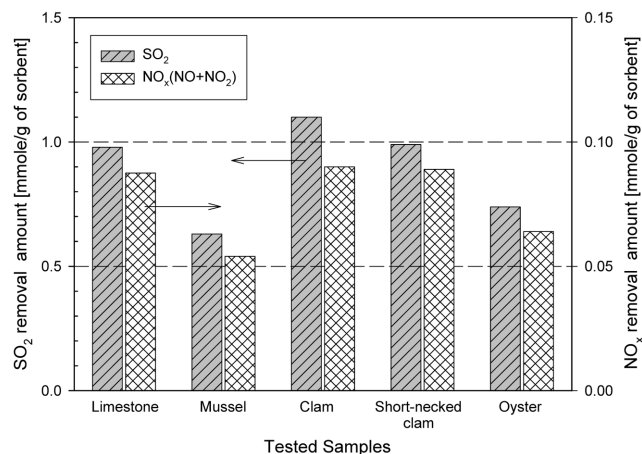


Fig. 2. SO_2/NO_x removal amount of tested adsorbents at reaction temperature of 150 °C.

tested samples were not largely different including ignition loss by CO_2 evolution. It should be also noted that the crystal phase of all the tested raw samples was identified to be calcite from the X-ray diffractometer analysis. Pore volume and specific surface area of treated samples showed similar values, except hard shelled mussel.

The reaction of samples prepared by waste shells and limestone was carried out in a fixed bed reactor; SO_2/NO_x removal capacity of the adsorbents was identified. As can be seen in Fig. 2, desulfurization capacity of the adsorbent was one order of magnitude higher than the denitrification capacity regardless of adsorbent species. This is because the Henry's Law constant and diffusion coefficient in the gas phase for SO_2 is much higher than those for NO [Yuan, 1990]. Waste shells of clam showed the highest value for SO_2/NO_x removal capacity among the tested adsorbents. It can be inferred that acid gas removal capacity of adsorbents was proportional to the specific surface area which was shown in Table 1.

Acid gas removal capacity of oyster shell was slightly lower even though the specific surface area is comparable to the short-necked clam or commercial limestone. The reason can be found in Fig. 3, which shows the SEM photographs of limestone, clam, and oyster. Fig. 3(A) and (C) showed fresh limestone and clam sample condition by SEM. Fig. 3(B) and (D) showed that the particles of treated limestone and clams were more increased in specific surface area than that of the fresh particles [Jung, 2000]. In addition, it appeared that the average pore diameter and pore volume of treated waste shells were much bigger than that of raw materials. This result indicates that the treating process can enhance the removal capacity of acid gases. As can be seen in Fig. 3(E) and (F), fresh oyster shell

Table 1. Physicochemical properties of tested adsorbents

	Chemical composition [wt%]						Pore volume [cc/g]	Surface area [m ² /g]
	SiO ₂	Al ₂ O ₃	Fe ₂ O ₃	CaO	MgO	Ignition loss		
Oyster	0.40	0.22	0.04	53.81	1.70	44.87	0.0869	12.98
Mussel	0.20	0.13	0.03	53.70	0.33	45.61	0.0129	6.51
Clam	0.46	0.20	0.04	53.92	0.22	45.16	0.1025	15.99
Short-necked clam	0.66	0.40	0.04	53.58	0.20	45.12	0.0888	12.83
Limestone	1.62	0.07	0.12	54.70	0.25	43.10	0.0697	11.98

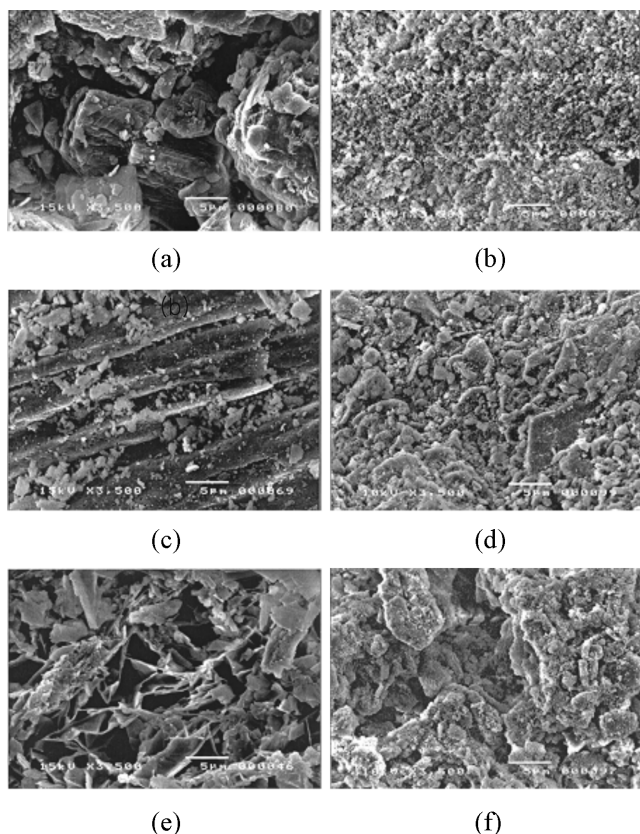


Fig. 3. SEM photographs of (a) fresh Danyang limestone, (b) treated Danyang limestone, (c) fresh clam, (d) treated clam, (e) fresh oyster, and (f) treated oyster.

shows a porous structure which makes it possible for a sintering of micro grain to occur. This leads to a lower sulfating activity of oyster adsorbent. Fig. 3 also shows the fine structure is well developed in both limestone and clam samples.

In conclusion, it is clearly indicated that waste clam shells can be used as acid gas cleaning agent to reduce air pollution problems. These results can be directly applied to industries and businesses which try to reduce their emissions of SO_2 and NO_x . The recycling of waste shells of shellfish helps the fishery and sea food industries worldwide that produce a large amount of waste shells.

ACKNOWLEDGMENTS

The present research has been conducted by the Research Grant

of Kwangwoon University in 2002.

REFERENCES

- Chu, K. J., Yoo, K. S. and Kim, K. T., "Characteristics of Gypsum Crystal Growth over Calcium-based Slurry in Desulfurization Reaction," *Materials Research Bulletin*, **32**(2), 197 (1997).
- Garea, A., Herrea, J. L., Marques, J. A. and Irabien, A., "Kinetics of Dry Flue Gas Desulfurization at Low Temperatures using $\text{Ca}(\text{OH})_2$: Competitive Reactions of Sulfation and Carbonation," *Chem. Eng. Sci.*, **56**(4), 1387 (2001).
- Jung, J. H., Shon, B. H., Yoo, K. S. and Oh, K. J., "Physicochemical Characteristics of Waste Sea Shell for Acid Gas Cleaning Absorbent," *Korean J. Chem. Eng.*, **17**, 585 (2000).
- Karlsson, H. T., Klingspore, J., Linne, M. and Bjerle, I., "Activated Wet-dry Scrubbing of SO_2 ," *J. of Air Pollution Control Association*, **33**(1), 23 (1983).
- Keener, T. C. and Davis, W. T., "Study of the Reaction of SO_2 with NaHCO_3 and Na_2CO_3 ," *J. of Air Pollution Control Association*, **34**(6), 651 (1984).
- Klingspor, J. S., "Improved Spray Dry Scrubbing through Grinding of FGD Recycle Material," *J. of Air Pollution Control Association*, **37**(7), 801 (1987).
- Nakamura, H., Ueno, T., Tatani, A. and Kotake, S., "Pilot-scale Test Results of Simultaneous SO_2 and NO_x Removal using Powdery form of LILAC Absorbent," *1995 SO_2 Control Symposium*, March, Florida, U.S.A. (1995).
- O'Dowd, W. J., Markussen, J. M., Pennline, H. W. and Resnik, K. P., "Characterization of NO_2 and SO_2 Removals in a Spray Dryer/Bag-house System," *Ind. Eng. Chem. Res.*, **33**, 2749 (1994).
- Ukawa, N., Takashina, T., Oshima, M. and Oishi, T., "Effects of Salts on Limestone Dissolution Rate in Wet Limestone Flue Gas Desulfurization," *Environ. Prog.*, **12**(4), 294 (1993).
- Yoo, K. S., Kim, S. D. and Park, S. B., "Sulfation of Al_2O_3 Support in a Flue Gas Desulfurization by $\text{CuO}/\gamma\text{-Al}_2\text{O}_3$ Sorbent," *Ind. Eng. Chem. Res.*, **33**(7), 1786 (1994).
- Yoon, G. L., Kim, B. T., Kim, B. O. and Han, S. H., "Chemical-Mechanical Characteristics of Crushed Oyster-shell," *Waste Management* **23**, available online(<http://www.sciencedirect.com>), 2003.
- Yuan, C. S., "Simultaneous Collection of SO_2 and NO_x via Spray Drying: Using Sodium-based and Calcium-based Sorbents with Select Additives," Ph.D. Dissertation, Illinois Univ., U.S.A. (1990).