

Enhanced cyclic stability of CO₂ adsorption capacity of CaO-based sorbents using La₂O₃ or Ca₁₂Al₁₄O₃₃ as additives

Cong Luo, Ying Zheng[†], Ning Ding, and Chuguang Zheng

State Key Laboratory of Coal Combustion, Department of Energy and Power Engineering,
Huazhong University of Science and Technology, Wuhan 430074, China

(Received 13 April 2010 • accepted 27 October 2010)

Abstract—To improve the stability of CaO adsorption capacity for CO₂ capture during multiple carbonation/calcination cycles, modified CaO-based sorbents were synthesized by sol-gel-combustion-synthesis (SGCS) method and wet physical mixing method, respectively, to overcome the problem of loss-in-capacity of CaO-based sorbents. The cyclic CaO adsorption capacity of the sorbents as well as the effect of the addition of La₂O₃ or Ca₁₂Al₁₄O₃₃ was investigated in a fixed-bed reactor. The transient phase change and microstructure were characterized by X-ray diffraction (XRD) and field emission scanning electron microscopy (FSEM), respectively. The experimental results indicate that La₂O₃ played an active role in the carbonation/calcination reactions. When the sorbents were made by wet physical mixing method, CaO/Ca₁₂Al₁₄O₃₃ was much better than CaO/La₂O₃ in cyclic CO₂ capture performance. When the sorbents were made by SGCS method, the synthetic CaO/La₂O₃ sorbent provided the best performance of a carbonation conversion of up to 93% and an adsorption capacity of up to 0.58 g-CO₂/g-sorbent after 11 cycles.

Key words: CO₂ Capture, CaO, Adsorption Capacity, Carbonation/Calcination Cycles, Sol-gel-combustion-synthesis (SGCS)

INTRODUCTION

It is now widely acknowledged that the combustion of fossil fuels contributes to the emission of CO₂ in the atmosphere, which in turn contributes to the greenhouse effect. One potential approach is the capture of CO₂ from flue gas followed by its sequestration in geological formations or perhaps ocean storage [1-4]. The purpose of CO₂ capture is to produce a concentrated stream of CO₂ suitable for compression and piping to a storage site. But the flue gas stream contains low concentrations of CO₂, so it is necessary to produce a nearly pure CO₂ stream suitable for sequestration. The post-combustion CaO-based high temperature carbonation/calcination cycle method [5] and chemical looping combustion method [6,7] have recently been identified to be two of the best candidates for future R&D as an emerging concept in carbon capture by the Technology Task Force of the European Technology Platform for Zero Emission Power Plants. The former method can be applied by using the existing technologies, because many of the components in these systems are commercially available [8,9]. The carbonation of CaO is a reversible reaction:



This reversible reaction (reaction 1) has the potential to be used in a clean, economically feasible CO₂ separation process under moderate conditions, for generation of electricity. Unfortunately, it is widely accepted that the adsorption capacity of the CaO-based sorbents decays through long-term capture and release cycles [10-12]. The carbonation conversion of natural limestone decreases quite quickly to about 20% after 10 cycles [13]. This problem, an indication of poor

reversibility of the carbonation/calcination cycles of CaO/CaCO₃, is a major challenge for the future application of CaO-based technology for capturing CO₂ and needs to be solved. Therefore, it is necessary to improve the reversibility of the CaO-based sorbents for extended operation cycles.

Some researchers focused on increasing the porosity and surface area of the CaO-based sorbents to overcome the loss-in-capacity problem after multiple carbonation/calcination cycles. Hughes et al. [14] increased the pore volume and pore surface area of limestone by a process of steam hydration conducted at 150 °C and 475 kPa. They found that the steam hydration/activation method can improve the long-term performance of the CaO-based sorbents. A CaO conversion of this sorbent was 52% when the cyclic adsorption was tested at 750 °C after 20 cycles. Gupta et al. [15] synthesized high surface area CaO sorbents from precipitated calcium carbonate. They suggested that a mesoporous structure with porosity in the 5-20 nm pore size range will be less susceptible to pore blockage, thus providing higher CO₂ capture capacity and better stability. When the CaO derived from the precipitated calcium carbonate was subjected to an adsorption test at 700 °C, the CaO conversion of this sorbent was up to 95% after two cycles.

Other researchers designed synthetic sorbents to enhance the cyclic performance of CaO-based sorbents. Various materials were added into CaO to improve the adsorption capacity or cyclic stability of CaO-based sorbents for reversible carbonation/calcination reactions. Li et al [16] investigated the effect of adding an inert phase of Ca₁₂Al₁₄O₃₃ into CaO. They showed that a weight ratio of CaO to Ca₁₂Al₁₄O₃₃ of 75 : 25 that is subjected to calcination at 900 °C for 1.5 h is optimal for preparing this sorbent. A CaO conversion of this sorbent was 65% after 50 cycles, when it was carbonated at 650 °C. Albrecht et al. [17] suggested that incorporating finely dispersed MgO or La₂O₃ in the CaO-based sorbent can reduce the rate of the decline

[†]To whom correspondence should be addressed.
E-mail: zhengying@mail.hust.edu.cn

of CaO activity during high temperature reactions. They also found that the sorbents subjected to the more severe initial calcination conditions can have higher adsorption capacity after many cycles. Liu et al. [18,19] proposed the performance of CaO sorbents derived from different precursors in the latest researches. The best performing CaO-based sorbents were obtained from D-gluconic acid. They also found that a simple wet mixing method can produce sintering-resistant sorbents from calcium and magnesium salts of D-gluconic acid.

In this paper, a few novel CaO-based sorbents were synthesized from inorganic calcium and aluminum (or lanthanum) salts as precursors. These modified sorbents were prepared by wet physical mixing method and sol-gel-combustion-synthesis (SGCS) method, respectively. The cyclic carbonation/calcination performance of these sorbents was investigated in a fixed bed reactor system. The objective of this work was to find a suitable method for each synthetic CaO-based sorbent without the problem of loss-in-capacity after many carbonation/calcination cycles.

EXPERIMENTAL SECTION

1. Preparation of the Wet Physical Mixing Method

All of the precursors used in this study were analytical grade. In this method, predetermined amounts of La(NO₃)₃·6H₂O (or Al(NO₃)₃·9H₂O) and the powdered pure CaCO₃ were added into distilled water with the weight ratio of CaO to La₂O₃ (or Ca₁₂Al₁₄O₃₃) of 80 : 20. This solution was then stirred for 15 h at room temperature and subsequently dried at 120 °C for another 5 h in a drying oven before it was calcined at 850 °C for 2 h in a muffle furnace.

2. Preparation of the Sol-gel-combustion-synthesis (SGCS) Method

In this method (Fig. 1), first, predetermined amounts of La(NO₃)₃·6H₂O (or Al(NO₃)₃·9H₂O) and Ca(NO₃)₂·4H₂O were added into distilled water with the weight ratio of CaO to La₂O₃ (or Ca₁₂Al₁₄O₃₃) of 80 : 20 and the mole ratio of water to metal ions of about 40 : 1. Then the citric acid was added into the solution at a ratio, citric acid to metal ions, of 1 : 1 at room temperature. Second, the mixture was continuously stirred and kept at 80 °C in an electric-heated thermostatic water bath for a sufficient period of 7 h to allow a well-dispersed sol to be formed. Third, the sol was placed at room temperature for 18 h to form a wet gel. The wet gel was then put into a drying oven at 80 °C for 5 h and subsequently dried at 110 °C for another 12 h until the dry gel was formed. Finally, the dry gel was put into a muffle furnace quickly at 600 °C to get it burnt out before it was calcined at 850 °C for 2 h in the muffle furnace.

3. Experimental System

Multi-cyclic CO₂ capture was tested in a fixed bed, which focused on the weight changes of the carbonation/calcination reactions. The

variation of sample mass was measured by a delicate electronic balance. All carbonation reactions were carried out at 850 °C in 100% CO₂, while calcination reactions were at 850 °C in 100% N₂ at atmospheric pressure so as to be consistent with the research of Manovic and Anthony [10]. The gas flow rate was 2 L/min, and the time for carbonation and calcination was 30 and 10 min, respectively. A three-way valve was used to switch between pure N₂ and pure CO₂. The microstructure of the samples was investigated by field emission scanning electron microscopy (FSEM, SIRION200, FEI Inc) with 20 kV of accelerating voltage under high vacuum. The phase composition of samples was determined by X-ray diffraction (XRD, X'Pert PRO, PANalytical B.V.) with Cu K α radiation, $\lambda=0.1542$ nm in the 2 θ range of 15°-85° with a scanning step of 0.02°.

4. Experimental Data Analysis Method

The carbonation conversion (X_n) and the adsorption capacity (C_n) were calculated using the equations as follows.

$$X_n = \frac{m_n - m_0}{m_0 \cdot b} \cdot \frac{W_{CaO}}{W_{CO_2}} \quad (2)$$

$$C_n = \frac{m_n - m_0}{m_0} \quad (3)$$

Where m_n is mass of the carbonated sample after n cycle(s), m₀ is mass of the calcined initial sample, b is content of CaO in the initial calcined sample. W_{CaO} and W_{CO₂} are mole mass of CaO and CO₂, respectively. As a result, X_n reflects only the reversibility of CaO in the sorbent, while C_n reflects the overall performance of sorbent.

RESULTS AND DISCUSSION

1. Performance of the Wet Physical Mixing Method

As the previous studies [16-21] indicated that modified sorbents often show slower decay in the initial calcium looping cycles, the carbonation conversions of the novel modified sorbents using either La₂O₃ or Ca₁₂Al₁₄O₃₃ as ‘inert’ material are higher than those of the pure CaCO₃ sorbent with number of cycles (Fig. 2(a)). The main reason is that the inert material usually acts as a physical barrier to prevent the sintering and aggregation of small CaCO₃ grains. It is also shown from Fig. 2(a) that CaO/Ca₁₂Al₁₄O₃₃ is much better than CaO/La₂O₃ and pure CaO on cyclic CO₂ capture. Li et al. [16] pointed out previously that when calcination temperatures in the preparation stage are in the range of 800-1,000 °C, the inert intermediate phase of Ca₁₂Al₁₄O₃₃ is formed from calcium and aluminum precursors and it can enhance the adsorption capacity for CaO based sorbent during cyclic reactions. After 11 cycles, the carbonation conversion of CaO/La₂O₃ sorbent is 36% and the carbonation conversion of pure CaO sorbent is 24%, while CaO/Ca₁₂Al₁₄O₃₃ sorbent provides the highest carbonation conversion of 52%. However, there is little difference in adsorption capacity between CaO/La₂O₃ sorbent and pure CaCO₃ sorbent after 11 cycles from Fig. 2(b). Therefore, this simple wet physical mixing method should be suitable for the synthetic CaO/Ca₁₂Al₁₄O₃₃ sorbent but not for the CaO/La₂O₃ sorbent.

2. Performance of the SGCS Method

When the sorbents were prepared by SGCS Method, changes had come to CaO/La₂O₃ sorbent. The results in Fig. 3 clearly show

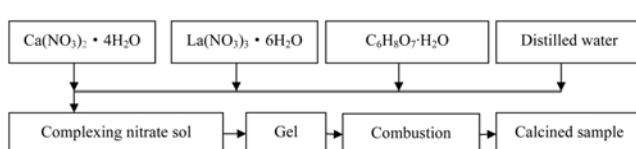


Fig. 1. The main technological process of sol-gel-combustion-synthesis (SGCS) method.

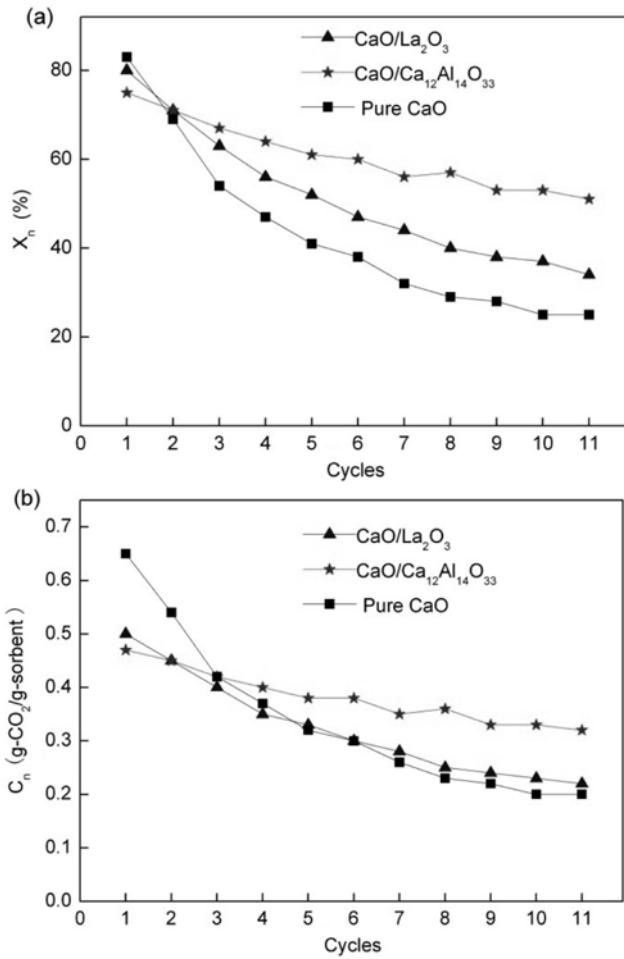


Fig. 2. The performance of the sorbents made by wet physical mixing method compared with pure CaCO₃. (a) Carbonation conversion; (b) adsorption capacity.

that the adsorption capacity of the two modified sorbents can be improved to be a satisfactorily high level through the SGCS method, especially using La₂O₃ as additive. In the severe carbonation condition of 850 °C in 100% CO₂, Fig. 3(a) shows that the carbonation conversions of the CaO/La₂O₃ (SGCS) sorbent are about 95% within 11 cycles, which is much higher than those of the CaO/Ca₁₂Al₁₄O₃₃ (SGCS) sorbent. Fig. 3(b) shows that the novel CaO/La₂O₃ (SGCS) sorbent is able to achieve high adsorption capacities during carbonation/calcination reactions. Its CaO adsorption capacity is up to 0.58 g-CO₂/g-sorbent after 11 cycles, almost the same as after the first cycle (0.60 g-CO₂/g-sorbent). As a result, when the synthetic sorbents were made by the SGCS method, the CaO/La₂O₃ (SGCS) sorbent had a perfect performance in improving the stability of CO₂ adsorption capacity during carbonation/calcination cycles.

3. Discussion

Li et al. [16] pointed out that during the cyclic carbonation/calcination of CaO/Ca₁₂Al₁₄O₃₃, the Ca₁₂Al₁₄O₃₃ binder does not take part in the reaction and may be considered as inert. However, unlike the Ca₁₂Al₁₄O₃₃, La₂O₃ cannot be considered as inert for the conditions used in the present investigation. Shirsat et al. [22] reported thermo-chemistry in the decomposition of La₂O₂CO₃. The decomposition reaction can be written as follows:

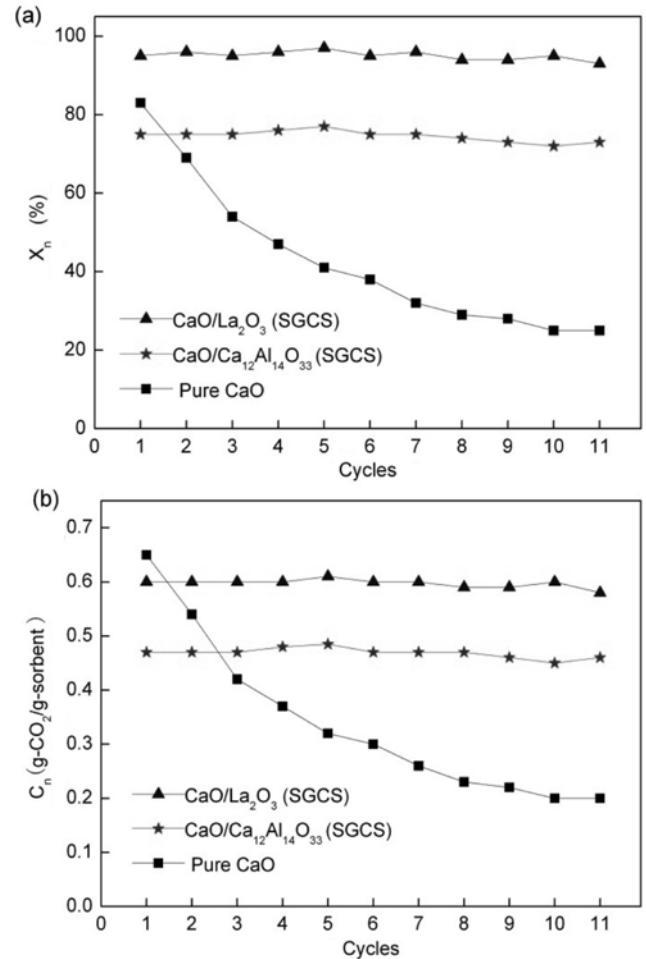


Fig. 3. The performance of the sorbents made by SGCS method compared with pure CaCO₃. (a) carbonation conversion; (b) adsorption capacity.



And the equilibrium pressure of CO₂ can be measured by the given equation as follows:

$$\ln p_{\text{CO}_2}(\text{pa}) (\pm 0.22) = -17502.2/T + 25.87 \quad (773 \leq T(\text{K}) \leq 1190) \quad (5)$$

From the above equation, when the temperature is 850 °C (1,124 K), the equilibrium pressure of CO₂ is 29,000 pa. As a result, in the process of carbonation of 100% CO₂ under 1 atm, La₂O₃ adsorbs CO₂ to form the La₂O₂CO₃, while in the process of calcination of 100% N₂ under 1 atm, La₂O₂CO₃ decomposes into La₂O₃ again.




When the sorbents were made by wet physical mixing method in our research, La₂O₃ was only mixed on the surface of CaO physically. However, Al₂O₃ was not only physically mixed with CaO, but also had a chemical reaction with CaO as follows:



As a result, Ca₁₂Al₁₄O₃₃ could have a much more well-distributed mixing than La₂O₃ within the CaO-based sorbents. Although both the addition of La₂O₃ and Ca₁₂Al₁₄O₃₃ could delay the sintering of CaO particles to give the CaO-based sorbent higher carbonation conversions during cyclic CO₂ capture, the CaO/Ca₁₂Al₁₄O₃₃ sorbent

was much better than the CaO/La₂O₃ sorbent in cyclic CO₂ capture performance by this simple method shown in Fig. 2.

However, since the sorbents were made by the SGCS method, the calcination of metal nitrates consisted of many physical processes and chemical reactions. In the process of the preparation, after the gel of nitrate and citric acid was ignited, metal nitrates acted as agent of oxidation while citric acted as fuel:



Reactions (7), (8) and (9) released a large amount of gas and heat, leading to the combustion of the dry gel. The particles of the product could be well-dispersed and sintered in the microstructure. Finally, even ultrafine nano-powders were produced. The well-dispersed additives in CaO particles could prevent small CaO particles from agglomeration effectively during high temperature carbonation/cal-

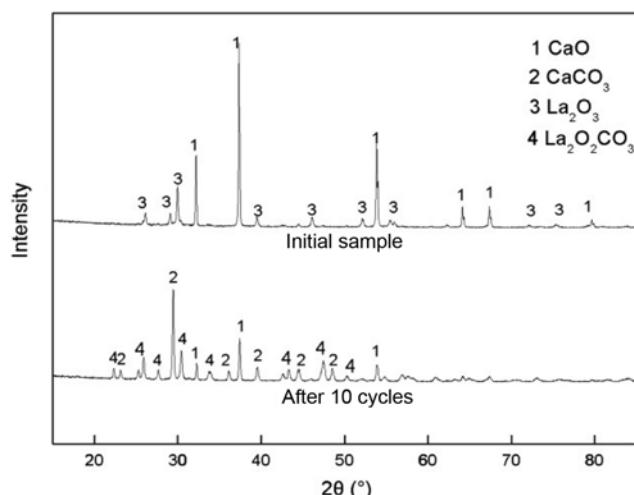


Fig. 4. XRD of the CaO/La₂O₃ (SGCS) sorbent.

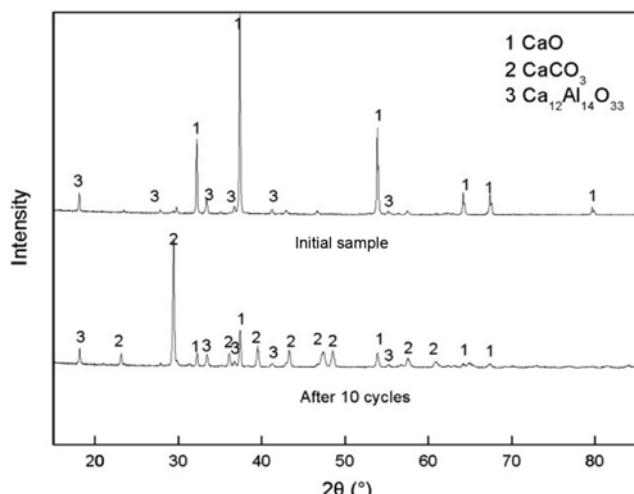


Fig. 5. XRD of the CaO/Ca₁₂Al₁₄O₃₃ (SGCS) sorbent.

cination reactions; thus the adsorption capacity of the synthetic CaO-based sorbents could be highly improved by this method.

In the case of CaO/La₂O₃ (SGCS) sorbent, XRD analysis of this sorbent shown in Fig. 4 indicates that the initial calcined sample

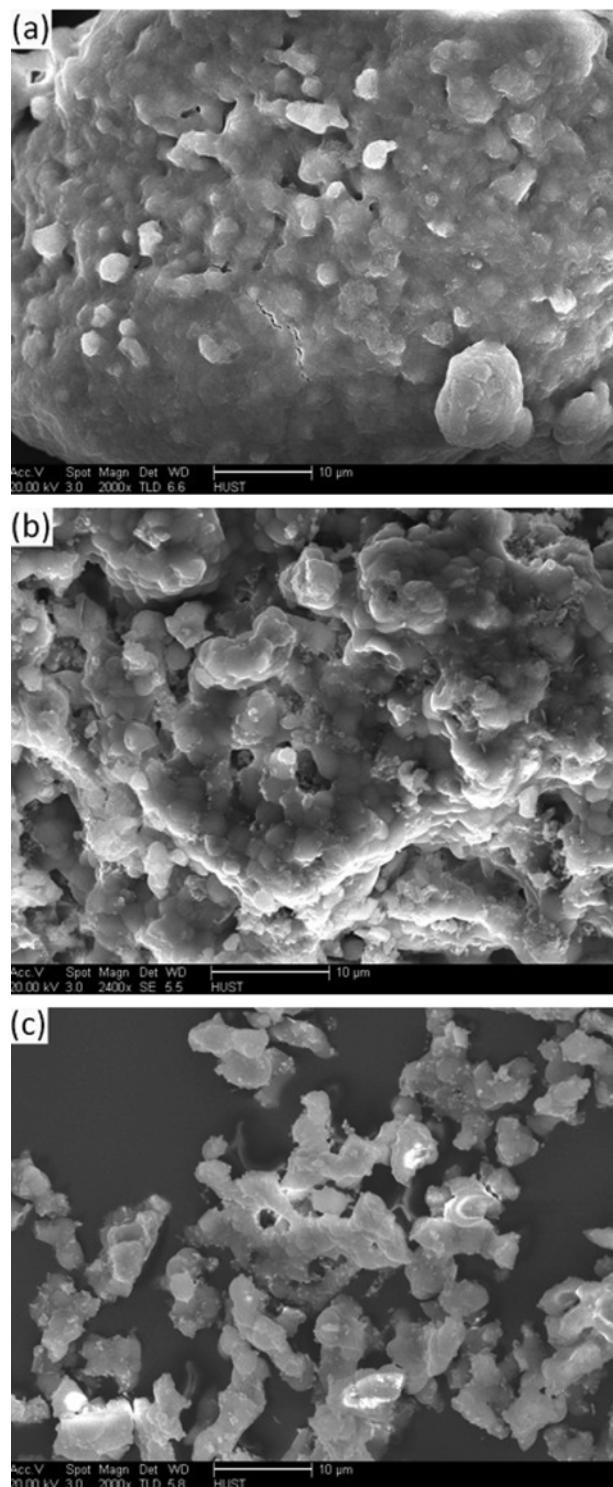


Fig. 6. FSEM photos of the sorbents made by SGCS method compared with pure CaCO₃. (a) pure CaCO₃ after 7 carbonation/calcination cycles; (b) CaO/Ca₁₂Al₁₄O₃₃ (SGCS) sorbent after 11 carbonation/calcination cycles; (c) CaO/La₂O₃ (SGCS) sorbent after 11 carbonation/calcination cycles.

exists only in two main materials: CaO and La₂O₃. After 10 cycles, this sample also exists only in two main materials: CaCO₃ and La₂O₂CO₃. But in the case of CaO/Ca₁₂Al₁₄O₃₃ (SGCS) sorbent, Al₂O₃ reacted with CaO into a stable framework of Ca₁₂Al₁₄O₃₃. XRD analysis of this sorbent shown in Fig. 5 indicates that the Ca₁₂Al₁₄O₃₃ binder does not take part in the cyclic reactions. This is the difference between the addition of La₂O₃ and Ca₁₂Al₁₄O₃₃, which results in the different performance in the cyclic CO₂ capture. Therefore, La₂O₃, acts as CO₂ transferor, which makes CO₂ molecules go through the CaCO₃ product layer much easier during carbonation process, and has a superior performance than Ca₁₂Al₁₄O₃₃ for CaO-based sorbents theoretically when both of them are prepared into ultrafine well-dispersed powders.

Fig. 6 shows the microstructure of the modified sorbents and the pure CaCO₃ sorbent after many carbonation/calcination cycles. There are little visible pores on the surface of the pure CaCO₃ sorbent due to severe sintering after seven carbonation/calcination cycles in Fig. 6(a). The blockage and collapse of pores of the CaCO₃ increases the hindrance to the passage of CO₂ during the carbonation process. As a result, the CaO adsorption capacity of the pure CaCO₃ drops sharply with the number of cycles. The surface of the modified sorbents made by SGCS method seems porous in Fig. 6(b), expansive and loose in Fig. 6(c). It can be found that the conglomeration of CaO particles does not occur after 11 carbonation/calcination cycles within the modified sorbents. This structure is beneficial to the CO₂ diffusion within the sorbents.

CONCLUSIONS

Modified CaO-based sorbents using La₂O₃ or Ca₁₂Al₁₄O₃₃ as additives are synthesized by SGCS method and wet physical mixing method in the present work. Unlike Ca₁₂Al₁₄O₃₃, La₂O₃ is not a completely inert material without the ability of adsorbing CO₂. But when the sorbents are made by wet physical mixing method, Ca₁₂Al₁₄O₃₃ can have a much more well-distributed mixing than La₂O₃ in CaO particles; thus CaO/Ca₁₂Al₁₄O₃₃ sorbent provides a relatively higher CO₂ adsorption capacity after multiple carbonation/calcination cycles.

However, when the sorbents are made by SGCS method, the particles of the product can be well-dispersed and sintered in the microstructure, which subsequently can prevent small CaO particles from agglomeration effectively. Moreover, not only can La₂O₃ retard the sintering of CaO particles but also adsorb CO₂ in the carbonation process. Therefore, La₂O₃, acts as CO₂ transferor, which makes CO₂ molecules go through the CaCO₃ product layer much more easily during the carbonation process, and has a superior performance than Ca₁₂Al₁₄O₃₃ theoretically for CaO-based sorbents when both of them are prepared into even ultrafine powders. The synthetic CaO/La₂O₃ (SGCS made) sorbent provides the best performance of a carbonation conversion of up to 93% and an adsorption capacity of up to 0.58 g-CO₂/g-sorbent after 11 cycles.

ACKNOWLEDGEMENTS

This work is supported by the National Basic Research Program of China (No. 2011CB707301), the National Natural Science Foundation of China (No. 50936001, 51021065), and Analytical and Testing Center of HUST for XRD and FSEM measurements.

REFERENCES

1. S. Bachu, *Prog. Energy Combust.*, **34**, 254 (2008).
2. Y. Seo, S. H. Jo, H. J. Ryu, D. H. Bae, C. K. Ryu and C. K. Yi, *Korean J. Chem. Eng.*, **24**, 457 (2007).
3. W. J. Choi, J. B. Seo, S. W. Cho, S. W. Park and K. J. Oh, *Korean J. Chem. Eng.*, **26**, 705 (2009).
4. B. Khoshandam, R. V. Kumar and L. Allahgholi, *Korean J. Chem. Eng.*, **27**, 766 (2010).
5. J. Blamey, E. J. Anthony, J. Wang and P. S. Fennell, *Prog. Energy Combust.*, **36**, 260 (2010).
6. H. J. Ryu, D. Shun, D. H. Bae and M. H. Park, *Korean J. Chem. Eng.*, **26**, 523 (2009).
7. Q. L. Song, R. Xiao, Z. Y. Deng, L. H. Shen and M. Y. Zhang, *Korean J. Chem. Eng.*, **26**, 592 (2009).
8. F. Fan, Z. S. Li and N. S. Cai, *Korean J. Chem. Eng.*, **26**, 1414 (2009).
9. H. J. Ryu, Y. C. Park, S. H. Jo and M. H. Park, *Korean J. Chem. Eng.*, **25**, 1178 (2008).
10. V. Manovic and E. J. Anthony, *Ind. Eng. Chem. Res.*, **48**, 8906 (2009).
11. V. Manovic and E. J. Anthony, *Ind. Eng. Chem. Res.*, **49**, 6916 (2010).
12. B. Feng, W.-q. Liu, X. Li and H. An, *Energy Fuels*, **20**, 2417 (2006).
13. J. C. Abanades and D. Alvarez, *Energy Fuels*, **17**, 308 (2003).
14. R. W. Hughes, D. Lu, E. J. Anthony and Y. Wu, *Ind. Eng. Chem. Res.*, **43**, 5529 (2004).
15. H. Gupta and L.-S. Fan, *Ind. Eng. Chem. Res.*, **41**, 4035 (2002).
16. Z.-S. Li, N.-S. Cai and Y.-Y. Huang, *Ind. Eng. Chem. Res.*, **45**, 1911 (2006).
17. K. O. Albrecht, K. S. Wagenbach, J. A. Satrio, B. H. Shanks and T. D. Wheelock, *Ind. Eng. Chem. Res.*, **47**, 7841 (2008).
18. W. Liu, B. Feng, Y. Wu, G. Wang, J. Barry and D. Costa, *Environ. Sci. Technol.*, **44**, 3093 (2010).
19. W. Liu, N. W. Low, B. Fen, G. Wang and D. Costa, *Environ. Sci. Technol.*, **44**, 841 (2010).
20. C. Luo, Y. Zheng, N. Ding, Q. Wu, G. Bian and C. Zheng, *Ind. Eng. Chem. Res.*, **49**, 11778 (2010).
21. L. Li, D. L. King, Z. Nie and C. Howard, *Ind. Eng. Chem. Res.*, **48**, 10604 (2009).
22. A. N. Shirsat, M. Ali, K. N. G. Kaimal, S. R. Bharadwaj and D. Das, *Thermochim. Acta*, **399**, 167 (2003).