

## METHANOL DECOMPOSITION OVER SUPPORTED PALLADIUM AND PLATINUM

Chung Lee, Hyung-Kee Yoon\*, Seung-Hyun Moon\* and Ki June Yoon<sup>†</sup>

Department of Chemical Engineering, Sung Kyun Kwan University, Suwon 440-746, Korea

\*District Heating and Cooling Lab., Korea Institute of Energy Research, Taejon 305-343, Korea

(Received 22 December 1997 • accepted 15 June 1998)

**Abstract** – Methanol decomposition over supported Pt and Pd catalysts was investigated in the temperature range from 453 to 573 K with the partial pressure of methanol up to 0.8 atm. The specific activity of Pd was higher than that of Pt, and alumina-supported Pd was more active than silica-supported Pd, although alumina-supported catalysts produced dimethyl ether as a by-product. A silica-supported Pd catalyst prepared from a tetraamine salt solution with a proper pH exhibited higher activity than the other silica-supported Pd catalysts. Dependence of the decomposition rate on the partial pressure of methanol was similar regardless of the metal, the support or the preparation method. The apparent reaction orders were near 0.3 at low pressures below about 0.4 atm and became near zero or slightly negative at higher pressures. The apparent activation energies were about the same for most of the catalysts and were in the range from 66 to 77 kJ/g-mol.

Key words : Methanol Decomposition, Palladium, Platinum, Supported, Kinetics

### INTRODUCTION

Decomposition of methanol to hydrogen and carbon monoxide, an endothermic reaction, can be utilized in a chemical heat pump system which absorbs low-temperature waste heat and then releases heat at a higher temperature by the reverse reaction. It has also been proposed that the methanol decomposition on board may be applied to automobiles since injection of the gaseous products into the engine provides higher thermal efficiency and less corrosion and pollution problems when compared with direct injection of liquid methanol [Takishita et al., 1985; Cheng and Kung, 1994]. Some other applications of dissociated methanol are considered for supplying hydrogen for fuel cells, supplemental gas turbine fuel at peak demand of electricity, fuel and cooling systems for hypersonic jets, and source of carbon monoxide and hydrogen for chemical processes [Cheng and Kung, 1994]. The catalysts for these applications are required to have high activity and selectivity especially at low temperatures.

Copper, nickel and noble metals are known to be effective for methanol decomposition. Below 573 K, copper and copper-based catalysts exhibit relatively low activity and produce significant amounts of formaldehyde and methyl formate along with hydrogen and carbon monoxide [Miyazaki and Yasumori, 1967; Cant et al., 1985; Madhusudhan Rao and Shankar, 1988; Idem and Bakhshi, 1994; Lee and Bell, 1996]. Nickel and noble metals are more active than copper and do not produce formaldehyde or methyl formate, but over these metals a small amount of methane is produced as a by-product by the methanation reaction [Yasumori et al., 1967; Bare et al., 1985;

Takishita et al., 1985; Hahm et al., 1989; Shimizu and Takeoka, 1989; Park et al., 1992; Lee et al., 1993; Yoon et al., 1993; Kim and Yoon, 1996]. Among these metals Pd and Pt seem to be more active and produce smaller amounts of methane than the others [Joo et al., 1991]. However, kinetic parameters such as reaction orders and activation energies over Pd and Pt have rarely been reported. In particular, studies on the dependence of methanol partial pressure above 0.15 atm are scarce [Yoon et al., 1993; Kim and Yoon 1996].

In this work, the activities and selectivities of an alumina-supported Pt catalyst and alumina- and silica-supported Pd catalysts were compared for the decomposition of methanol. The activation energies and reaction orders were determined in the temperature range from 453 to 573 K and in the methanol partial pressure range from about 0.05 to 0.8 atm.

### EXPERIMENTAL

#### 1. Chemicals and Catalyst Preparation

Silica (Oriental Chemical Industries, Type B granules, pore volume 0.65 cm<sup>3</sup>/g) and  $\gamma$ -alumina (Strem Chemicals 13-2,550, cylindrical pellet, pore volume 0.365 cm<sup>3</sup>/g) were used as the supports. The silica granules were crushed and particles of -18/+40 mesh size were selected and then heat-treated at 1,073 K for 3 h to increase the strength and thermal stability. The alumina pellets were crushed and particles of -18/+80 mesh size were selected and then dried at 673 K for 1 h before use.

The precursor of Pt was chloroplatinic acid (Aldrich, assay 40 % Pt). The precursors of Pd were palladium chloride (Inuishi Precious Metals, assay 60 % Pd) and tetraamine palladium chloride hydrate (Aldrich, assay 39.5 % Pd). The catalysts were prepared by employing the incipient wetness method (dry impregnation). The chloroplatinic acid was dissolved in distilled

<sup>†</sup>To whom all correspondence should be addressed.  
E-mail : kijyoon@yurim.skku.ac.kr

water and the palladium chloride was dissolved in 1 N HCl solution. The tetraamine palladium chloride was dissolved in aqueous ammonia solutions whose pH's were adjusted to 8.1, 10.0, 11.4 and 12.2, respectively. The pH adjustment was done in order to see if it would affect the percentage exposed or the catalytic activity [Benesi et al., 1968]. After the impregnation, the catalysts were calcined in air at 773 K for 4 h. The metal contents were all 2 wt% nominal. The catalysts were designated as  $\text{Pt}/\text{Al}_2\text{O}_3$ ,  $\text{Pd}/\text{Al}_2\text{O}_3$  and  $\text{Pd}/\text{SiO}_2(\text{a})$  for the catalysts prepared from the chloride salts, and as  $\text{Pd}/\text{SiO}_2(\text{b})$  for the catalysts prepared from the amine salt, where b indicates the pH of the solution.

## 2. Reaction and Chemisorption Experiments

The reaction was carried out under ambient pressure in a conventional tubular microreactor made of 1/4 inch stainless steel tubing. Liquid methanol (Matsunoen Chemicals, 99.6+%) was fed by a syringe pump (Keun-A Mechatronics, KASP 005/150 MT) to an evaporator which was filled with glass beads and heated by a heating band and then to the reactor. Hydrogen for the activation of the catalyst and nitrogen for the adjustment of the partial pressure of methanol were fed through the mass flow controllers. The lines were heated to around 333 K by a heating wire to prevent condensation of methanol.

The reactor was normally loaded with about 200 mg of the catalyst. In some cases when the activity was very high, the loaded catalyst was reduced to 40 mg and mixed with 160 mg of the support. The catalyst was activated with flowing hydrogen at 473 K for 1 h and then the reaction experiments were done with a total gas flow rate of 50-100  $\text{cm}^3/\text{min}$  (GHSV = 15000-30000  $\text{cm}^3/\text{g} \cdot \text{h}$ ). The partial pressure of methanol in the feed ranged from 0.05 to 0.8 atm. The effluent gas was analyzed with two gas chromatographs, one equipped with a Chromosorb 102 column (Alltech) using He as the carrier gas for the analysis of methane, carbon dioxide, methanol and dimethyl ether and the other with a Carbosieve S-II column using Ar as the carrier gas for the analysis of hydrogen, carbon monoxide, methane and carbon dioxide.

The hydrogen chemisorption experiments were carried out in a conventional glass adsorption apparatus by following the conventional procedure. The catalyst activation procedure was the same as described above. For the Pt catalyst, the adsorption experiment was carried out at room temperature. For the Pd catalysts, the adsorption experiment was carried out at 373 K to avoid the formation of  $\beta$  hydride of palladium [Benson et al., 1973].

Table 1. Results of hydrogen chemisorption

Catalyst	Metal precursor	$\text{H}_2$ Chem. ( $\mu\text{mol/g-cat.}$ )	Active surface area ( $\text{m}^2/\text{g-cat.}$ )	% exposed
$\text{Pt}/\text{Al}_2\text{O}_3$	$\text{H}_2\text{PtCl}_6$	54.4	5.24	100
$\text{Pd}/\text{Al}_2\text{O}_3$	$\text{PdCl}_2$	35.8	3.39	38.1
$\text{Pd}/\text{SiO}_2(\text{a})$	$\text{PdCl}_2$	14.6	1.38	15.5
$\text{Pd}/\text{SiO}_2(8.1)^a$	$(\text{NH}_3)_4\text{PdCl}_2$	10.9	1.04	11.6
$\text{Pd}/\text{SiO}_2(10.0)^a$	$(\text{NH}_3)_4\text{PdCl}_2$	10.4	0.99	11.0
$\text{Pd}/\text{SiO}_2(11.4)^a$	$(\text{NH}_3)_4\text{PdCl}_2$	10.4	0.99	11.1
$\text{Pd}/\text{SiO}_2(12.2)^a$	$(\text{NH}_3)_4\text{PdCl}_2$	12.2	1.15	12.9

<sup>a</sup>The number in parentheses denotes the pH of the metal precursor solution.

## RESULTS AND DISCUSSION

### 1. Hydrogen Chemisorption

The results of hydrogen chemisorption are shown in Table 1. The percentage exposed of Pt on alumina was about 100 %. The percentage exposed of Pd on alumina was much higher than that on silica, which is a usually observed phenomenon due to different interactions between the metal ions and the two supports. Benesi et al. [1968] have reported that platinum amine ions can be highly dispersed on silica under high pH, but this was not found to be the case in our work for the palladium amine ions. The reason for this is not clear, but one might speculate that the poor dispersion of Pd is due to a different property of Pd itself from Pt or due to the different interaction of the silica with platinum amine ions and palladium amine ions. Rather, the percentage exposed of Pd obtained from the tetraamine salt was somewhat smaller than that obtained from the chloride salt and was shown to be little affected by the pH employed.

### 2. Activity and Selectivity

In Fig. 1, activities of the catalysts prepared from the chloride precursors ( $\text{Pd}/\text{Al}_2\text{O}_3$ ,  $\text{Pd}/\text{SiO}_2(\text{a})$  and  $\text{Pt}/\text{Al}_2\text{O}_3$ ) for metha-

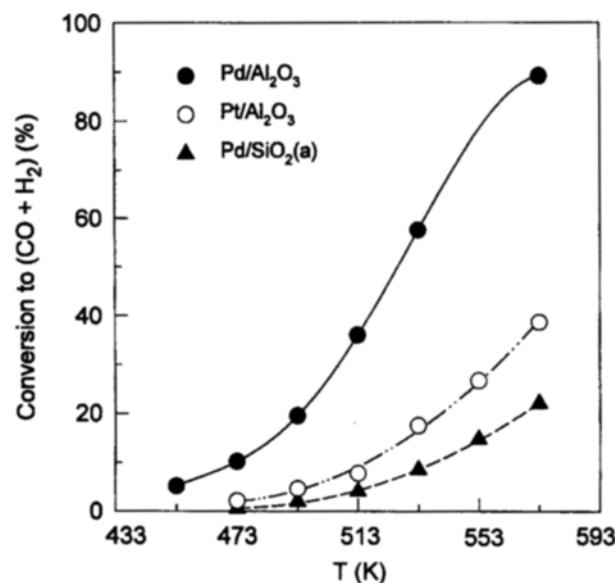


Fig. 1. Conversion for methanol decomposition to CO and  $\text{H}_2$  with temperature over supported Pd and Pt catalysts ( $W=200$  mg,  $P_{\text{A,in}}=0.2$  atm, total flow rate=100  $\text{cm}^3/\text{min}$ ).

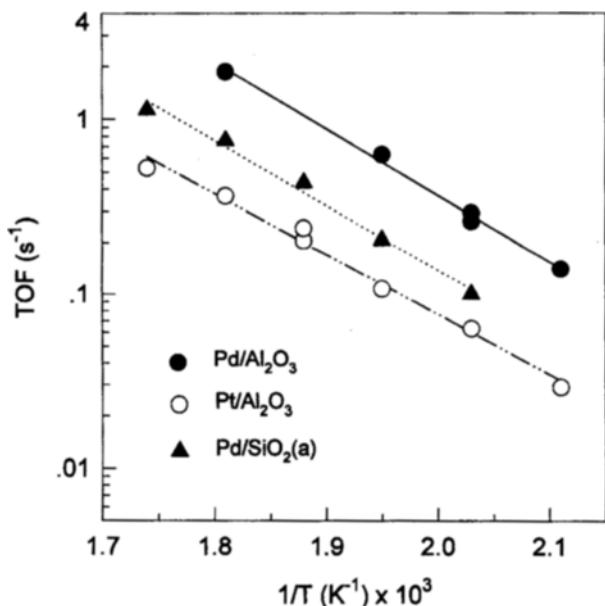


Fig. 2. TOF of methanol decomposition vs.  $1/T$  over the Pd and Pt catalysts prepared from the chloride precursors ( $P_{A,in} = 0.2$  atm, total flow rate=100  $\text{cm}^3/\text{min}$ ).

nol decomposition (conversion of methanol to CO and  $\text{H}_2$  only) are compared in terms of conversion under the same conditions. The conversion in Fig. 1 does not include the fraction of methanol converted to dimethyl ether. Per g catalyst basis,  $\text{Pd}/\text{Al}_2\text{O}_3$  was much more active than  $\text{Pt}/\text{Al}_2\text{O}_3$ , but  $\text{Pd}/\text{SiO}_2(\text{a})$  was less active than  $\text{Pt}/\text{Al}_2\text{O}_3$ . However, if the activities were compared in terms of the turnover frequencies (TOFs) based on the hydrogen chemisorption (Fig. 2),  $\text{Pd}/\text{Al}_2\text{O}_3$  was again the most active,  $\text{Pd}/\text{SiO}_2(\text{a})$  the next, and  $\text{Pt}/\text{Al}_2\text{O}_3$  was the least active. Therefore, it can be said that the specific activity per active surface area, or the TOF, of Pd is higher than that of Pt. In addition, since  $\text{Pd}/\text{Al}_2\text{O}_3$  is more active than  $\text{Pd}/\text{SiO}_2(\text{a})$ , a support effect seems to exist.

TOFs for the  $\text{Pd}/\text{SiO}_2(\text{b})$  catalysts prepared from the amine salt with different solution pH(b) are shown in Fig. 3. The specific activity of  $\text{Pd}/\text{SiO}_2(10.0)$  was a little bit higher than that of  $\text{Pd}/\text{SiO}_2(\text{a})$ , and the other  $\text{Pd}/\text{SiO}_2(\text{b})$  catalysts showed a little bit lower activities than  $\text{Pd}/\text{SiO}_2(\text{a})$ . Since silica is susceptible to dissolve at pH above 9 or 10 [Moulijn et al., 1993], the surface structure of the support may be altered with the pH. This might have caused the different activity with different pH in spite of the similar percentage exposed of the Pd. However, the activity of  $\text{Pd}/\text{SiO}_2(10.0)$  was still somewhat lower than that of  $\text{Pd}/\text{Al}_2\text{O}_3$ . Compared with a  $\text{Ni}/\text{SiO}_2$  catalyst in the literature [Yoon et al., 1993],  $\text{Pd}/\text{Al}_2\text{O}_3$  and  $\text{Pd}/\text{SiO}_2(10.0)$  are more active but  $\text{Pt}/\text{Al}_2\text{O}_3$  is less active, even though some difference in the partial pressure dependence is taken into account. For example, at 473 K and under the partial pressure of methanol of 0.2 atm, the TOFs over  $\text{Pd}/\text{Al}_2\text{O}_3$ ,  $\text{Pd}/\text{SiO}_2(10.0)$ ,  $\text{Pd}/\text{SiO}_2(\text{a})$  and  $\text{Pt}/\text{Al}_2\text{O}_3$  are 0.14, 0.098, 0.052 and  $0.029 \text{ s}^{-1}$ , respectively, while the TOF over the  $\text{Ni}/\text{SiO}_2$  catalyst is  $0.088 \text{ s}^{-1}$  under the methanol partial pressure of 0.05 atm at which the rate shows the maximum with respect to the partial pressure.

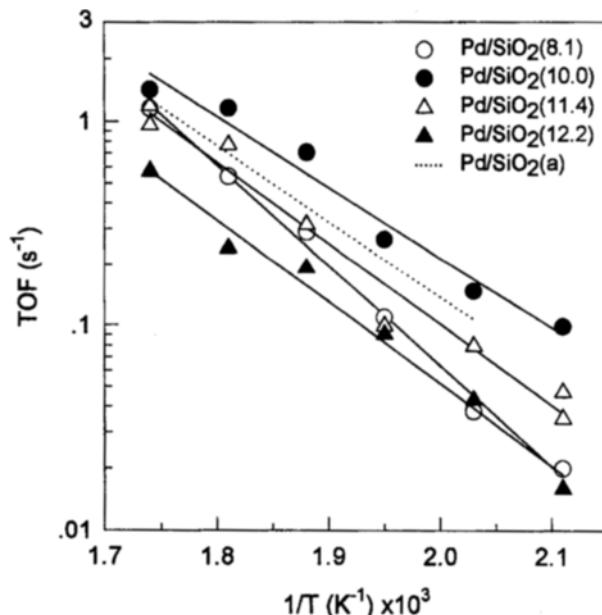


Fig. 3. TOF of methanol decomposition vs.  $1/T$  over  $\text{Pd}/\text{SiO}_2$  (reaction conditions are same as in Fig. 1).

Although the alumina is more favorable than the silica as the support for the decomposition activity, it catalyzes the dehydration of methanol to dimethyl ether (DME) due to its acidity [Spivey, 1991; Lee et al., 1993], which may be undesirable for some applications of the methanol decomposition. The activities of the alumina-supported catalysts as well as the alumina for the methanol dehydration are shown in Fig. 4 in terms of the conversion of methanol. The alumina tested for this reaction had been treated under the same conditions employed for the calcination of the supported catalysts. Over the alumina only, CO and  $\text{H}_2$  were not detected but only DME and  $\text{H}_2\text{O}$  were produced. The dehydration activity of  $\text{Pd}/\text{Al}_2\text{O}_3$

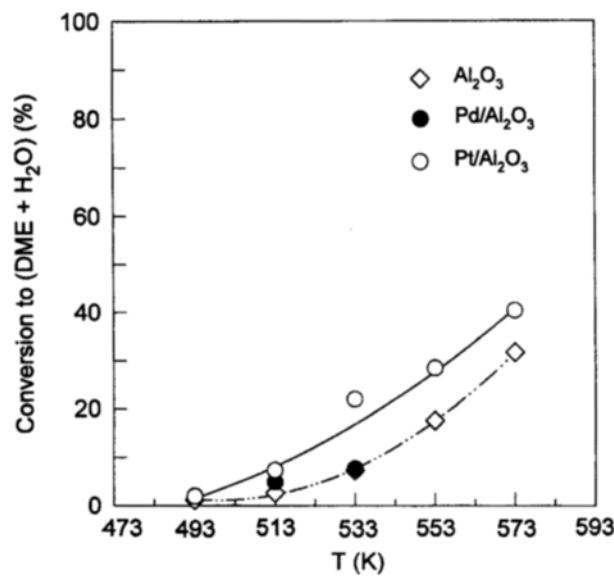


Fig. 4. Conversion for methanol dehydration to DME and  $\text{H}_2\text{O}$  with temperature over  $\text{Al}_2\text{O}_3$  and  $\text{Al}_2\text{O}_3$ -supported catalysts (reaction conditions are same as in Fig. 1).

up to 533 K was almost the same as that of the alumina only, but that of  $\text{Pt}/\text{Al}_2\text{O}_3$  was considerably higher than that of the alumina up to 573 K. This means that the Pd metal particles on alumina do not affect the dehydration activity of the alumina, but the Pt metal particles on alumina exhibit a significant enhancement of the dehydration activity of the alumina. There seems to be some kind of interaction between the Pt particles and the alumina, and this may be a cause for the relatively lower specific activity of  $\text{Pt}/\text{Al}_2\text{O}_3$  than that of  $\text{Pd}/\text{Al}_2\text{O}_3$  in methanol decomposition. By the interaction Pt may alter the number or the strength of the active sites on the alumina [Spivey, 1991], but since the methanol dehydration is not a subject of main interest in this work, no further detailed study or discussion will be given afterwards.

Product selectivities over  $\text{Pt}/\text{Al}_2\text{O}_3$ ,  $\text{Pd}/\text{Al}_2\text{O}_3$  and  $\text{Pd}/\text{SiO}_2(\text{a})$  with temperature are given in Table 2. As mentioned above, comparable amounts of CO and DME were produced over  $\text{Pt}/\text{Al}_2\text{O}_3$  at above 513 K, and over  $\text{Pd}/\text{Al}_2\text{O}_3$  the selectivity to CO is much higher than that to DME even at high conversions. No DME was produced over  $\text{Pd}/\text{SiO}_2(\text{a})$ , and this is due to the nearly neutral character of the silica. Methane formation was observed at high temperatures (or high conversions) over both  $\text{Pt}/\text{Al}_2\text{O}_3$  and  $\text{Pd}/\text{Al}_2\text{O}_3$ . Due to different conversions and  $S_{\text{CO}}$  as well as from the limited experiments in this work, it is not clear which of Pd and Pt is more active for the formation of methane. Over  $\text{Pd}/\text{SiO}_2(\text{a})$ , no methane formation was observed even at 573 K, but the methane conversion was considerably low. If the conversion becomes higher, the possibility for methane formation cannot be ruled out. On the other hand, the methanation activity of Pd or Pt is clearly lower than that of Ni when compared with the result in an earlier work [Yoon et al., 1993], which reported that

**Table 2. Product selectivities with temperature**

( $P_{\text{A,in}}=0.2$  atm, total flow rate=100  $\text{cm}^3/\text{min}$ , catalyst wt =200 mg)

Catalyst	Temp. (K)	Overall conv. (%)	Selectivity (%) <sup>1)</sup>		
			$S_{\text{CO}}$	$S_{\text{DME}}$	$S_{\text{CH}_4}$
$\text{Pt}/\text{Al}_2\text{O}_3$	473	2.1	100	-	-
	493	6.5	70.9	29.1	-
	513	15.1	51.6	48.4	-
	533	39.5	44.4	55.6	-
	553	55.9	47.8	51.0	1.2
	573	79.8	48.3	50.5	1.1
$\text{Pd}/\text{Al}_2\text{O}_3$	453	5.1	100	-	-
	473	10.2	100	-	-
	493	21.5	90.9	9.1	-
	513	40.8	88.1	11.9	-
	533	65.2	88.3	11.7	-
	573	98.3	90.7	-	9.1
$\text{Pd}/\text{SiO}_2(\text{a})$	473	0.6	100	-	-
	493	2.0	100	-	-
	513	4.0	100	-	-
	533	8.5	100	-	-
	553	14.8	100	-	-
	573	22.1	100	-	-


<sup>1)</sup> $\text{Si}(\%)=100 \times (\text{moles of carbon in product i})/(\text{total moles of methanol converted})$ , i=CO, DME or  $\text{CH}_4$ .

methane formation was observed at as low as 493 K with a lower methane conversion.

From the discussion above,  $\text{Pd}/\text{Al}_2\text{O}_3$  seems to be an excellent catalyst for methanol decomposition provided that the dehydration activity of alumina is effectively suppressed. This may be done by neutralizing the acid sites without affecting the activity of Pd adversely. Another possible method is use of other supports which do not catalyze side reactions but help Pd retain the high activity. These suggestions may be tested in future work.

### 3. Apparent Reaction Orders and Activation Energies

Dependence of the activity of methanol decomposition on the partial pressure of methanol was investigated and the results are given in Figs. 5 and 6. The methanol conversions were maintained below 20 % in these experiments, and the conversions became lower with increasing partial pressure. Although the partial pressure dependence over  $\text{Pd}/\text{Al}_2\text{O}_3$  at 553 K was observed to be similar to that at lower temperatures, the conversions were considerably high (30-60 %) and therefore the partial pressure dependence at this temperature should be used with some reservation. The partial pressure given was the average value between the reactor inlet and outlet, and the reaction rate, only for the decomposition to CO and  $\text{H}_2$ , was also the average value in the bed. As shown in the Figures, patterns of the dependence on the partial pressure look alike regardless of the catalyst and temperature. Therefore, the dependence over  $\text{Pd}/\text{SiO}_2(\text{b})$  is considered to be similar to that over  $\text{Pd}/\text{SiO}_2(\text{a})$  and was not investigated in this work. At low partial pressures below about 0.4 atm, the reaction orders were around 0.3. As the partial pressure increased, the orders became near zero or slightly negative. The relatively low reaction orders and their decrease with the partial pressure may be explained by adsorption inhibition [Kim and Yoon, 1996]. Although the detailed reaction mechanism is not investigated in this work, a great portion of the surface is considered to be covered with adsorbed species including methanol and in-

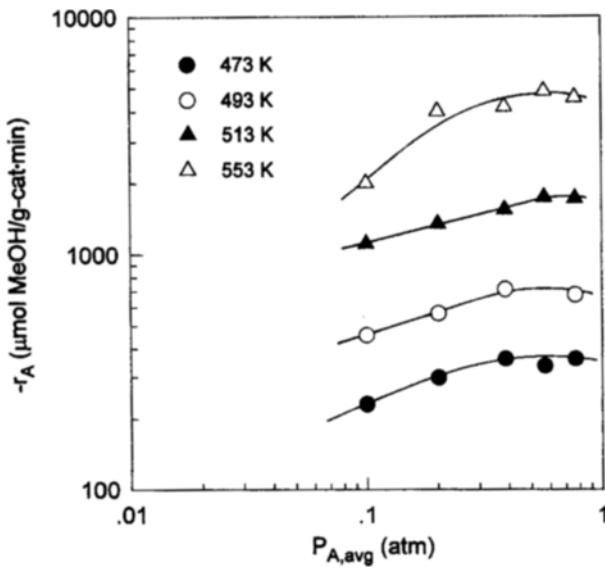

**Fig. 5. Rate of methanol decomposition vs. partial pressure of methanol over  $\text{Pd}/\text{Al}_2\text{O}_3$ .**

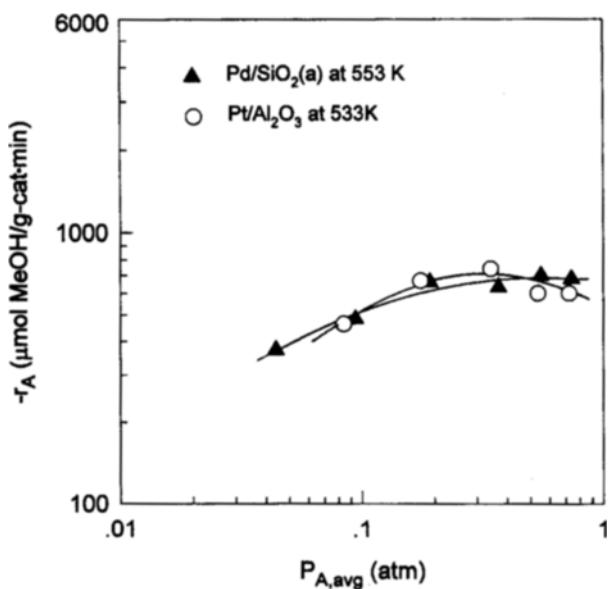


Fig. 6. Rate of methanol decomposition vs. partial pressure of methanol over  $\text{Pd/SiO}_2(\text{a})$  and  $\text{Pt/Al}_2\text{O}_3$ .

termediate species, and due to the presence of these species adsorption of methanol and subsequent decomposition steps may be inhibited. With the increase of the partial pressure the surface coverage will become greater, which results in lowering of the reaction order. In fact, negative reaction orders have also been observed over a nickel catalyst with increasing partial pressure of methanol [Yoon et al., 1993].

The apparent activation energies ( $E_{app}$ 's) were estimated from Figs. 2 and 3 and the results are given in Table 3. Except for  $\text{Pd/SiO}_2(8.1)$ , the values were about the same ranging from 66 to 77 kJ/g-mol. Although the exceptionally high activation energy for  $\text{Pd/SiO}_2(8.1)$  is not well understood, it largely appears that the activation energy is little affected by the metal, the support or the preparation method. The value for a Ni catalyst in an earlier work [Yoon et al., 1993] was also similar to them.

For Pd, Pt and Ni, the rate determining step in the mechanism of methanol decomposition is generally considered to be the formation of methoxy species on the surface. Contrary to Cu on which methoxy is stable at high temperatures, the methoxy is rapidly decomposed to CO and  $\text{H}_2$  on Pd, Pt and Ni without producing formaldehyde and methyl formate [Gates and Kesmodel, 1983; Bare et al., 1985; Yoon et al., 1993; Lee and Bell, 1996]. Similar partial pressure dependence and apparent activation energies for the supported Pd catalysts in this work suggest that the rate determining step is the same

and the inherent catalytic property of the metal is altered only to a small extent, but different activities depending on the support may be considered due to the support effect. Although the nature of the support effect is not clearly understood, some speculations may be proposed. As it has been reported that the formation of methoxy species is facilitated by adsorbed oxygen on Pd while the methoxy species is difficult to form on a clean surface [Gates and Kesmodel, 1983], the oxygen on the support at the periphery of the metal particles may facilitate the methoxy formation to a different extent depending on the support. Another speculation is that an adsorbed intermediate of methanol or methoxy species formed on the support near the metal particles may be readily decomposed by the metal. The concentration of the adsorbed intermediate on the support may be different depending on the support, and that on the alumina may be considered to be the highest. Although the support effect may result in changes of the apparent activation energy to some extent, it did not come out to be large for the catalysts in this work.

## CONCLUSIONS

The specific activity of Pd for methanol decomposition was higher than that of Pt. Although alumina-supported Pd produced dimethyl ether as a by-product and silica-supported Pd did not, the former is more active than the latter. A silica-supported Pd catalyst prepared from the tetraamine salt solution with a proper pH exhibited higher activity than the other silica-supported Pd catalysts. These suggest that a support effect on the activity of methanol decomposition may be present. Dependence of the rate on the partial pressure of methanol was similar to one another regardless of the metal, the support or the preparation method. The apparent reaction orders were near 0.3 at low pressures below about 0.4 atm and became near zero or slightly negative at higher pressures. The apparent activation energies were about the same for most of the catalysts and were in the range from 66 to 77 kJ/g-mol.

## ACKNOWLEDGMENT

The authors gratefully acknowledge the financial support of the Korea Institute of Energy Research.

## NOMENCLATURE

DME: dimethyl ether

$E_{app}$  : apparent activation energy [kJ/g-mol of methanol]

$P_{A,avg}$  : average partial pressure of methanol between reactor inlet

Table 3. Apparent activation energies of methanol decomposition

Catalyst	$\text{Pt/Al}_2\text{O}_3^a)$	$\text{Pd/Al}_2\text{O}_3^a)$	$\text{Pd/SiO}_2(\text{a})$	$\text{Pd/SiO}_2(8.1)$
$E_{app}$ (kJ/g-mol)	66.6	72.5	71.2	94.5
Catalyst	$\text{Pd/SiO}_2(10.0)$	$\text{Pd/SiO}_2(11.4)$	$\text{Pd/SiO}_2(12.2)$	$\text{Ni/SiO}_2^b)$
$E_{app}$ (kJ/g-mol)	66.2	75.9	77.2	63

<sup>a</sup>Dehydration of methanol occurred simultaneously, but only the rate data for the methanol decomposition were used in the data analysis.

<sup>b</sup>From Yoon et al. [1993].

and outlet [atm]

 $P_{A,in}$  : partial pressure of methanol at reactor inlet [atm] $r_A$  : reaction rate of methanol decomposition [ $\mu\text{mol}/(\text{g}\cdot\text{cat}\cdot\text{min})$ ] $S_i$  : selectivity of i based on carbon balance, i=CO, DME or  $\text{CH}_4$  [- or %]

T : temperature [K]

TOF : turnover frequency [ $\text{s}^{-1}$ ]

W : catalyst weight [mg]

## REFERENCES

Bare, S. R., Stroscio, J. A. and Ho, W., "Characterization of the Adsorption and Decomposition of Methanol on Ni(110)," *Surf. Sci.*, **150**, 399 (1985).

Benesi, H. A., Curtis, R. M. and Studer, H. P., "Preparation of Highly Dispersed Catalytic Metals. Platinum on Silica Gel," *J. Catal.*, **10**, 328 (1968).

Benson, J. E., Hwang, H. S. and Boudart, M., "Hydrogen-Oxygen Titration Method for the Measurement of Supported Palladium Surface Areas," *J. Catal.*, **30**, 146 (1973).

Cant, N. W., Tonner, S. P., Trimm, D. L. and Wainwright, M. S., "Isotopic Labelling Studies of the Mechanism of Dehydrogenation of Methanol to Methyl Formate over Copper-Based Catalysts," *J. Catal.*, **91**, 197 (1985).

Cheng, W.-S. and Kung, H. H.(Eds.), "Methanol Production and Use," Chap. 1, Marcel Dekker, New York (1994).

Gates, J. A. and Kesmodel, L. L., "Methanol Adsorption and Decomposition on Clean and Oxygen Precovered Pd(111)," *J. Catal.*, **83**, 437 (1983).

Hahn, H.-S., Kim, E.-Y., Sung, B.-P. and Lee, W.-Y., "Methanol Synthesis from Synthesis Gas over Pd/SiO<sub>2</sub>," *HWAHAK KONGHAK*, **27**, 16 (1989).

Idem, R. O. and Bakhshi, N. N., "Production of Hydrogen from Methanol. 2. Experimental Studies," *Ind. Eng. Chem. Res.*, **33**, 2056 (1994).

Joo, O. S., Han, S. H. and Uhm, S. J., "The Effect of Metals on the Methanol Decomposition," Abstracts of 1991 Spring KICHE Meeting, Seoul, p.41 (1991).

Kim, S. I. and Yoon, K. J., "Methanol Decomposition over Cu-Ni/SiO<sub>2</sub>," *HWAHAK KONGHAK*, **34**, 658 (1996).

Lee, D.-K. and Bell, A. T., "FTIR Studies of Methanol Decomposition on Cu/SiO<sub>2</sub>," *HWAHAK KONGHAK*, **34**, 300 (1996).

Lee, T. J., Kim, J. H., Chang, W. C., Lee, D. J. and Kim, Y. K., "CO Hydrogenation over Supported Iridium Catalysts Derived from Iridium Carbonyls," *HWAHAK KONGHAK*, **31**, 593 (1993).

Madhusudhan Rao, V. and Shankar, V., "High Activity Copper Catalyst for One-step Conversion of Methanol to Methyl Formate at Low Temperature," *J. Chem. Tech. Biotechnol.*, **42**, 183 (1988).

Miyazaki, E. and Yasumori, I., "Kinetics of the Catalytic Decomposition of Methanol, Formaldehyde and Methyl Formate over a Copper-wire Surface," *Bull. Chem. Soc. Japan*, **40**, 2012 (1967).

Moulijn, J. A., van Leeuwen, P. W. N. M. and van Santen, R. A. (Eds.), "Catalysis," Elsevier, Amsterdam, p.343 (1993).

Park, S. H., Kim, J. H., Lee, T. J. and Kim, D. H., "Methanation Kinetics of Carbon Oxides over Supported Ru and Ni Catalysts," *HWAHAK KONGHAK*, **30**, 423 (1992).

Shimizu, M. and Takeoka, S., "Kinetic Study of Methanol Decomposition over Raney Nickel Alloy Catalyst," *Kagaku Kogaku Ronbunshi*, **15**(2), 284 (1989).

Spivey, J. J., "Review: Dehydration Catalysts for the Methanol/Dimethyl Ether Reaction," *Chem. Eng. Comm.*, **110**, 123 (1991).

Takishita, T., Sakai, T., Yamaguchi, I., Ayusawa, T. and Kin, E., "Research on Spark Ignition Engine Fueled with Dissociated-Methanol Gas," *Transactions of Jap. Soc. Auto. Eng.* (in Japanese), No. 31, 21 (1985).

Yasumori, I., Nakamura, T. and Miyazaki, E., "Catalytic Decomposition of Methanol over Nickel Wire," *Bull. Chem. Soc. Japan*, **40**, 1372 (1967).

Yoon, K. J., Jeong, K. S. and Yie, J. E., "Kinetics of Methanol Decomposition over Ni/SiO<sub>2</sub>," *HWAHAK KONGHAK*, **31**, 569 (1993).