


Comments on the Paper "Thermal Decomposition of Poly(γ -methyl L-glutamate)"

A paper dealing with the pyrolysis-gas chromatography-mass spectrometry (GC-MS) of poly(γ -methyl L-glutamate) (PMLG) appeared recently in this journal.¹ Pyrolysis products of up to m/z 85 were eluted from the GC column and identified by MS.


On the basis of these results, it was concluded that the primary decomposition products evolving from PMLG are methanol, carbon dioxide, methane, and some other gaseous materials.¹

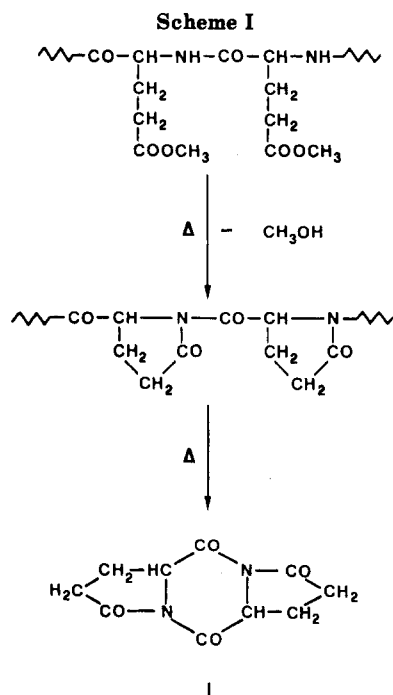

The authors were, apparently, unaware of our recent results² on the thermal decomposition of PMLG, investigated by direct pyrolysis-mass spectrometry (DP-MS).

In the DP-MS technique,² polymers are introduced via a direct insertion probe and the temperature is increased gradually to a point at which thermal decomposition reactions occur; the volatile products formed are then ionized and detected.

Two diketopiperazines (I and II) were detected, together with methanol, among the pyrolysis products of PMLG.²

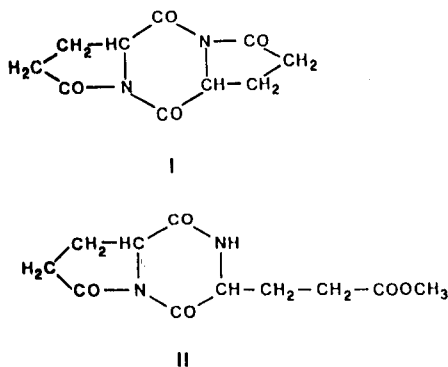

These findings gave us a firm basis so as to propose² a primary thermal fragmentation mechanism for PMLG (Scheme I).

In fact, one of the advantages of the DP-MS technique is that the pyrolysis is accomplished under a high vacuum and, therefore, that the thermal products formed are volatilized and removed readily from the hot zone. This,

together with the low probability of molecular collision and the fast detection, reduces, to a large extent, the occurrence of secondary reactions. Consequently, the thermal fragments detected are due almost exclusively to primary reactions. The information thus obtained is, therefore, of particular importance in order to assess the primary thermal decomposition mechanism of a particular polymer.²

Secondary and/or tertiary decomposition reactions cannot be avoided by using pyrolysis-GC-MS, since the pyrolysis is performed at atmospheric pressure and the pyrolysis products are kept for some time in the GC column at a high temperature.

In view of our previous DP-MS results,² the pyrolysis products of PMLG which were detected by pyrolysis-GC-MS in ref 1 appear to be smaller, secondary, products. It is difficult to derive a mechanism of primary thermal decomposition of PMLG from this kind of information (see Scheme I).

Rather, it should be realized that pyrolysis-GC-MS experiments are actually concerned with the thermal decomposition of diketopiperazines I and II, which are, themselves, the primary pyrolysis products originating from PMLG.

Acknowledgment. Partial financial support from the Italian Ministry of Public Education and from Consiglio Nazionale delle Ricerche (Roma) is gratefully acknowledged.

Registry No. I, 14612-22-7; II, 104807-55-8; PMLG (homopolymer), 25086-16-2; PMLG (SRU), 25036-43-5.

References and Notes

- (1) Kojima, T.; Kurotu, T.; Kawaguchi, T. *Macromolecules* 1986, 19, 1281.
- (2) Ballistreri, A.; Giuffrida, M.; Maravigna, P.; Montaudo, G. *J. Polym. Sci., Polym. Chem. Ed.* 1985, 23, 1145.
- (3) (a) Dipartimento di Scienze Chimiche, Università di Catania.
(b) Istituto per la Chimica e la Tecnologia dei Materiali Polimerici, Consiglio Nazionale delle Ricerche.

Alberto Ballistreri,^{3a} Mario Giuffrida,^{3b}
Pietro Maravigna,^{3a} and Giorgio Montaudo^{*3a}

*Dipartimento di Scienze Chimiche, Università di Catania
95125 Catania, Italy, and Istituto per la Chimica e la
Tecnologia dei Materiali Polimerici, Consiglio Nazionale
delle Ricerche, 95125 Catania, Italy*

Received May 28, 1986

Trialkylsilyl Triflates, Novel Initiators for Cationic Polymerization

We wish to report that trialkylsilyl trifluoromethanesulfonates are highly effective novel initiators for the cationic polymerization of vinyl monomers and oxacyclic compounds.

Trialkylsilyl trifluoromethanesulfonates (triflates) have enjoyed wide use as electrophilic reagents in organic chemistry.¹⁻⁵ They are highly reactive toward electron-rich olefins and to carbonyl and oxacyclic compounds. Nevertheless recent authoritative reviews⁶⁻¹⁰ contain no mention of their use as initiators for the cationic polymerization of such monomers.

Representative results for the initiation of the cationic polymerization of some common electron-rich monomers, using trimethylsilyl triflate (1) and triisopropylsilyl triflate (2), are given in Table I. Careful purification of reagents ensured that triflic acid was not responsible for these polymerizations. The polymerizations proceed rapidly at