

Crystal structure and magnetic properties of novel chiral nitroxides existing as racemic conglomerates

Naohiko Ikuma, Rui Tamura,* Satoshi Shimono, Naoyuki Kawame, Osamu Tamada, Naoko Sakai, Jun Yamauchi and Yukio Yamamoto

Graduate School of Human and Environmental Studies, Kyoto University, Kyoto 606-8501, Japan.
Fax: +81 75 753 7915; e-mail: tamura@fisher.jinkan.kyoto-u.ac.jp


10.1070/MC2003v013n03ABEH001787

Racemic samples of novel chiral cyclic nitroxides 2-(4-hydroxyphenyl)-2,5,5-trimethylpyrrolidine-1-oxy **1**, *trans*-2-(4-hydroxyphenyl)-2,5-dimethyl-5-phenylpyrrolidine-1-oxy **2** and *trans*-2,5-bis(4-hydroxyphenyl)-2,5-dimethylpyrrolidine-1-oxy **3** having 4-hydroxyphenyl groups on the stereogenic centres adjacent to the NO radical moiety have been found to exist as racemic conglomerates in the crystalline state, and the origin of the conglomerate formation has been studied by X-ray crystallographic analysis and magnetic susceptibility measurements.

The spontaneous resolution of chiral crystals built from achiral compounds or the racemates of chiral compounds in condensed phases is a useful phenomenon especially for the preparation of ordered three-dimensional chiral crystals and liquid crystals.¹

Here we report that the racemic samples of chiral nitroxides **1**, *trans*-**2** and *trans*-**3** exist as racemic conglomerates in a stable crystalline state, which are very rare for nitroxide radicals.^{1–4} Racemic and enantiomerically enriched nitroxides **1**, *trans*-**2** and *trans*-**3** have been prepared analogously to the preparation of *trans*-(±)- and (2*S*,5*S*)-2,5-dimethyl-2,5-diphenylpyrrolidine-1-oxy^{5,6} from *trans*-(±)- and (2*R*,5*R*)-2,5-dimethylpyrrolidine, respectively,⁷ and recrystallised from Et₂O, CHCl₃ and MeOH, respectively. Their thermal, optical and magnetic properties are summarised in Table 1.

Interestingly, as expected from the identity of IR spectra between the enantiomerically enriched material and the racemate, all the racemic samples of **1**, *trans*-**2** and *trans*-**3** have found to exist as not a racemic compound but a rare racemic con-

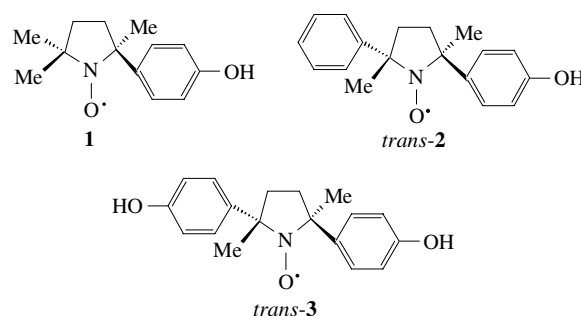

glomerate consisting of chiral crystals by X-ray crystallographic analysis.[†] They have commonly a head-to-tail type of homochiral supramolecular 1D zigzag chains characterised by strong intermolecular hydrogen bonds between the NO radical and the phenolic OH groups [O...O distances of 2.725(6), 2.752(3) and 2.665(5) Å for **1**, *trans*-**2** and *trans*-**3**, respectively] [Figures 1(a), 2(a) and 3]. It is easily envisaged that the formation of such a homochiral supramolecular zigzag arrangement along a two-fold screw axis in preference to a centrosymmetric dimer structure in the crystalline state should be due to the *para* disposition of the phenolic OH group.⁸

Since at first glance it was difficult to find out the primary interactions, which control the homochiral packing of the homochiral 1D zigzag chains, *i.e.*, the origin of the formation of the racemic conglomerates, the molar magnetic susceptibility χ_{mol} was measured for **1**, *trans*-**2** and *trans*-**3** at the temperatures ranging between 2 and 300 K using a SQUID susceptometer at a field of 0.5 T (Figure 4). This is because the measurement of the temperature dependence of the magnetic susceptibility of molecular magnetic materials often affords useful information

Table 1 Melting points, specific rotations, EPR *g*-factors and hyperfine coupling constants and magnetic data for nitroxides **1**–**3**.

Compound	mp/°C ^a	ee (%) ^b	[α] _D ^{25 c}	EPR ^d		<i>C</i> _H /emu K mol ^{−1}	<i>θ</i> /K
				<i>g</i>	<i>a</i> _N /mT		
(<i>S</i>)- 1	161.7	88	−118.66	2.0067	1.38	0.38	+0.20
(decomp.)							
(±)- 1	151.0	—	—	2.0073	1.38	0.37	+0.15
(decomp.)							
(2 <i>S</i> ,5 <i>S</i>)- 2	180.8	97	−202.18	2.0070	1.33	0.37	−0.33
(decomp.)							
(±)- 2	168.5	—	—	2.0070	1.33	0.37	−0.30
(decomp.)							
(2 <i>S</i> ,5 <i>S</i>)- 3	177.2	97	−187.30	2.0067	1.34	0.38	−0.01
(decomp.)							
(±)- 3	173.8	—	—	2.0080	1.35	0.38	−0.02
(decomp.)							

^aMeasured by DSC. ^bDetermined by HPLC analysis using a chiral stationary phase column (Daicel Chiralcel OD-H, 0.4×25 cm) and a mixture of hexane and propan-2-ol (9:1) as the mobile phase. ^cMeasured in THF, *c* 1.00. ^dMeasured in THF at 25 °C. ^eCurie constants. ^fWeiss temperature.

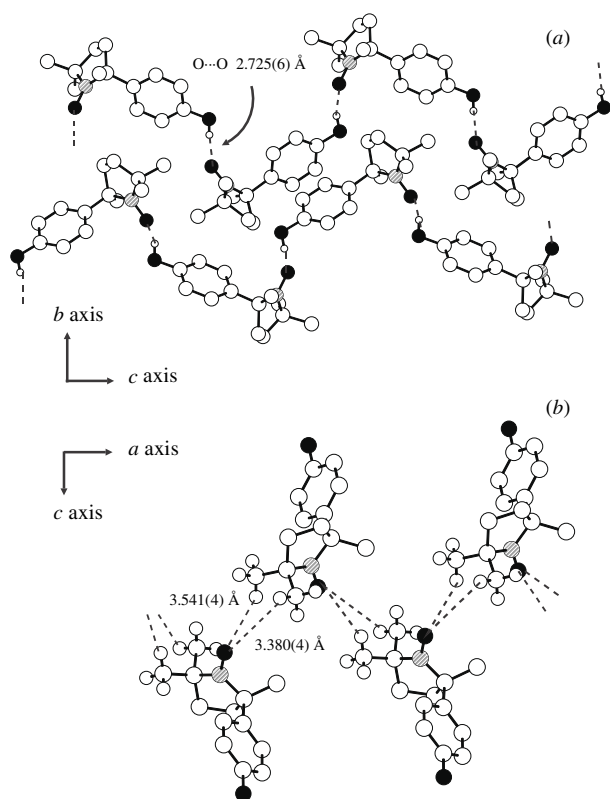


Figure 1 Crystal structure of (±)-**1** viewed down the (a) *a* axis and (b) *b* axis. The carbon, hydrogen, nitrogen, and oxygen atoms are represented by large open, small open, crosshatched, and closed circles, respectively. Hydrogen atoms except the OH and two methyl groups on the pyrrolidinyl C(5) are omitted.

on weak intermolecular interactions in the crystal lattice.⁹ The racemic sample showed the same magnetic behaviour as the enantiomerically enriched one for each of **1**, *trans*-**2** and *trans*-**3** because of their existence as conglomerates. Three typical magnetic behaviours, such as ferro-, antiferro- and paramagnetic interactions, were observed for **1**, *trans*-**2** and *trans*-**3**, respectively, although the former two were weak (Table 1).

Appearance of a weak ferromagnetic interaction for **1** is consistent with its crystal structure in which the intra- and intermolecular spin polarization exchange coupling can be transmitted ferromagnetically in accord with the McConnell mechanism;¹⁰ *i.e.*, the sandwich-type weak C–H...O...H–C interactions [H...O distances of 3.380(4) and 3.541(4) Å] between the oxygen atom of a NO group and the two methyl groups on the pyrrolidinyl C(5) of the neighbouring molecule giving another homochiral 1D zigzag chain along the *a* axis seems responsible for the weak ferromagnetic interaction [Figure 1(b)].^{9,11} This zigzag chain along the *a* axis and the foregoing homochiral 1D zigzag chain along the *c* axis formed by strong OH...ON hydrogen bonds are alternately weaved along the *b* axis into the homochiral 3D network structure.[‡]

The observed weak antiferromagnetic behaviour of *trans*-**2** is explained by the dipole–dipole interactions between the NO groups [the shortest O...O distance is 6.399(3) Å] along the *c* axis [Figure 2(b)]. The 1D zigzag chains along the *b* axis, which were formed by the O–H...O–N hydrogen bonds, were further connected with one another on the *ab* plane by the C(sp³)–H...O–N interactions [H...O distance of 2.875(2) Å] between the pyrrolidinyl C(4)Hs of a homochiral chain and the N–O groups of the neighbouring chain to give a sheet structure [Figure 2(a)]. Thus, the above dipole–dipole interactions between the NO groups along the *c* axis may be responsible for the homochiral stacking of the homochiral *ab* sheets along the *c* axis.

In the paramagnetic crystals of *trans*-**3**, in which the O...O distance (7.547 Å) between the nearest NO groups was too long to show an antiferromagnetic behaviour, a combination of

† The X-ray data were collected at 294 K on an Enraf-Nonius Kapp CCD diffractometer. The crystal structure was solved by the direct methods and refined by full-matrix least squares. All non-hydrogen atoms were refined anisotropically. All of the crystallographic calculations were performed using the maXus software package.¹²

Crystal data for (±)-**1** (conglomerate): C₁₃H₁₈NO₂, *M_r* = 220.292, 0.30×0.20×0.13 mm, orthorhombic, space group *P*2₁2₁2₁, *a* = 8.6141(4) Å, *b* = 10.7211(6) Å, *c* = 13.4213(6) Å, *V* = 1239.5(1) Å³, *Z* = 4, *d_{calc}* = 1.391 g cm^{−3}, 2θ_{max} = 53.4°, MoKα (*λ* = 0.71073 Å), *μ* = 0.79 cm^{−1}, *φ*–*ω* scans, *T* = 298 K, 1517 independent reflections, 945 observed reflections [*I* > 2.0σ(*I*)], 148 refined parameters, *R* = 0.066, *R_w* = 0.181, Δ*ρ*_{max} = 0.239 eÅ^{−3}, Δ*ρ*_{min} = −0.401 eÅ^{−3}.

Crystal data for (±)-**2** (conglomerate): C₁₈H₂₀NO₂, *M_r* = 282.363, 0.25×0.16×0.10 mm, orthorhombic, space group *P*2₁2₁2₁, *a* = 10.4826(3) Å, *b* = 11.5410(4) Å, *c* = 12.5330(4) Å, *V* = 1516.2(1) Å³, *Z* = 4, *d_{calc}* = 1.237 g cm^{−3}, 2θ_{max} = 55.74°, MoKα (*λ* = 0.71073 Å), *μ* = 0.80 cm^{−1}, *φ*–*ω* scans, *T* = 298 K, 2072 independent reflections, 1572 observed reflections [*I* > 2.0σ(*I*)], 193 refined parameters, *R* = 0.042, *R_w* = 0.104, Δ*ρ*_{max} = 0.247 eÅ^{−3}, Δ*ρ*_{min} = −0.264 eÅ^{−3}.

Crystal data for (±)-**3** (conglomerate): C₁₈H₂₀NO₃, *M_r* = 298.362, 0.25×0.18×0.15 mm, orthorhombic, space groups *P*2₁2₁2₁, *a* = 10.4680(3) Å, *b* = 10.5485(3) Å, *c* = 13.5817(5) Å, *V* = 1499.7(1) Å³, *Z* = 4, *d_{calc}* = 1.321 g cm^{−3}, 2θ_{max} = 53.41°, MoKα (*λ* = 0.71073 Å), *μ* = 0.90 cm^{−1}, *φ*–*ω* scans, *T* = 298 K, 1825 independent reflections, 1070 observed reflections [*I* > 2.0σ(*I*)], 203 refined parameters, *R* = 0.046, *R_w* = 0.105, Δ*ρ*_{max} = 0.247 eÅ^{−3}, Δ*ρ*_{min} = −0.292 eÅ^{−3}.

Atomic coordinates, bond lengths, bond angles and thermal parameters have been deposited at the Cambridge Crystallographic Data Centre (CCDC). These data can be obtained free of charge via www.ccdc.cam.ac.uk/conts/retrieving.html (or from the CCDC, 12 Union Road, Cambridge CB2 1EZ, UK; fax: +44 1223 336 033; or deposit@ccdc.cam.ac.uk). Any request to the CCDC for data should quote the full literature citation and CCDC reference numbers 204742–204744. For details, see ‘Notice to Authors’, *Mendeleev Commun.*, Issue 1, 2003.

‡ Contribution of the OH...ON hydrogen bond to the intermolecular spin polarization exchange coupling is considered to be negligible with respect to **1**, *trans*-**2** and *trans*-**3** because the spin densities on the phenolic oxygen and hydrogen atoms have been found to be very low by MO calculations (UHF/6-31G* level using Spartan 02).

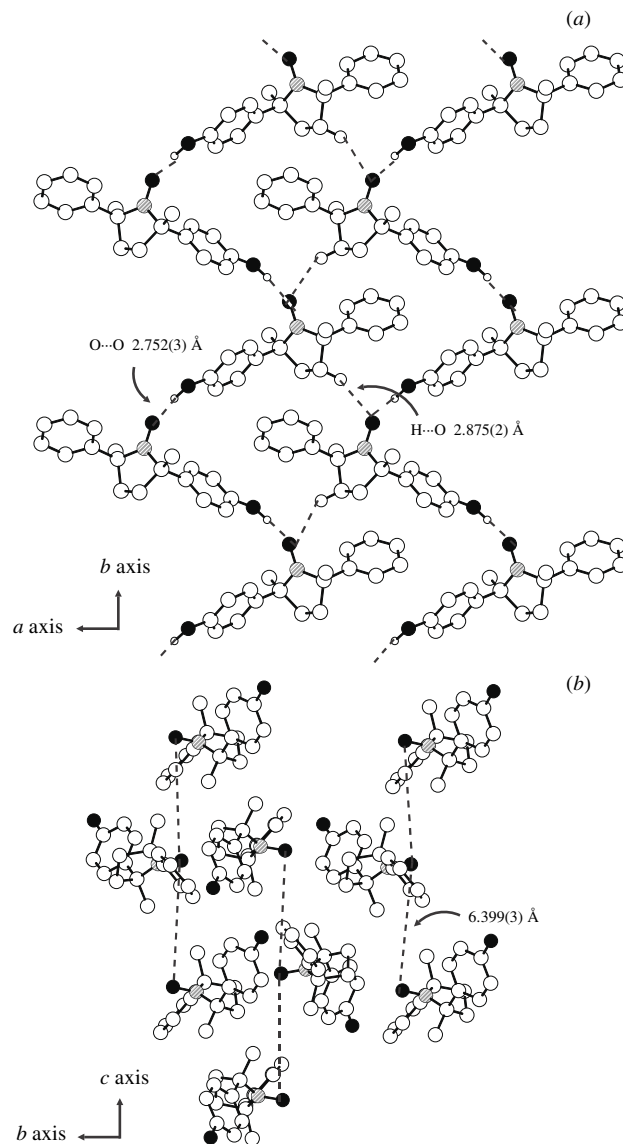


Figure 2 Crystal structure of *trans*-(±)-**2** viewed down the (a) *c* axis and (b) *a* axis. The carbon, hydrogen, nitrogen, and oxygen atoms are represented by large open, small open, crosshatched, and closed circles, respectively. Hydrogen atoms except the OH group and one hydrogen atom on the pyrrolidinyl C(4) are omitted in (a), while all hydrogen atoms are done in (b).

hydrogen bonds between the neighbouring phenolic OH groups [O...O distance of 2.761(5) Å] with the O–H...O–N hydrogen bonds provides a homochiral 1D ribbon structure along the *c* axis (Figure 3). No appreciable interribbon interaction other than van der Waals interactions was seen. Probably, in this case such a homochiral crystal packing should be energetically favoured over any heterochiral packing of the homochiral 1D zigzag chains.

Thus, the origin of the conglomerate formation with respect to **1**, *trans*-**2** and *trans*-**3** can be interpreted in terms of strong

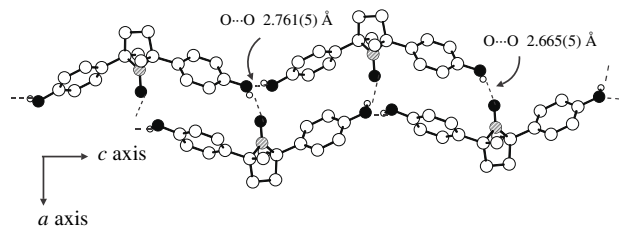


Figure 3 Crystal structure of *trans*-(±)-**3** viewed down the *b* axis. The carbon, hydrogen, nitrogen, and oxygen atoms are represented by large open, small open, crosshatched, and closed circles, respectively. Hydrogen atoms except the OH group are omitted.

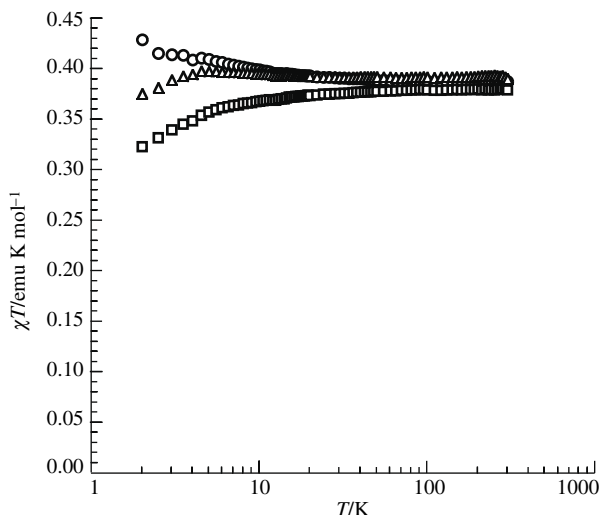


Figure 4 Temperature dependence of the magnetic susceptibility of (S)-**1** (represented by circles), trans-(2S,5S)-**2** (squares) and trans-(2S,5S)-**3** (triangles).

intermolecular OH...ON hydrogen bonds together with weak attractive forces such as C(spⁿ)H...ON interactions and dipole–dipole interactions between the NO groups.

References

- [doi>1](#) L. Perez-Garcia and D. B. Amabilino, *Chem. Soc. Rev.*, 2002, **31**, 342.
- 2 J. Jacques, A. Collet and S. H. Wilen, *Enantiomers, Racemates, and Resolutions*, Krieger Publishing Co., Malabar, FL, 1994.
- 3 A. Collet, M.-J. Brienne and J. Jacques, *Chem. Rev.*, 1980, **80**, 215.
- 4 (a) R. Tamura, S. Susuki, N. Azuma, A. Matsumoto, F. Toda, A. Kamimura and K. Hori, *Angew. Chem., Int. Ed. Engl.*, 1994, **33**, 878; (b) R. Tamura, S. Susuki, N. Azuma, A. Matsumoto, F. Toda, T. Takui, D. Shiomi and K. Itoh, *Mol. Cryst. Liq. Cryst.*, 1995, **271**, 91; (c) R. Tamura, S. Susuki, N. Azuma, A. Matsumoto, F. Toda and Y. Ishii, *J. Org. Chem.*, 1995, **60**, 6820.
- 5 B. Nicholas, M. Steenbock, M. Klapper, K. Mullen, V. Enkelmann and K. Cabera, *Liebigs Ann. Chem.*, 1996, 1413.
- [doi>6](#) J. Einhorn, C. Einhorn, F. Ratajczak, I. Gautier-Luneau and J.-L. Pierre, *J. Org. Chem.*, 1997, **62**, 9385.
- 7 R. P. Short, R. M. Kennedy and S. Masamune, *J. Org. Chem.*, 1989, **54**, 1755.
- [doi>8](#) K. Kinbara, Y. Hashimoto, M. Sukegawa, H. Nohira and K. Saigo, *J. Am. Chem. Soc.*, 1996, **118**, 3441.
- 9 (a) *Magnetism: Molecules to Materials II*, eds. J. S. Miller and M. Drillon, Wiley–VCH, Weinheim, 2001; (b) *Magnetic Properties of Organic Molecules*, ed. P. M. Lahti, Marcel Dekker, New York, 1999; (c) [doi>S. Nakatsuji and H. Anzai, J. Mater. Chem., 1997, **7**, 2161.](#)
- 10 H. M. McConnell, *J. Chem. Phys.*, 1963, **39**, 1910.
- 11 T. Nogami, T. Ishida, M. Yasui, F. Iwasaki, N. Takeda, M. Ishikawa, T. Kawakami and K. Yamabuchi, *Bull. Chem. Soc. Jpn.*, 1996, **68**, 1841.
- 12 S. Mackay, C. J. Gilmore, C. Edwards, M. Tremayne, N. Stuart and K. Shankland, *maXus: A Computer Program for the Solution and Refinement of Crystal Structures from Diffraction data*, University of Glasgow, Scotland, UK, Nonius BV, Delft, The Netherlands and MacScience Co. Ltd., Yokohama, Japan, 1998.

Received: 29th April 2003; Com. 03/2113