



## Molecular Crystals and Liquid Crystals

Publication details, including instructions for authors and subscription information:

<http://www.tandfonline.com/loi/gmcl16>

### Near Neighbour Correlations and the Dielectric Properties of Liquid Crystals

S. Chandrasekhar<sup>a</sup> & B. R. Ratna<sup>a</sup>

<sup>a</sup> Raman Research Institute, Bangalore, 560 080, India

Version of record first published: 20 Apr 2011.

To cite this article: S. Chandrasekhar & B. R. Ratna (1982): Near Neighbour Correlations and the Dielectric Properties of Liquid Crystals, *Molecular Crystals and Liquid Crystals*, 82:6, 193-198

To link to this article: <http://dx.doi.org/10.1080/01406568208247002>

PLEASE SCROLL DOWN FOR ARTICLE

Full terms and conditions of use: <http://www.tandfonline.com/page/terms-and-conditions>

This article may be used for research, teaching, and private study purposes. Any substantial or systematic reproduction, redistribution, reselling, loan, sub-licensing, systematic supply, or distribution in any form to anyone is expressly forbidden.

The publisher does not give any warranty express or implied or make any representation that the contents will be complete or accurate or up to date. The accuracy of any instructions, formulae, and drug doses should be independently verified with primary sources. The publisher shall not be liable for any loss, actions, claims, proceedings, demand, or costs or damages whatsoever or howsoever caused arising directly or indirectly in connection with or arising out of the use of this material.

## NEAR NEIGHBOUR CORRELATIONS AND THE DIELECTRIC PROPERTIES OF LIQUID CRYSTALS

S.CHANDRASEKHAR and B.R.RATNA  
 Raman Research Institute, Bangalore 560 080, India

(Submitted for publication June 11, 1982)

### Abstract

It is demonstrated experimentally that there can be a reversal of the sign of the dielectric anisotropy ( $\Delta\epsilon$ ) with decreasing temperature in a nematic. The results are explainable in terms of the Maier-Meier mean field theory and indicate that the occurrence of the smectic phase and the consequent dipole correlations within the smectic layers is not a necessary condition for the sign reversal of  $\Delta\epsilon$ .

The idea of near neighbour antiparallel correlations (or antiferroelectric short range order) in nematic liquid crystals composed of polar molecules was first proposed in 1973 and its consequences were discussed on the basis of the Bethe-Peierls cluster approximation.<sup>1</sup> A prediction of the theory is that the mean dielectric constant  $\bar{\epsilon}=(\epsilon_1+2\epsilon_2)/3$ , where  $\epsilon_1$  and  $\epsilon_2$  are the values along and perpendicular to the director, should show a discontinuous increase on going from the nematic to the isotropic phase. This has been found to be the case in a number of strongly positive materials,<sup>2-4</sup> the most striking confirmation being provided by the recent high precision measurements of Bradshaw and Raynes<sup>4</sup> on some cyano compounds which reveal even a pretransition effect in the antiparallel correlations. Negative dielectric anisotropy materials<sup>5</sup> also exhibit a discontinuous change in  $\bar{\epsilon}$  at  $T_{NI}$  evidently because of the antiparallel correlation of the longitudinal component ( $\mu_{\parallel}$ ) of the dipole moment. With non-polar materials,<sup>6</sup> on the other hand, there is no abrupt change in  $\bar{\epsilon}$  at  $T_{NI}$ .

A reversal of the sign of the dielectric anisotropy  $\Delta\epsilon=(\epsilon_1-\epsilon_2)$  with decrease of temperature has been observed in

a few compounds<sup>7,8</sup>,  $\Delta\epsilon$  changing from a relatively weak positive value near  $T_{NI}$  to a weak negative value at lower temperatures. As it happens, in these compounds this reversal is accompanied by the occurrence of a smectic A phase at lower temperatures. It has therefore been argued<sup>7,8</sup> that the smectic layer structure gives rise to a *parallel* correlation of  $\mu_t$ , the transverse component of the dipole moment, in addition to the antiparallel correlation of the longitudinal component  $\mu_l$ , thus resulting in a crossover of  $\epsilon_1$  and  $\epsilon_2$ . Now the smectic A layers are known to be *liquid-like*, and while it is true that the molecular distribution function in each layer cannot be strictly cylindrically symmetric as far as the near neighbours are concerned (since the molecules themselves are not cylindrically symmetric) the question arises as to whether the parallel correlations within each layer will be strong enough to bring about a reversal of the sign of  $\Delta\epsilon$ .

Another possible explanation of this unusual temperature variation of the dielectric anisotropy follows directly from the theory of Maier and Meier.<sup>5</sup> According to this theory

$$\Delta\epsilon = \epsilon_1 - \epsilon_2 = \frac{4\pi N_A \rho h F}{M} \left[ \alpha_a - \frac{F \mu^2}{2k_B T} (1 - 3\cos^2 \beta) \right] S \quad (1)$$

where  $\rho$  is the density,  $h$  the cavity field factor,  $F$  the reaction field factor,  $M$  the molecular weight,  $\alpha_a$  the polarizability anisotropy,  $\beta$  the angle which the net dipole moment ( $\mu$ ) makes with the long molecular axis and  $S$  the orientational order parameter. Consequently if the polarizability and permanent dipolar contributions in the square brackets on the right hand side of eqn.(1) are nearly balanced, there can be a reversal of  $\Delta\epsilon$  with temperature because of the factor  $T^{-1}$  in the second term. Indeed as was shown by us earlier<sup>9</sup> it is this  $T^{-1}$  factor which is responsible for the reversal of the sign of the Kerr constant of p-azoxyanisole (PAA) in the isotropic phase at  $T_{NI} + 5^\circ\text{K}$ . But if  $\beta$  of PAA had been slightly less than its actual value, the temperature at which  $\Delta\epsilon = 0$  would have occurred below  $T_{NI}$ . Theoretical curves illustrating this are shown in fig. 1; the parameters used in the curves are those for PAA with  $\alpha_a = 21 \text{ \AA}^3$ .

We now demonstrate experimentally that this sign reversal of  $\Delta\epsilon$  can actually be observed in nematics. In order to do this, measurements were made on PAA mixed with small quantities of a positive nematogen, 4'-n-pentyl-4-cyanoterphenyl (5CT) or 4-n-methoxybenzylidene-4'-phenylazoaniline (MBPAA). The mixture

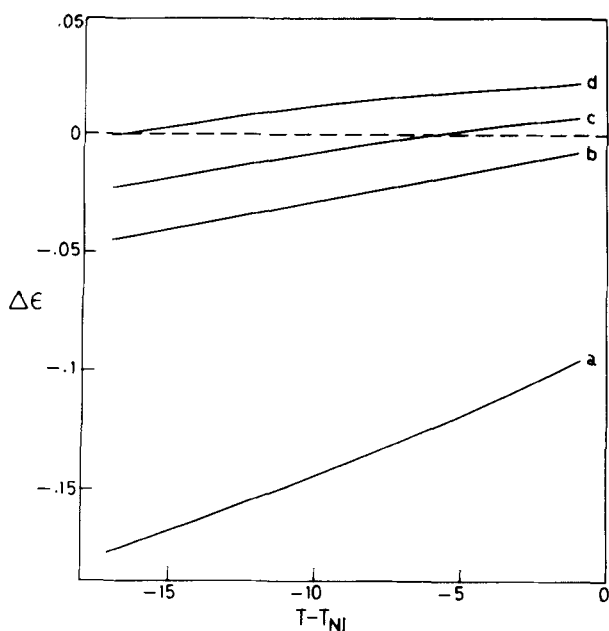


FIG.1 Theoretical curves calculated from eqn.(1) for various values of  $\beta$ : (a)  $64^\circ$ , (b)  $62.5^\circ$ , (c)  $62.25^\circ$  and (d)  $62^\circ$ .

are also purely nematogenic and do not show a smectic phase. The purpose of adding 5CT or MBPAA was to reduce the effective  $\beta$  of PAA slightly and to increase  $T_{NI}$  by a few degrees.

The crystal-nematic ( $T_{CN}$ ) and the nematic-isotropic ( $T_{NI}$ ) transition temperatures of the pure components are given in Table I below.

Table I

Compound	Molecular structure	$T_{CN}(^\circ\text{C})$	$T_{NI}(^\circ\text{C})$
PAA	<chem>COc1ccc(cc1)/N=N/c2ccc(cc2)OC</chem>	118	135.2
5CT	<chem>CCCCCc1ccc(cc1)-c2ccc(cc2)-c3ccc(cc3)C#N</chem>	130	239
MBPAA	<chem>COc1ccc(cc1)/C=N/c2ccc(cc2)/N=N/c3ccccc3</chem>	150	187.6

The principal dielectric constants were determined at 1592 Hz using a Wayne Kerr B642 bridge. Samples (125  $\mu\text{m}$  thick) were aligned using a 15 kgauss magnetic field.  $\epsilon_1(H \parallel E)$  and  $\epsilon_2(H \perp E)$  were measured on the same sample by rotating the cell through  $90^\circ$  at each temperature. Other experimental details are as described in an earlier paper.<sup>10</sup> Measurements were first made on pure PAA and it was ascertained that the values are in agreement with the reported data for this compound.<sup>5</sup> Fig.2 shows the dielectric constants  $\epsilon_1$  and  $\epsilon_2$  for a 99.3 PAA/0.7 5CT (mole %) mixture and fig.3 the dielectric anisotropy  $\Delta\epsilon$  for mixtures of two different compositions.

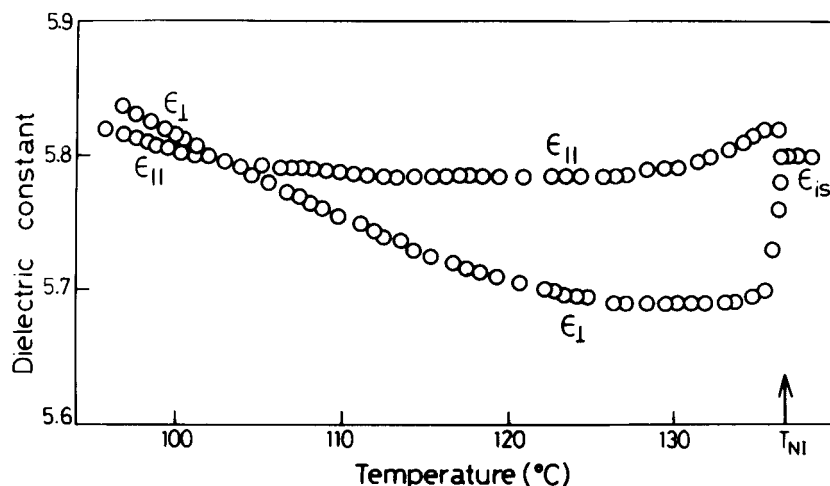


FIG.2 Principal dielectric constants of 99.3 PAA/0.7 5CT (mole %) mixture;  $T_{NI} = 136.6^\circ\text{C}$ .

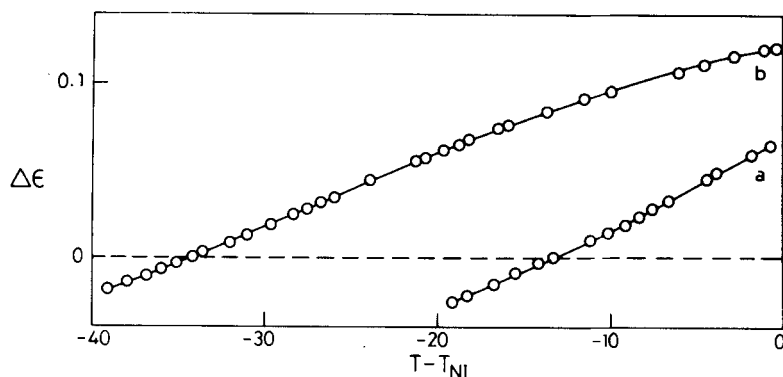


FIG.3 The dielectric anisotropy as a function of temperature for mixtures of PAA and 5CT. (a) 0.6 mole % 5CT;  $T_{NI} = 136.2^\circ\text{C}$ , (b) 0.7 mole % 5CT;  $T_{NI} = 136.6^\circ\text{C}$ .

The trends can be seen to be in qualitative accord with what is expected from the Maier-Meier theory - the crossover temperature decreasing with increasing proportion of the positive 5CT.

It was found that for concentrations greater than about 30 mole % of 5CT, the PAA/5CT mixture exhibits an induced smectic phase.<sup>11</sup> However it is extremely unlikely that this will affect the present conclusions which are based on measurements at very low concentrations of 5CT for which the mixture is purely nematogenic. Nevertheless to clinch the argument, measurements were also made on PAA/MBPAA mixtures. In this case the mixture shows only a nematic phase for all compositions (fig. 4). The temperature variation of  $\Delta\epsilon$  for mixtures of three different compositions are shown in fig.5 and again qualitatively the trend is as expected from the Maier-Meier theory. Thus it would seem reasonable to conclude that the parallel correlations within the smectic layers cannot be a dominant mechanism for the reversal of the sign of the dielectric anisotropy.

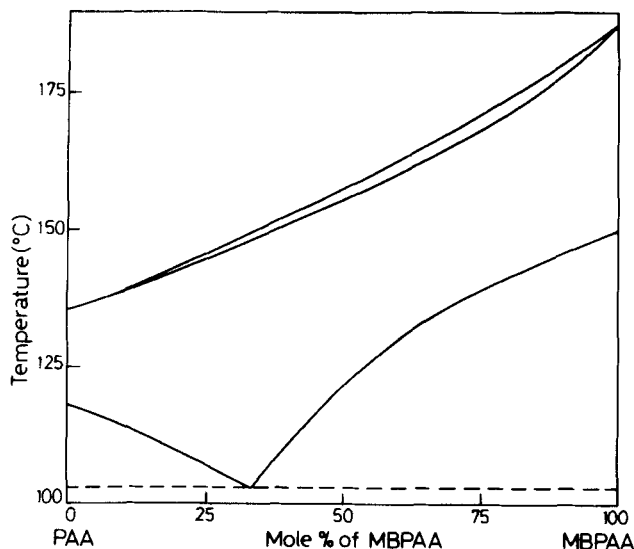


FIG.4 Phase diagram of mixtures of PAA and MBPAA.

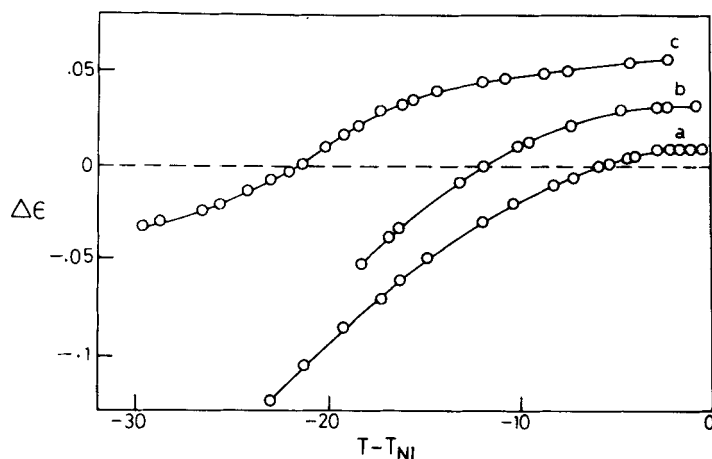


FIG.5 The dielectric anisotropy as a function of temperature for various concentrations of MBPAA in PAA: (a) 1.7 mole % MBPAA;  $T_{NI} = 135.6^{\circ}\text{C}$ , (b) 3.0 mole % MBPAA;  $T_{NI} = 136.0^{\circ}\text{C}$  and (c) 4.7 mole % MBPAA;  $T_{NI} = 136.6^{\circ}\text{C}$ .

### References

- 1 N.V.Madhusudana and S.Chandrasekhar, in 'Proceedings of the International Liquid Crystals Conference', Bangalore, December 1973, Pramana Supplement I, p.57; N.V.Madhusudana, K.L.Savithramma and S.Chandrasekhar, Pramana, **8**, 22 (1977).
- 2 M.Schadt, J.Chem.Phys. **56**, 1494 (1972).
- 3 B.R.Ratna and R.Shashidhar, Mol.Cryst.Liq.Cryst. **42**, 113 (1977).
- 4 M.J.Bradshaw and E.P.Raynes, Mol.Cryst.Liq.Cryst.Letters, **72**, 73 (1981)
- 5 W.Maier and G.Meier, Z.Naturforsch. **16a**, 262 (1961).
- 6 W.H.de Jeu and Th.W.Lathouwers, Z.Naturforsch. **29a**, 905 (1974).
- 7 W.H.de Jeu, W.J.A.Goossens and P.Bordewijk, J.Chem.Phys. **61**, 1985 (1974).
- 8 L.Benguigui, J.de Physique, **40**, 705 (1979).
- 9 N.V.Madhusudana and S.Chandrasekhar, Liquid Crystals and Ordered Fluids, Vol.2, Eds. J.F.Johnson and R.S.Porter, p.657, Plenum (1974).
- 10 B.R.Ratna and R.Shashidhar, Pramana, **6**, 278 (1976).
- 11 The complete phase diagram together with other studies of the PAA/5CT mixture will be reported separately.