

This article was downloaded by: [Tomsk State University of Control Systems and Radio]

On: 21 February 2013, At: 12:00

Publisher: Taylor & Francis

Informa Ltd Registered in England and Wales Registered Number: 1072954  
Registered office: Mortimer House, 37-41 Mortimer Street, London W1T 3JH, UK



## Molecular Crystals and Liquid Crystals

Publication details, including instructions for authors and subscription information:

<http://www.tandfonline.com/loi/gmcl16>

### The Influence of the Finite Size of the Light Spot on the Laser Induced Reorientation of Liquid Crystals

L. Csillag<sup>a</sup>, I. Jánossy<sup>a</sup>, V. F. Kitaeva<sup>b</sup>, N. Kroo<sup>a</sup>  
& N. N. Sobolev<sup>b</sup>

<sup>a</sup> Central Research Institute for Physics, Budapest  
114. P.O.B. 49, Hungary

<sup>b</sup> Lebedev Physical Institute, Moscow, USSR

Version of record first published: 14 Oct 2011.

To cite this article: L. Csillag, I. Jánossy, V. F. Kitaeva, N. Kroo & N. N. Sobolev (1982): The Influence of the Finite Size of the Light Spot on the Laser Induced Reorientation of Liquid Crystals, *Molecular Crystals and Liquid Crystals*, 84:1, 125-135

To link to this article: <http://dx.doi.org/10.1080/00268948208072136>

PLEASE SCROLL DOWN FOR ARTICLE

Full terms and conditions of use: <http://www.tandfonline.com/page/terms-and-conditions>

This article may be used for research, teaching, and private study purposes. Any substantial or systematic reproduction, redistribution, reselling, loan, sub-licensing, systematic supply, or distribution in any form to anyone is expressly forbidden.

The publisher does not give any warranty express or implied or make any representation that the contents will be complete or accurate or up to

date. The accuracy of any instructions, formulae, and drug doses should be independently verified with primary sources. The publisher shall not be liable for any loss, actions, claims, proceedings, demand, or costs or damages whatsoever or howsoever caused arising directly or indirectly in connection with or arising out of the use of this material.

# The Influence of the Finite Size of the Light Spot on the Laser Induced Reorientation of Liquid Crystals

L. CSILLAG, I. JÁNOSSY, V. F. KITAEVA,\* N. KROO  
and N. N. SOBOLEV\*

*Central Research Institute for Physics, Budapest 114. P.O.B. 49, Hungary*  
*\*Lebedev Physical Institute, Moscow, USSR*

*(Received July 31, 1981)*

The threshold intensity for the laser induced deformation of nematic liquid crystals is calculated as a function of the spot size of the illuminating beam. It is shown, that due to the small size of the light spot, the optical threshold is higher than that expected from the Fredericks threshold formula for static electric fields of infinite large dimension in the cell plane. Experimental data measured on a homeotrop OCB (octyl-cyano-biphenyl) sample fit well the theoretical curve. Results obtained on the temperature and wavelength dependence of the threshold can be interpreted on the basis of the given theory.

## 1 INTRODUCTION

As it was reported by us previously,<sup>1</sup> by illuminating a nematic liquid crystal-line film with a focused laser beam, an increase in the beam divergence and a ring system appearing in it can be detected. This effect could be explained as an orientational deformation due to a Fredericks transition in optical fields. It has been shown, that in analogy with the static Fredericks effect, for homeotrop cell and at normal incidence this deformation starts only above a certain threshold laser power. The focused laser light, however, has a spatial intensity distribution—in the simplest case a Gaussian distribution—with a half-width of some tens of microns which is comparable with the sample thickness. Therefore it can be expected, that the actual optical threshold value differs from that of the Fredericks transition in a static electric field with practically infinite large dimensions in the cell plane.

This problem is studied in this paper both theoretically and experimentally. First we calculate the value of the laser intensity threshold by a simplified

model for the case of a homeotrop nematic cell and at normal incidence of the laser beam. Then experimental results on a nematic OCB (octyl-cyanobiphenyl) sample are described showing that good agreement exists between the theoretically expected and the measured values. Additional measurements are also reported on the temperature and wavelength dependence of this threshold value giving a further support to our calculations.

## 2 CALCULATION OF THE THRESHOLD

We investigate a homeotropic sandwich-like cell of a nematic liquid crystal (NLC), in which the  $L$  director is fixed uniformly at the boundaries, and which is illuminated with a linearly polarized and focused laser beam. It is assumed that the focal length of the focusing lens is large enough so that the laser beam can be considered as a parallel beam within the sample.

The light beam interacts with the molecules through its electric field  $E$ . The torque  $\Gamma^{(E)}$  induced by  $E$  in a nematic is then

$$\Gamma^{(E)} = D \times E = \epsilon_o \epsilon_a E L (E \times L)$$

where  $\epsilon_a$  is the anisotropy of the dielectric constant;  $\epsilon_a = n_e^2 - n_o^2$ ,  $n_e$ ,  $n_o$  being the extraordinary and ordinary refractive indices. We study only the cases, when  $n_e > n_o$ .

We choose the coordinate system so, that the cell plane coincides with the ( $x$ ,  $y$ ) plane (vertical plane), and the  $L$  director is parallel with the  $z$  axis,  $L \parallel z$ . The light beam has a polarization in the  $x$  direction (in the horizontal plane) falling perpendicularly on the cell, so the propagation vector  $k \parallel z$  and  $L$ .

The stationary configuration can be determined in general from the balance between the electric and elastic torques. In our case there is always a trivial solution for the balance; the unperturbed configuration, in which  $L \equiv (0, 0, 1)$ . To calculate the threshold we follow the usual procedure looking for the value of the light intensity at which the linearized equation of the balance of torques has a non-trivial solution.

The exact solution of the problem is very complicated. Therefore two simplifications will be used. First, we assume that the elastic constants are equal; second, the actual Gaussian transversal intensity distribution will be replaced by a  $\Pi$ -shape distribution.

In the one constant approximation the elastic torque is<sup>2</sup>

$$\Gamma^{(e)} = KL \times \Delta L$$

where  $K$  denotes the Frank elastic constant. The director turns in this approximation only in the ( $x$ ,  $z$ ) plane, and both the elastic and electric torque has only a  $y$ -component.

In linear approximation the elastic torque is

$$\Gamma_y^{(e)} = K \Delta \theta$$

with  $\theta = L_x$ ; while the electric torque can be given as

$$\Gamma_y^{(E)} = \epsilon_o \epsilon_a E_x (\theta E_x + E_z).$$

$E_x$  is determined by the continuity of the tangential component of  $E$ ;  $E_x = E_o$ , where  $E_o$  is the electric vector of the incoming light beam.  $E_z$  can be calculated from the condition  $D_z = 0$ , which leads to

$$E_z = -\frac{\epsilon_a}{n_e^2} \theta E_x$$

With the above values of  $E_z$  and  $E_x$  we get

$$\Gamma_y^{(E)} = \epsilon_o \epsilon_a \frac{n_o^2}{n_e^2} E_o^2 \theta.$$

The linearized equation of torques is

$$K \Delta \theta + \epsilon_o \epsilon_a \frac{n_o^2}{n_e^2} E_o^2 \theta = 0.$$

Taking into account that  $E_o$  is only a function of the distance  $r$  from the center of the laser beam,  $\theta$  can be written as

$$\theta(r, z) = \theta_o(r) \sin \frac{\pi}{l} z$$

( $l$  denotes the sample thickness), where  $\theta_o$  obeys the equation

$$\frac{\partial^2 \theta_o}{\partial r^2} + \frac{1}{r} \frac{\partial \theta_o}{\partial r} + \left[ \frac{\epsilon_o \epsilon_a}{K} \frac{n_o^2}{n_e^2} E_o^2(r) - \left( \frac{\pi}{l} \right)^2 \right] \theta_o = 0 \quad (1)$$

In the actual experiments  $E_o^2(r)$  is a Gaussian function:

$$E_o^2(r) = \epsilon^2 \exp(-r^2/r_o^2).$$

Here we take for simplicity

$$E_o^2(r) = \begin{cases} \epsilon^2 & r < r_o \\ 0 & r > r_o \end{cases}$$

where  $r_o$  is an "effective" radius of the laser beam. (The connection between  $r_o$  and the full width of the beam at half maximum (FWHM),  $\delta = 2(\ln 2)^{1/2} r_o$ ). In this case the non-trivial solution of Eq. (1) with boundary conditions  $\theta_o(0) = 1, \theta_o'(0) = 0$  and  $\theta_o \rightarrow 0$  for  $r \rightarrow \infty$  is

$$\theta_o(r) = \begin{cases} J_o(\lambda r) & r < r_o \\ aK_o(\mu r) & r > r_o \end{cases}$$

where  $J_o$  and  $K_o$  denote the 0-order Bessel and modified Hankel functions resp. (3) and

$$\lambda^2 = \epsilon^2 \frac{\epsilon_o \epsilon_a}{K} \frac{n_o^2}{n_e^2} - \left( \frac{\pi}{l} \right)^2; \quad \mu = \frac{\pi}{l}.$$

$\lambda$  can be determined from the condition, that both  $\theta_o$  and  $\partial\theta_o/\partial r$  should be continuous at  $r_o$ . This condition leads to

$$\gamma \frac{J'_o(\gamma)}{J_o(\gamma)} = \kappa \frac{K'_o(\kappa)}{K_o(\kappa)} \quad (2)$$

with  $\gamma = \lambda r_o$ ,  $\kappa = \mu r_o = \pi r_o/l$ . The solution of Eq. (2) is given in Figure 1.

The power of the light beam is in the cell

$$P = cr_o^2 \pi \epsilon_o n_o \epsilon^2 (c \text{ light velocity})$$

The threshold power therefore can be written as

$$P_{th} = P_o(\gamma^2(\kappa) + \kappa^2) \quad (3)$$

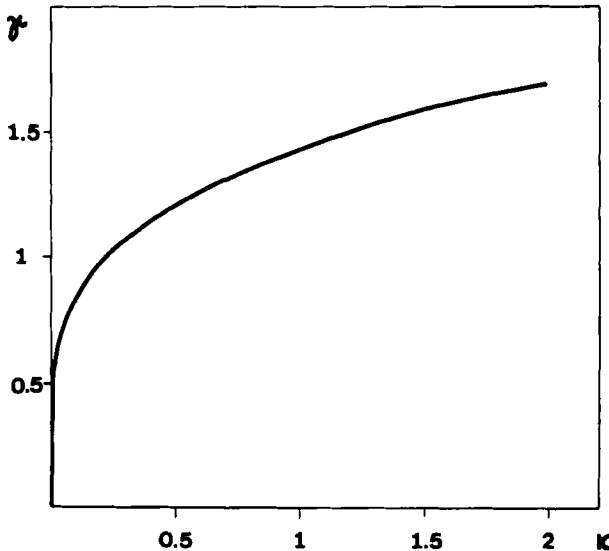


FIGURE 1 The solution of Eq. (2).

with

$$P_o = \frac{c \pi K}{n_e^2 - n_o^2} \frac{n_e^2}{n_o}. \quad (4)$$

In Figure 2,  $P/P_o$  is given as a function of  $r_o/l$  (full line). The dashed line on this figure gives the threshold, if we apply simply the Fredericks threshold formula  $\epsilon_{th} = \pi/l(K/\epsilon_o\epsilon_a)^{1/2}$ . The difference between the two curves is remarkable. The ratio of the two thresholds goes to infinity as  $r_o/l \rightarrow 0$ . Therefore we can conclude, that it is very important to take into account the finite radius of the laser beam.

It is interesting to note that even for very large  $r_o/l$  values  $\epsilon_{th}$  does not reduce to the usual Fredericks formula. In this limit

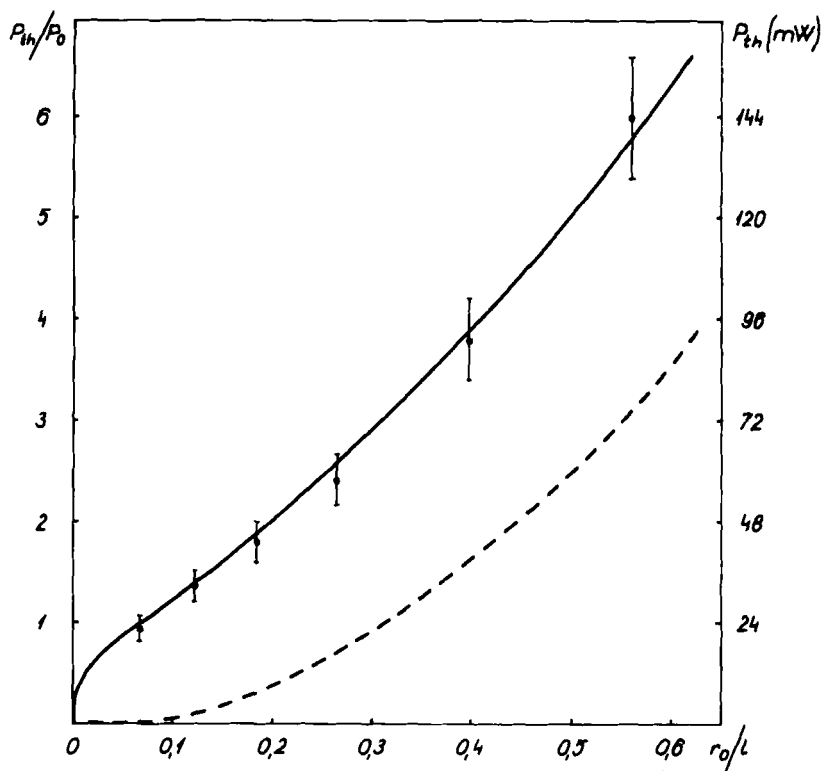


FIGURE 2 Full line:  $P_{th}/P_o$  as a function of  $r_o/l$  according to our model. Dashed line: the power corresponding to the Fredericks threshold formula. The experimental points were measured on OCB at 36.5°C; the power scale for this measurement is given at the right hand side of the figure. A good agreement between theory and experiment is obtained with  $P_o = 24$  mW.

$$\epsilon_{th} = \frac{n_e}{n_o} \frac{\pi}{l} \left( \frac{K}{\epsilon_o \epsilon_a} \right)^{1/2} \quad (r_o/l \rightarrow \infty).$$

The factor  $n_e/n_o$  comes from the coupling between the light propagation and the deformation field. The importance of this coupling has been emphasized in a previous publication.<sup>1</sup>

### 3 EXPERIMENTAL

For the experimental verification of the curve corresponding to the formula (3), two measurements were carried out. In the first exploratory experiment a homeotrop nematic MBBA cell of 150  $\mu\text{m}$  thickness was illuminated with an argon ion laser beam of 65  $\mu\text{m}$  diameter (FWHM).<sup>1</sup> At 21.5°C we got for the threshold  $45 \pm 10$  mW, while the theoretically expected value was 35 mW, which we found to be satisfactory, taking into account the simplifying assumptions and experimental uncertainties.

In the second, more accurate and detailed investigation a homeotropic OCB sandwich-like cell of 150  $\mu\text{m}$  thickness was studied. The aim of this work was to investigate the dependence of the threshold laser power first on the spot size of the focused laser beam in the middle of the nematic temperature range (36.5°C) and then its dependence on temperature in the nematic range as well as its dependence on the wavelength in the visible region.

The experimental setup was similar to that described earlier.<sup>1</sup> The linearly polarized beam of an argon ion laser, oscillating at 515 nm in the fundamental transversal ( $\text{TEM}_{00}$ ) mode, was focused with lenses of different focal lengths to a small spot onto the NLC sample. The polarization plane of the incoming beam could be changed with the aid of a polarization rotator (Spectra Physics Model 310-21). The cell consisted of two circular glass plates separated with a teflon spacer of 150  $\mu\text{m}$  thickness and sealed off with an epoxy resin. The homeotropic alignment was achieved by treating the glass surfaces with a weak solution of CTAB in chloroform.<sup>4</sup> The alignment was carefully tested with the conoscopic method. The normal incidence of the beam was adjusted carefully with the aid of the spot reflected from the cell boundaries.

The laser power was measured with a Spectra Physics power meter (Model 404), which had a calibration accuracy of  $\pm 15\%$ . Our power values refer always to the plane of the NLC sample i.e., the reflection losses on the lens and windows are taken into account. The intensity stability of the laser was better than 0.5%.

For focusing the laser beam, six lenses with different focal lengths ( $7.5 \div 50$  cm) and of different quality were used. The lenses were always carefully adjusted for paraxial beam propagation. At a given lens, the minimal beam diameter of the focused beam could be determined with the effect itself; at a con-



stant laser power the lens position was changed till the maximal number of fringes could be observed.

The intensity distribution in the sample plane was scanned with a pinhole of  $5\ \mu\text{m}$  diameter mounted on a linear stage, which could be moved across the beam with an accuracy of  $\pm 0.2\ \mu\text{m}$ . In all cases we got a nearly Gaussian intensity distribution. Some examples are given in Figure 3.

It should be mentioned here that according to the laser beam propagation laws,<sup>5</sup> the size of the focused beam near its minimum changes very slowly; in our case, over the  $150\ \mu\text{m}$  thickness of the cell, the variation of the beam diameter was less than 1% even for the lens of shortest focal length ( $f = 7.5\ \text{cm}$ ).

For determining the threshold, the diameter of the largest dark ring, observed in the transmitted beam on a screen was measured as a function of the incident laser power; this dependence proved to be nearly linear below 10 rings (Figure 4). We defined the threshold as the intersection point of this line with the power axis.

All measurements were carried out on the same OCB sample, in a time interval of about one month. During this time no ageing could be observed.

The temperature of the cell was controlled by a water thermostat, with an accuracy of  $\pm 0.2^\circ\text{C}$ .

At each measuring point, after starting the illumination we waited till the

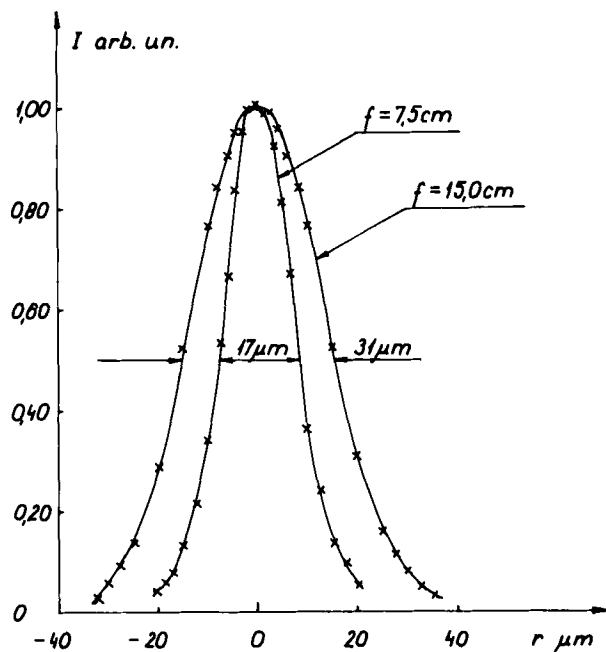


FIGURE 3 Intensity distribution of the laser beam at the sample with different lenses.

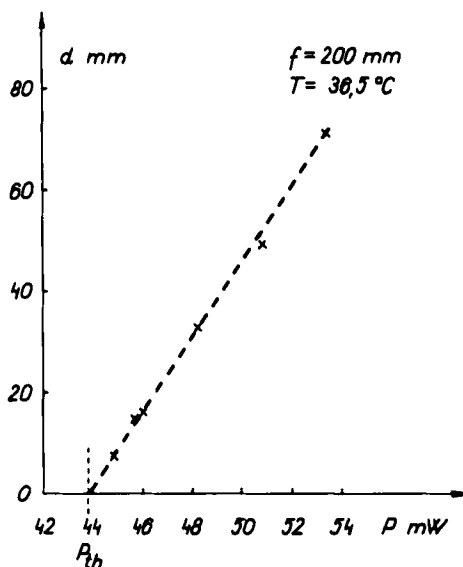


FIGURE 4 The diameter of the largest dark ring as a function of the incident laser power.

pattern had stabilized; this sometimes lasted at low power levels about 10–15 minutes. Between two measurements there was always a 1–2 minutes pause to avoid memory effects. The measurements were carried out repeatedly, at different places of the cell and with different planes of polarization of the incident beam. Places with the smallest diffuse light scattering were always chosen. The results measured under different conditions commonly did not differ more than a few mW. The spread amounted  $\pm 2$  mW with the lens  $f = 15$  cm and  $\pm 5$  mW with that of 30 cm focus resp., i.e., the statistical error in our measurement was  $\pm 10\%$ . It should be noted, that there may still be an additional systematic error of  $\pm 15\%$  due to the calibration accuracy of the power meter, which could be the main source of the error in  $P_o$  and especially in the wavelength dependence of  $P_{th}$ .

## 4 RESULTS

The threshold intensity was measured as a function of the spot size at a fixed temperature ( $36.5^\circ\text{C}$ ). The experimental data are given in Figure 1. A good agreement between the theoretical curve and the experimental data is found with  $P_o = 24$  mW.

The theoretical expression for  $P_o$ , given by Eq. (3) contains the material parameters of the nematic. In the actual case  $P_o$  can be determined however only with a certain arbitrariness, because our theoretical model assumes that the

elastic constants are equal, while in reality they are different. Therefore, to compare the theoretical and experimental values, we invert Eq. (3) and evaluate an "effective" elastic constant from the threshold value. Using the experimental data of Karat *et al.*<sup>6</sup>  $n_e = 1.678$ ;  $n_o = 1.533$  (36.5°C,  $\lambda = 515$  nm extrapolated from 546 and 589 nm) and taking  $P_o = 24$  mW we get

$$K_{\text{eff}} = (0.66 \pm 0.1) \times 10^{-11} \text{ N}.$$

According to Karat *et al.*<sup>7</sup> the actual values of the elastic constants at this temperature are:

$$K_1 = 1.07 \times 10^{-11} \text{ N}; \quad K_2 = 0.45 \times 10^{-11} \text{ N}; \quad K_3 = 1.05 \times 10^{-11} \text{ N}.$$

Thus  $K_{\text{eff}}$  is comparable with the elastic constants measured independently.

In further experiments the temperature and wavelength dependence of the threshold was measured at a fixed spot size. The temperature dependence of the threshold was determined at  $r_o = 18.6 \mu\text{m}$ . The results are given in Table I; in Figure 5 the effective elastic constant, determined from the thresholds is plotted against the temperature. For comparison the elastic data of Karat *et al.*<sup>7</sup> are presented in the same figure. As it can be seen, the effective elastic constant is in the whole temperature range near to  $K_1$  and  $K_3$  and it shows a pre-transitional increase below 35°C. This increase can be evidently attributed to the sharp increase of  $K_2$  and  $K_3$  in the same temperature region.

The wavelength dependence of the threshold was investigated by comparing the thresholds for 515 nm (a green line of the argon laser) with that for two different wavelengths: for a blue line of the same argon ion laser (476 nm) and for the red line of an He-Ne laser (633 nm).

In the case of the blue line, the measured threshold, with a spot diameter of  $30 \mu\text{m}$  ( $f = 15$  cm lens) and at 36.5°C temperature:

$$P_{th}(476 \text{ nm}, 30 \mu\text{m}, 36.5^\circ\text{C}) = (31.2 \pm 4) \text{ mW},$$

For 515 nm:

$$P_{th}(515 \text{ nm}, 30 \mu\text{m}, 36.5^\circ\text{C}) = (33 \pm 4) \text{ mW}.$$

In the case of the red He-Ne laser, higher temperature and lens with the shortest focus ( $f = 7.5$  cm) had to be used due to the smaller power available.

TABLE I

Temperature dependence of laser threshold ( $f = 150$  nm, OCB homeotrop cell,  $l = 150 \mu\text{m}$ , normal incidence,  $\lambda = 515$  nm)

$t^\circ\text{C}$	34.0	34.4	34.8	36.3	38.0	39.4
$P_{th}$ mW	51.0	43.5	38.0	34.0	29.0	24.5

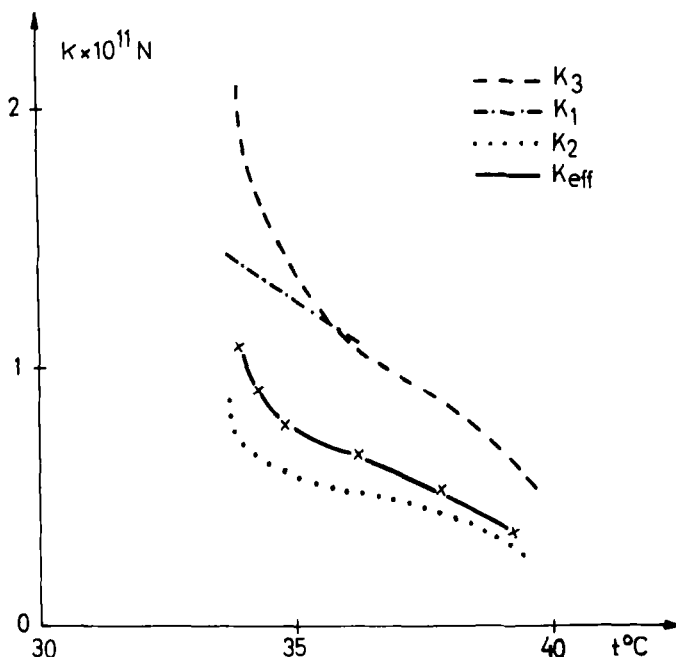


FIGURE 5 The effective elastic constant as a function of the temperature (full line). For comparison the elastic data of Karat and Madhusudana<sup>7</sup> are presented also.

We found with a spot diameter of  $27\ \mu\text{m}$  and at  $38^\circ\text{C}$ :

$$P_{th}(633\ \text{nm}, 27\ \mu\text{m}, 38^\circ\text{C}) = (25.6 \pm 4)\text{mW},$$

while for  $515\ \text{nm}$ :

$$P_{th}(515\ \text{nm}, 27\ \mu\text{m}, 38^\circ\text{C}) = (26 \pm 4)\text{mW},$$

In both cases the thresholds proved to be practically the same.

The theoretical formula, Eq. (3) predicts a very slow variation of  $P_{th}$  with the wavelength, i.e., as  $n_e^2/n_o(n_e^2 - n_o^2)^{-1}$  changes with  $\lambda$ . These small changes, however are well inside the experimental error and we can conclude, that the observed very weak dependence on the wavelength gives additional support to our interpretation of the effect.

## 5 SUMMARY

In the paper we described a simple theoretical model of the Fredericks transition induced by optical fields. This model predicts the threshold intensity as a function of the spot size of the laser beam. The experimental data fit well the theoretical curve. From the fitting parameter,  $P_o$ , and "effective" elastic con-

stant was determined, which turned out to be for OCB near to the actual elastic constants. The temperature dependence of  $K_{eff}$  followed well the temperature dependence of  $K_3$ ; in particular the same pretransitional increase was found near to the nematic-smectic A transition. The wavelength dependence of the threshold was found to be weak, in agreement with the theory.

In conclusion, the theoretical model explains the main features of the experimental observations and provides a reliable numerical value for the threshold. This proves the underlying idea, i.e. that the observed phenomena is due to a Fredericks transition in optical field, which can be described by the continuum theory of nematics, taking into account the finite size of the deforming light beam.

The theory, used here involves two simplifications. First, it assumes a  $\Pi$  shape instead of a Gaussian. This approximation could be overcome by some numerical calculation; it is however doubtful whether this would be worthwhile if at the same time the second simplification, the one constant approximation were maintained.

The theory becomes much more complicated if the elastic constants are not assumed to be equal. As it can be shown, if  $K_1 \neq K_2$  the cylindrical symmetry of the deformation is lost. Furthermore in this case the  $\theta$  variable is not sufficient to describe the deformation, because the director should have an  $y$ -component too. In addition the coupling between the electromagnetic wave and the director field becomes more complicated in the presence of such deformation. All these circumstances cause considerable mathematical difficulties. On the other hand they may give rise to some original features in the cases of circularly polarized light beam or slightly oblique incidence, which cannot be described by our simplified model. Further work is planned in this direction.

## References

1. L. Csillag, I. Jánossy, V. F. Kitaeva, N. Kroó, N. N. Sobolev and A. S. Zolotko, to be published in *Mol. Cryst. Liq. Cryst.*
2. P. G. de Gennes, *The Physics of Liquid Crystals*, Clarendon Press, Oxford, 1974.
3. Janke-Emde-Lösch, *Tafeln höherer funktionen*, B. G. Teubner Verlagsgesellschaft, Stuttgart, 1960.
4. J. E. Proust and L. Ter-Minassian-Saraga, *Solid State Comm.*, **11**, 1227 (1972).
5. H. Kogelnik and T. Li, *Proc. IEEE*, **54**, 1312 (1966).
6. P. P. Karat and N. V. Madhusudana, *Mol. Cryst. Liq. Cryst.*, **36**, 51 (1976).
7. P. P. Karat and N. V. Madhusudana, *Mol. Cryst. Liq. Cryst.*, **40**, 239 (1977).

Note: Since the submission of our manuscript we became aware of some new theoretical and experimental investigations closely related to our recent work:

- B. Ya. Zel'dovich, N. V. Tabirian and B. S. Chilingarian, *ZhETF*, **81**, 72-83 (1981).  
S. D. Durbin, S. M. Arakelian and Y. R. Shen, *Optic Letters*, **6**, 411-413 (1981).