

This article was downloaded by: [Tomsk State University of Control Systems and Radio]

On: 20 February 2013, At: 11:50

Publisher: Taylor & Francis

Informa Ltd Registered in England and Wales Registered Number: 1072954

Registered office: Mortimer House, 37-41 Mortimer Street, London W1T 3JH, UK



## Molecular Crystals and Liquid Crystals

Publication details, including instructions for authors and subscription information:

<http://www.tandfonline.com/loi/gmcl16>

### NMR and X-ray Investigations of a Plastic Crystalline Phase in MBBA

S. Arumugam<sup>a</sup>, S. V. Bhat<sup>a</sup>, N. Kumar<sup>a</sup>, K. V. Ramanathan<sup>a b</sup> & R. Srinivasan<sup>a</sup>

<sup>a</sup> Department of Physics, Indian Institute of Science, Bangalore, 560 012

<sup>b</sup> Sophisticated Instruments Facility, Indian Institute of Science, Bangalore, 560 012

Version of record first published: 28 Mar 2007.

To cite this article: S. Arumugam, S. V. Bhat, N. Kumar, K. V. Ramanathan & R. Srinivasan (1985): NMR and X-ray Investigations of a Plastic Crystalline Phase in MBBA, *Molecular Crystals and Liquid Crystals*, 126:2-4, 161-173

To link to this article: <http://dx.doi.org/10.1080/00268948508084787>

PLEASE SCROLL DOWN FOR ARTICLE

Full terms and conditions of use: <http://www.tandfonline.com/page/terms-and-conditions>

This article may be used for research, teaching, and private study purposes. Any substantial or systematic reproduction, redistribution, reselling, loan, sub-licensing, systematic supply, or distribution in any form to anyone is expressly forbidden.

The publisher does not give any warranty express or implied or make any representation that the contents will be complete or accurate or up to date. The accuracy of any instructions, formulae, and drug doses should be

independently verified with primary sources. The publisher shall not be liable for any loss, actions, claims, proceedings, demand, or costs or damages whatsoever or howsoever caused arising directly or indirectly in connection with or arising out of the use of this material.

# NMR and X-ray Investigations of a Plastic Crystalline Phase in MBBA

S. ARUMUGAM, S. V. BHAT, N. KUMAR, K. V. RAMANATHAN<sup>†</sup>  
and R. SRINIVASAN<sup>‡</sup>

*Department of Physics, Indian Institute of Science, Bangalore 560 012*

*(Received June 29, 1984; in final form September 12, 1984)*

Wideline and high resolution NMR studies have been carried out on MBBA in its isotropic, nematic and solid phases. Isotropic and nematic phase spectra correspond to what has been reported earlier. In the solid phase, contrary to expectations, very intense narrow signals similar to signals of the isotropic phase have been observed for the first time at temperatures close to the solid  $\leftrightarrow$  nematic phase transition temperature. This indicates rapid reorientational or translational motion in the system. The X-ray results however confirm the existence of translational order. The results are interpreted as indicative of the existence of a plastic crystalline phase in MBBA.

## 1. INTRODUCTION

The mesomorphic and solid-state polymorphic behaviour of liquid crystals in  $n0.m$  ( $C_nH_{2n+1}$  OPhCHNPhC<sub>m</sub>H<sub>2m+1</sub>) series of compounds have recently attracted a great deal of attention.<sup>1</sup> In particular, the compound 10.4 (N-p-methoxybenzylidene-p-n-butylaniline-MBBA) has been shown to exhibit complex polymorphic behaviour below its 'melting temperature' of 22°C. Through adiabatic calorimetry, Mayer et al.,<sup>2,3</sup> measured the temperature dependence of the specific heat of MBBA and interpreted their results as indicative of the existence of a metastable crystalline state in addition to a stable crystalline state and a glassy nematic phase.<sup>4</sup> X-ray powder pattern studies of Lydon and Kessler<sup>5</sup> show anomalous behaviour around 15°C, in that the diffraction peak at  $2\theta = 5.2^\circ$  gains intensity before

<sup>†</sup>Sophisticated Instruments Facility, Indian Institute of Science, Bangalore 560 012.

<sup>‡</sup>Since then deceased. This paper is dedicated to the memory of late Prof. R. Srinivasan.

finally losing it. The authors offer two possible explanations for this behaviour, in terms of (a) a monotropic metastable crystal  $\rightarrow$  nematic transition followed by the formation of the stable crystalline form, or (b) the possibility of a monotropic smectic phase and the nematic phase. A large number of other experimental investigations such as calorimetry and dielectric studies,<sup>6</sup> infrared<sup>7,8</sup> and Raman spectroscopy,<sup>9-12</sup> positron life-time measurements,<sup>13,14</sup> neutron diffraction,<sup>15</sup> ESR spin probe<sup>16,17</sup> and some NMR studies<sup>4,18-22</sup> have been directed towards the understanding of the nature of the polymorphism in MBBA. Even though there is general agreement among these reports regarding the occurrence of a number of distinct phases in solid MBBA, the nature of these phases is not yet unambiguously established.

We undertook wideline proton NMR studies at ambient pressure and under high hydrostatic pressures, high resolution NMR and X-ray powder diffraction studies of MBBA to clarify its rather complex behaviour below its nematic phase. The analysis of these results presented below lead us to the conclusion that MBBA exhibits a plastic crystalline state just below its nematic phase. To the best of our knowledge this is the first report of the occurrence of a plastic crystalline phase in a substance which also exhibits liquid crystalline order. A preliminary account of this work has been published earlier.<sup>23</sup>

## 2. EXPERIMENTAL

### 2.1 Sample

MBBA has the tendency to absorb moisture and decompose into anisaldehyde and p-butylaniline<sup>24</sup> and the nematic to isotropic transition temperature ( $T_{NI}$ ) decreases drastically in the presence of such molecules. In the present studies MBBA was repeatedly distilled under vacuum of about 0.1 torr. The experiments were all carried out almost immediately after the distillation after sealing the sample in a tube. The temperature  $T_{NI}$  for the sample was 45.8°C and was measured both by DSC and proton NMR. Further distillation did not increase the transition temperature  $T_{NI}$ .

### 2.2 Wideline NMR

Wideline NMR experiments were performed at 10 MHz using a home made oscillator-detector system with a Varian magnet. Temperature variation was carried out by passing cold nitrogen gas through a glass Dewar wherein the sample was kept. Above the room temperature, the nitrogen gas was heated and passed on to the sample. One junction

of the copper-constantan thermocouple was kept right inside the sample and the other junction in a reference ice-bath. Very low amplitude for modulation was used to avoid modulation broadening and it was possible to see in the spectrum the structure at the centre of the signal in the nematic phase. For studies at high pressures a beryllium-copper (Be-Cu) lock-nut type<sup>25</sup> pressure vessel which can withstand a pressure of 14 kbars was used. The sample was kept inside a teflon tube which was placed inside the radio frequency coil which in turn was kept in another teflon tube. The space was filled with silver chloride which acted as a pressure transmitting medium. Pressure experiments were carried out up to 5 kbars. At ambient pressure, only the smaller teflon tube was used, wherein the sample was transferred quickly and tightly sealed so that no moisture could get in. In these experiments the accuracy in temperature measurement was  $\pm 1^\circ\text{C}$ . To start with, the experiment was carried out in the temperature region  $-196^\circ\text{C}$  to  $50^\circ\text{C}$  and later it was concentrated in the region of nematic phase and just below it.

### 2.3 High resolution NMR

Spectra were recorded using a Bruker WH-270 spectrometer operating in the FT mode.  $^1\text{H}$ ,  $^{13}\text{C}$  and  $^2\text{H}$  resonances were recorded with the frequencies of operation being 270, 67.89 and 41.44 MHz respectively. Both  $^{13}\text{C}$  and  $^2\text{H}$  spectra were recorded with broad-band decoupling of proton resonances being employed. 5 mm dia sample tube was used for recording  $^1\text{H}$  spectra and 10 mm dia sample tube was used for recording  $^2\text{H}$  and  $^{13}\text{C}$  spectra. Temperature variation was carried out using Bruker B-ST 100/700 temperature controller. The readings of the controller were also calibrated by directly measuring the sample temperature in a separate experiment. The accuracy in measuring the temperature was  $\pm 1^\circ\text{C}$ . The experiments were carried out in the isotropic phase, nematic phase and below the nematic phase down to  $-60^\circ\text{C}$ .

## 3. RESULTS


### 3.1 NMR Studies

In the wideline NMR experiment, first the sample was heated to  $48^\circ\text{C}$  and the PMR spectrum corresponding to the isotropic phase was observed. The sample was cooled slowly and just below the isotropic  $\leftrightarrow$  nematic transition wings started appearing and these wings were moving out on further cooling the sample. These observations are in

accordance with the results reported earlier.<sup>26</sup> While cooling, the wings were present down to 13°C. Further cooling of the sample resulted in the sudden appearance of a sharp signal at the centre and the disappearance of the wings. Proceeding further, it was observed that, the intensity of the central sharp signal reduced drastically down to -5°C and slowly thereafter and finally disappeared at -40°C. With higher modulation it could be observed with very much reduced intensity on a broad background signal. At -68°C even this disappeared completely and further cooling of the sample resulted in broadening of the entire signal. Figure 1 shows the wideline NMR spectra recorded in the isotropic and nematic phases and at temperatures just below and well below the nematic phase. While heating from -196°C the strong sharp signal appeared again and was present till 19°C. Above this temperature this disappeared and signal, characteristic of nematic phase, appeared. These results are quite unexpected since the solid phase being an ordered phase all translational motions are expected to freeze. Consequently the NMR line is expected to be broader in the solid phase than in the nematic phase due to increased dipolar couplings. However, the observation in the solid phase of an intense sharp line and the absence of wings which were present in the nematic phase indicates that in the phase below the nematic phase there is a high degree of reorientational motion of the molecules.

When MBBA was subjected to 1.5 kbars of hydrostatic pressure, the sharp signal which appeared at low temperature and at ambient pressure, appeared at room temperature itself. The nematic and isotropic phases were reached by heating the sample to about 55°C and 76°C respectively. At 3 kbar and at room temperature, the sharp signal was still present but with reduced intensity. At this pressure we did not attempt to reach the isotropic phase, because heating the Be-Cu pressure cell will weaken the material. At 5 kbar pressure the sharp signal was not present even at room temperature.

High resolution proton magnetic resonance spectrum recorded in the isotropic phase of MBBA is shown in Figure 2 (a). The assignment of the spectrum has already been reported in the literature.<sup>26</sup> The spectral width in this case was 5000 Hz. In the nematic phase three broad peaks covering a spectral range of about 41500 Hz was observed (Figure 3). As the sample was cooled further, at 15°C, the broad peaks completely disappeared and four sharp lines covering a spectral range of only 5000 Hz appeared. These lines were broader than the lines of the isotropic spectrum, but each line could be identified with different groups of lines of the isotropic spectrum as seen in Figure

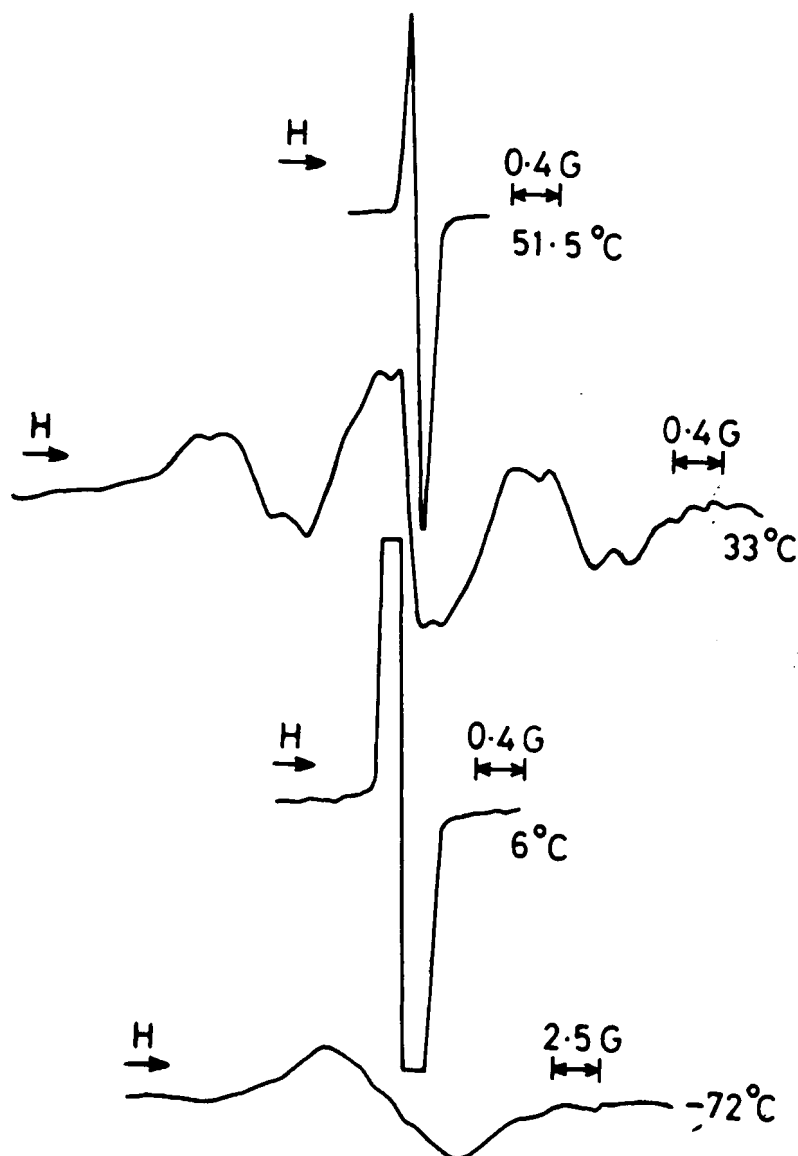FIGURE 1  $^1\text{H}$  wideline NMR spectra of MBBA at different temperatures.

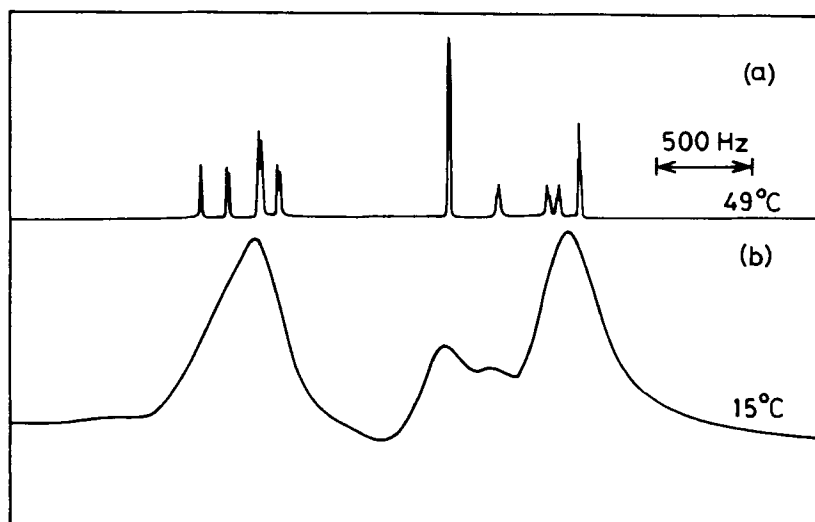


FIGURE 2  $^1\text{H}$  high resolution NMR of MBBA (a) in the isotropic phase and (b) in the phase just below the nematic phase.

2 (b). On further cooling these sharp lines persisted, but as the temperature was lowered they tended to become broader. At  $-40^\circ\text{C}$  the spectrum appears to consist only of two lines because of broadening and finally around  $-60^\circ\text{C}$  all lines completely disappear leaving a broad background signal (Figure 4). As the sample is warmed up from low temperatures the spectral pattern reverses, with the exception that the solid to nematic transition is observed at  $19^\circ\text{C}$ . Numerical integrated intensity over the region of the sharp lines in the low temperature phase as compared to that of the nematic phase spectrum

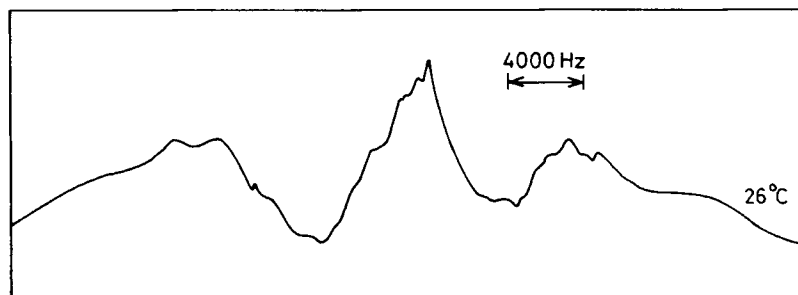


FIGURE 3  $^1\text{H}$  high resolution NMR spectrum of MBBA in the nematic phase.



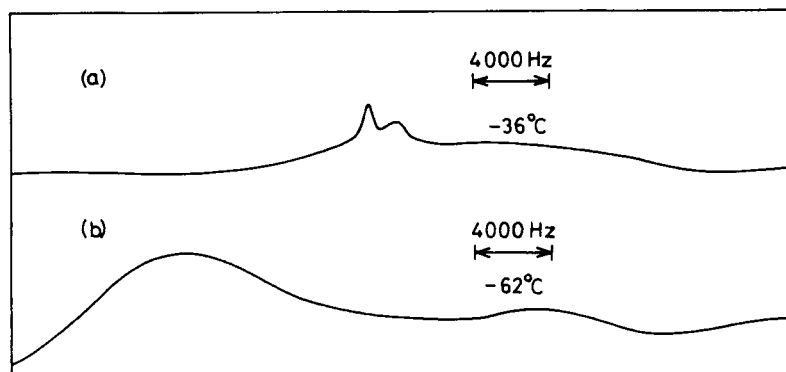


FIGURE 4  $^1\text{H}$  high resolution NMR spectra of MBBA in the solid phase.

recorded under identical conditions of spectrometer settings indicates that the bulk of the material contributes to these sharp signals. There are strong indications that on cooling to the new phase from the nematic, the entire intensity resides in the narrow lines at the transition point; on cooling an increasing fraction of the molecules contribute to the broad signal. This continues till about  $-60^\circ\text{C}$  when the entire spectrum is broad.

$^2\text{H}$  and  $^{13}\text{C}$  spectra were also recorded in the isotropic, nematic and phase just below the nematic phase. It was observed that in these cases also the low temperature phase spectrum consisted of narrow lines similar to the isotropic phase whereas the nematic phase spectrum consisted of much broader lines. In Figure 5,  $^{13}\text{C}$  spectra in the three phases are shown.

We believe that this is the first report of an observation of a narrow line NMR spectrum in MBBA in the solid phase though similar observation has been made in stearic acid in its crystalline form earlier.<sup>27</sup> We have taken up X-ray studies to characterise this phase of MBBA and to understand the unusual behaviour described above.

### 3.2 X-ray diffraction studies

A sample of MBBA was cooled to  $0^\circ\text{C}$  so that it is in the solid form. Powder X-ray diffractograms were taken of this sample while slowly warming it, using a Philips powder X-ray diffractometer. A typical diffractogram is shown in Figure 6 which indicates the crystalline nature of the sample. The pattern is also similar to the ones obtained by Janik *et al.*<sup>3</sup> and Lydon and Kessler.<sup>5</sup>

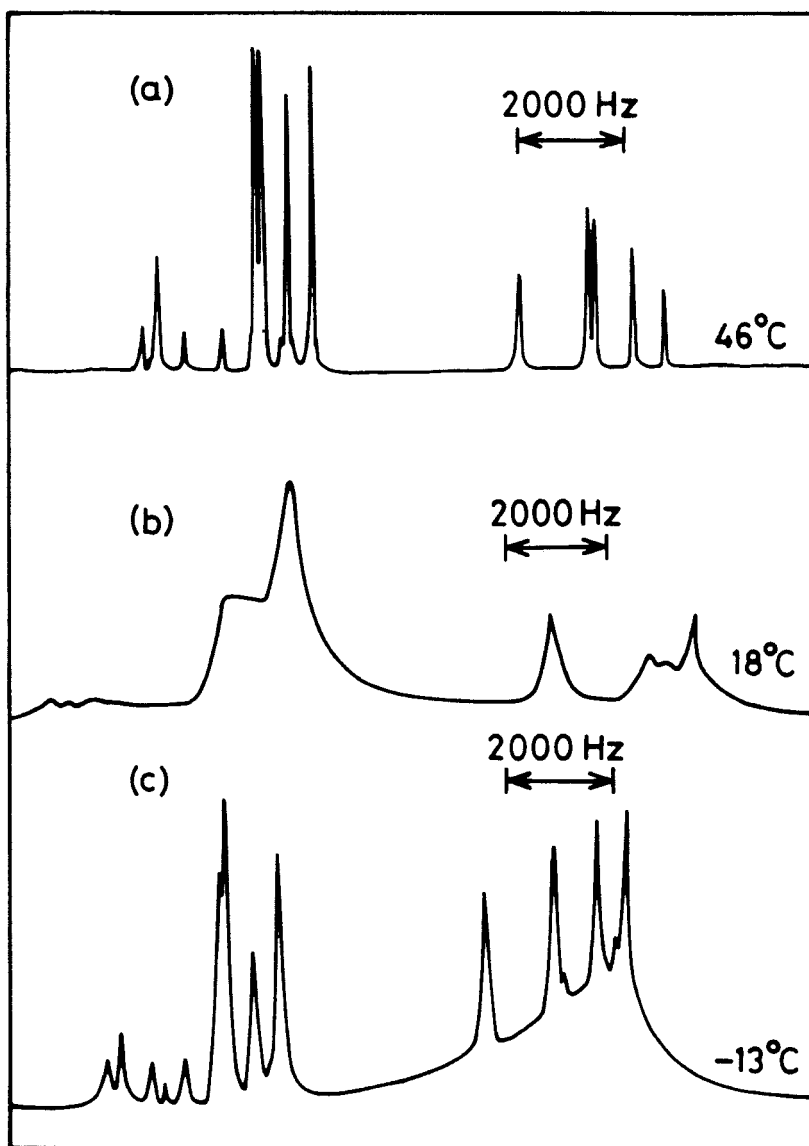


FIGURE 5  $^{13}\text{C}$  high resolution NMR spectra of MBBA at different temperatures.

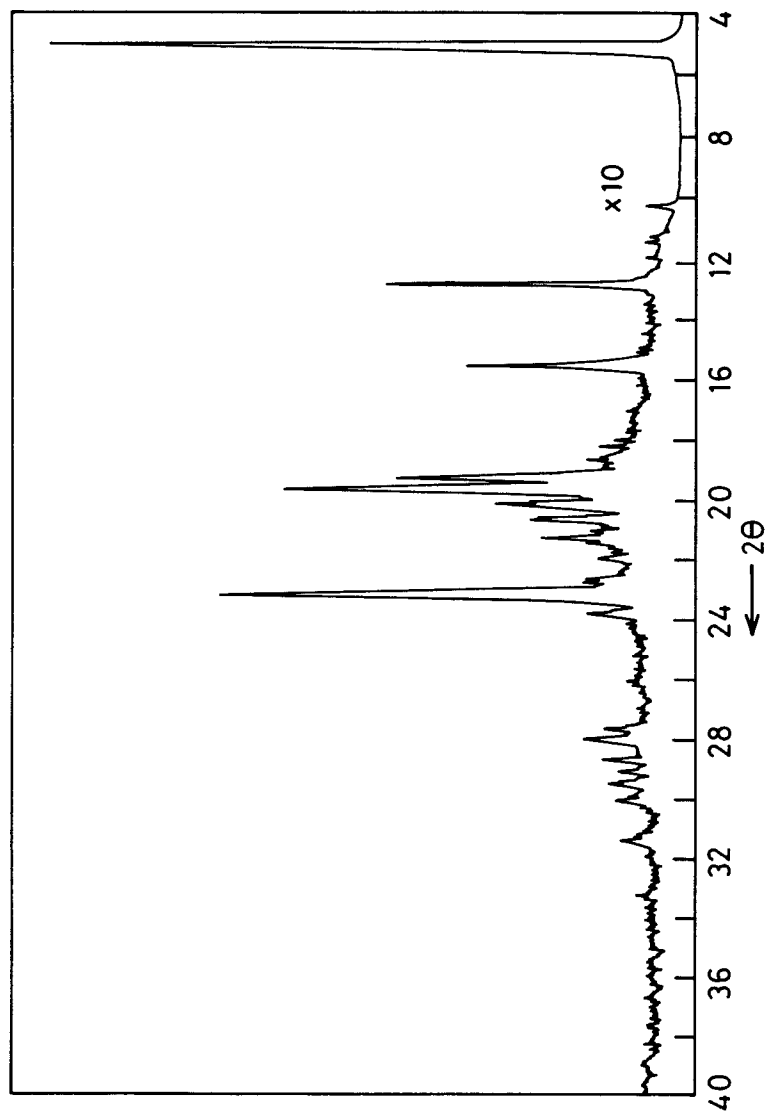


FIGURE 6 X-ray powder diffraction pattern of MBBA just below the nematic phase.

#### 4. DISCUSSION

The NMR results obtained just below the nematic phase are obviously contrary to what is expected. Whereas one would expect in this phase a signal much broader than the signal in the nematic phase, appearance of sharp, intense and narrow signals is clearly anomalous.

It must be pointed out at this stage, that anomalous behaviours have been observed in MBBA before in many other studies like X-ray diffraction,<sup>5</sup> spin-spin relaxation measurements,<sup>21</sup> ESR spin probe study,<sup>17</sup> absorption spectra,<sup>28</sup> IR and Raman studies,<sup>29–31</sup> dielectric studies,<sup>32,33</sup> time-of-flight neutron spectroscopy<sup>34</sup> and Mossbauer study.<sup>35</sup> Most of these have been explained as due to increased mobility of various parts such as tails or the rings of the molecules of the substance in a proposed metastable state of MBBA. Further, in the majority of the studies this behaviour is reported to be monotropic, occurring while warming up of a rapidly frozen sample. We wish to emphasize the fact that what we observe is independent of the direction of change of temperature, of time and of the thermal history of the sample and whether the sample is cooled outside the magnet or within it. Therefore we conclude that what we see is a stable phase of MBBA. This conclusion is also borne out by the fact that the powder X-ray diffraction pattern just below the nematic phase as shown in Figure 6 is very similar to that of 'stable' phase as observed by Janik *et al.*<sup>3</sup> Moreover, the isotropic liquid like very narrow (width 0.06 G) nature of the NMR lines can be accounted for only by assuming that the entire molecule is rapidly tumbling almost isotropically on the NMR time scale and not by allowing motion of just part of the molecule, either the segmental or the ring protons. Thus on the basis of the X-ray diffraction results indicative of crystalline order and the NMR results indicating rapid tumbling, we conclude that MBBA goes into a plastic crystalline state just below its nematic phase.

That such a transition to a plastic crystalline state is plausible can be seen in terms of Onsager's model<sup>36</sup> of onset of liquid crystalline order. In this model, it is the collision of the rod-like molecules occurring at a rate faster than a critical value which maintains the orientational order of the nematogens. Thus it is conceivable that on cooling the substance below its nematic phase into the solid phase with translational order, the collisions between the molecules cease and thus complete reorientational disorder is established where correlation time turns out to be shorter than the NMR time scale.

It must be pointed out that, high resolution NMR spectra similar

to that exhibited by MBBA below its nematic phase have been observed in a few other liquid crystalline substances. Most of them however are in amphiphilic systems<sup>37</sup>—in their so called viscous isotropic mesophases—where individual molecules are supposed to form globular micelles which are located on the sites of a cubic lattice and 'are undergoing thermal rotatory motion at the lattice points analogous to the thermal rotatory motion of the globular molecules at the lattice points in the optically isotropic, non-amphiphilic cubic plastic crystals.'<sup>38</sup>

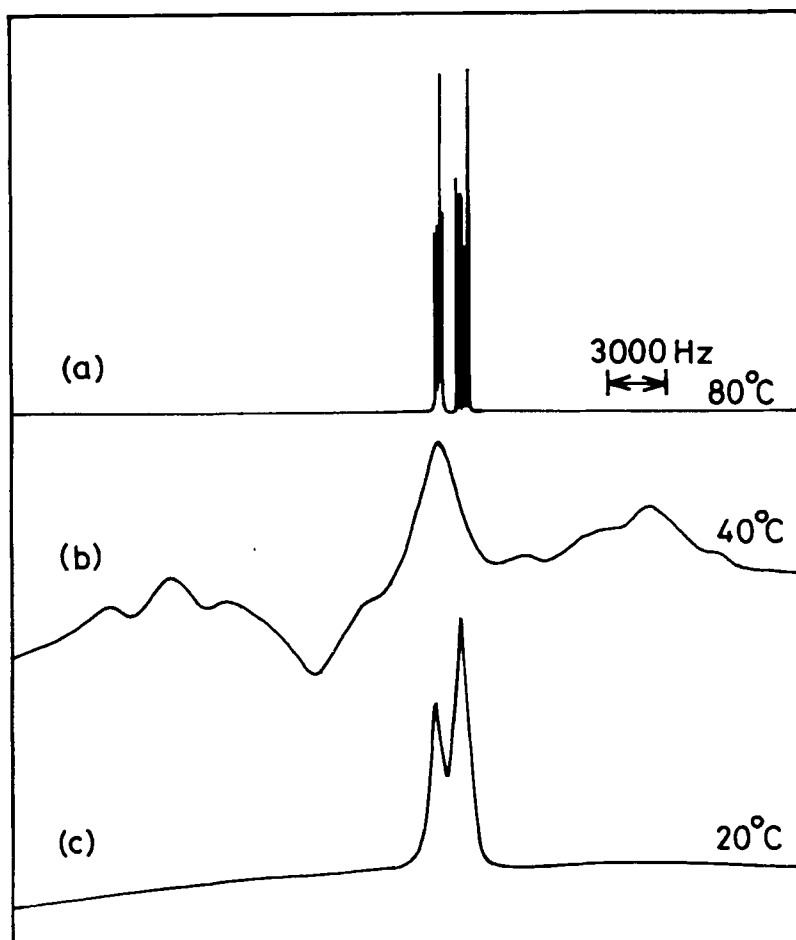


FIGURE 7 <sup>1</sup>H high resolution NMR spectra of EBBA in its (a) isotropic (b) nematic and (c) below nematic phase.

Finally, an earlier ESR spin probe study<sup>39</sup> seems to indicate the presence of the plastic crystalline phase in MBBA though the phenomenon has been interpreted as melting of frozen molecular mobility on a small scale below the temperature of the bulk melting. However, as our results clearly indicate, the mobility is present over the entire sample along with translational order, establishing that what is actually observed is a plastic crystalline state. The transition temperature from nematic to this plastic crystalline state has a positive pressure coefficient, as indicated by our high pressure NMR results and from Clausius-Clapeyron equation one can conclude that the specific volume of this phase is less than that of the nematic phase.

Preliminary study of N-(p-ethoxybenzylidene)p'-n-butaniline (EBBA) a substance with an additional CH<sub>2</sub> group attached to the methoxy sidechain of MBBA, showed similar behaviour. Figure 7 shows <sup>1</sup>H high resolution NMR spectra of EBBA recorded at 80°C, 40°C and 20°C in the isotropic, nematic and the plastic crystalline phases respectively. It is clear that EBBA behaves in a manner similar to MBBA and it is possible that other members of the series also show similar behaviour.

### Acknowledgments

The authors thank the referee for suggestions which have helped clarify the presentation. One of us (S.A) acknowledges the Department of Atomic Energy (India) for the financial support.

### References

1. A. J. Leadbetter, M. A. Mazid, B. A. Kelly, J. W. Goodby and G. W. Gray, *Phys. Rev. Lett.*, **43**, 630 (1979).
2. J. Mayer, T. Waluga and J. A. Janik, *Phys. Lett.*, **41A**, 102 (1972).
3. J. A. Janik, J. M. Janik, J. Mayer, E. Sciesinka, J. Sciesinski, J. Twardowski, T. Waluga and W. Witko, *J. de Physique*, **36**, C1, 159 (1975).
4. M. Kumagai, G. Soda and H. Chihara, *J. Magn. Reson.*, **42**, 28 (1981).
5. J. E. Lydon and J. O. Kessler, *J. de Physique*, **36** C1, 153 (1975).
6. J. K. Moscicki, X. P. Nguyen, S. Urban, S. Wrobel, M. Rachwalska and J. A. Janik, *Mol. Cryst. Liq. Cryst.*, **40**, 177 (1977).
7. J. M. Janik, J. A. Janik and W. Witko, *Acta Physica Polonica*, **44A**, 483 (1973).
8. N. Kirov and P. Simova, *Spectrochim. Acta.*, **29A**, 55 (1973).
9. G. Vergoten, *Advances in Raman Spectroscopy*, **1**, 219 (1972).
10. C. Destrade and H. Gasparoux, *J. de Physique Lett.*, **36**, 105 (1975).
11. P. Arendt, H. D. Koswig, P. Reich and W. Pilz, *Mol. Cryst. Liq. Cryst.*, **75**, 295 (1981).
12. W. J. Borer, S. S. Mitra and C. W. Brown, *Phys. Rev. Lett.*, **27**, 379 (1971).
13. W. W. Walker, *Appl. Phys.*, **16**, 433 (1978).

14. P. C. Jain and S. R. S. Kaffle, *Liq. Cryst., Proc. Int. Conf.*, 405, 1979 (Pub. 1980). Ed. S. Chandrasekhar, Heydon, London.
15. V. K. Dolganov, N. Kroo, L. Rosta and E. F. Sheka, *Mol. Cryst. Liq. Cryst.*, **64**, 115 (1980).
16. J. I. Spielberg and E. Gelerinter, *Chem. Phys. Lett.* **92**, 184 (1982).
17. A. E. Stillman, L. L. Jones, R. N. Schwartz and B. L. Bales, *Liq. Cryst. Ordered Fluids*, **3**, 399 (1978).
18. M. Froix and J. Pochan, *Mol. Cryst. Liq. Cryst.*, **46**, 147 (1978).
19. E. Heinze, S. Grande and J. K. Moscicki, *Acta Physica Polonica*, **53A**, 909 (1978).
20. E. Heinze and S. Grande, *Phys. Status Solidi*, **87 B**, K43 (1978).
21. M. Ito, K. Fujimura, T. Kanamoto, S. Kondo, K. Tanaka and M. Takeda, *Mol. Cryst. Liq. Cryst.*, **69**, 71 (1981).
22. B. Kronberg and D. F. R. Gilson, *Chem. Phys. Lett.*, **47**, 503 (1977).
23. S. Arumugam, S. V. Bhat and R. Srinivasan, *Bulletin of Magnetic Resonance*, **5**, 226 (1983).
24. A. Denat, B. Gosse and J. P. Gosse, *Chem. Phys. Lett.*, **18**, 235 (1973).
25. K. V. Ramanathan and R. Srinivasan, *J. Phys. E.: Sci. Instrum.*, **11**, 480 (1978).
26. Y. S. Lee, Y. Y. Hsu and D. Dolphin, *Liquid Crystals and Ordered Fluids*, **2**, 357 (1973).
27. T. J. R. Cyr, W. R. Janzen and B. A. Dunell in *Advances in Chemistry series*, **63**, 13 (1967). Ed. R. F. Gould, American Chemical Society, Washington, D.C.
28. E. Sciesinska, J. Sciesinski, J. Twardowski and J. A. Janik, *Mol. Cryst. Liq. Cryst.*, **27**, 125 (1974).
29. W. Witko and J. M. Janik, *Acta Physica Polonica*, **54 A**, 521 (1978).
30. J. Le Brumant, N. A. Tuan and M. Jaffrain in *Mol. Spectros. Dense Phases*, Proc. 12th Eur. Congr. Mol. Spectros. 1975 (Pub. 1976) 287, Ed. M. Grosmann, S. G. Elkomoss, J. Ringeissen, Elsevier, Amsterdam, The Netherlands.
31. N. Kirov, M. P. Fontana and F. Cavatorta, *J. Mol. Struct.*, **59**, 147 (1980).
32. J. K. Moscicki, *Solid State Commun.*, **20**, 481 (1976).
33. V. K. Agarwal, V. P. Arora and A. Mansingh, *J. Chem. Phys.*, **66**, 2817 (1977).
34. A. V. Bielushkin, I. Natkaniec, V. K. Dolganov and E. F. Sheka, *J. de Physique*, **42**, C6, 34 (1981).
35. W. J. LaPrice and D. L. Uhrich, *J. Chem. Phys.*, **71**, 1498 (1979).
36. L. Onsager, *Ann. N. Y. Acad. Sci.*, **51**, 627 (1949).
37. A. Johansson and B. Lindman in *Liquid crystals and Plastic crystals*, Ed. G. W. Gray and P. A. Winsor Vol. 2 Ellis Harwood Ltd. (1974) pp 192-230.
38. P. A. Winsor in *Liquid crystals and Plastic crystals*, Ed. G. W. Gray and P. A. Winsor, Vol. 1 Ellis Harwood Ltd. (1974) pp 48-59.
39. K. Murakami and J. Sohma, *Japn. J. Appl. Phys.*, **18**, 415 (1979).