



Molecular Crystals and Liquid Crystals Science and Technology. Section A. Molecular Crystals and Liquid Crystals

Publication details, including instructions for authors and subscription information:

<http://www.tandfonline.com/loi/gmcl19>

Synthesis of Hyperbranched Platinum-Poly(yne) Polymers by Self Polycondensation

Kiyotaka Onitsuka^a, Nobuaki Ohshiro^a, Masanori Fujimoto^a, Fumie Takei^a & Shigetoshi Takahashi^a

^a The Institute of Scientific and Industrial Research, Osaka University, Mihogaoka, Ibaraki, Osaka, 567-0047, Japan

Version of record first published: 24 Sep 2006

To cite this article: Kiyotaka Onitsuka, Nobuaki Ohshiro, Masanori Fujimoto, Fumie Takei & Shigetoshi Takahashi (2000): Synthesis of Hyperbranched Platinum-Poly(yne) Polymers by Self Polycondensation, Molecular Crystals and Liquid Crystals Science and Technology. Section A. Molecular Crystals and Liquid Crystals, 342:1, 159-166

To link to this article: <http://dx.doi.org/10.1080/10587250008038260>

PLEASE SCROLL DOWN FOR ARTICLE

Full terms and conditions of use: <http://www.tandfonline.com/page/terms-and-conditions>

This article may be used for research, teaching, and private study purposes. Any substantial or systematic reproduction, redistribution, reselling, loan,

sub-licensing, systematic supply, or distribution in any form to anyone is expressly forbidden.

The publisher does not give any warranty express or implied or make any representation that the contents will be complete or accurate or up to date. The accuracy of any instructions, formulae, and drug doses should be independently verified with primary sources. The publisher shall not be liable for any loss, actions, claims, proceedings, demand, or costs or damages whatsoever or howsoever caused arising directly or indirectly in connection with or arising out of the use of this material.

Synthesis of Hyperbranched Platinum-Poly(yne) Polymers by Self Polycondensation

KIYOTAKA ONITSUKA, NOBUAKI OHSHIRO,
MASANORI FUJIMOTO, FUMIE TAKEI and
SHIGETOSHI TAKAHASHI

*The Institute of Scientific and Industrial Research, Osaka University,
Mihogaoka, Ibaraki, Osaka 567-0047, Japan*

A hyperbranched polymer constructed by platinum-acetylide units has been synthesized by self polycondensation of a dinuclear platinum complex having one terminal acetylene and two platinum-chloride groups as an AB_2 monomer in the presence of a copper catalyst in amine. The hyperbranched polymer is soluble in common organic solvents and characterized by means of spectral analyses and GPC.

INTRODUCTION

Highly branched polymers such as dendrimers and hyperbranched polymers have recently received much attention as materials with unique physical and chemical properties.^[1] It has been reported that hyperbranched polymers show properties similar to those of dendrimers.^[2] Since the same reaction sequences are repeated for the stepwise growth of dendrimers, much endeavor may be required for the synthesis of dendrimers having a well-defined structure. In contrast, hyperbranched polymers may be easily prepared in a large quantity


though the structure of hyperbranched polymers is not so well-controlled as those of dendrimers.^[3]

In attempts to develop novel functional materials some organometallic dendrimers have been prepared, but hyperbranched polymers composed of organometallic compounds are quite rare in spite of the synthetic advantage of hyperbranched polymers over dendrimers.^[4] As an extension of our study on organometallic polymers constructed with group 10 metals and acetylenes,^[5] we recently reported the synthesis of platinum-acetylide dendrimers up to the third generation containing 45 platinum atoms in the molecule.^[6,7] Herein we present the one-pot synthesis of novel hyperbranched organometallic polymers with a backbone composed of platinum-acetylide units by self polycondensation of a dinuclear platinum-acetylide complex.

RESULTS AND DISCUSSIONS


First, we attempted to prepare hyperbranched platinum-acetylide polymers by polycondensation between triethynylmesitylene (A_3 monomer) and dichlorobis(phosphine)platinum (B_2 monomer) in a 2:3 molar ratio (SCHEME 1). Treatment of triethynylmesitylene **1** with dichloroplatinum complex **2** in the presence of a catalytic amount of CuCl in diethylamine at room temperature gave polymer **3**, of which molecular weight was confirmed by GPC analysis to be $M_w = 62,000$ (polystyrene standards). The IR spectrum of **3** showed absorptions at 3246 and 2093 cm^{-1} , which are assignable to $\nu_{\text{C-H}}$ and $\nu_{\text{C}\equiv\text{C}}$, respectively. Further characterization, however, was difficult due to low solubility of **3**. Similar results have been reported by Lewis and co-workers several years ago.^[8] By varying the molar ratio of **1** to **2**, the molecular weights of the resulting polymers became smaller than that of

3. Poor solubility, however, did not improve, suggesting that polymer **3** has a highly cross-linking structure with a three-dimensional network.

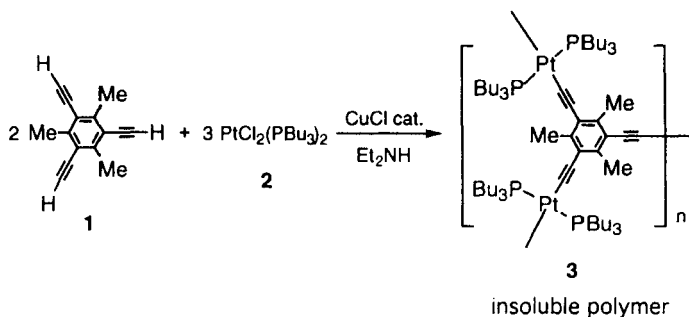

SCHEME 1


To avoid the formation of cross-linked polymers, methodology for the synthesis of hyperbranched platinum-acetylide polymers was changed into self polycondensation of AB₂ type monomer.^[3] Dinuclear platinum-acetylide complex **4**, which has two platinum-chloride moieties and one terminal acetylene, was selected as an AB₂ type monomer. Complex **4** was prepared as shown in SCHEME 2, using two kinds of trialkylsilyl groups, trimethylsilyl and tri-*iso*-propylsilyl groups, for protection of terminal acetylenes.^[7] Stepwise cross-coupling reaction of 1,3-dibromo-5-iodobenzene **5** with equimolar amounts of tri-*iso*-propylsilylacetylene and then with excess trimethylsilylacetylene by Pd-Cu catalysts gave a triethynylbenzene derivative **6**.^[9] Selective removal of the trimethylsilyl group was performed by treatment of K₂CO₃ in aqueous methanol to give compound **7**. Platinum moieties were introduced by the reaction with excess dichloroplatinum complex in the presence of a CuCl catalyst in piperidine-toluenen under reflux to give dinuclear platinum-acetylide **8**. Desilylation of **8** by treatment of Bu₄NF afforded the target complex **4**.

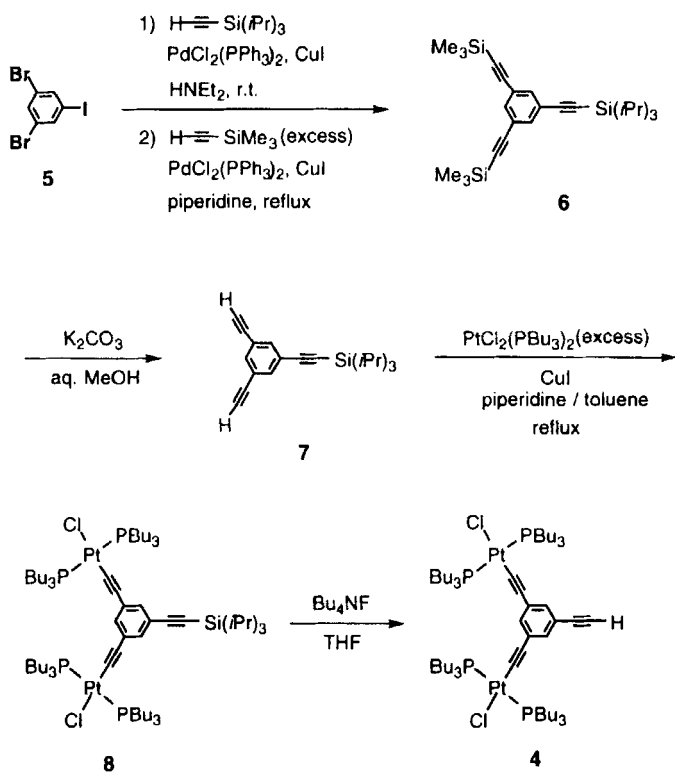

SCHEME 2

Self polycondensation of **4** was carried out in the presence of a CuCl catalyst in diethylamine at room temperature (SCHEME 3). Pale yellow polymer **9**, which is soluble in common organic solvents, was isolated by column chromatography on alumina as highly viscous oil in 91% yield. The GPC analysis of polymer **9** showed the average molecular weight $M_w = 16,000$ (polystyrene standards) and the polydispersity index $M_w / M_n = 1.28$. Though the concentration of monomer was varied from 12.3 mmol/L to 2.0 mmol/L, no significant difference was observed in the molecular weight of the resulting


polymer. Since we have already found that the GPC analysis using polystyrene standards apparently shows about a half value of the real molecular weights of platinum-acetylide dendrimers,^[6,7] the molecular weight of **9** should be estimated to be about 32,000, which corresponds to about 20 units of monomer **4**.

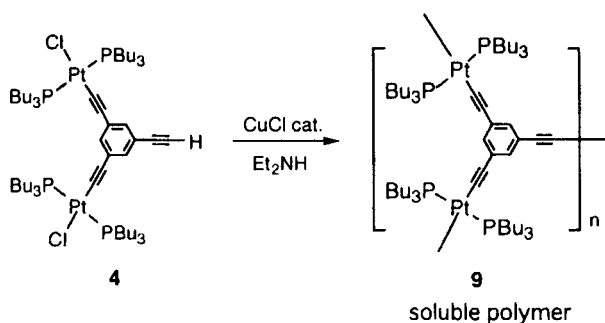

SCHEME 3


In the IR spectrum of **9**, an absorption due to $\nu_{\text{C}\equiv\text{C}}$ was found at 2096 cm^{-1} , while no $\nu_{\text{C}\equiv\text{H}}$ absorption was observed. The ^1H NMR spectrum of **9** was similar to that of monomer **4** except for the absence of a signal assignable to the proton of terminal acetylene. The ^{31}P NMR spectrum of **9** showed two singlet signals at δ 7.11 ($J_{\text{Pt-P}} = 2381\text{ Hz}$) and 3.58 ($J_{\text{Pt-P}} = 2371\text{ Hz}$) in a 1:1.2 intensity ratio. The former was assigned to the phosphines bound to a chloroplatinum moiety $\text{C}\equiv\text{CPt}(\text{PBu}_3)_2\text{Cl}$ and the latter to those bound to a diethynylplatinum moiety $\text{C}\equiv\text{CPt}(\text{PBu}_3)_2\text{C}\equiv\text{C}$. However, the ratio of chloroplatinum and diethynylplatinum moieties must be 1:1 in an ideal hyperbranched polymer prepared from **4**. This results may admit of two interpretations. One ascribes the structural defect to the loss of the terminal chloroplatinum moieties and the other to the formation of a cyclic structure. Since no signals attributed to the terminal groups

converted from chloroplatinum moieties were observed in the ^1H NMR spectrum of **9** as mentioned above, the former does not seem reasonable. Therefore, polymer **9** is proposed to be a hyperbranched polymer with a partial cyclic structure as shown in SCHEME 4.

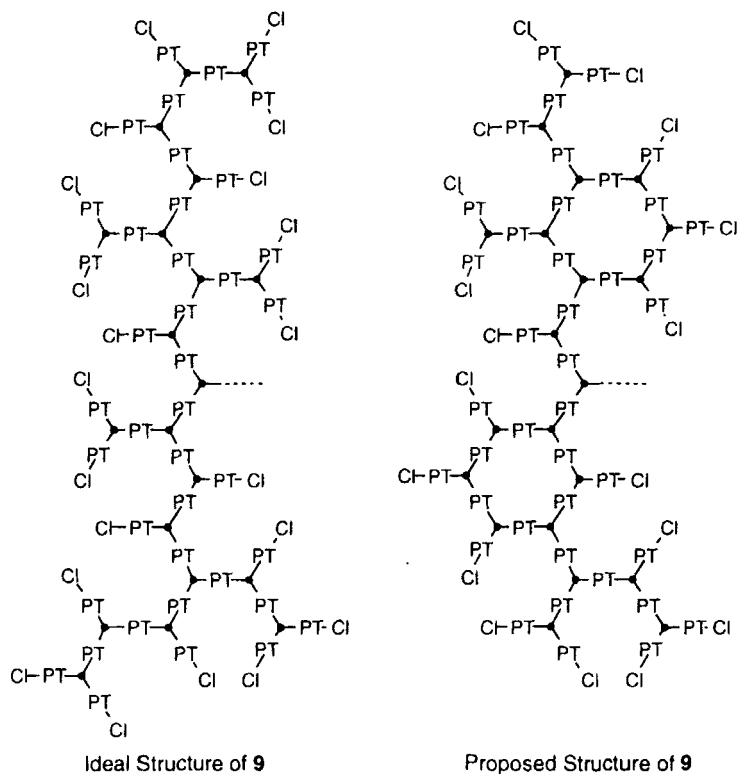

SCHEME 4

The thermogravimetric analysis showed that **9** is thermally stable up to about 350 °C. Reaction of **9** with **2** in refluxing piperidine in the presence of a CuI catalyst resulted in the depolymerization of **9** to give trinuclear platinum complex **10** (SCHEME 5).

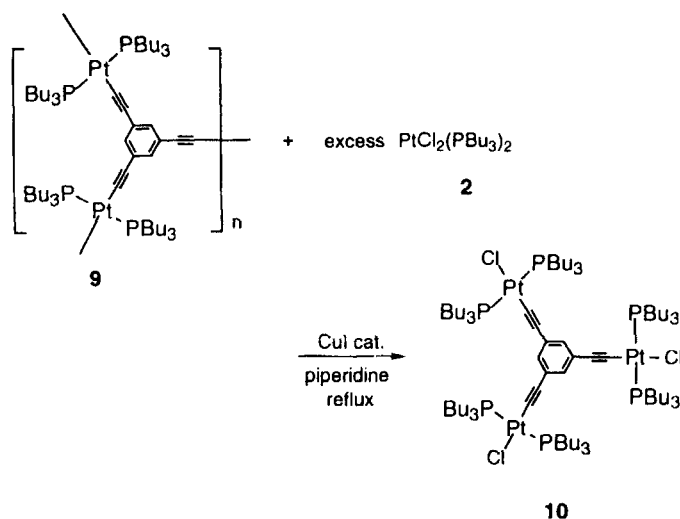

SCHEME 5

In conclusion, the self polycondensation of AB₂ monomer **4** successfully produces a hyperbranched platinum-acetylide polymer **9** though there are a little structural defects like a cyclic structure in the molecule.

ACKNOWLEDGMENTS

This work was supported by Grant-in-Aid for Scientific Research on Priority Areas, "Metal-assembled Complexes" (No. 10149228) from the Ministry of Education, Science, Sports and Culture.

References

- [1] G. R. Newkome, C. N. Moorefield, and F. Vögtle, *Dendritic Molecules: Concepts, Syntheses, Perspectives*; VCH: Weinheim, 1996; D. A. Tomalia, A. M. Naylor, and W. A. Goddard III, *Angew. Chem., Int. Ed. Engl.*, **29**, 138 (1990); H.-B. Meckelburger, W. Jaworek, and F. Vögtle, *Angew. Chem., Int. Ed. Engl.*, **31**, 1571 (1992); J. Issberner, R. Moors, and F. Vögtle, *Angew. Chem., Int. Ed. Engl.*, **33**, 2413 (1994).
- [2] Y. H. Kim, and O. W. Webster, *Macromolecules*, **25**, 5561 (1992).
- [3] Y. H. Kim, and O. W. Webster, *J. Am. Chem. Soc.*, **112**, 4592 (1990); C. J. Hawker, R. Lee, J. M. J. Fréchet, *J. Am. Chem. Soc.*, **113**, 4583 (1991); S. G. Gaynor, S. Edelman, K. Matyjaszewski, *Macromolecules*, **29**, 1079 (1996); G. Yang, M. Jikei, and M. Kakimoto, *Macromolecules*, **31**, 5964 (1998).
- [4] W. T. S. Huck, B. H. M. Snellink-Ruël, J. W. Th. Lichtenbelt, F. C. J. M. van Veggel, and D. N. Reinhoudt, *J. Chem. Soc. Chem. Commun.*, **1997**, 9.
- [5] N. Hagihara, K. Sonogashira, and S. Takahashi, *Adv. Polym. Sci.*, **41**, 149 (1981).
- [6] N. Ohshiro, F. Takei, K. Onitsuka, and S. Takahashi, *Chem. Lett.*, **1996**, 871; N. Ohshiro, F. Takei, K. Onitsuka, and S. Takahashi, *J. Organomet. Chem.*, **569**, 195 (1998).
- [7] K. Onitsuka, M. Fujimoto, N. Ohshiro, and S. Takahashi, *Angew. Chem., Int. Ed. Engl.*, **38**, 689 (1999).
- [8] M. S. Kahn, D. J. Schwartz, N. A. Pasha, A. K. Kakkar, B. Lin, P. R. Raithby, and J. Lewis, *Z. Anorg. Allg. Chem.*, **616**, 121 (1992).
- [9] S. Takahashi, Y. Kuroyama, K. Sonogashira, N. Hagihara, *Synthesis*, **1980**, 627.