



## Molecular Crystals and Liquid Crystals Science and Technology. Section A. Molecular Crystals and Liquid Crystals

Publication details, including instructions for authors and subscription information:

<http://www.tandfonline.com/loi/gmcl19>

## Synthesis and Luminescent Properties of Lanthanide-Cored Supramolecular Complexes Based on Porphyrins for Optical Amplification

Kyung Lim Paik<sup>a</sup> & Hwan Kyu Kim<sup>a</sup>

<sup>a</sup> Dept. of Polymer Sci. & Eng., Hannam Univeristy, Taejon, 306-791, Korea

Version of record first published: 24 Sep 2006

To cite this article: Kyung Lim Paik & Hwan Kyu Kim (2001): Synthesis and Luminescent Properties of Lanthanide-Cored Supramolecular Complexes Based on Porphyrins for Optical Amplification, Molecular Crystals and Liquid Crystals Science and Technology. Section A. Molecular Crystals and Liquid Crystals, 370:1, 185-188

To link to this article: <http://dx.doi.org/10.1080/10587250108030067>

PLEASE SCROLL DOWN FOR ARTICLE

Full terms and conditions of use: <http://www.tandfonline.com/page/terms-and-conditions>

This article may be used for research, teaching, and private study purposes. Any substantial or systematic reproduction, redistribution, reselling, loan, sub-licensing, systematic supply, or distribution in any form to anyone is expressly forbidden.

The publisher does not give any warranty express or implied or make any representation that the contents will be complete or accurate or up to date. The accuracy of any instructions, formulae, and drug doses should be independently verified with primary sources. The publisher shall not be liable for any loss, actions, claims, proceedings, demand, or costs or damages whatsoever or howsoever

caused arising directly or indirectly in connection with or arising out of the use of this material.

## Synthesis and Luminescent Properties of Lanthanide-Cored Supramolecular Complexes Based on Porphyrins for Optical Amplification

KYUNG LIM PAIK and HWAN KYU KIM

*Dept. of Polymer Sci. & Eng., Hannam Univeristy, Taejon 306-791, Korea;*

*E-mail: hwankkim@eve.hannam.ac.kr*


**Abstract** We have investigated the development of lanthanide-cored supramolecular complexes containing porphyrins to circumvent the solubility problem and maximize the optical amplification properties. Their chemical structures were identified by FT-IR,  $^1\text{H-NMR}$ , UV-Vis absorption and emission spectroscopies. FB-Por 1 and 2 show a very intense UV-visible absorption band at 419 nm, which is attributed to the Soret band. In addition, the relatively weak bands at 516, 551, 591 and 647 nm are assigned to the Q bands. Upon a photoexcitation wavelength with 430 nm, the PL spectra of FB-Por 1 and 2 exhibit a strong band at 653 nm and a weak peak at 715 nm. Zn-Por 1 and 2 show a very intense band at 420 nm for B-band  $\pi\text{-}\pi^*$  transitions. In addition, the weak bands at 547 and 585 nm were assigned to the Q bands. With an excitation wavelength of 430 nm, the PL spectra of Zn-Por 1 and 2 show a moderate band at 596 nm and a strong band at 646 nm.

**Keywords** Lanthanide-cored supramolecular complex; Porphyrins, Ligand-exchange reaction, Optical amplification, Photoluminescence


### INTRODUCTION

To achieve the superhigh speed telecommunication systems, the development of integrated planar waveguide optical amplifiers is extremely essential. At present, erbium-doped silica amplifiers are widely used. But, the poor solubility of lanthanide cations ( $\text{Ln}^{3+}$ ) in conventional inorganic/organic media leads to the low amplification property. When the higher doping concentration of lanthanide cations was introduced, clustered  $\text{Ln}^{3+}$  species can be formed, which in turn has limited the amplification property. It is ascribed to the

cooperative energy-transfer processes (i.e., self-quenching process) between the clustered  $\text{Ln}^{3+}$  species. Their processes reduced the intensity of luminescence. To circumvent the solubility problem and maximize the optical amplification property, we have investigated the development of lanthanide-cored supramolecular complexes containing porphyrins. In this paper, we describe the synthesis and luminescent properties of lanthanide-cored supramolecular complexes containing porphyrins.

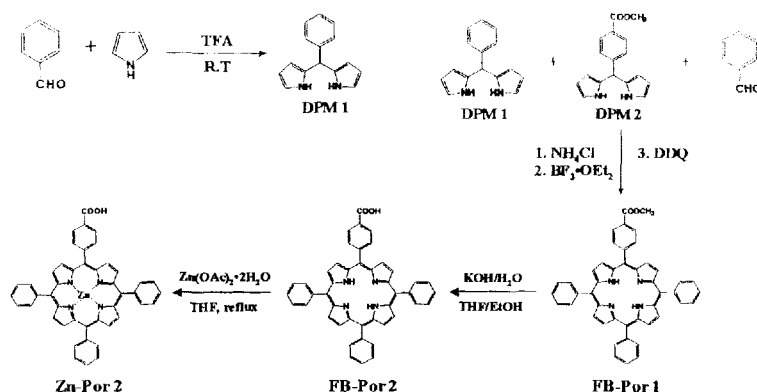

SCHEME 1 Synthetic routes to the dipyrromethane and the porphyrins.

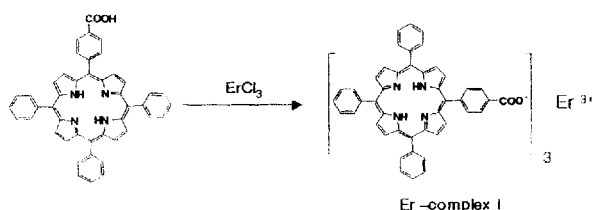

SCHEME 2 Synthetic routes to the lanthanide-cored supramolecular complex based on porphyrin.

## RESULTS AND DISCUSSION

### Preparation of lanthanide-cored supramolecular complexes based on porphyrins

The dipyrromethane and porphyrins were synthesized according to a procedure described by Lindsey et al. [1]. The synthetic routes to the dipyrromethane and porphyrins were shown in SCHEME 1. Their chemical structures were identified by FT-IR,  $^1\text{H-NMR}$ , UV-Vis absorption and emission spectroscopies. A  $^1\text{H-NMR}$  spectrum of FB-Por 1 showed two characteristic peaks of 4.1 and

−2.85 ppm assigned to the methoxycarbonyl and the pyrrole N-H groups, respectively. Those peaks disappeared in the Zn-Por 2, after the insertion of Zn(II) ion into a pre-hydrolyzed porphyrin [3]. In the UV-visible spectrum, FB-Por 1 and 2 showed a very intense band at 419 nm, which was attributed to the Soret band. In addition, the relatively weak bands at 516, 551, 591 and 647 nm were assigned to the Q bands. Upon a photoexcitation wavelength with 430 nm, the PL spectra of FB-Por 1 and 2 exhibited a strong band at 653 nm and a weak peak at 715 nm (see FIGURE 1).

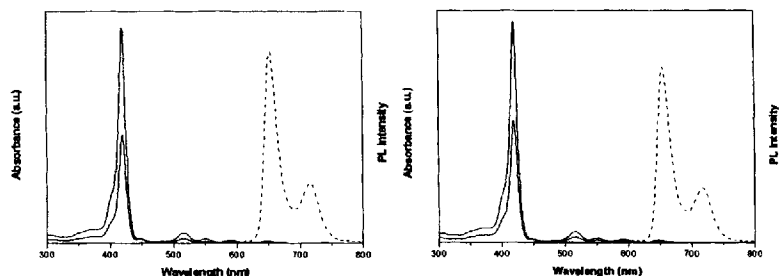


FIGURE 1 UV-Vis absorption and PL spectra of FB-Por (COOCH<sub>3</sub>) (left) and FB-Por (COOH) (right) in chloroform solution

Also, Zn-Por 1 and 2 showed a very intense band at 420 nm for B-band  $\pi \sim \pi^*$  transitions. In addition, the weak bands at 547 and 585 nm were assigned to the Q bands. Generally, metalloporphyrins were more symmetrical macrocycles than free based porphyrins, so that their Q band spectra consisted of only two bands. With an excitation wavelength of 430 nm, the PL spectra of Zn-Por 1 and 2 showed a moderate band at 596 nm and a strong peak at 646 nm (see FIGURE 2).

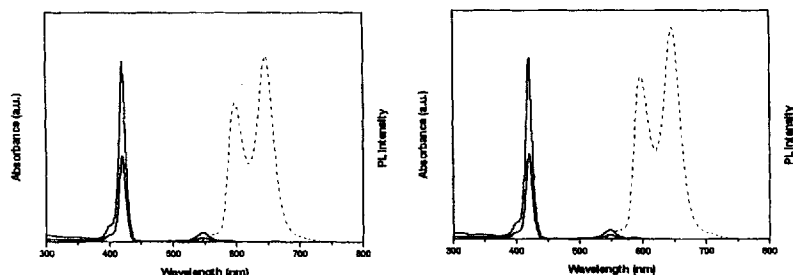


FIGURE 2 UV-Vis absorption and emission spectra of Zn-Por (COOCH<sub>3</sub>) (left) and Zn-Por (COOH) (right) in chloroform solution.

As shown in SCHEME 2, lanthanide-cored supramolecular complexes based on porphyrin were synthesized using the ligand-exchange reaction. First, we synthesized an Er-cored supramolecular complex using the Er(III) Acetate, according to the previous Frechet's method [2]. But, the reaction did not proceed because of the chemical stability of Er(III) Acetate and steric hinderance of porphyrin. So, we achieved successfully the synthesis of Er-cored supramolecular complexes based on porphyrins using  $\text{ErCl}_3$  in a different synthetic method. Their chemical structures were identified by FT-IR,  $^1\text{H}$ -NMR, UV-Vis absorption and emission spectroscopies. In progress, their luminescent and optical amplification properties are being investigated.

#### ACKNOWLEDGMENT

HKK greatly acknowledges that this work was financially supported by grant No. 1999-2-308-003-3 from the interdisciplinary research program of the KOSEF.

#### REFERENCES

- [1] C.H. Lee, J.S. Lindsey, Tetrahedron, **50**, 11427 (1994).
- [2] M. Kawa, M.J. Frechet, Chem. Mater., **10**, 286 (1998).
- [3] C. Luo, D.M. Guldi, H. Imahori, K. Tamaki, Y. Sakata, J. Am. Chem. Soc., **122**, 6535 (2000).