



Molecular Crystals and Liquid Crystals

Publication details, including instructions for authors and subscription information:

<http://www.tandfonline.com/loi/gmcl20>

Magnetic Properties of Cs + and (CH₃)₄N + Salts of TCNQ

Makoto Inokuchi^a, Keiko Suzuki^a, Minoru Kinoshita^a, Yuko Hosokoshi^b & Katsuya Inoue^b

^a Department of Materials Science and Engineering, Faculty of Science and Engineering, Science University of Tokyo in Yamaguchi, Onoda, Yamaguchi, 756-0884, Japan

^b Institute for Molecular Science, Myodaiji, Okazaki, Aichi, 444-8585, Japan

Version of record first published: 18 Oct 2010

To cite this article: Makoto Inokuchi, Keiko Suzuki, Minoru Kinoshita, Yuko Hosokoshi & Katsuya Inoue (2002): Magnetic Properties of Cs + and (CH₃)₄N + Salts of TCNQ, *Molecular Crystals and Liquid Crystals*, 376:1, 507-512

To link to this article: <http://dx.doi.org/10.1080/10587250210798>

PLEASE SCROLL DOWN FOR ARTICLE

Full terms and conditions of use: <http://www.tandfonline.com/page/terms-and-conditions>

This article may be used for research, teaching, and private study purposes. Any substantial or systematic reproduction, redistribution, reselling, loan, sub-licensing, systematic supply, or distribution in any form to anyone is expressly forbidden.

The publisher does not give any warranty express or implied or make any representation that the contents will be complete or accurate or up to date. The accuracy of any instructions, formulae, and drug doses should be independently verified with primary sources. The publisher shall not be liable for any loss, actions, claims, proceedings, demand, or costs or damages whatsoever or howsoever caused arising directly or indirectly in connection with or arising out of the use of this material.



Magnetic Properties of Cs^+ and $(\text{CH}_3)_4\text{N}^+$ Salts of TCNQ

MAKOTO INOKUCHI^a, KEIKO SUZUKI^a,
MINORU KINOSHITA^a, YUKO HOSOKOSHI^b and
KATSUYA INOUE^b

^aDepartment of Materials Science and Engineering, Faculty of Science and Engineering, Science University of Tokyo in Yamaguchi, Onoda, Yamaguchi 756-0884, Japan and

^bInstitute for Molecular Science, Myodaiji, Okazaki, Aichi 444-8585, Japan

Abstract $\text{Cs}(\text{TCNQ})_{1.5}$ and $[(\text{CH}_3)_4\text{N}](\text{TCNQ})_{1.5}$ were prepared with using chemicals and solvents purified carefully and were recrystallized under an inert atmosphere to minimize the effect of air. We investigated their magnetic properties and the effect of oxygen on the magnetism. It was found that both paramagnetic susceptibilities (χ_p) of $\text{Cs}(\text{TCNQ})_{1.5}$ and $[(\text{CH}_3)_4\text{N}](\text{TCNQ})_{1.5}$ were very small, especially χ_p of $\text{Cs}(\text{TCNQ})_{1.5}$ was remarkably small such as $10 \sim 40 \times 10^{-6} \text{ emu} \cdot \text{mol}^{-1}$ all over the temperature region. After the specimen was exposed to air, χ_p was measured again; for $\text{Cs}(\text{TCNQ})_{1.5}$, χ_p increased clearly by about $20 \times 10^{-6} \text{ emu} \cdot \text{mol}^{-1}$; however for $[(\text{CH}_3)_4\text{N}](\text{TCNQ})_{1.5}$, χ_p was not changed. This result suggests that the magnetism of the Cs salt was sensitive to oxygen and that the Me_4N salt is stable to air.

Keywords TCNQ salt; $[(\text{CH}_3)_4\text{N}](\text{TCNQ})_{1.5}$; $\text{Cs}(\text{TCNQ})_{1.5}$; magnetic properties; molecular conductor

INTRODUCTION




On the history of the development of molecular conductors, TCNQ (tetracyanoquinodimethane) was the epoch-making electron acceptor which gave the first organic metal TTF-TCNQ in 1973 [1]. Before the

discovery of TTF-TCNQ, many kinds of its salts were prepared and their physical properties were studied. TCNQ takes one electron and forms the radical anion as TCNQ^- . Almost all TCNQ salts have 1 : 1 or 1 : 2 stoichiometry as $(\text{M}^+ \cdot \text{TCNQ}^-)$ or $((\text{M}^+ \cdot \text{TCNQ}^-) \cdot \text{TCNQ})$. Among the salts, the cesium salt is known to form an exceptional 1 : 1.5 salt as $(\text{Cs}^+ \cdot \text{TCNQ}^-) \cdot 0.5\text{TCNQ}$ and the tetramethylammonium salt was reported recently to have a 1 : 1.5 stoichiometry of $((\text{CH}_3)_4\text{N}^+ \cdot \text{TCNQ}^-) \cdot 0.5\text{TCNQ}$ as well [2,3]. These TCNQ salts show various kinds of magnetism largely deviating from Curie's law. However, the origin of behavior has not been fully understood yet. Therefore, we prepared the crystals of $\text{Cs}(\text{TCNQ})_{1.5}$ and $[(\text{CH}_3)_4\text{N}](\text{TCNQ})_{1.5}$ under an inert atmosphere as pure as possible and reexamined their magnetic properties with a SQUID magnetometer.

In this paper, we report the magnetic properties of $\text{Cs}(\text{TCNQ})_{1.5}$ and $[(\text{CH}_3)_4\text{N}](\text{TCNQ})_{1.5}$ and the effect of oxygen on these magnetism.

EXPERIMENTAL

$\text{CsTCNQ}_{1.5}$ and $\text{Me}_4\text{NTCNQ}_{1.5}$ were synthesized as follows [2,3];



On preparing samples, we used chemicals and anhydrous solvents purified carefully; TCNQ (sublimed 5 times), CsI (recrystallized from MeOH), LiI (Aldrich 99.99% grade), NMe_4Cl (recrystallized from MeOH/ Et_2O), MeCN (distilled over NaOH), Et_2O (distilled over Na) and MeOH (dried with molecular sieve and distilled). In order to investigate the effect of air, the recrystallization was carried out in an atmosphere of argon by the following method; two round bottom flasks were connected with a three-way glass tube and the remaining end of the tube was joining to a vacuum/argon line; ether and the solution of the sample in acetonitrile were placed in each flask. The atmosphere in the flasks was replaced with argon after freeze-and-thaw cycles for solvents and then, the glass apparatus was placed in the dark. As ether

vapor passed through the glass tube and dissolved into acetonitrile gradually, the crystal was growing for two weeks. After that, the filtration of the crystal and all preparations for the magnetic measurements were performed in a glove box where argon gas was flowing, and when the sample was moved from a glove box to the magnetometer, it was kept under inert condition as possible. Magnetic susceptibility and magnetization were measured by use of a Quantum Design MPMS SQUID magnetometer. The paramagnetic susceptibility was obtained by subtracting the core susceptibility (χ_{core}) from the measured susceptibility; χ_{core} was estimated by Pascal's law; $\chi_{\text{core}}(\text{CsTCNQ}_{1.5}) = -216.6 \times 10^{-6} \text{ emu} \cdot \text{mol}^{-1}$; $\chi_{\text{core}}(\text{Me}_4\text{N}^+\text{TCNQ}_{1.5}^-) = -246.2 \times 10^{-6} \text{ emu} \cdot \text{mol}^{-1}$; $\chi(\text{TCNQ}) = -121 \times 10^{-6} \text{ emu} \cdot \text{mol}^{-1}$; $\chi(\text{Cs}^+) = -35.1 \times 10^{-6} \text{ emu} \cdot \text{mol}^{-1}$.

RESULTS AND DISCUSSION

Magnetic Susceptibilities

Figure 1a shows the temperature dependence of paramagnetic susceptibility (χ_p) observed on CsTCNQ_{1.5}. The lower curve is χ_p measured just after the recrystallization under an inert atmosphere of argon. As can be seen from this curve, χ_p is remarkably small such as $10 \sim 40 \times 10^{-6} \text{ emu} \cdot \text{mol}^{-1}$ all over the temperature region, while χ_p is a little dependent on temperature. This result suggests that almost all the spins of TCNQ radical anions are forming diamagnetic pairs in the crystal. As temperature is lowered, χ_p decreases gradually down to 200 K, becomes almost constant and then increases below 100 K. The behavior around room temperature is dependent on sample; some samples showed a peak at 280 ~ 290 K as shown in Fig. 1a, while others exhibited the monotonous increase of χ_p without any peak.

The upper curve in Fig. 1a shows χ_p observed after the specimen was exposed to air for 20 minutes. As being compared with the lower curve under an atmosphere of Ar, it should be noted that χ_p increased by about $20 \times 10^{-6} \text{ emu} \cdot \text{mol}^{-1}$ over the wide temperature range, while the shape is very similar. This result suggests that air, possibly oxygen, attaches to the surface of the sample and affects χ_p of CsTCNQ_{1.5}. A series of the measurements for the specimen exposed to air for 1 min., 5 hrs. and 12 hrs. and further in oxygen for 1 hr were performed. As the

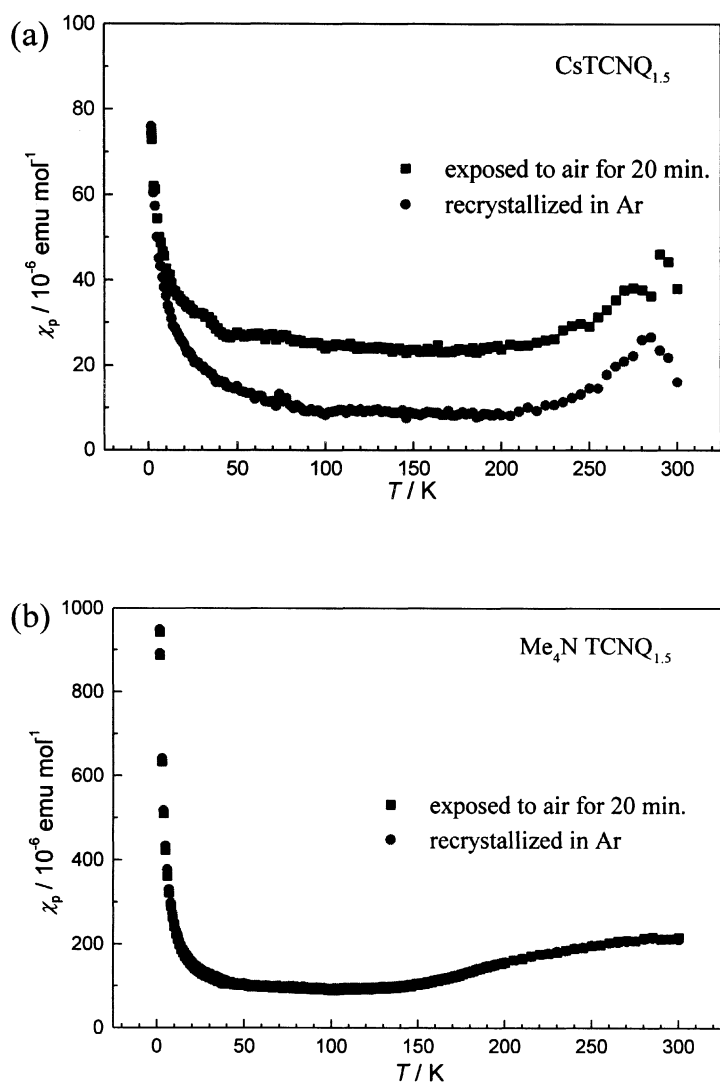


FIGURE 1 The temperature dependence of magnetic susceptibilities of $\text{Me}_4\text{N TCNQ}_{1.5}$ and $\text{CsTCNQ}_{1.5}$

results, χ_p for the sample exposed to air for 1 min. increased like Fig 1a. As the sample was exposed to air longer, χ_p increased slightly as the effect seems to saturate; χ_p for the sample in air for 12 hrs. is nearly equal to χ_p exposed to oxygen for 1 hr.

Figure 1b shows χ_p measured on $\text{Me}_4\text{N TCNQ}_{1.5}$ recrystallized under an inert atmosphere and exposed to air by the same way as the Cs salt. As can be seen from this figure, χ_p was not changed for the specimen in air for 20 minutes and even in oxygen. The effect of air could not be observed on the Me_4N salt. While χ_p was larger than that of the Cs salt, χ_p was rather small such as $100 \text{ emu} \cdot \text{mol}^{-1}$.

Magnetizations

Figure 2 shows the magnetic field dependence of the magnetization $\text{CsTCNQ}_{1.5}$ at 1.85K. The magnetization grows slowly and the hysteretic behavior was not observed at this low temperature on our measurement. Subsequently, the magnetization was measured at 1.85K on the sample after exposure to oxygen. The result was the same as Fig.2.

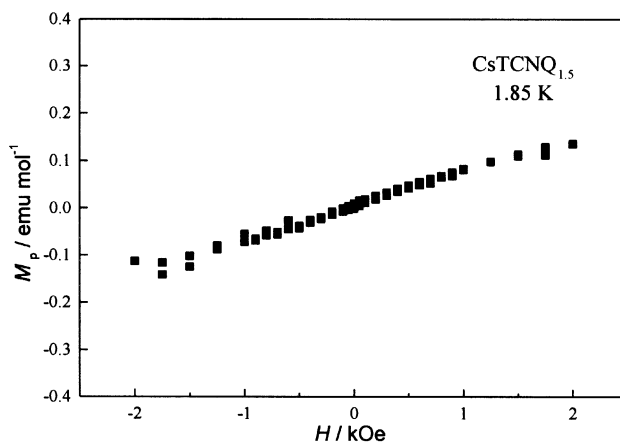


FIGURE 2 The magnetic field dependence of the magnetization of $\text{CsTCNQ}_{1.5}$ in the applied field range $\pm 2 \text{ kOe}$ at 1.85K

CONCLUSION

We prepared the crystals of $\text{Cs}(\text{TCNQ})_{1.5}$ and $[(\text{CH}_3)_4\text{N}](\text{TCNQ})_{1.5}$ under an inert atmosphere as pure as possible and investigated their magnetic properties and the effect of oxygen on the magnetism. It was found that both paramagnetic susceptibilities (χ_p) of the Cs salt and the Me_4N salt were small, especially that χ_p of the Cs salt was remarkably small such as $10 \sim 40 \times 10^{-6} \text{ emu} \cdot \text{mol}^{-1}$ all over the temperature region. This fact could mean that almost all the spins of TCNQ radical anions are forming diamagnetic pairs. After the specimen was exposed to air, χ_p was measured again; for the Cs salt, χ_p increased clearly by about $20 \times 10^{-6} \text{ emu} \cdot \text{mol}^{-1}$, however for the Me_4N salt, χ_p was not changed. This result suggests that the magnetism of the Cs salt was sensitive to oxygen and that the Me_4N salt is stable to air.

The origin of the magnetic behavior of TCNQ salts has not been understood yet. A further study will be needed in order to clarify the mechanism that the magnetic susceptibilities are remarkably small and that oxygen affects the magnetism of TCNQ salts.

Acknowledgments

We wish to acknowledge Professor Toyonari Sugimoto (Osaka City University) for his advice on the sample preparations. We thank Professor Hideki Yamochi (Kyoto University) for providing us with TCNQ. A part of this study was the collaboration with Mr. Sogo Seki and Mr. Akihiro Yoshida, to whom our thanks are due. This work was partly supported by the Grant-in-Aid for Science Research from the Japan Society for the Promotion of Science and by the Joint Studies Program (1999 ~ 2000) of the Institute for Molecular Science.

References

1. L.B.Coleman, et al. *Solid State Commun.* **12**(1973) 1125.
2. C. J. Fritchie, Jr, and P. Arthur, Jr, *Acta Crystallogr.*, **21**(1966)295; J. Siemons, P.E. Bierstedt and P.G. Kepler, *J. Chem. Phys.*, **39** (1963) 3523.
3. K.Ueda, T. Sugimoto, et al., *Chem. Phys. Lett.* **261**(1996)295; K.Ueda, T. Sugimoto, et al, *Chem Phys. Lett.*, **261**(1996)139.