



## Molecular Crystals and Liquid Crystals

Publication details, including instructions for authors and subscription information:

<http://www.tandfonline.com/loi/gmcl20>

### Some Characteristics of a Liquid-Crystal Phase Grating for THz Waves

Chia-Jen Lin<sup>a</sup>, Chuan-Hsien Lin<sup>a</sup>, Cho-Fan Hsieh<sup>a</sup>,  
Ru-Pin Pan<sup>a</sup>, Yu-Tai Li<sup>b</sup> & Ci-Ling Pan<sup>b</sup>

<sup>a</sup> Department of Electrophysics, National Chiao Tung University, Hsinchu, Taiwan, Republic of China

<sup>b</sup> Department of Photonics and Institute of Electro-Optical Engineering, National Chiao Tung University, Hsinchu, Taiwan, Republic of China

Version of record first published: 05 Oct 2009

To cite this article: Chia-Jen Lin, Chuan-Hsien Lin, Cho-Fan Hsieh, Ru-Pin Pan, Yu-Tai Li & Ci-Ling Pan (2009): Some Characteristics of a Liquid-Crystal Phase Grating for THz Waves, *Molecular Crystals and Liquid Crystals*, 507:1, 114-121

To link to this article: <http://dx.doi.org/10.1080/15421400903050301>

PLEASE SCROLL DOWN FOR ARTICLE

Full terms and conditions of use: <http://www.tandfonline.com/page/terms-and-conditions>

This article may be used for research, teaching, and private study purposes. Any substantial or systematic reproduction, redistribution, reselling, loan, sub-licensing, systematic supply, or distribution in any form to anyone is expressly forbidden.

The publisher does not give any warranty express or implied or make any representation that the contents will be complete or accurate or up to date. The accuracy of any instructions, formulae, and drug doses should be independently verified with primary sources. The publisher shall not be liable for any loss, actions, claims, proceedings, demand, or costs or damages whatsoever or howsoever caused arising directly or indirectly in connection with or arising out of the use of this material.

## Some Characteristics of a Liquid-Crystal Phase Grating for THz Waves

**Chia-Jen Lin<sup>1</sup>, Chuan-Hsien Lin<sup>1</sup>, Cho-Fan Hsieh<sup>1</sup>,  
Ru-Pin Pan<sup>1</sup>, Yu-Tai Li<sup>2</sup>, and Ci-Ling Pan<sup>2</sup>**

<sup>1</sup>Department of Electrophysics, National Chiao Tung University,  
Hsinchu, Taiwan, Republic of China

<sup>2</sup>Department of Photonics and Institute of Electro-Optical  
Engineering, National Chiao Tung University, Hsinchu,  
Taiwan, Republic of China

*We propose and demonstrate an electrically controlled liquid crystal phase grating for the terahertz wave. The performance of the device was characterized by a terahertz time-domain spectrometer. The experimental results were in a good agreement with the prediction by classic diffraction theory.*

**Keywords:** liquid crystal; phase grating; terahertz devices; terahertz wave

## INTRODUCTION

In the past decade, terahertz (THz) photonics had progressed remarkably. THz technology and its applications including ultrafast dynamics in materials, communication, biomedical imaging, and environmental surveillance were realized [1–3]. However, essential quasi-optic components such as phase shifters, modulators, attenuators, polarizers, and beam splitters in the THz range are relatively underdeveloped. For controlling electromagnetic waves, the periodic structures such as gratings are frequently employed. In the THz range, tunable devices based on optically and electrically controlled


This work was supported in part by the National Science Council grants NSC 95-2221-E-009-249, PPAEU-II and the ATU program of the Ministry of Education, Taiwan, Republic of China.

Address correspondence to Ci-Ling Pan, Department of Physics, National Tsing Hua University, Hsinchu, Taiwan 30013, Republic of China. E-mail: clpan@faculty.nctu.edu.tw

Downloaded by [University of California, San Diego] at 14:33 08 August 2012

## Downloaded by [University of California, San Diego] at 14:33 08 August 2012

Downloaded by [University of California, San Diego] at 14:33 08 August 2012



Downloaded by [University of California, San Diego] at 14:33 08 August 2012


materials with different refractive indices as shown in Figure 1. The electric fields of electromagnetic waves that pass through materials 1, 2 and the total field  $E$  detected at an angle of  $\phi$  from the incident beam can be written as,

$$\begin{aligned} E_1(\phi) &= \sum_{n=1}^{odd} \int_{nl}^{(n+1)l} E_0 e^{iky \sin \phi} e^{i(n_1 + i\kappa_1)kd} dy, \\ E_2(\phi) &= \sum_{n=0}^{even} \int_{nl}^{(n+1)l} E_0 e^{iky \sin \phi} e^{i(n_2 + i\kappa_2)kd} dy, \\ E &= E_1(\phi) + E_2(\phi), \end{aligned} \quad (1)$$

where  $E_0$  is the amplitude of the incident electric field,  $\phi$  is the diffraction angle,  $k$  is the wave number of the electromagnetic wave in free space,  $l$  is the width of each material,  $d$  is the thickness of the grating, and  $n_1 + i\kappa_1$  and  $n_2 + i\kappa_2$  are complex refractive indices of materials 1 and 2, respectively.

The grating was designed such that the efficiency of the 0th order diffracted THz waves would be highest around 0.3–0.5 THz. Parallel grooves having a period of 2.0 mm, a width of 1.0 mm, and a groove-depth of 2.5 mm were fabricated by stacking ITO (indium-tin-oxide) film coated fused silica substrates, for which the refractive index is 1.95 in the THz frequency region (0.2–0.8 THz). The surfaces of the fused silica were coated with polyimide (SE-130B, Nissan) and rubbed for alignment. The grooves were filled with the NLC, E7 (Merck), and sealed with a sheet of fused silica coated with DMOAP. Therefore, this device was constructed with alternate sections with 1.0 mm thick NLC layer and 1.0 mm thick fused silica sheet. The dimension of the NLC layers was 20.0 mm  $\times$  2.5 mm  $\times$  1.0 mm. In previous work, we have shown that the LC layer as thick as 1.5 mm can have a good alignment [13].

A schematic illustration of the device and the relationship between the NLC director and applied electric field are shown in Figure 2. The NLC E7 was aligned along the x-direction by the alignment layer. Since E7 is a birefringent material with positive dielectric anisotropy, the molecules tend to be aligned parallel to the direction of the applied electric field when the applied voltage is larger than the threshold voltage. The complex refractive indices of E7 in the THz frequency range have previous reported by our group [12]. There are no resonances from 0.2 to 1.2 THz. The value of the real part of the refractive indices for the ordinary wave and the extraordinary wave are respectively 1.58 and 1.71. The corresponding imaginary indices are

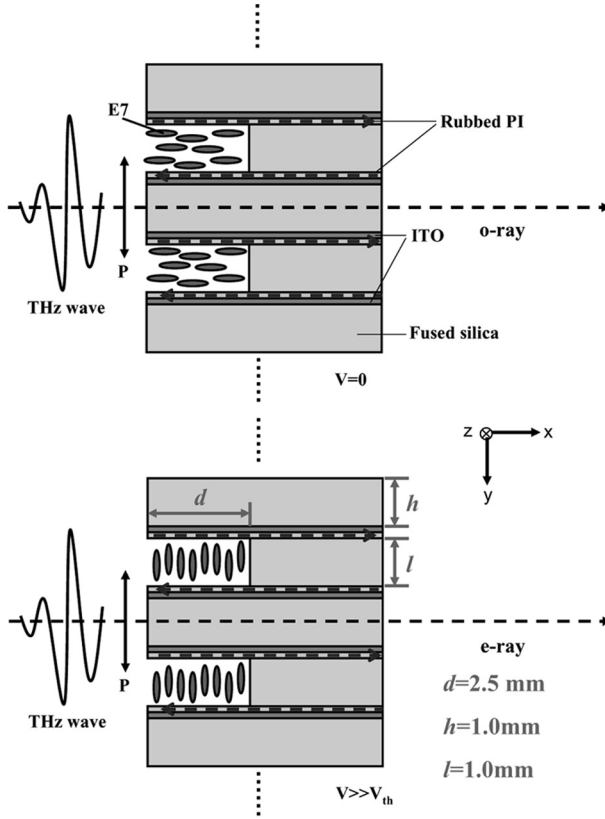


**FIGURE 2** Schematic illustration of electrically controlled NLC based THz phase grating. The polarization and propagation direction of incident THz wave are parallel to y- and x-axis, respectively. The director of NLC is rotated from x- to y-axis with increasing applied bias. ITO: indium-tin-oxide film as electrode, P: polarization of THz wave, V: bias,  $V_{th}$ : threshold voltage. The dimensions of the structure are shown.

$\kappa_o$  (0.010) to  $\kappa_e$  (0.007). The effective refractive index of NLC experienced by the THz propagating through the device can be written as

$$n_{eff} = \left( \frac{\cos^2 \theta}{n_o^2} + \frac{\sin^2 \theta}{n_e^2} \right)^{-1/2}, \quad (2)$$

where  $n_o$  and  $n_e$  are ordinary and extraordinary indices of refraction of NLC and  $\theta$  is the reorientation angle of NLC molecules from the original orientation. A stack of ITO film coated fused silica sheets without

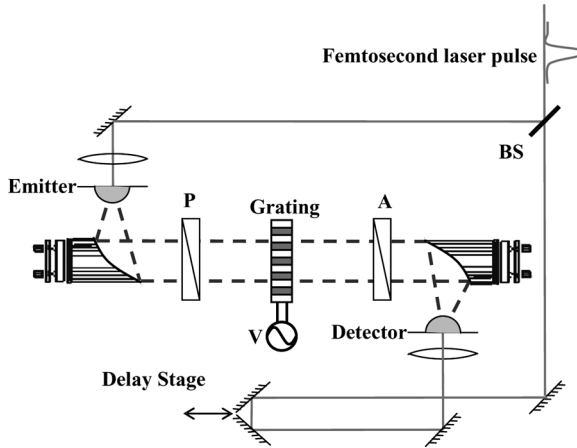


**FIGURE 3** Schematic diagram of the THz-TDS system. P: polarizer, A: analyzer, BS: beam splitter, V: bias. Dashed line indicates the propagation trace of the THz wave.

filling NLC, identically in dimension to that of the grating was prepared as the reference. The data presented below, were obtained at room temperature  $23 \pm 0.5^\circ\text{C}$ .

A photoconductive antenna-based terahertz time-domain spectrometer (THz-TDS) [15] was utilized to measure the 0th order diffraction spectra of the device. This is shown in Figure 3. Briefly, the pump beam from a femtosecond mode-locked Ti:sapphire laser illuminated a dipole antenna fabricated on low-temperature-MBE-grown GaAs to generate the broadband THz signal, which was collimated and collected through the THz phase grating by off-axis parabolic gold mirrors. A pair of parallel wire-grid polarizers (Specac, No. GS57204) was placed before and after the device under test. The 0th order diffracted pulse of THz radiation was coherently detected by another photoconductive antenna of the same type gated by ultrafast pulses from the same laser.

## RESULTS AND DISCUSSIONS

The 0th order diffracted THz pulses transmitted through the phase grating for both ordinary and extraordinary waves and that of the reference (black, red, and blue curves) were presented in Figure 4. The applying voltages are 0 and  $90 V_{\text{rms}}$  for o-ray and e-ray, respectively. An oscillating component can be seen arriving 3.0 ps and

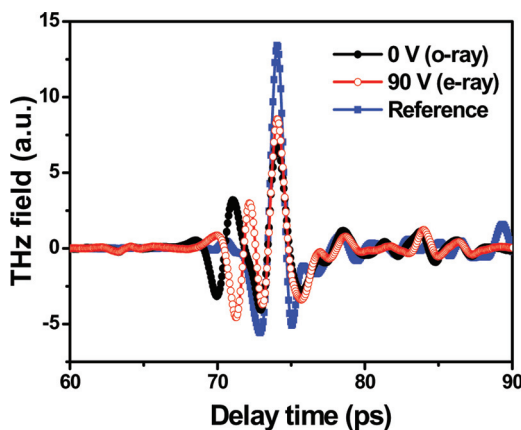


**FIGURE 4** Temporal profiles of the 0th order diffracted THz pulses through the phase grating bias at 0 V (o-ray) and 90 V (e-ray) and that of a reference sample.

1.9 ps before the main pulse for ordinary and extraordinary waves, respectively. This is attributed to the propagation time difference between the waves through fused silica and NLC. The calculated delay times,  $\delta nd/c$ , where  $\delta n$  is the difference of the refractive indices between fused silica and NLC,  $d$  is groove depth and  $c$  is the speed of light in vacuum, are 3.1 ps and 2.0 ps for o- and e-ray, respectively. These are very close to the experimental observed time difference.

The diffraction efficiencies of the incident THz pulse at various frequencies,  $\eta$ , are determined by applying fast Fourier transform algorithms to time-domain waveforms and normalizing the magnitudes of the diffracted signals for o-ray and e-ray with respect to that of the reference. In Figure 5, we plot the diffraction efficiency of the phase grating with the LC driven at different applying voltages as a function of frequency. The experimental results are in good agreements with the theoretical predictions according to Eq. (1). These results clearly demonstrated that the diffraction efficiency of the phase grating was the highest at the frequency of 0.3 THz, according to our design. For ordinary wave at 0.3 THz, the phase difference between fused silica and E7 was close to  $2\pi$ . Therefore, the transmission of the grating was higher. The THz wave was mainly concentrated in the 0th order. In contrast, the phase difference is close to  $\pi$  for extraordinary waves at 0.3 THz. The diffraction efficiency was smaller for the 0th order, because the THz wave was mostly diffracted into the 1st order.



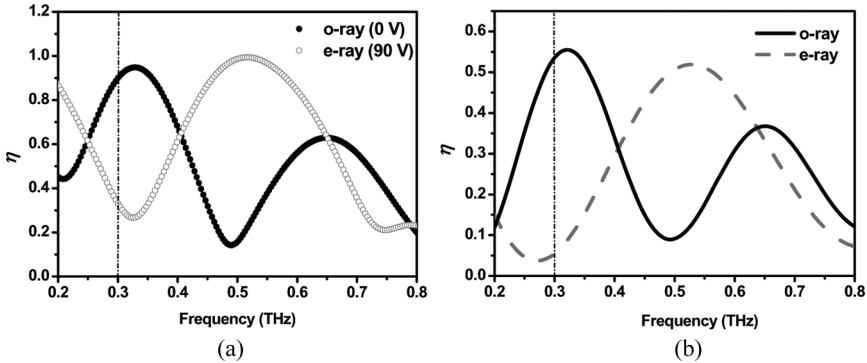

**FIGURE 5** (a) Experimental observation and (b) theoretical calculation of diffraction efficiencies of the phase grating as a function of frequency. Curves for the grating driven at two different applied voltages corresponding to o-ray and e-ray are shown.

## CONCLUSIONS

We propose and demonstrate an electrically controlled liquid crystal phase grating for the terahertz wave. The performance of the device was characterized by a terahertz time-domain spectrometer. The experimental results were in a good agreement with the theoretic prediction by classic diffraction theory. Applications of the device include beam splitting, scanning, and modulation of the THz wave.

## REFERENCES

- [1] Ferguson, B. & Zhang, X.-C. (2002). *Nature Materials*, 1, 26.
- [2] Mittleman, D. (2002). *Sensing with THz radiation*, Springer-Verlag: New York.
- [3] Siegel, P. H. (2002). *IEEE Trans. Microwave Theory Tech.*, 50, 910.
- [4] Libon, I. H., Baumgärtner, S., Hempel, M., Hecker, N. E., Feldmann, J., Koch, M., & Dawson, P. (2000). *Appl. Phys. Lett.*, 76, 2821.
- [5] Kleine-Ostmann, T., Dawson, P., Pierz, K., Hein, G., & Koch, M. (2004). *Appl. Phys. Lett.*, 84, 3555.
- [6] Kersting, R., Strasser, G., & Unterrainer, K. (2000). *Electron. Lett.*, 36, 1156.
- [7] Tsai, T. R., Chen, C. Y., Pan, C.-L., Pan, R.-P., & Zhang, X.-C. (2003). *Appl. Opt.*, 42, 2372.
- [8] Pan, R.-P., Tsai, T.-R., Chen, C.-Y., & Pan, C.-L. (2003). *J. Biological Physics*, 29, 335.
- [9] Pan, R.-P., Tsai, T.-R., Wang, C., Chen, C.-Y., & Pan, C.-L. (2004). *Mol. Cryst. Liq. Cryst.*, 409, 137.
- [10] Pan, R.-P., Hsieh, C.-F., Pan, C.-L., & Chen, C.-Y. (2008). *J. Appl. Phys.*, 103, 1.
- [11] Tang, T.-T., Pan, R.-P., Wang, Y.-C., & Pan, C.-L. (2008). *Ferroelectrics*, 364, 72.

- [12] Chen, C.-Y., Hsieh, C.-F., Lin, Y.-F., Pan, R.-P., & Pan, C.-L. (2004). *Opt. Express*, *12*, 2625.
- [13] Wu, H.-Y., Hsieh, C.-F., Tang, T.-T., Pan, R.-P., & Pan, C.-L. (2006). *IEEE Photon. Technol. Lett.*, *18*, 1488.
- [14] Lin, C.-J., Li, Y.-T., Hsieh, C.-F., Pan, R.-P., & Pan, C.-L. (2008). *Optics Express*, *16*, 2995.
- [15] Pan, C.-L., Hsieh, C.-F., Pan, R.-P., Tanaka, M., Miyamaru, F., Tani, M., & Hangyo, M. (2005). *Opt. Express*, *13*, 3921.