

This article was downloaded by:

On: 14 January 2011

Access details: *Access Details: Free Access*

Publisher *Taylor & Francis*

Informa Ltd Registered in England and Wales Registered Number: 1072954 Registered office: Mortimer House, 37-41 Mortimer Street, London W1T 3JH, UK



## Molecular Simulation

Publication details, including instructions for authors and subscription information:

<http://www.informaworld.com/smpp/title~content=t713644482>

### Characterization of a novel self-association of an alternating copolymer into nanotubes in solution

C. Malardier-Jugroot<sup>ab</sup>; T. G. M. van de Ven<sup>ab</sup>; M. A. Whitehead<sup>a</sup>

<sup>a</sup> Chemistry Department, McGill University, Montreal, Canada <sup>b</sup> Pulp and Paper Research Centre, McGill University, Montreal, Canada

**To cite this Article** Malardier-Jugroot, C. , van de Ven, T. G. M. and Whitehead, M. A.(2005) 'Characterization of a novel self-association of an alternating copolymer into nanotubes in solution', *Molecular Simulation*, 31: 2, 173 — 178

**To link to this Article:** DOI: 10.1080/08927020512331328716

**URL:** <http://dx.doi.org/10.1080/08927020512331328716>

PLEASE SCROLL DOWN FOR ARTICLE

Full terms and conditions of use: <http://www.informaworld.com/terms-and-conditions-of-access.pdf>

This article may be used for research, teaching and private study purposes. Any substantial or systematic reproduction, re-distribution, re-selling, loan or sub-licensing, systematic supply or distribution in any form to anyone is expressly forbidden.

The publisher does not give any warranty express or implied or make any representation that the contents will be complete or accurate or up to date. The accuracy of any instructions, formulae and drug doses should be independently verified with primary sources. The publisher shall not be liable for any loss, actions, claims, proceedings, demand or costs or damages whatsoever or howsoever caused arising directly or indirectly in connection with or arising out of the use of this material.

# Characterization of a novel self-association of an alternating copolymer into nanotubes in solution

C. MALARDIER-JUGROOT†‡\*, T.G.M. VAN DE VEN†‡ and M.A. WHITEHEAD†

†Chemistry Department, McGill University, Montreal, Canada

‡Pulp and Paper Research Centre, McGill University, Montreal, Canada

(Received April 2004; in final form October 2004)

The characterization of the association of an alternating copolymer was performed using theoretical methods (quantum mechanics and molecular mechanics) and experimental methods (cryo-Transmission Electron Microscopy (cryo-TEM), neutron reflectivity and neutron scattering). The most stable conformation obtained for the self-association at pH 7 using theoretical methods is a tubular structure in which eight SMA molecules make one twist of a helix. The tubes can grow in length by continued regular stacking of benzene rings. The nanotubes have inner and outer diameters of about 28 and 41 Å, respectively. The hydrophobic groups are mainly located inside the tube and the hydrophilic groups are mainly on the exterior surface of the tube. They can also associate with themselves creating planes of aligned tubes, which can stack upon each other. The association of alternating copolymers into nanotubes is a novel self-association process.

The association of SMA octamers into a tubular structure at pH7 was confirmed experimentally by cryo-TEM and the nanotubes observed were several micrometers long. The shape as well as the inner and outer diameter of the nanotubes were also characterized by neutron scattering and the conformation at the air–water interface by neutron reflectivity.

**Keywords:** Alternating copolymer; Self-assembly; Quantum mechanics; cryo-TEM; Neutron scattering

## 1. Introduction

Self-assembly is a very efficient method to obtain well-defined, and often defect-free, nano-architectures. The association and variety of shapes and properties of block copolymers have been extensively studied. Applications of those associations range from foam stability to drug delivery. In contrast, the associations of alternating copolymers have been rarely studied. The present paper investigates the association of a specific alternating copolymer, poly (styrene-alt-maleic anhydride) (SMA), both numerically and experimentally.

Poly(styrene-alt-maleic anhydride) is an alternating copolymer, for instance, used in the medical field to enhance the properties of anti-tumor drugs, in the semiconductor field as an etch resist, and in the pulp and paper industry as a surface sizing agent to enhance printing. SMA is composed of alternating hydrophobic and hydrophilic groups and its chemical structure is pH-dependent. The different ionization states are shown in

figure 1. The association of the SMA chains has previously been observed at neutral pH by dynamic light scattering [2] over a wide range of molecular weights, with a hydrodynamic radius in the order of microns. A theoretical approach is used in this paper to characterize precisely the association of SMA in solution and to explain the pH dependence of SMA conformations.

## 2. Monomer conformations

Two methods of optimization have been combined to obtain the ground state configuration of monomers at different pH values: the Tree Branch method [3] and a series of scans in energy [4–6] using the molecular modelling softwares Gaussian 98W [7] and Hyperchem.¶ The calculations performed in this study are gas phase calculations and the difference in pH will be modelled using the different degrees of ionization of the polymer in solution (figure 1) The configurations obtained for the

\*Corresponding author. E-mail: cecile.malardier@mail.mcgill.ca

¶HyperChem release 5.11 (1999) Hypercube Inc.

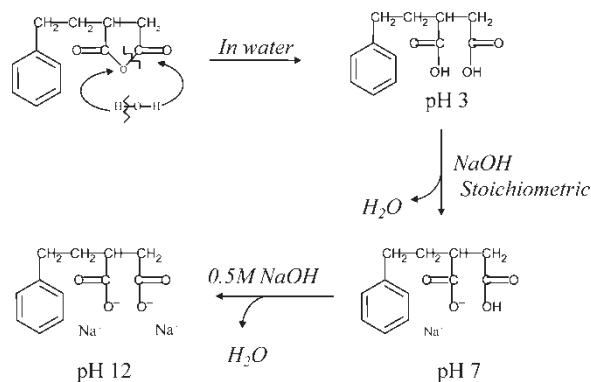


Figure 1. pH dependence of the molecular structure of poly SMA.

monomer at three different pH values are shown in figure 2. The main difference between the configurations occurs at pH 7 where the presence of a hydrogen bond stiffens the conformation of the molecule and as a result, the orientations of the binding sites for a second monomer are very different for pH 7 from those at pH 3 or 12. This hydrogen bond is very strong (1.68 Å), compared to a typical hydrogen bond (1.80 Å for water) and is expected therefore to be present in aqueous solution.

### 3. Dimer conformations

The dimer structure of SMA possesses two chiral centres and therefore, all the structures need to be investigated. For the dimer conformation, four structures will be optimized: the RR, the RS, the SR and the SS conformations. The structures were optimized at the PM3 level of theory using series of scans in energy. These structures were reoptimized at the RHF/6-31G\*\*.

The structures of the dimers obtained at pH 3 and 12 show a 90° angle between the first monomer and the second (figure 3). The structures obtained at pH 7 are very linear compared to pH 3 and 12. In addition, the hydrogen bond observed in the monomer conformation is still present in the dimer structures (figure 3).

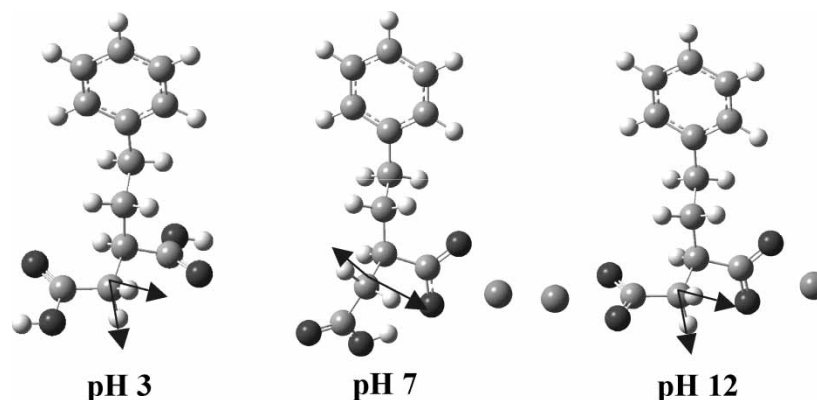


Figure 2. Optimized conformation of styrene maleic anhydride at three different pH values at the RHF/6-31G\*\* level of theory. The orientations of the binding sites (→) at pH 7 are very different from the orientations of the binding sites at pH 3 or 12.

### 4. Quadramer conformations

Figure 4 summarizes the chirality dependence of the quadrimers at different pH values. The study of the quadramer conformations at different pH values shows that the polymer at pH 7 is linear, unlike at pH 3 and 13 (figure 4). The linearity arises from the stiffening of the molecule by the internal H-bond observed in the monomer and dimer conformation. This conformation does not depend on the chirality of the chain [8].

In addition, the orientation of the benzene groups at pH 7 are very similar for all the different possible chiralities of the chain. The linearity of the conformation and the similar orientation of the benzene groups therefore allow strong association between the polymer chains.

At low or high pH, no association was observed because the conformation is an irregular helix. The irregularity of the helix at pH 3 and 13 is due to the chirality dependence of the conformation at low and high pH.[8] The study of the quadrimers, pentamers and hexamers showed that the conformation of SMA at pH 7 is repetitive from the trimer.

### 5. Association at pH 7

When two molecular chains at pH 7 associate, the angle between them is 90°, therefore, by associating eight SMA molecules, a tube can be formed. The front view of this tube is a square due to the 90° angle between two chains. As an example, the association of dodecamers was studied using molecular modelling and the most stable conformation was found to be a tubular conformation for which the inside of the tube is mainly hydrophobic, whereas the exterior is mainly hydrophilic (figure 5). The cavity of the tube was determined to be about 28 Å and the external diameter about 41 Å. The tubular structure is maintained by stacking interactions between the benzene groups of poly (styrene-maleic anhydride) and therefore this interaction, studied in the gas phase, is likely to be stable in water.

This way of self-assembly in nanotubes has not been recognized before: a recent review on organic nanotubes mentions four possible strategies for the molecular

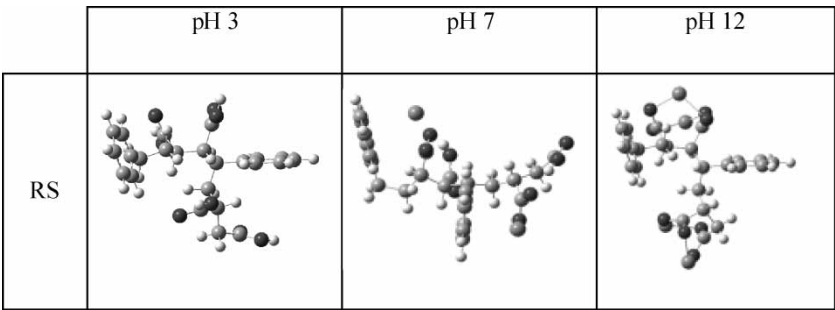


Figure 3. Optimized structure of dimers of SMA of RS chirality at pH 3, 7 and 12.







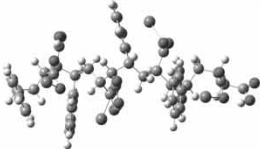





pH	Chirality	Optimised structure	Backbone
pH 3	SR RR SR		
	SR SR SR		
pH 7	SR RR SR		
	SR SR SR		
pH 12	SR RR SR		
	SR SR SR		

Figure 4. Optimized structure and schematic backbone representation of quadrimers of SMA of different chirality at pH 3, 7 and 12. At pH 7, the structures are linear, independent of the chirality of the chains.

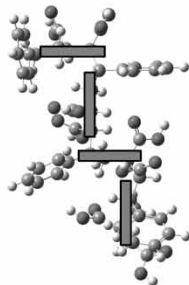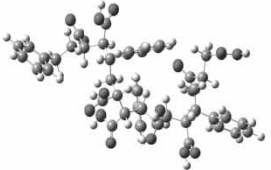


Figure 5. Front view and side view of the configuration of the tubular association of SMA dodecamers at pH 7 at the molecular mechanical level.

assembly of tubular materials [1], but the self-assembly of rigid alternating copolymers is not considered.

The interactions occurring between the chains are hydrophobic interactions, protecting the benzene groups from contact with water.

This association can grow in two directions: at the tube ends to increase the length (longitudinal growth); between the tubes to increase the width (radial growth) (figure 6). In addition, the association does not depend on the molecular weight nor on the polydispersity of the SMA chains; indeed small chains can easily associate with long chains (figure 6). The tubes can also associate with themselves creating planes of aligned tubes as depicted in figure 6. The planes can then associate with an angle of  $45^\circ$  between the orientations of the tubes in the planes due to the orientation of the benzene groups with respect to the tube growth.
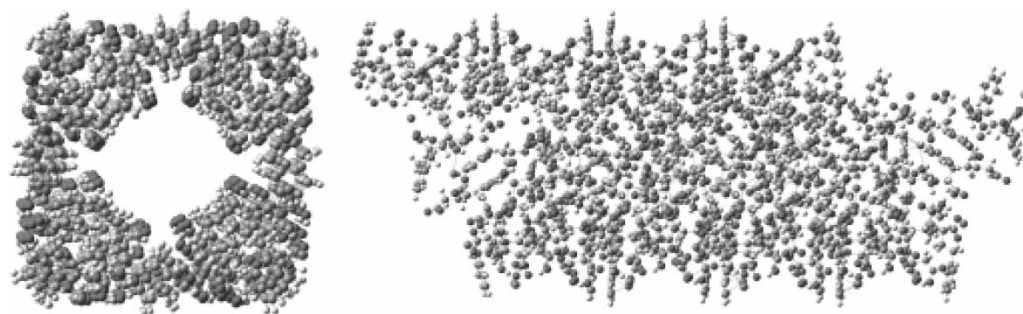
## 6. Cryo-TEM characterization

We performed experiments to observe the tubular structures in water by cryo-TEM. In these experiments, a drop of an aqueous solution of octamers of SMA (of molecular weight 1600) at a given pH was refrigerated in liquid nitrogen. The frozen sample was cut, and a replica of the top surface was obtained by first spraying a platinum–carbon mixture at  $45^\circ$  with respect to the surface and then by spraying carbon normal to the surface. In preparing samples for cryo-TEM, the surface often fractures at locations where there were discontinuities in structure

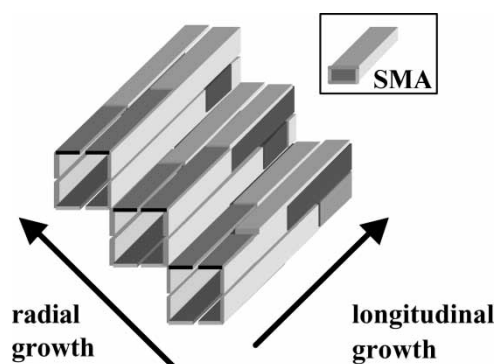


Figure 6. Schematic representation of the growth of the SMA association at pH 7 in the radial and longitudinal directions.

occur. The results obtained with this method for pH 7 shows very long lines with a spacing of about  $50 \text{ \AA}$  (figure 7(b)), which closely corresponds to the diameter of the nanotubes calculated theoretically. These lines are organized in sheets, one on top of the other, with the lines of one sheet making an angle of  $45^\circ$  with the other sheet (figure 7). This angle is due to the stacking interaction between benzene groups, which make a  $45^\circ$  angle with the main axis of the tube. No regular structure was observed by cryo-TEM at pH 12.

## 7. Neutron scattering characterization

In order to fully characterize the association at the molecular level and the macromolecular properties

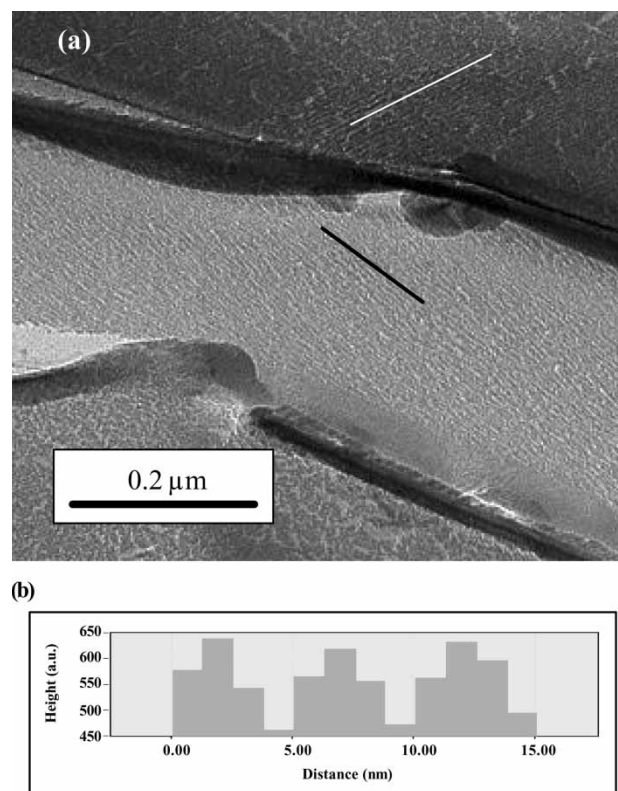


Figure 7. (a) cryo-TEM picture of the association of SMA in solution (1% wt) at pH 7. The lines represent the direction of the tubular association of SMA. (b) Height profile of three lines of the cryo-TEM image, confirming that the diameter of one tube is about  $50 \text{ \AA}$ .



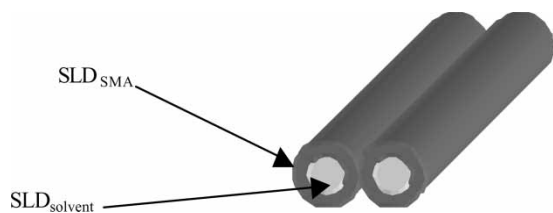


Figure 8. Hollow cylinder model selected to fit the experimental profiles (SLD is the scattering length density).

influencing the structure of SMA at pH 7, a neutron scattering study has been performed at ILL (Grenoble, France).

The model used to fit the experimental profiles is modelled by hollow cylinders (nanotubes) interacting with a spherical potential [9] (figure 8). This model is an approximation of the real structure, which is composed of nanotubes interacting to form sheets packed upon each other and neglects the effect of the packing of the sheets upon each other. The fitted result for a 2% wt SMA solution at pH 7 (molecular weight 40,000) is shown in figure 9. The fitted inner and outer radii of the nanotube are 14 and 19 Å, respectively, which closely correspond to the numerically predicted radii. The profile at pH 7 can be compared to the profile at pH 12 where no structure factor was observed in the latter (figure 10). The same internal and external radii were observed for different concentrations.

## 8. Neutron Reflectivity

To understand the mechanism of association at pH 7 and the influence of the conformation of SMA at the air–water interface, neutron reflectivity experiments [10,11] were performed at NIST (Washington, USA). These experiments were performed with 1%wt solutions of the deuterated ethyl esters of poly (styrene-maleic anhydride), used in order to label the hydrophilic part of SMA.

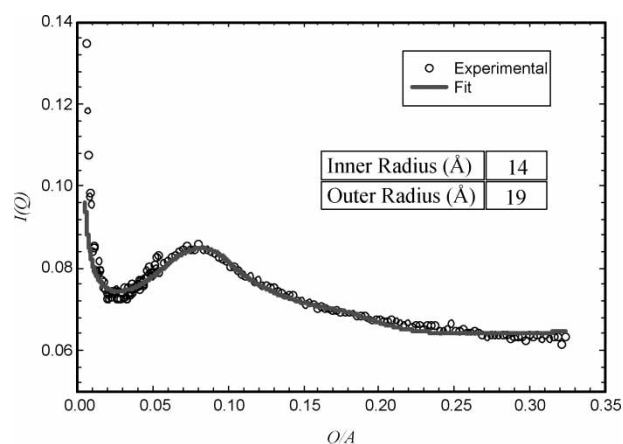


Figure 9. Neutron scattering profile and fitting curve of 2% wt SMA solution at pH 7.

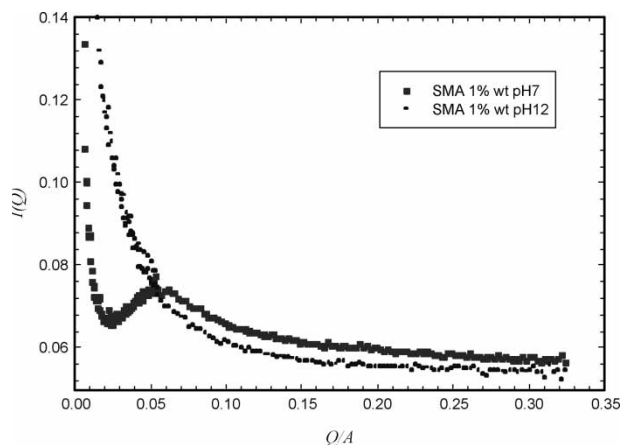


Figure 10. Neutron scattering profile of 1% wt SMA solution at pH 7 and 12.

The results obtained show that a complete monolayer of SMA is formed at the air–water interface at pH 3 and 7, with a surface coverage of about 1.2 mg/m<sup>2</sup>. At pH 13, the polymer is more soluble and forms an incomplete monolayer (coverage 0.9 mg/m<sup>2</sup>). SMA adsorbs in a flat configuration, with the benzene groups sticking out in the air. The association does influence the conformation at the air–water interface at pH 7, as a 5 h delay is observed in obtaining a stable signal (figure 11). (Such a delay was not observed at low or high pH). This delay is likely due to the slow establishment of an equilibrium between associated SMA molecules in solution and single SMA molecules at the air–water interface [12].

## 9. Conclusion

The association of an alternating copolymer observed by DLS was characterized by theoretical and experimental methods. The conformational study of the monomers at three pH values (3, 7 and 12) showed a unique conformation at pH 7 where a strong hydrogen bond

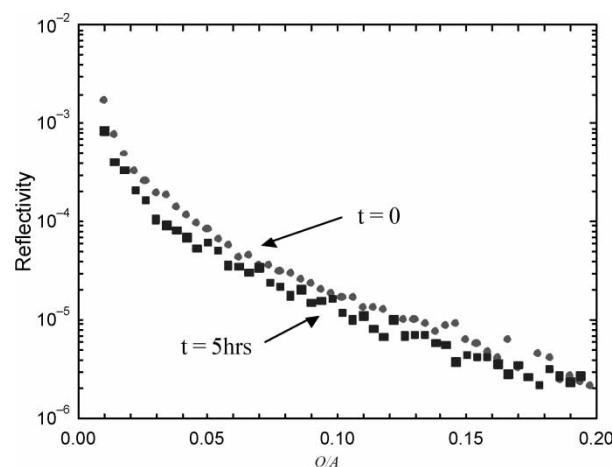


Figure 11. Neutron reflectivity profile of the ethyl ester of SMA, residing at an air–water interface at pH 7.

induces a change in the orientation of the binding sites compared to the conformation at pH 3 and 12. The conformation of the quadrimer at pH 7 is very linear and the linearity is not dependent on the chirality of the chain. This conformation will allow an association between the SMA chains at pH 7.

The association consists of eight SMA chains associated into a nanotube with an inner diameter of 28 Å and an outer diameter of 41 Å. Furthermore, the nanotubes can then associate to form a 2-dimensional structure, the planes obtained by self-association of the nanotubes can stack upon each other by hydrophobic interaction and form a 3-dimensional architecture. The association of alternating copolymers into nanotubes has not been recognized before.

The structure predicted by theoretical calculations was confirmed and observed by cryo-TEM and neutron scattering. In addition, an equilibrium was observed between associated SMA molecules in solution and single SMA molecules at the air–water interface by neutron reflectivity.

## Acknowledgements

This work was supported by NSERC and by the “Wood Pulp” Network of Centers of Excellence (Canada). NIST and NCNR (Washington, USA) are thanked for support and neutron reflectometer facilities; ILL (Grenoble, France) is thanked for support and neutron scattering facilities. The authors gratefully acknowledge Dr T. Cosgrove and Dr R. Richardson (University of Bristol, UK) for help with the neutron reflectivity and scattering experiments and Dr H. Vali and Dr S.K. Sears (McGill University, Canada) for the cryo-TEM experiments. Paprican and NSERC are acknowledged for funding of an IRC.

## References

- [1] T.B. Bong, T.D. Clark, J.R. Granja, M.R. Ghadiri. Tubular organic materials. *Angew. Chem. Int. Ed.*, **40**, 988–1011 (2001).
- [2] G. Garnier, M. Duskova-Smrckova, R. Vyhnlkova, T.G.M. van de Ven J.-F. Revol. Association in solution and adsorption at an air–water interface of alternating copolymers of maleic anhydride and styrene. *Langmuir*, **16**, 3757–3763 (2000).
- [3] F. Villamagna, M.A. Whitehead. Comparison of complete conformational searching and the energy-optimized tree branch method in molecular mechanics calculations. *J. Chem. Soc., Faraday Trans.*, **90**(1), 47–54 (1994).
- [4] C. Malardier-Jugroot, A.C. Spivey, M.A. Whitehead. Study of the influence of the non-pyridyl nitrogen hybridisation on the stability of axially chiral analogues of 4-(dimethylamino)pyridine (DMAP). *J. Mol. Struct. (Theochem)*, **623**, 263 (2003).
- [5] C.-H. Yu, M. Norman, L. Schäfer, M. Ramek, A. Peeters, C. van Alsenoy. Ab-initio conformational analysis of N-formyl-L-alanine amide including electron correlation. *J. Mol. Struct. (Theochem)*, **567–568**, 361 (2001).
- [6] R. Benassi, F. Taddei. Thermochemical properties and homolytic bond cleavage of organic peroxyacids and peroxyesters: an empirical approach based on *ab initio* MO calculations. *J. Mol. Struct. (Theochem)*, **303**, 83 (1994).
- [7] Gaussian 98W (Revision A.5), Frisch, M. J. *et al.*, Gaussian, Inc., Pittsburgh PA, 1998.
- [8] C. Malardier-Jugroot, T.G.M. van de Ven, M.A. Whitehead (to be submitted to *J. Phys. Chem. A*).
- [9] J.-C. Dore, R. Benfield, D. Grandjean, G. Schmid, M. Kroll, D. Le Bolloc’h. Characterization of Porous Solids VI Studies. *Surface Science and Catalysis*, **144**, 163 (2002).
- [10] J. Penfold, R.M. Richardson, A. Zarbakhsh, J.R.P. Webster, D.G. Bucknall, A.R. Rennie, R.A. Jones, T. Cosgrove, R.K. Thomas, J.S. Higgins, P.D.I. Fletcher, E. Dickinson, S.J. Roser, I.A. McLure, A.R. Hillman, R.W. Richards, E.J. Staples, A.N. Burgess, E.A. Simister, J.W. White. Recent advances in the study of chemical surfaces and interfaces by specular neutron reflection. *J. Chem. Soc., Faraday Trans.*, **93**(22), 3899 (1997).
- [11] R. Richardson, R. Pelton, T. Cosgrove, J. Zhang. A neutron reflectivity study of Poly(N-isopropylacrylamide) at the air–water interface with and without sodium dodecyl sulfate. *Macromolecules*, **33**, 6269 (2000).
- [12] C. Malardier-Jugroot, T.G.M. van de Ven, R. Richardson, T. Cosgrove, M.A. Whitehead (in preparation)