

Acceptorless, intramolecular, alkyl dehydrogenation in the solid-state in a rhodium phosphine complex; reversible uptake of three equivalents of H₂ per molecule

Thomas M. Douglas and Andrew S. Weller*

Received (in Montpellier, France) 3rd December 2007, Accepted 18th December 2007

First published as an Advance Article on the web 21st January 2008

DOI: 10.1039/b718615k

Addition of H₂ to the phosphine alkene ligated complex [Rh(dppe)(PCyp₂Cyp')][BAR₄^F] **1** (Cyp = cyclo-C₅H₉; Cyp' = cyclo-C₅H₇, Ar^F = 3,5-(CF₃)₂C₆H₃) in the solid state results in hydrogenation of the alkene and uptake of two further equivalents of H₂ to afford the dihydride–dihydrogen complex [Rh(dppe)(PCyp₃)(H)₂(η²-H₂)][BAR₄^F] **2**. Placing **2** under a vacuum or argon results in sequential loss of H₂ and dehydrogenation of one of the cyclopentyl rings to reform **1**. The hydrogenation–dehydrogenation cycle has been repeated 5 times without apparent degradation and has been followed by solid-state ³¹P{¹H} NMR spectroscopy. Intermediates on this process have been trapped using acetonitrile to give stable complexes that have been characterised in solution. We have previously shown that this hydrogenation–dehydrogenation process also happens in the solution-state; and evidence is presented that shows that, apart from a subtle difference, the same overall transformation occurs in the solid-state.

Introduction

The selective activation of C–H bonds in hydrocarbons has been a long-standing topic of interest.^{1,2} Transition metal catalyzed alkane dehydrogenation to afford the corresponding olefin is particularly interesting as it delivers valuable unsaturated functionality. Although many dehydrogenations require a sacrificial hydrogen acceptor,³ “acceptorless” dehydrogenation using transition metal catalysts has been achieved.⁴ As well as this synthetic utility, the dehydrogenation of alkanes,⁵ or alkane analogs such as ammonia boranes,⁶ also represents a possible vector for the storage and transportation of H₂, which is of current interest due to the potential use of hydrogen as an energy carrier.⁷ Many of these elegant systems, however, are not as yet truly reversible, or require forcing conditions (heat) and only work in solution. Of interest, then, would be a system that performed this transformation reversibly at ambient, or near ambient, conditions in the solid-state. We report here such a system, that operates by a reversible acceptorless alkyl dehydrogenation in the solid-state to store and release up to three equivalents of H₂ per cycle.

We have recently reported the remarkably quick acceptorless dehydrogenation of one alkyl ring of *tris*-cyclopentylphosphine (PCyp₃) in the complex [Rh(dppe)Cl(PCyp₃)] on addition of Na[BAr₄^F], to afford [Rh(dppe)(PCyp₂Cyp')][BAr₄^F] **1** in quantitative yield (Scheme 1, Ar^F = 3,5-(CF₃)₂C₆H₃).^{8,9} This generates a hybrid phosphine–olefin ligand on a square planar Rh(i) centre. Addition of H₂ to **1** in CH₂Cl₂ solution results in hydrogenation of the alkene and the formation of the dihydrogen–dihydride complex **2**, [Rh(dppe)(PCyp₃)(η²-H₂)(H)₂][BAr₄^F]. This reaction is rever-

sible, and placing **2** under a vacuum relatively rapidly (~1 h) regenerates **1**. Intermediates in this process have been observed spectroscopically and also studied using computational methods.⁹ We now report that these reversible hydrogenation–dehydrogenation reactions also occur in the solid-state by solid–gas reactions. This represents not only a relatively rare example of an organometallic solid–gas reaction with small molecules^{10–13} but also, as far as we are aware, the first example of reversible and acceptorless alkyl dehydrogenation to be reported in the solid-state. Alkene hydrogenation^{11,14–16} and C–H activation^{16,17} (an early mechanistic step in alkane dehydrogenation²) have been described in the solid-state and in one case dehydrogenation of cyclopentene has also been reported, although a hydrogen acceptor is required and the reaction was not reported to be reversible.¹¹

Results and discussion


Addition of H₂ to light orange powder **1** at just above room temperature (40 °C) results in a subtle change in color to very pale yellow. This change can be followed spectroscopically by ³¹P{¹H} solid-state NMR (SSNMR) spectroscopy (Scheme 2 and Fig. 1), which shows a change consistent with the complete conversion of **1** to a new complex. Although we were not successful in using ¹H SSNMR to resolve a bound dihydrogen ligand,¹⁸ rapid vacuum transfer of CD₂Cl₂ at 78 K onto the pale yellow solid gave solution ³¹P{¹H} and ¹H NMR spectra (at 180 K) that showed a ~1 : 1 mixture of [Rh(dppe)(PCyp₃)(η²-H₂)(H)₂][BAr₄^F] **2** and [Rh(dppe)(PCyp₃)(L)(H₂)][BAr₄^F] **3**, the latter of which we have previously characterized as being a dihydride complex with a weakly bound ligand (C–H agostic or solvent) in the sixth coordination site.⁹ We have demonstrated previously that the bound dihydrogen ligand in **2** is sufficiently labile so that it is easily lost in

Department of Inorganic Chemistry, University of Oxford, Oxford, OX1 3QR. E-mail: andrew.weller@chem.ox.ac.uk



Placing the pale yellow, “hydrogen charged”, solid under a vacuum at room temperature results in a very rapid (seconds) darkening to deep red. This same transformation can be effected on replacing the H₂ atmosphere by flushing Ar over the solid. A slower (1 h) return to the pale orange of the starting material occurs either under vacuum or argon (as monitored by ³¹P{¹H} SSNMR and solution NMR spectroscopies). The ³¹P{¹H} SSNMR of the fully-cycled material show that **1** is returned unchanged, and the cycle can be repeated (five times) with no appreciable decomposition.

Solution trapping experiments suggest the identity of this dark red intermediate present in the solid-state. Vacuum transfer of CD_2Cl_2 onto the red solid results in a very broad room temperature solution $^3\text{1P}\{^1\text{H}\}$ NMR spectrum suggesting a dynamic process (Fig. 2). Cooling to 200 K arrests this processes and, still broad, signals are observed at $\delta \sim 74, 62$ and 23 that demonstrate a new product has been formed, which we assign to $[\text{Rh}(\text{dppe})\text{PCyp}_3(\text{L})][\text{BAr}_4^{\text{F}}]$ (L = agostic C–H, solvent or adventitious water) **5**. The hydride region of the ^1H NMR spectrum at low temperature is featureless showing that loss of the hydride ligands has occurred. The alkene region (δ 6.0–3.5) is also featureless, demonstrating that dehydrogenation of the PCyp_3 ligand has not occurred. Solutions of **5** slowly return to give **1** on standing at room



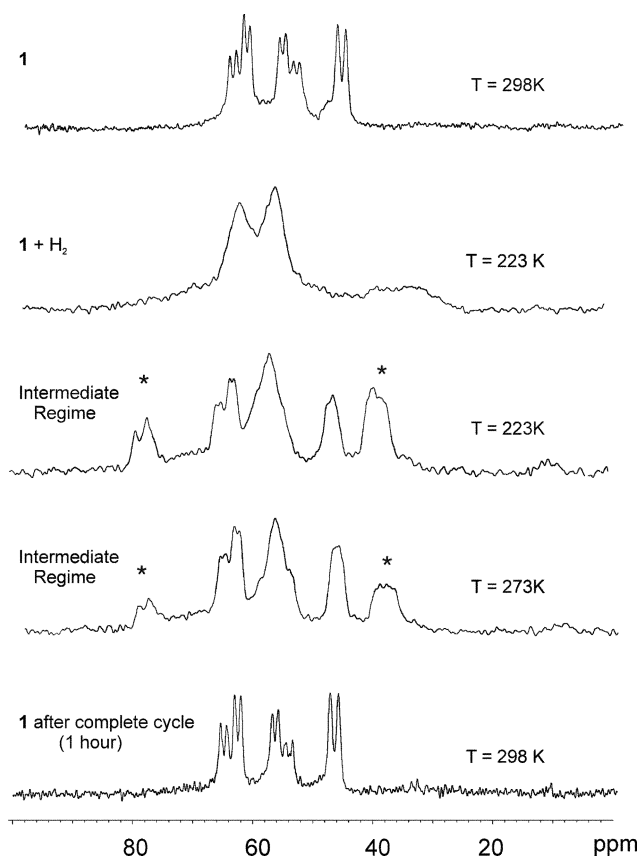


Fig. 1 Solid state $^{31}\text{P}\{^1\text{H}\}$ NMR (121.4 MHz) spectra of (a) **1**, (b) **1** + H_2 (i.e. complex **2**), (c, d) the intermediate regime demonstrating gradual H_2 loss from **2**, and (e) complex **1** after a complete cycle. * marks the peaks assigned to the intermediate species. The spin rate for all spectra was ca. 8000 Hz. Low temperature (223 K) used in an attempt to reduce the H_2 loss from complex **2**.

temperature. Vacuum transfer of $\text{CD}_2\text{Cl}_2/\text{MeCN}$ to the deep red intermediate in the solid-state gives $[\text{Rh}(\text{dppe})\text{PCyp}_3(\text{NC-Me})][\text{BAR}_4^{\text{F}}]$ **6**, with no **4** observed. The same product is observed by addition of MeCN to a CD_2Cl_2 solution of **5** or slow (24 h) loss of H_2 from **4**.⁹ No hydride signals were observed in the high field region. As complex **6** would result from addition of MeCN to a complex such as $[\text{Rh}(\text{dppe})\text{PCyp}_3(\text{L})][\text{BAR}_4^{\text{F}}]$ **5** we suggest that placing **2** under vacuum results in the loss of 2 equivalents of H_2 in the solid-state to give **5**. This is in contrast to solution experiments that show that the dihydride **3** is initially formed on application of a vacuum to **2**.⁹ Both solution and solid-state processes eventually give **1**—the dehydrogenated product. Thus although the solid-state and solution experiments follow the same overall transformation, they differ in the nature of the “low-hydride” intermediates that are observed (**5** versus **3**, respectively). Although the reasons for this are not completely clear at the present time we speculate that the structural change associated with stabilizing the vacant site in **3** is energetically less favorable in the solid state than for **5**. Changes between solution and solid-state reactivity with regard to hydrogen addition/ligand reorientation¹³ and selectivity¹⁹ have been noted previously.

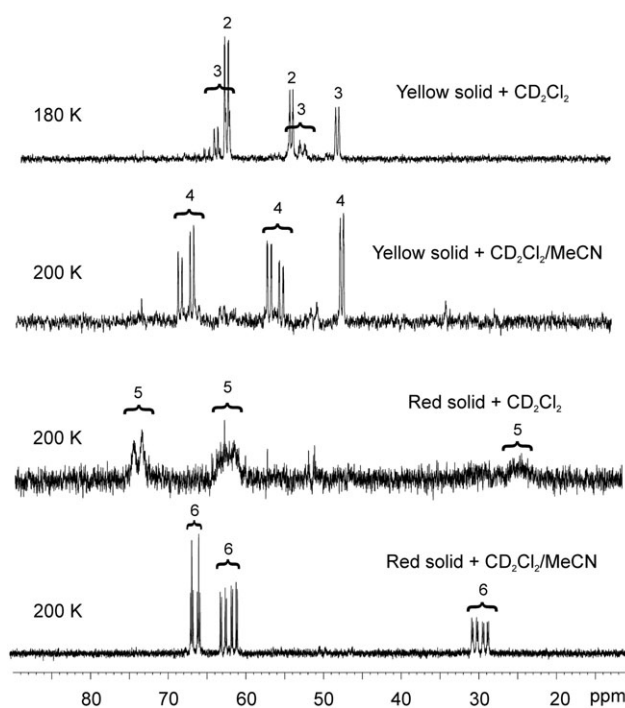


Fig. 2 $^{31}\text{P}\{^1\text{H}\}$ NMR (202.5 MHz) spectra of yellow and red solids after addition of CD_2Cl_2 or $\text{CD}_2\text{Cl}_2/\text{MeCN}$. Complex **2** (top spectrum) displays a tightly coupled ABMX coupling pattern and the outer AB lines are of low intensity. See ref. 9 for more details.

In conclusion we have demonstrated that a remarkably undemanding reversible acceptorless dehydrogenation of a cyclic alkane aids the storage and release of up to 3 equivalents of H_2 per molecule occurs in the solid-state. Although this overall would result in a modest H_2 storage uptake and release of 0.35% (w/w), which is clearly impractical for mobile applications,⁷ that this process occurs in the solid-state suggests that it might offer new opportunities in this technologically important area. Very recently a similar, solution only, process has been reported using $\text{RuH}_2(\eta^2\text{-H}_2)_2(\text{PCyp}_3)_2$ that stores 1.7% H_2 but this requires an acceptor (ethene) to promote transfer hydrogenation.²⁰

Experimental

All manipulations, unless otherwise stated, were performed under an atmosphere of argon, using standard Schlenk-line and glove-box techniques. Glassware was oven dried at 130°C overnight and flamed under vacuum prior to use. CD_2Cl_2 was distilled under vacuum from CaH_2 and stored over 3 Å molecular sieves. $[\text{Rh}(\text{dppe})(\text{PCyp}_2\text{Cyp}')][\text{BAR}_4^{\text{F}}]$ **1** was prepared by a published literature method.^{8,9} Complexes **2**, **3**, **4** and **6** have previously been prepared.⁹ ^1H , $^{31}\text{P}\{^1\text{H}\}$ and $^{13}\text{C}\{^1\text{H}\}$ solution NMR spectra were recorded on Bruker Avance 400 MHz and Bruker Avance 500 MHz spectrometers. Residual protio solvent was used as the reference for ^1H NMR spectra (CD_2Cl_2 : $\delta = 5.33$). $^{13}\text{C}\{^1\text{H}\}$ spectra were referenced to the perdeuterio solvent signal. $^{31}\text{P}\{^1\text{H}\}$ spectra were referenced against 85% H_3PO_4 (external). $^{31}\text{P}\{^1\text{H}\}$ Solid State NMR spectra were recorded on a Varian Unity Inova spectrometer with a 4 mm rotor (o.d.) and MAS probe. Operating

frequency (121.4 MHz for ^{31}P). Spectra were recorded using cross polarization experiments and referenced against 85% H_3PO_4 for ^{31}P . Contact time = 1 ms, recycle delay = 10 s. Chemical shifts are quoted in ppm. Coupling constants are quoted in Hz.

Solid state NMR spectra for $[(\text{dppe})\text{Rh}(\text{PCyp}_2\text{Cyp}')][\text{BAR}_4^{\text{F}}]$ (**1**)

$^{31}\text{P}\{^1\text{H}\}$ NMR (121.4 MHz, 298 K): δ 66.02 [dd, $J(\text{PP})$ 285 Hz, $J(\text{RhP})$ 120 Hz], 57.77 [dd, $J(\text{PP})$ 285 Hz, $J(\text{RhP})$ 115 Hz], 49.23 ppm [d, $J(\text{RhP})$ 159 Hz].

Preparation of $[(\text{dppe})(\text{PCyp}_3)\text{Rh}(\eta^2\text{-H}_2)(\text{H})_2][\text{BAR}_4^{\text{F}}]$ (**2**) in the solid state

For solid state NMR. Finely powdered $[(\text{dppe})\text{Rh}(\text{PCyp}_2\text{Cyp}')][\text{BAR}_4^{\text{F}}]$ (**1**) (30 mg, 1.87×10^{-2} mmol) was loaded into a 4 mm rotor (o.d.) which was then placed inside a J. Young's flask. The whole assembly was hydrogenated under 4 atm (298/77 = 3.8) at 40 °C overnight to give **2** as a very pale yellow solid. The rotor was stoppered with a close fitting plug, removed from the flask, and immediately put into an NMR spectrometer at low temperature (223 K) in an attempt to reduce the loss of H_2 from **2**. $^{31}\text{P}\{^1\text{H}\}$ NMR spectra were recorded over a 1 h period with slow warming to 298 K, this resulted in spectra consistent with complete conversion of **1** to **2**, the observation of an intermediate (**5**) and the recovery of complex **1**.

Solution trapping experiments. Finely powdered $[(\text{dppe})\text{Rh}(\text{PCyp}_2\text{Cyp}')][\text{BAR}_4^{\text{F}}]$ (**1**) (5 mg, 3.13×10^{-3} mmol) was hydrogenated at ~4 atm H_2 pressure (298 K/77 K = 3.8) and heated at 40 °C overnight to give **2** as a very pale yellow solid. CD_2Cl_2 was vacuum transferred (at 77 K) into a sample of the pale yellow solid and the resulting solution was characterised by ^1H and $^{31}\text{P}\{^1\text{H}\}$ NMR spectroscopy at 180 K, giving spectra fully consistent with a mixture of **2** and **3** in a 1 : 1 ratio.⁹ Vacuum transfer of $\text{CD}_2\text{Cl}_2/\text{MeCN}$ into a sample of the yellow solid gave spectra consistent with **4**⁹ as the only product.

Preparation of $[(\text{dppe})\text{Rh}(\text{PCyp}_3)(\text{L})][\text{BAR}_4^{\text{F}}]$ (**5**) (L = agostic interaction, vacant site or weakly bound adventitious ligand) in the solid state

A solid sample of **2** (5 mg, 3.11×10^{-3} mmol) was placed under vacuum at 298 K for 5 seconds giving a deep red solid. CD_2Cl_2 was vacuum transferred (at 77 K) into this red solid and ^1H and $^{31}\text{P}\{^1\text{H}\}$ NMR spectroscopy of the resulting solution at 200 K tentatively identified the complex as $[(\text{dppe})\text{Rh}(\text{PCyp}_3)(\text{L})][\text{BAR}_4^{\text{F}}]$ **5**. Vacuum transfer of $\text{CD}_2\text{Cl}_2/\text{MeCN}$ into a sample of the red solid gave ^1H and $^{31}\text{P}\{^1\text{H}\}$ NMR spectra fully consistent with those previously reported for **6**.⁹

^1H NMR (500.1 MHz, CD_2Cl_2 , 200 K): δ 7.92–7.31 (m, 20H, ArH), 7.70 (s, 8H, BAR_4^{F}), 7.51 (s, 4H, BAR_4^{F}), 2.88–0.85 (m, 31H, CH_2/CH). $^{31}\text{P}\{^1\text{H}\}$ NMR (202.5 MHz, CD_2Cl_2 , 200 K): δ 73.90 (br m), 61.92 (br m), 23.52 ppm (v br m).

Acknowledgements

The Royal Society and the EPSRC for funding. The EPSRC solid-state NMR service at the University of Durham, and in

particular Dr David Apperly, are thanked for acquiring the solid-state NMR spectra.

References

- R. H. Crabtree, *J. Chem. Soc., Dalton Trans.*, 2001, 2437–2450.
- Activation and Functionalization of C–H Bonds*, ed. K. I. Goldberg and A. S. Goldman, American Chemical Society, Washington, 2004.
- C. M. Jensen, *Chem. Commun.*, 1999, 2443–2449.
- (a) T. Aoki and R. H. Crabtree, *Organometallics*, 1993, **12**, 294–298; (b) K. M. Zhu, P. D. Achord, X. W. Zhang, K. Krogh-Jespersen and A. S. Goldman, *J. Am. Chem. Soc.*, 2004, **126**, 13044–13053; (c) W. W. Xu, G. P. Rosini, M. Gupta, C. M. Jensen, W. C. Kaska, K. Krogh-Jespersen and A. S. Goldman, *Chem. Commun.*, 1997, 2273–2274.
- (a) S. Hodoshima, H. Arai, S. Takaiwa and Y. Saito, *Int. J. Hydrogen Energy*, 2003, **28**, 1255–1262; (b) D. E. Schwarz, T. M. Cameron, P. J. Hay, B. L. Scott, W. Tumas and D. L. Thorn, *Chem. Commun.*, 2005, 5919–5921; (c) A. Moores, M. Poyatos, Y. Luo and R. H. Crabtree, *New J. Chem.*, 2006, **30**, 1675–1678.
- (a) M. C. Denney, V. Pons, T. J. Hebdon, D. M. Heinekey and K. I. Goldberg, *J. Am. Chem. Soc.*, 2006, **128**, 12048–12049; (b) C. W. Yoon and L. G. Sneddon, *J. Am. Chem. Soc.*, 2006, **128**, 13992–13993; (c) R. J. Keaton, J. M. Blacquire and R. T. Baker, *J. Am. Chem. Soc.*, 2007, **129**, 1844–1845.
- (a) L. Schlapbach and A. Züttel, *Nature*, 2001, **414**, 353–358; (b) W. Grochala and P. P. Edwards, *Chem. Rev.*, 2004, **104**, 1283–1315.
- T. M. Douglas, H. Le Notre, S. K. Brayshaw, C. G. Frost and A. S. Weller, *Chem. Commun.*, 2006, 3408–3410.
- T. M. Douglas, S. K. Brayshaw, R. Dallanegra, G. Kociok-Köhn, S. A. Macgregor, G. L. Moxham, A. S. Weller, T. Wondimagegn and P. Vadivelu, *Chem.–Eur. J.*, 2008, **14**, 1004–1022.
- (a) N. J. Coville and L. Cheng, *J. Organomet. Chem.*, 1998, **571**, 149–169; (b) M. Mediati, G. N. Tachibana and C. M. Jensen, *Inorg. Chem.*, 1992, **31**, 1827–1832; (c) C. S. Chin, B. Lee and S. Kim, *Organometallics*, 1993, **12**, 1462–1466; (d) S. Aime, W. Dastru, R. Gobetto, J. Krause and E. Sappa, *Organometallics*, 1995, **14**, 3224–3228; (e) K. Osakada and H. Ishii, *Inorg. Chim. Acta*, 2004, **357**, 3007–3013; (f) M. Olivan, A. V. Marchenko, J. N. Coalter and K. G. Caulton, *J. Am. Chem. Soc.*, 1997, **119**, 8389–8390; (g) C. Bianchini, C. Mealli, M. Peruzzini and F. Zanobini, *J. Am. Chem. Soc.*, 1992, **114**, 5905–5906.
- A. R. Siedle and R. A. Newmark, *Organometallics*, 1989, **8**, 1442–1450.
- G. J. Kubas, C. J. Unkefer, B. I. Swanson and E. Fukushima, *J. Am. Chem. Soc.*, 1986, **108**, 7000–7009.
- J. Matthes, T. Pery, S. Grundemann, G. Buntkowsky, S. Sabo-Etienne, B. Chaudret and H. H. Limbach, *J. Am. Chem. Soc.*, 2004, **126**, 8366–8367.
- C. Bianchini, S. Moneti, M. Peruzzini and F. Vizza, *Inorg. Chem.*, 1997, **36**, 5818–5825.
- (a) C. Bianchini, E. Farnetti, M. Graziani, J. Kaspar and F. Vizza, *J. Am. Chem. Soc.*, 1993, **115**, 1753–1759; (b) C. Bianchini, P. Frediani, M. Graziani, J. Kaspar, A. Meli, M. Peruzzini and F. Vizza, *Organometallics*, 1993, **12**, 2886–2887.
- C. Bianchini, M. Graziani, J. Kaspar, A. Meli and F. Vizza, *Organometallics*, 1994, **13**, 1165–1173.
- (a) A. R. Siedle, R. A. Newmark, K. A. Brownwensley, R. P. Skarjune, L. C. Haddad, K. O. Hodgson and A. L. Roe, *Organometallics*, 1988, **7**, 2078–2079; (b) C. Bianchini, M. Peruzzini and F. Zanobini, *Organometallics*, 1991, **10**, 3415–3417.
- G. J. Kubas, J. E. Nelson, J. C. Bryan, J. Eckert, L. Wisniewski and K. Zilm, *Inorg. Chem.*, 1994, **33**, 2954–2960.
- W. Weng, C. Y. Guo, C. Moura, L. Yang, B. M. Foxman and O. V. Ozerov, *Organometallics*, 2005, **24**, 3487–3499.
- M. Grellier, L. Vendier and S. Sabo-Etienne, *Angew. Chem., Int. Ed.*, 2007, **46**, 2613–2615.