

This article was downloaded by:

On: 28 January 2011

Access details: *Access Details: Free Access*

Publisher *Taylor & Francis*

Informa Ltd Registered in England and Wales Registered Number: 1072954 Registered office: Mortimer House, 37-41 Mortimer Street, London W1T 3JH, UK



Phosphorus, Sulfur, and Silicon and the Related Elements

Publication details, including instructions for authors and subscription information:

<http://www.informaworld.com/smpp/title~content=t713618290>

NEW NONGEMINAL CYCLOPHOSPHAZENES

Patty Wisian-Neilson^a; June-Ho Jung^a; Srinagesh K. Potluri^a; Clayton E. Mauldin^a; Hongming Zhang^a

^a Southern Methodist University, Dallas, Texas, USA

Online publication date: 12 August 2010

To cite this Article Wisian-Neilson, Patty , Jung, June-Ho , Potluri, Srinagesh K. , Mauldin, Clayton E. and Zhang, Hongming(2004) 'NEW NONGEMINAL CYCLOPHOSPHAZENES', *Phosphorus, Sulfur, and Silicon and the Related Elements*, 179: 4, 817 – 820

To link to this Article: DOI: 10.1080/10426500490427222

URL: <http://dx.doi.org/10.1080/10426500490427222>

PLEASE SCROLL DOWN FOR ARTICLE

Full terms and conditions of use: <http://www.informaworld.com/terms-and-conditions-of-access.pdf>

This article may be used for research, teaching and private study purposes. Any substantial or systematic reproduction, re-distribution, re-selling, loan or sub-licensing, systematic supply or distribution in any form to anyone is expressly forbidden.

The publisher does not give any warranty express or implied or make any representation that the contents will be complete or accurate or up to date. The accuracy of any instructions, formulae and drug doses should be independently verified with primary sources. The publisher shall not be liable for any loss, actions, claims, proceedings, demand or costs or damages whatsoever or howsoever caused arising directly or indirectly in connection with or arising out of the use of this material.

NEW NONGEMINAL CYCLOPHOSPHAZENES

Patty Wisian-Neilson, June-Ho Jung, Srinagesh K. Potluri,
Clayton E. Mauldin, and Hongming Zhang
Southern Methodist University, Dallas, Texas, USA

(Received August 21, 2003; accepted October 3, 2003)

A series of new nongeminally-substituted cyclic phosphazenes with various substituents has been prepared via deprotonation-substitution reactions at the Me groups of both the cis and trans isomers of [(Me)(Ph)PN]₃. Treatment of [(Me)(Ph)PN]₃ with n-BuLi followed by reaction with organic electrophilic reagents affords a variety of cyclic derivatives, [(RCH₂)(Ph)PN]₃, [R = Me, Cl, Br, I, (CH₂)₂Br, CH₂CH=CH₂, SR, C(=O)OLi, C(=O)OMe, C(=O)OEt]. The structures of these cis cyclic phosphazenes, which were obtained by x-ray diffraction, illustrate the basket-like shape of the molecules. Heating the cis and trans isomers of the parent [(Me)(Ph)PN]₃ produced mixtures of cyclic trimers and tetramers. The latter were isolated and characterized by x-ray crystallography. Nanoparticles of gold and silver were prepared by reduction of metal salts with a reducing agent in the presence of selected trimers.


Keywords: Nanoparticles; nongeminal; P–C substituents; phosphazene; tetramer; trimer

Although a number of cyclic phosphazenes with alkyl and aryl groups have been prepared and studied,¹ nongeminal substitution of alkyl and aryl groups at phosphorus is relatively new. By contrast, the preparation of phosphazene polymers with nongeminal alkyl and aryl substituents, e.g., [(Me)(Ph)PN]_n, via condensation polymerization of N-silylphosphoranimines is well-established.² Cyclic phosphazenes with nongeminal substituents present interesting stereochemical variety since two isomers are possible for nongeminal trimers, [RR'PN]₃ and four isomers may exist for the corresponding tetramers. In this

The authors thank the Robert A. Welch Foundation, the Petroleum Research Fund administered by the American Chemical Society, and the National Science Foundation for generous financial support.


Address correspondence to Patty Wisian-Neilson, Department of Chemistry, Southern Methodist University, Dallas, TX 75275. E-mail: pwisian@smu.edu

The diverse reactivity of a class of silicon-nitrogen-phosphorus compounds known as N-silylphosphoranamines, $\text{Me}_3\text{SiN}=\text{P}(\text{X})\text{R}'\text{R}''$, has been exploited to make a number of new compounds, including the polyphosphazenes with P—C bonded alkyl and aryl substituents.² In the course of these studies, it was found that treatment of $\text{Me}_3\text{SiN}=\text{P}(\text{X})(\text{Me})(\text{Ph})$, where X = OPh or OCH_2CF_3 , with simple alcohols facilitates cleavage of the silicon-nitrogen bonds as well as the phosphorus-oxygen bonds. While mixtures of products were obtained with most alcohols, treatment of $\text{Me}_3\text{SiN}=\text{P}(\text{OPh})(\text{Me})(\text{Ph})$, **1**, with $\text{CF}_3\text{CH}_2\text{OH}$ in a 6:1 mole ratio in the absence of solvent gives ca. 90% yields of a mixture of the *cis* and *trans* isomers of $[(\text{Me})(\text{Ph})\text{PN}]_3$, **2**.³ A large amount of phenol was also formed suggesting that the initial reaction might have produced the intermediate N—H phosphoranimine which then lost PhOH (Eq. 1). It was necessary to remove the PhOH by washing with aqueous base before these isomers were separated by column chromatography. The ratio of *trans* to *cis* isomers was ca. 2.8 to 1. Both isomers were fully characterized by NMR spectroscopy, x-ray crystallography, and elemental analysis. The *cis* isomer is particularly interesting since the phenyl groups on the same side of the nearly planar PN ring resemble a basket.



polymer formation can be observed.⁴ The same type of equilibrium between trimers and tetramers occurs when either the *cis* or the *trans* isomers of **2** are heated. At 220°C the trimers predominate with the *trans* isomer favored over the *cis* by at least 3:1. Less than 15% of the trimers were converted to tetramers at this temperature as determined by ³¹P NMR spectroscopy. However, at 250°C, up to 70% of the trimers were converted to tetramers after almost two weeks. Thus it was possible to isolate significant quantities of the tetramers. Indeed, each of the four possible isomers were separated using a sequence based on solubility differences, column chromatography, and formation of HCl adducts. Crystallographic analysis of each isomer shows that these have geometries that may be identified as cone, partial cone, 1,2-alternate, and 1,3-alternate by analogy to calix[4]arene or as *cis*, α -*trans*, β -*trans*, and γ -*trans* respectively.⁵

Like the well-studied polymer, poly(methylphenylphosphazene), [Me(Ph)PN]_n, there are three reactive sites in the simple *cis* and *trans* isomers of the trimer [(Me)(Ph)PN]₃, **2**. Although the aryl groups are susceptible to electrophilic aromatic substitution⁶ and the lone pairs of electrons on the backbone nitrogen atom coordinate readily to many Lewis acids,⁷ the methyl group provides the richest source of new polymers via deprotonation-substitution reactions.⁸ Hence, we have focused on the derivatization of methyl groups¹ to form new nongeminal substituted cyclic phosphazenes.⁹ Simple deprotonation with *n*-BuLi followed by treatment with the simple electrophile MeI was used to demonstrate the feasibility of the process (Eq. 2). The *trans* isomer cleanly goes to the tri-substituted derivative with three equivalents of the reagents, but the *cis* isomer yields both di- and tri-substituted products under similar conditions. This is likely due to the fact that the deprotonated ion formed from the *cis* isomer is less soluble. A variety of other electrophiles have been used since the initial report⁹ and afford variations of mono-, di-, and tri-substituted nongeminal cyclics, [(RCH₂)(Ph)PN]₃, where R = Cl, Br, I, (CH₂)₂Br, CH₂CH=CH₂, SR, C(=O)OLi, C(=O)OMe, and C(=O)OEt.

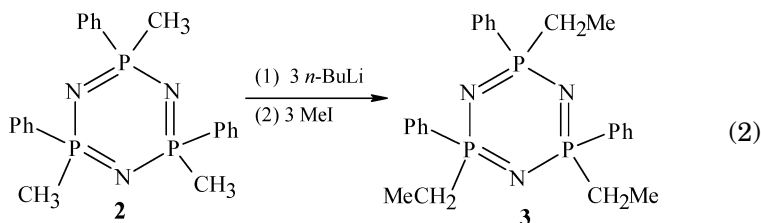

Several of these new cyclic phosphazenes have been used to stabilize metal nanoparticles as has been observed for the analogous polymer, [(Me)(Ph)PN]_n.¹⁰ Nanoparticles of gold and silver were prepared by reduction of metal salts such as NaAuCl₄ or AgNO₃ with a reducing agent (e.g., NaBH₄) in the presence of the trimer [(LiOOCCH₂)(Ph)PN]₃ in water. The metal nanoparticle composites were characterized by UV-vis spectroscopy and transmission electron microscopy (TEM).

REFERENCES

- [1] a) K. D. Gallicano, R. T. Oakley, and N. L. Paddock, *J. Inorg. Nucl. Chem.*, **42**, 923 (1980); b) K. D. Gallicano, R. T. Oakley, N. L. Paddock, and R. D. Sharma, *Can. J. Chem.*, **59**, 2654 (1981); c) R. T. Oakley and N. L. Paddock, *Can. J. Chem.*, **53**, 3038 (1975); d) T. N. Ranganathan, S. M. Todd, and N. L. Paddock, *Inorg. Chem.*, **12**, 316 (1973); e) P. J. Harris and L. A. Jackson, *Organometallics*, **2**, 1477 (1983).
- [2] R. H. Neilson and P. Wisian-Neilson, *Chem. Rev.*, **88**, 541 (1988).
- [3] P. Wisian-Neilson, R. S. Johnson, H. Zhang, et al., *Inorg. Chem.*, **41**, 4775 (2002).
- [4] a) H. R. Allcock and D. B. Patterson, *Inorg. Chem.*, **16**, 197 (1977); b) H. R. Allcock and G. Y. Moore, *Macromolecules*, **8**, 377 (1975).
- [5] a) R. A. Shaw, B. W. Fitzsimmons, and B. C. Smith, *Chem. Rev.*, **62**, 247 (1962); b) A. J. Berlin, B. Grushkin, and L. R. Moffet, Jr., *Inorg. Chem.*, **7**, 589 (1968).
- [6] P. Wisian-Neilson, M. Bahadur, J. M. Iriarte, and C. E. Wood, *Macromolecules*, **27**, 4471 (1994).
- [7] P. Wisian-Neilson and F. J. Garcia-Alonso, *Macromolecules*, **26**, 7156 (1993).
- [8] a) P. Wisian-Neilson, M. S. Islam, S. Ganapathiappan, et al., *Macromolecules*, **22**, 4382 (1989); b) A. L. Crumbliss, D. Cooke, J. Castillo, and P. Wisian-Neilson, *Inorg. Chem.*, **32**, 6088 (1993); c) P. Wisian-Neilson, L. Bailey, and M. Bahadur, *Macromolecules*, **27**, 7713 (1994); d) P. Wisian-Neilson and G.-F. Xu, *Macromolecules*, **29**, 3457 (1996); e) P. Wisian-Neilson and M. A. Schaefer, *Macromolecules*, **22**, 2003 (1989); f) P. Wisian-Neilson and C. Zhang, *Macromolecules*, **31**, 908 (1998).
- [9] J.-H. Jung, H. Zhang, and P. Wisian-Neilson, *Inorg. Chem.*, **41**, 6720 (2002).
- [10] C. H. Walker, J. V. St. John, and P. Wisian-Neilson, *J. Am. Chem. Soc.*, **123**, 3846 (2001).