

This article was downloaded by:

On: 30 January 2011

Access details: *Access Details: Free Access*

Publisher *Taylor & Francis*

Informa Ltd Registered in England and Wales Registered Number: 1072954 Registered office: Mortimer House, 37-41 Mortimer Street, London W1T 3JH, UK



Spectroscopy Letters

Publication details, including instructions for authors and subscription information:

<http://www.informaworld.com/smpp/title~content=t713597299>

Raman Spectroscopic Study of the Antimony Containing Mineral Partzite $\text{Cu}_2\text{Sb}_2(\text{O},\text{OH})_7$

Silmarilly Bahfenne^a; Ray L. Frost^a

^a Inorganic Materials Research Program, School of Physical and Chemical Sciences, Queensland University of Technology, Brisbane, Queensland, Australia

Online publication date: 05 April 2010

To cite this Article Bahfenne, Silmarilly and Frost, Ray L.(2010) 'Raman Spectroscopic Study of the Antimony Containing Mineral Partzite $\text{Cu}_2\text{Sb}_2(\text{O},\text{OH})_7$ ', *Spectroscopy Letters*, 43: 3, 202 – 206

To link to this Article: DOI: 10.1080/00387010903284364

URL: <http://dx.doi.org/10.1080/00387010903284364>

PLEASE SCROLL DOWN FOR ARTICLE

Full terms and conditions of use: <http://www.informaworld.com/terms-and-conditions-of-access.pdf>

This article may be used for research, teaching and private study purposes. Any substantial or systematic reproduction, re-distribution, re-selling, loan or sub-licensing, systematic supply or distribution in any form to anyone is expressly forbidden.

The publisher does not give any warranty express or implied or make any representation that the contents will be complete or accurate or up to date. The accuracy of any instructions, formulae and drug doses should be independently verified with primary sources. The publisher shall not be liable for any loss, actions, claims, proceedings, demand or costs or damages whatsoever or howsoever caused arising directly or indirectly in connection with or arising out of the use of this material.

Raman Spectroscopic Study of the Antimony Containing Mineral Partzite $\text{Cu}_2\text{Sb}_2(\text{O},\text{OH})_7$

Silmarilly Bahfenne
and Ray L. Frost

Inorganic Materials Research
Program, School of Physical and
Chemical Sciences, Queensland
University of Technology,
Brisbane, Queensland, Australia

ABSTRACT Raman spectroscopy of the mineral partzite $\text{Cu}_2\text{Sb}_2(\text{O},\text{OH})_7$ complemented with infrared spectroscopy were studied and related to the structure of the mineral. The Raman spectrum shows some considerable complexity with a number of overlapping bands observed at 479, 520, 594, 607, and 620 cm^{-1} with additional low-intensity bands found at 675, 730, 777, and 837 cm^{-1} . Raman bands of partzite in the spectral region 590 to 675 cm^{-1} are attributable to the ν_1 symmetric stretching modes. The Raman bands at 479 and 520 cm^{-1} are assigned to the ν_3 antisymmetric stretching modes. Raman bands at 1396 and 1455 cm^{-1} are attributed to SbOH deformation modes. A complex pattern resulting from the overlapping band of the water and OH units is found. Raman bands are observed at 3266, 3376, 3407, 3563, 3586, and 3622 cm^{-1} . The first three bands are assigned to water stretching vibrations. The three higher wavenumber bands are assigned to the stretching vibrations of the OH units. It is proposed that based upon observation of the Raman spectra that water is involved in the structure of partzite. Thus, the formula $\text{Cu}_2\text{Sb}_2(\text{O},\text{OH})_7$ may be better written as $\text{Cu}_2\text{Sb}_2(\text{O},\text{OH})_7 \cdot x\text{H}_2\text{O}$.

KEYWORDS antimony oxide, bindheimite, brandholzite, lewisite, partzite bahianite, Raman spectroscopy, romeite, stetefeldtite, stibiconite, valentinite

INTRODUCTION

It is interesting to note that very few papers have been published on the spectroscopy of antimonate minerals. What research has been published is related to the analysis of pigments.^[1–3] This work involves the chemical analysis of pigments and their detection using Raman spectroscopy. Some spectroscopic studies of calcium and copper antimonates have been forthcoming.^[4–6] It has been found that for arsenate-bearing minerals, the hydroxyl unit was coordinated directly to the metal ion and formed hydrogen bonds to the arsenate anion.^[7] Raman spectroscopy has proven especially useful for the study of related minerals.^[8–16] According to Khozhatelev,^[17] there are eight recognized intrinsically supergene ochreous antimony-bearing minerals: senarmonite Sb_2O_3 , valentinite

Received 22 July 2009;
accepted 21 August 2009.

Address correspondence to Ray L. Frost, Inorganic Materials Research Program, School of Physical and Chemical Sciences, Queensland University of Technology, GPO Box 2434, Brisbane, Queensland 4001, Australia. E-mail: r.frost@qut.edu.au

Sb₂O₃, stibiconite Sb³⁺Sb⁵⁺O₆(OH), bindheimite Pb₂Sb₂O₆(O,OH), stetefeldite Ag₂Sb₂(O,OH)₇, partzite Cu₂Sb₂(O,OH)₇, tripuhyite Fe²⁺Sb⁵⁺O₆, and bystromite Mg₂Sb₂⁵⁺O₆. According to Mason and Vitaliano,^[18] antimony oxides and antimonates fall into two structural groups, a cubic group with a pyrochlore structure and a tetragonal group with a trirutile structure. Partzite belongs to the first group. The mineral partzite first discovered in 1865 and is a copper antimony oxy-hydroxide of formula Cu₂Sb₂(O,OH)₇. The mineral is found in the oxidized zone of antimony-bearing sulphide deposits.^[18] The mineral is obtained from the Blind Spring Hill district, 2 miles SE of Benton, Mono County, California.^[19] The mineral may be associated with the minerals bindheimite, lewisite, and stibiconite. The mineral is located in several districts worldwide including Mt. Monger, near Doigs, Western Australia. The mineral can vary in color from olive green to yellowish-green blackish to green black to black.

Farmer reported the infrared spectra of some synthetic antimonite minerals (see pp. 413 and 414 and tables 17–19).^[20] For the synthetic compound NaSb(OH)₆, which is a compound with an octahedral structure, infrared bands were observed at 600 and 628 cm⁻¹ (very intense) 735, 775 cm⁻¹ (medium intensity), and 528 and 586 cm⁻¹. Siebert researched the infrared spectra of selected synthetic antimonates.^[21,22] Siebert assigned bands in the 528 to 775 cm⁻¹ region to the stretching vibrations of SbO units; in the 1030 to 1120 cm⁻¹ to the deformation modes of SbOH units; and in the 3220 to 3400 cm⁻¹ to the stretching bands of SbOH and water units. The aim of this article is to report the Raman spectra of partzite and to relate the spectra to the chemistry and formula of partzite. The article follows the systematic research on Raman and infrared spectroscopy of secondary minerals containing oxy-anions formed in the oxidation zone of minerals.

EXPERIMENTAL

Minerals

The mineral is obtained from the Blind Spring Hill district, 2 miles SE of Benton, Mono County, California. The mineral was supplied by the Mineralogical research company. The mineral is cubic and

is of point group 4/m 2/m. The composition of the mineral has been published by Anthony et al. (p. 427).^[19] The mineral analysis gave Sb₂O₄ as 47.65%, CuO 32.11%, with some other cations present such as FeO 2.33%, PbO 2.01%, and Ag₂O 6.12%. The structure of the mineral was confirmed by X-ray diffraction.

Raman Spectroscopy

Crystals of partzite were placed on a polished metal surface on the stage of an Olympus BHSM microscope, which is equipped with 10×, 20×, and 50× objectives. The microscope is part of a Renishaw 1000 Raman microscope system, which also includes a monochromator, a filter system, and a CCD detector (1024 pixels). The Raman spectra were excited by a Spectra-Physics model 127 He-Ne laser producing highly polarized light at 633 nm and collected at a nominal resolution of 2 cm⁻¹ and a precision of ±1 cm⁻¹ in the range between 100 and 4000 cm⁻¹. Repeated acquisition on the crystals using the highest magnification (50×) was accumulated to improve the signal to noise ratio in the spectra. Spectra were calibrated using the 520.5 cm⁻¹ line of a silicon wafer. Further details have been published previously.^[8–16] Alignment of all crystals in a similar orientation has been attempted and achieved. However, differences in intensity may be observed due to minor differences in the crystal orientation. The Raman spectra of the oriented single crystals are reported in accordance with the parallel/perpendicular notation. It is noted that the mineral partzite is very dark in color, almost black, yet Raman spectra were readily obtained.

Band component analysis was undertaken using the Peakfit (Jandel, Erkrath, Germany) software package, which enabled the type of fitting function to be selected and allowed specific parameters to be fixed or varied accordingly. Band fitting was done using a Lorentz-Gauss cross-product function with the minimum number of component bands used for the fitting process. The Lorentz-Gauss ratio was maintained at values greater than 0.7 and fitting was undertaken until reproducible results were obtained with squared correlations (*r*²) greater than 0.995. Band fitting of the spectra is quite reliable provided that there is some band separation or changes in the spectral profile.

RESULTS AND DISCUSSION

The Raman spectrum of partzite in the 100 to 1500 cm^{-1} region is reported in Fig. 1. The Raman spectrum shows some considerable complexity with a number of overlapping bands observed at 479, 520, 594, 607, and 620 cm^{-1} with additional low-intensity bands found at 675, 730, 777, and 837 cm^{-1} . According to Siebert,^[21,22] all bands in these positions are assignable to SbO stretching vibrations. The observation of multiple bands attributable to symmetric stretching vibrations in the Raman spectrum provides evidence for the nonequivalence of SbO units in the partzite structure.

In the infrared spectrum of antimony pentoxide an intense band is observed at 740 cm^{-1} and low-intensity bands at ~ 370 , 450, and 680 cm^{-1} .^[23] The infrared spectrum of valentinite (Sb_2O_3)₄ showed bands in similar positions.^[23] Farmer reported the infrared band positions of synthetic antimonates of formula MSbO_4 where M is Cr, Fe, Ga, or Rh with a rutile-type structure.^[20] As such these structures should have four Raman active bands ($A_{1g} + B_{1g} + B_{2g} + E_g$) and four infrared active bands ($A_{2u} + 3E_u$). Infrared bands were observed at 660 to 735 cm^{-1} , 520 to 585 cm^{-1} , 285 to 375 cm^{-1} , and 170 to 190 cm^{-1} . Although no assignment was given to these bands, one possible interpretation is that the first band is attributed to the antisymmetric stretching mode, the second to the symmetric stretching mode, the third to bending modes, and

the fourth to a lattice mode. Hence the Raman bands of partzite in the spectral region 590 to 675 cm^{-1} are attributable to the ν_1 symmetric stretching modes. The Raman bands at 479 and 520 cm^{-1} may therefore be assigned to the ν_3 antisymmetric stretching modes. The set of bands at 362, 387, and 418 cm^{-1} may be assigned to the CuO stretching vibrations.

The most intense Raman band in this spectral region is the band at 971 cm^{-1} . Shoulder bands are observed at 907, 938, and 982 cm^{-1} . This band at 971 cm^{-1} and associated shoulders are attributed to some sulfate impurities and are assigned to the ν_1 (SO_4)²⁻ symmetric stretching mode. Hence, the three Raman bands of low intensity at 1074, 1096, and 1126 cm^{-1} are assigned to the ν_3 (SO_4)²⁻ antisymmetric stretching mode. The observation of these bands is in many ways not unexpected, because the mineral partzite is formed from antimony sulphide deposits. Raman bands at 1396 and 1455 cm^{-1} are attributed to δSbOH deformation modes.

The Raman spectrum of partzite in the OH stretching region is displayed in Fig. 2. The Raman spectrum shows a complex set of overlapping bands. The bands are well defined and are readily resolved into component bands. The higher wavenumber bands at 3563, 3586, and 3622 cm^{-1} are attributed to hydroxyl stretching vibrations of the OH of the Sb-OH units. The Raman bands at 3266, 3376, and 3407 cm^{-1} are assigned to OH stretching bands of water. It is proposed that, based upon observation

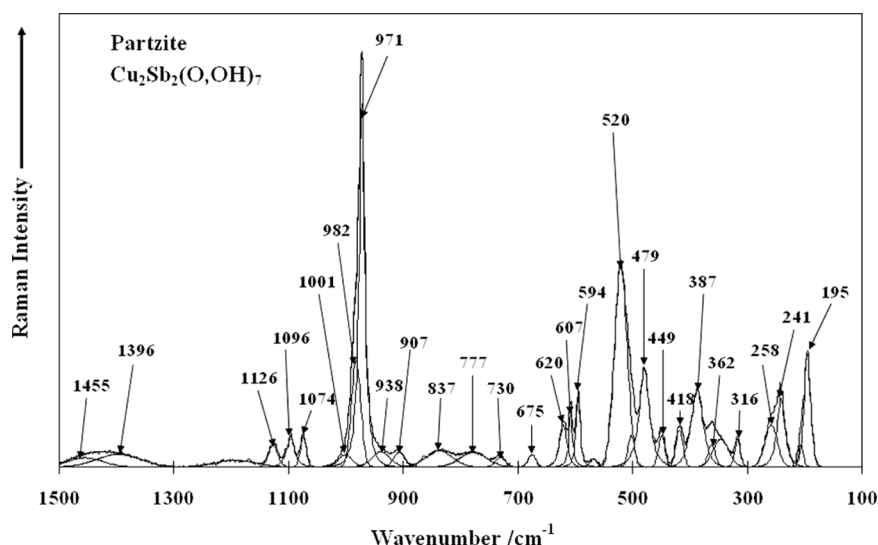


FIGURE 1 Raman spectrum of partzite in the 100 to 1500 cm^{-1} region.

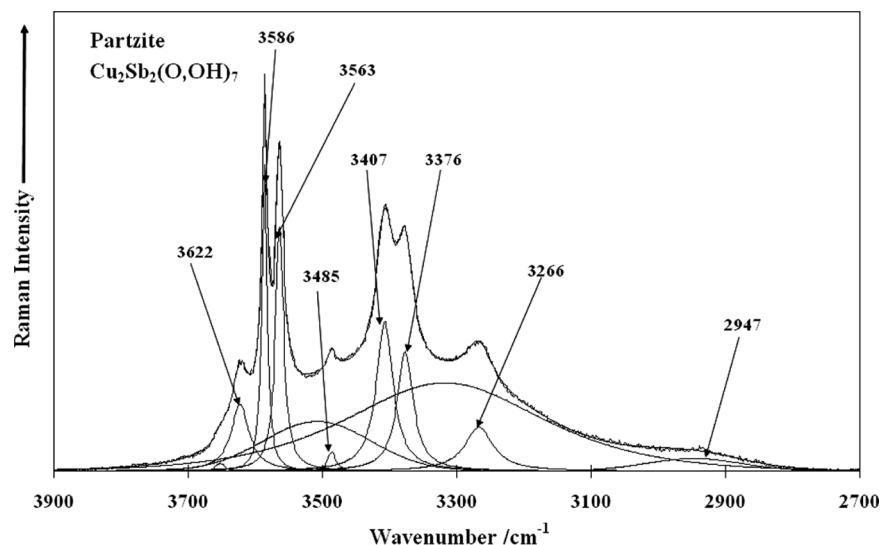


FIGURE 2 Raman spectrum of partzite in the 2700 to 3900 cm^{-1} region.

of the Raman spectra, water is involved in the structure of partzite. Thus, the formula $\text{Cu}_2\text{Sb}_2(\text{O},\text{OH})_7$ may be better written as $\text{Cu}_2\text{Sb}_2(\text{O},\text{OH})_7 \cdot x\text{H}_2\text{O}$. Further research on this mineral is necessary and determination of the exact formulation is required.

CONCLUSIONS

The Raman spectrum of the mineral partzite has been obtained for the first time as well as the spectra related to the mineral structure. The Raman spectrum shows some considerable complexity, with a number of overlapping bands observed at 479, 520, 594, 607, and 620 cm^{-1} with additional low-intensity bands found at 675, 730, 777, and 837 cm^{-1} . Raman bands of partzite in the spectral region 590 to 675 cm^{-1} are attributable to the ν_1 symmetric stretching modes. The Raman bands at 479 and 520 cm^{-1} are assigned to the ν_3 antisymmetric stretching modes. Raman bands at 1396 and 1455 cm^{-1} are attributed to SbOH deformation modes.

Raman bands are observed in the spectral regions associated with water and hydroxyl unit stretching vibrations. Raman spectra complemented with infrared spectra clearly show that the spectrum of water is obtained for this mineral. The formula is currently understood to be $\text{Cu}_2\text{Sb}_2(\text{O},\text{OH})_7$. Anthony et al. indicated that the formula is questionable.^[19] The formula may be better written as $\text{Cu}_2\text{Sb}_2(\text{O},\text{OH})_7 \cdot x\text{H}_2\text{O}$. It is noted that Anthony et al.^[19] also questioned the formula of the mineral partzite.

ACKNOWLEDGMENTS

The financial and infrastructure support of the Queensland University of Technology Inorganic Materials Research Program of the School of Physical and Chemical Sciences is gratefully acknowledged. The Australian Research Council (ARC) is thanked for funding the instrumentation.

REFERENCES

- Correia, A. M.; Oliveira, M. J. V.; Clark, R. J. H.; Ribeiro, M. I.; Duarte, M. L. Characterization of Pousao pigments and extenders by micro-X-ray diffractometry and IR and Raman microspectroscopy. *Anal. Chem.* **2008**, *80*, 1482–1492.
- Correia, A. M.; Clark, R. J. H.; Ribeiro, M. I. M.; Duarte, M. L. T. S. Pigment study by Raman microscopy of 23 paintings by the Portuguese artist Henrique Pousao (1859–1884). *J. Raman Spectros.* **2007**, *38*, 1390–1405.
- Clark, R. J. H.; Cridland, L.; Kariuki, B. M.; Harris, K. D. M.; Withnall, R. Synthesis, structural characterization and Raman spectroscopy of the inorganic pigments lead tin yellow types I and II and lead antimonate yellow: Their identification on medieval paintings and manuscripts. *J. Chem. Soc.* **1995**, 2577–2582.
- Husson, E.; Repelin, Y.; Vandenborre, M. T. Vibrational spectra and force field of calcium antimonate (CaSb_2O_6) and calcium arsenate (CaAs_2O_6). *Spectrochim. Acta Mol. Biomol. Spectros.* **1984**, *40A*, 1017–1020.
- Haeusel, H. Infrared and Raman spectra and normal coordinate calculations on trirutile-type compounds. *Spectrochim. Acta Mol. Biomol. Spectros.* **1981**, *37A*, 487–495.
- Vandenborre, M. T.; Husson, E.; Brusset, H.; Cerez, A. Vibrational spectra and calculation of force field of antimonates of lead antimonate (PbSb_2O_6) structure type. *Spectrochim. Acta Mol. Biomol. Spectros.* **1980**, *36A*, 1045–1052.
- Sumin De Portilla, V. I. Infrared spectroscopic investigation of the structure of some natural arsenates and the nature of hydrogen-bonds in their structures. *Can. Mineral.* **1974**, *12*, 262–268.
- Frost, R. L.; Cejka, J.; Ayoko, G. Raman spectroscopic study of the uranyl phosphate minerals phosphuranylite and yingjiangite. *J. Raman Spectros.* **2008**, *39*, 495–502.

9. Frost, R. L.; Cejka, J.; Ayoko, G. A.; Dickfos, M. J. Raman spectroscopic study of the uranyl carbonate mineral voglite. *J. Raman Spectros.* **2008**, *39*, 374–379.
10. Frost, R. L.; Cejka, J.; Dickfos, M. J. Raman and infrared spectroscopic study of the molybdate-containing uranyl mineral calcumolite. *J. Raman Spectros.* **2008**, *39*, 779–785.
11. Frost, R. L.; Dickfos, M. J.; Cejka, J. Raman spectroscopic study of the uranyl carbonate mineral zellerite. *J. Raman Spectros.* **2008**, *39*, 582–586.
12. Frost, R. L.; Hales, M. C.; Wain, D. L. Raman spectroscopy of smithsonite. *J. Raman Spectros.* **2008**, *39*, 108–114.
13. Frost, R. L.; Keeffe, E. C. Raman spectroscopic study of the selenite minerals-chalcomenite $\text{CuSeO}_3 \cdot 2\text{H}_2\text{O}$, clinochalcomenite and cobaltomenite. *J. Raman Spectros.* **2008**, *39*, 1789–1793.
14. Frost, R. L.; Locke, A.; Martens, W. N. Synthesis and Raman spectroscopic characterisation of the oxalate mineral wheatleyite $\text{Na}_2\text{Cu}^{2+}(\text{C}_2\text{O}_4)_2 \cdot 2\text{H}_2\text{O}$. *J. Raman Spectros.* **2008**, *39*, 901–908.
15. Frost, R. L.; Reddy, B. J.; Dickfos, M. J. Raman spectroscopy of the nickel silicate mineral pecoraite—an analogue of chrysotile (asbestos). *J. Raman Spectros.* **2008**, *39*, 909–913.
16. Palmer, S. J.; Frost, R. L.; Ayoko, G.; Nguyen, T. Synthesis and Raman spectroscopic characterization of hydrotalcite with CO_3^{2-} and $(\text{MoO}_4)^{2-}$ anions in the interlayer. *J. Raman Spectros.* **2008**, *39*, 395–401.
17. Khozhatelev, B. L. The number of supergene antimony minerals. **1962**, 20–24.
18. Mason, B.; Vitaliano, C. J. The mineralogy of the antimony oxides and antimonates. *Mineral. Mag. J. Mineral. Soc.* **1953**, *30*, 100–112.
19. Anthony, J. W.; Bideaux, R. A.; Bladh, K. W.; Nichols, M. C. *Handbook of Mineralogy III, Halides, Hydroxides, Oxides*; Mineral Data Publishing: Tucson, AZ, 1997.
20. Farmer, V. C. *Mineralogical Society Monograph 4: The Infrared Spectra of Minerals*; 1974.
21. Siebert, H. Infrared spectra of telluric acids, tellurates, and antimonates. *Z. Anorg. Allg. Chem.* **1959**, *301*, 161–170.
22. Siebert, H. *Anwendungen der Schwingungsspektroskopie in der Anorganischen Chemie (Anorganische und Allgemeine Chemie in Einzeldarstellungen, Bd. 7)* [Application of Vibrational Spectroscopy in Inorganic Chemistry (Monographs in Inorganic and General Chemistry, Vol. 7)], 1966.
23. Gadsden, J. A. *Infrared Spectra of Minerals and Related Inorganic Compounds*; Butterworth: London, 1975.